



Universidade de São Paulo

Biblioteca Digital da Produção Intelectual - BDPI

Departamento de Materiais e Mecânica - IF/FMT

Comunicações em Eventos - IF/FMT

2013-09-29

Enhanced ferromagnetism in CuO nanowires on the top of CuO nanograins.

Encontro da SBPMat, XII, 2013, Campos do Jordão.

<http://www.producao.usp.br/handle/BDPI/45508>

Downloaded from: Biblioteca Digital da Produção Intelectual - BDPI, Universidade de São Paulo

Enhanced ferromagnetism in CuO nanowires on the top of CuO nanograins

J. A. Souza¹, A. Zuniga¹, D. Criado¹, S. H. Masunaga², and R. F. Jardim²

¹ Universidade Federal do ABC - Santo André, SP, Brazil

² Instituto de Física, Universidade de São Paulo, São Paulo, SP, Brazil

In the past few years, a considerable effort has been devoted in order to grow magnetoelectric nanostructured materials. Besides fundamental science, they are very attractive in the electronic/spintronic industry as well as magnetic storage media, solar energy conversion due to their nanometer scale. It is believed that CuO is a magnetoelectric multiferroic system where a ferroelectric order is induced by the onset of a magnetic coupling at low temperatures. Furthermore, its simplest composition is the bases of cuprates which bring about the well-known high-temperature superconductivity. Bulk samples of CuO (which has an unpaired electron in the *d*-shell) show two antiferromagnetic phase transitions – a commensurate collinear state with the magnetic moments along the monoclinic *b* axis at $T_N \sim 213$ K and an incommensurate spiral state with half of the magnetic moments in the *ac* plane at $T_N \sim 230$ K.

We have produced CuO nanostructured samples by using electrical resistive heating method. CuO nanowires of 50-90 nm in diameter and length up to 1.2 μm grew homogeneously and straightly on a 170 nm layer of CuO nanograins which are on the top of a diamagnetic Cu_2O layer. At low magnetic fields, the magnetization (ZFC/FC) as a function of temperature resembles superparamagnetic behavior. However, a long range antiferromagnetic ordering is induced by a magnetic field of 5 kOe in the sample with homogeneous distribution of nanowires. A very strong ferromagnetic-like contribution displaying remanent magnetization and coercivity was found to coexist in the system. Our results reveal clear experimental evidence that ferromagnetic-like behavior shows up along with the presence of long range AFM ordering. The ferromagnetic-like behavior is observed below and above the induced T_N , suggesting that this behavior is not dependent on the original magnetic state of the core, whether it is PM or AFM. The effective magnetic moment was estimated to be $\sim 1 \times 10^{-2} \mu_B/\text{f.u.}$ producing a nearly temperature independent coercive field around 70 Oe.

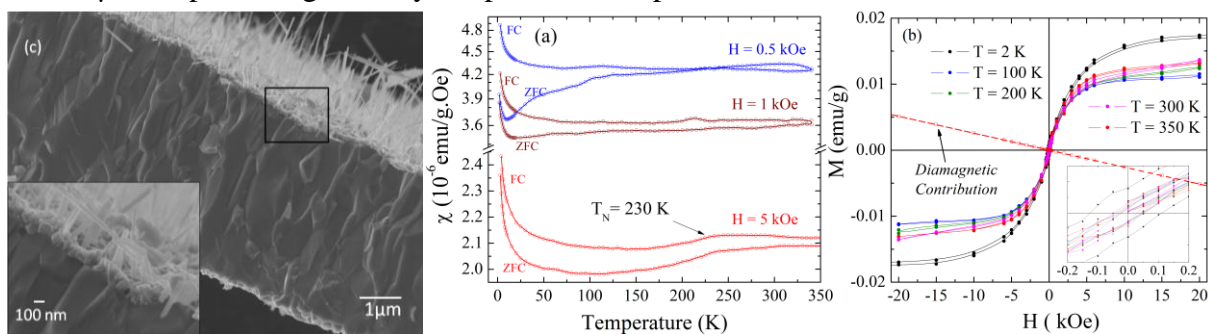


Fig.: (a) Image of scanning electron microscopy showing CuO nanowires/nanograins on Cu_2O layer. (b) Magnetization as a function of both temperature and magnetic field.

Keywords: CuO, nanowires, nanograins, enhanced magnetism

joseantonio.souza@ufabc.edu.br –UFABC CEP 09.210-170, Santo André, SP, Brazil