

Oxygen Partial Pressure and Oxygen Concentration Flammability: Can They Be Correlated?

Susana Tapia Harper

Alfredo Juarez, Horacio Perez III, David B. Hirsch, & Harold D. Beeson

The Partial Pressure Question

- Assuming an Ideal gas mixture

21% volume $O_2 = 21$ mole % O_2

$$(v_{O_2}/V) = p_{O_2}/P$$

$$p_{O_2} = (v_{O_2}/V) * P$$


- If the available oxidizer is the driver for combustion then should flammability for.....

30% O_2 , 10.2 psi (3.1 pp) = 100% O_2 , 3.1 psi (3.1 pp)


Test Method and Environmental Conditions

- Flammability Data Examined
 - Primarily NASA-STD-6001 Test 1 Maximum Oxygen Concentration self-extinguishment thresholds
 - 6" Self Extinguishment Criteria
 - Vary Oxygen Concentration until a threshold is identified for Self Extinguishment to occur.
 - Threshold allows performance comparisons across environments of equivalent O₂ PP
 - Material ignition susceptibility
 - Burn Rates

Max O₂ Concentration Self Extinguishment Thresholds & Equivalent Normoxic O₂ Concentrations (NASA 6001 Flamm)

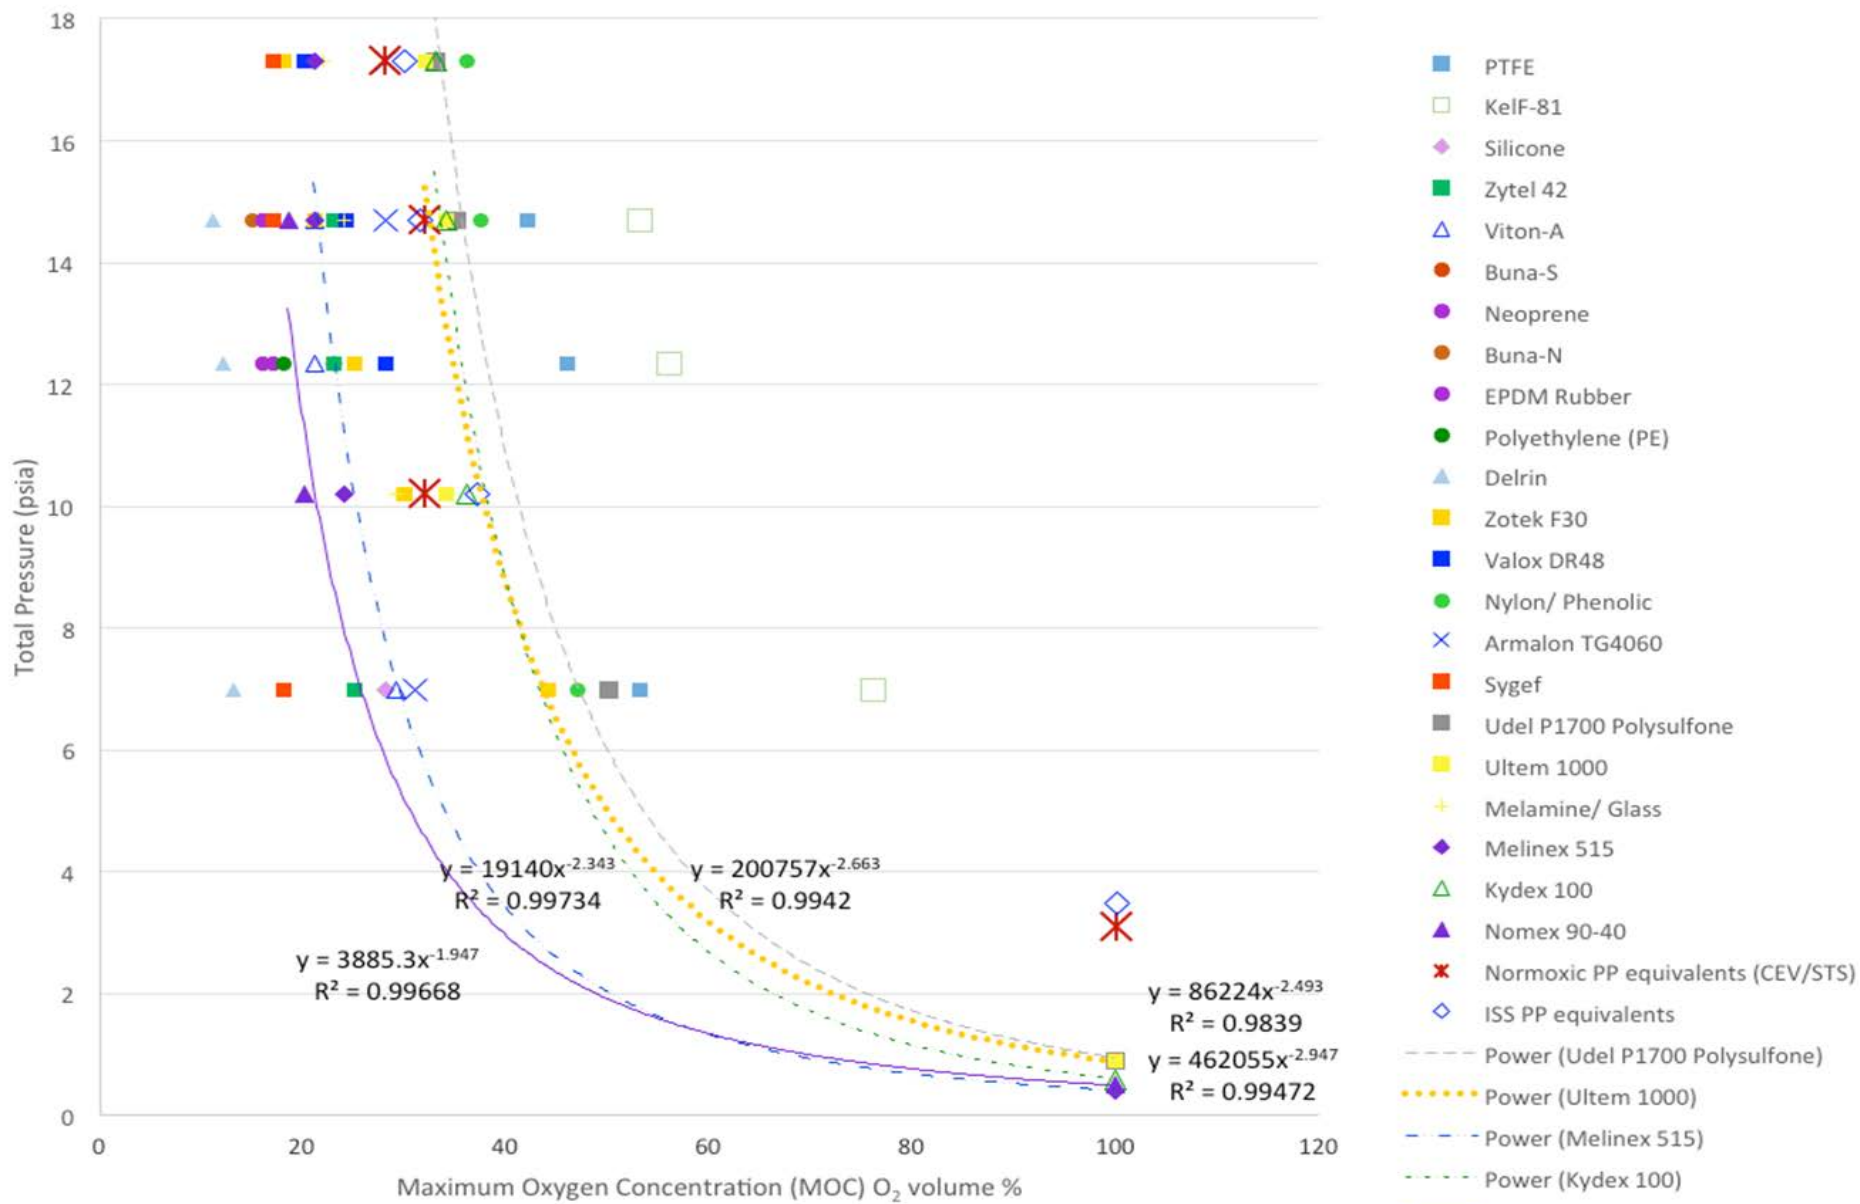

Max O₂ Total Pressures Self Extinguishment Thresholds & Equivalent Partial Pressures (NASA 6001 Flamm)

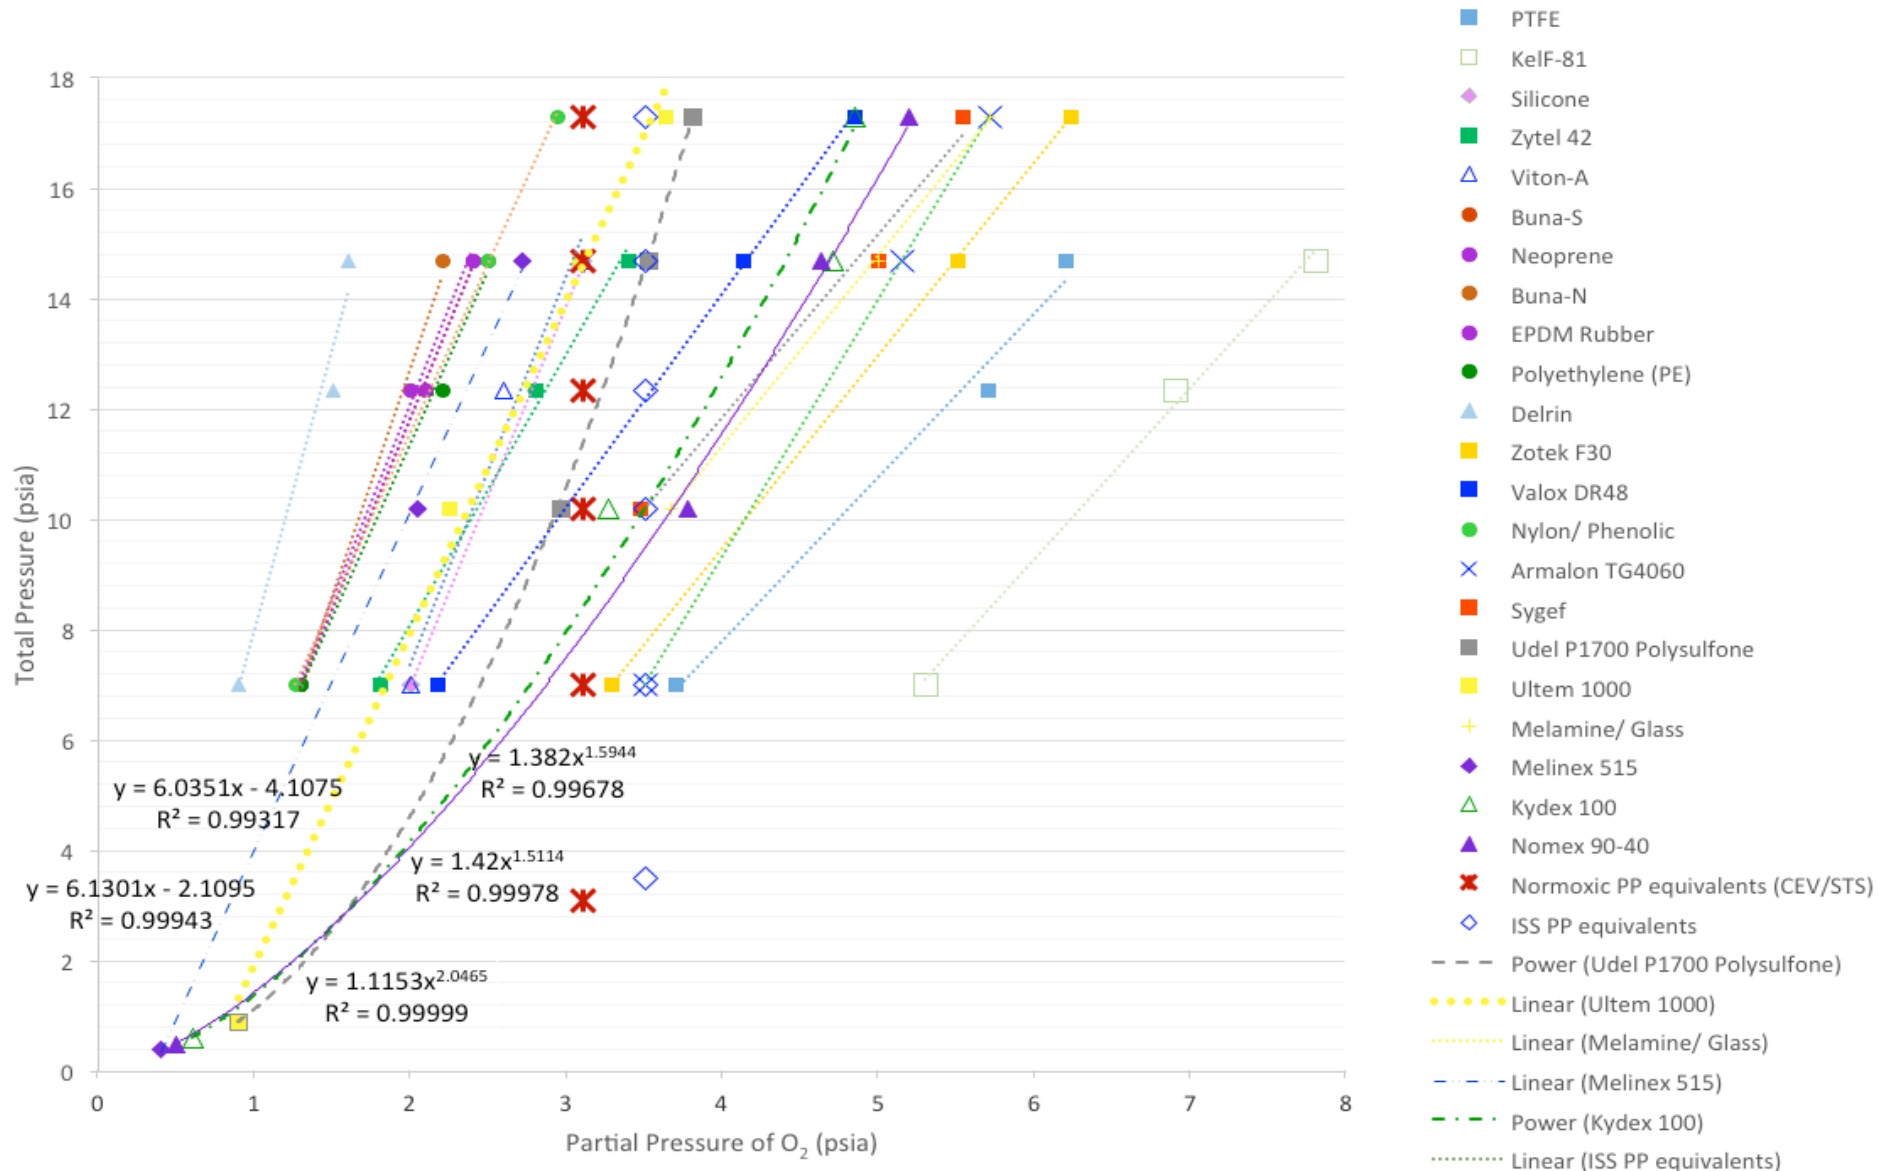

Total Pressure Dependencies

- For pressures above 41 kPa (6 psia)
 - All show a strong dependence on oxygen concentration with little relation to total pressures
- Below 41 kPa (6 psia)
 - MOCs and required oxygen partial pressures show increased dependence on total pressure.
- Power equation models fit trends precisely across
 - Pressure ranges spanning 2.8–119.3 kPa (0.4–17.3 psia)
 - Both MOC and partial pressure against total pressures.
- Required O₂ partial pressure necessary to sustain propagation decreases with decreased total pressures.
 - Increased flammability risk at lower total pressure conditions despite equivalent partial pressure
 - Conversely, oxygen concentration primary driver despite equivalent partial pressure

Application of Findings

- Lower O₂% / higher P data cannot be conservatively applied to higher O₂% / lower P environments despite equivalent partial pressures.

21 O₂%, 14.7 psi (3.1 pp)  30 O₂%, 10.2 psi (3.1 pp)

- Higher O₂% / lower P data can be conservatively applied to evaluate the risk of lower O₂% higher P equivalent PP environments

30 O₂%, 10.2 psi (3.1 pp)  21 O₂%, 14.7 psi (3.1 pp)

Other Supporting Research

- Flame spread rate testing (Olson and Miller)
 - Performed along normoxic curve (18-100 O₂%)
 - Flame spread rate increased with higher O₂% despite O₂ pp remaining constant
- Burn Rates (Yang, Hamins, and Donneley)
 - Polymethyl methacrylate (PMMA) spheres
 - Burn rates increased significantly as O₂% was increased (19.9-30 O₂%)
 - little effect was observed with increased pressures from 50.0–150 kPa (7.25–21.75 psia) .

Increased Pressure Dependencies

- Certain materials exhibited higher dependencies on total pressure
 - Kel-F ($(CF_2CClF)_n$), PTFE ($(C_2F_4)_n$), Zotek F30 ($(C_2H_2F_2)_n$),
 - highly halogenated
 - Armalon TG4060
 - fluorocarbon fiberglass composite, saturated chains of highly electronegative halogenated molecules (F, Cl)
 - Nomex
 - aramid structure with dense electron clouds
- All highly stable with few susceptible reaction sites.
 - Oxygen Molecular Collision Rate Competition for Reaction Sites?

Ignition Sequence

- Available Reaction Sites Ignition Sequence Pyrolysis
 1. Flammable gas mixing
 2. Ignition induction
- Proposed additional mechanism step in ignition sequence
- Limited Reaction Sites Ignition Sequence
 1. Oxygen molecular collision rate competition for reaction sites
 2. Pyrolysis
 3. Flammable gas mixing
 4. Ignition Induction
- Theory would be successful in describing observed experimental trends

Future Work

- Additional testing in low pressure ranges
- Acquisition of burn rate data at the various equivalent partial pressure conditions.

Conclusions

- Partial pressure of oxygen equivalency does not represent flammability equivalency
- Oxygen Concentration % is the primary driver for flammability despite equivalent partial pressure
- Higher O₂% /lower P data can be conservatively applied to evaluate the risk of lower O₂% higher P equivalent PP environments

21 O₂%, 14.7psi(3.1pp)  30 O₂%, 10.2 psi(3.1pp)

30 O₂%, 10.2 psi(3.1pp)  21 O₂%, 14.7psi(3.1pp)

NASA



WHITE SANDS TEST FACILITY

Back-up Slides

Pressure effects
on Self
Extinguishment
Thresholds &
Normoxic & ISS
environment
conditions for
comparison

Material	psia (total pressure)													
	Determined at 99.8 % volume O ₂													
	0.4	0.5	0.6	0.9	7	10.2	12.35	14.7	17.3					
MOP (psia)	MOP (psia)	MOP (psia)	MOP (psia)	MOC (vol%)	MOP (psia)	MOC (vol%)	MOP (psia)	MOC (vol%)	MOP (psia)	MOC (vol%)	MOP (psia)	MOC (vol%)	MOP (psia)	MOC (vol%)
PTFE					53	3.7			46	5.7	42	6.2		
KelF-81					76	5.3			56	6.9	53	7.8		
Silicone					28	2.0			23	2.8	21	3.1		
Zytel 42					25	1.8			23	2.8	23	3.4		
Viton-A					29	2.0			21	2.6	21	3.1		
Buna-S					18	1.3			17	2.1	16	2.4		
Neoprene					18	1.3			17	2.1	16	2.4		
Buna-N					18	1.3			16	2.0	15	2.2		
EPDM Rubber					18	1.3			16	2.0	16	2.4		
Polyethylene (PE)					18	1.3			18	2.2	17	2.5		
Delrin					13	0.9			12	1.5	11	1.6		
Zotek F30					47	3.3					37.5	5.5	36	6.2
Valox DR48					31	2.2					28.1	4.1	28	4.8
Nylon/ Phenolic					18	1.3					17	2.5	17	2.9
Armalon TG4060					50	3.5					35	5.1	33	5.7
Sygef							34	3.5			34	5.0	32	5.5
Udel P1700														
Polysulfone				0.9			29	3.0			24	3.5	22	3.8
Ultem 1000				0.9			24	2.4			21	3.1	21	3.6
Melamine/ Glass							36	3.7			34	5.0	33	5.7
Melinex 515	0.4						20	2.0			18.5	2.7		
Kydex 100			0.6				32	3.3			32	4.7	28	4.8
Nomex 90-40		0.5					37	3.8			31.5	4.6	30	5.2
Normoxic environment partial pressure equivalents (CEV/STS)					44	3.1	30	3.1	25	3.1	21	3.1	18	3.1
ISS environment partial pressure equivalents					50	3.5	34	3.5	28	3.5	24.1	3.5	20	3.5

MOC = Maximum oxygen concentration which consistently results in material self-extinguishment

MOP = Maximum oxygen partial pressure when extinguishment occurs (based on MOC with the exception of 99.8% testing)

Pressure Effects on NASA STD-6001 Test 1 Maximum O₂ Concentration Flammability Thresholds

