

# Filled $\text{Nd}_z\text{Fe}_x\text{Co}_{4-x}\text{Sb}_{12-y}\text{Ge}_y$ skutterudites: processing and thermoelectric properties

## **Jon Mackey**

Materials Science and Engineering,  
Case Western Reserve University

## **Alp Sehirlioglu**


Materials Science and Engineering,  
Case Western Reserve University

## **Fred Dynys**

NASA Glenn Research Center

NASA Cooperative Agreement: NNX08AB43A

NASA/USRA Contract: 04555-004


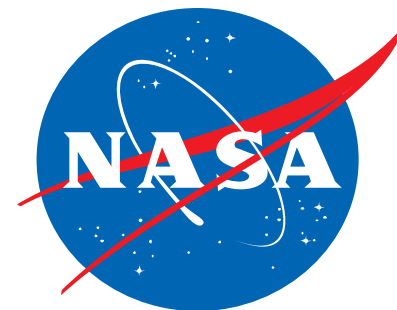


## System Background

- Skutterudites are based on  $\text{CoAs}_3$  mineral; first mined in Skutterud, Norway.
- Exhibit a high figure of merit for n-type systems ( $ZT=1.7$ ).
- Relatively low cost system.
- Introduce a range of fillers (A) to scatter various phonon wavelengths.
- Introduce disorder on pnictogen ring sites (X).
  - Dominate heat carrying modes are associated with pnictogen vibration.
- Tune electronic properties (A,B,X) for optimal thermoelectric power factor.

## Crystal Structure

Body-centered cubic space group  $Im-3$

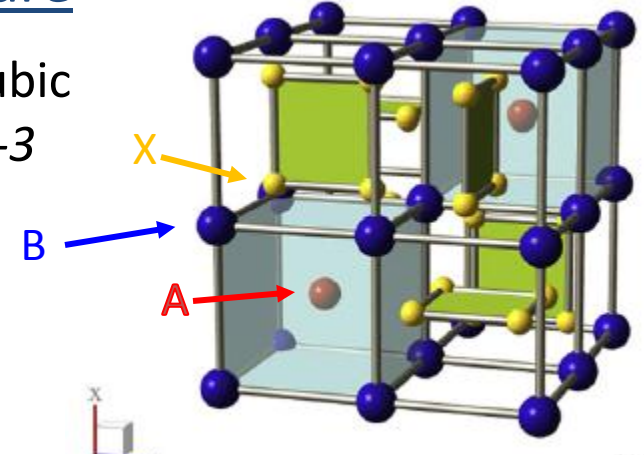

Eilertsen *et al.* Acta Mater. **60** (2012) 2178-2185.  
Chi *et al.* Phys. Rev. B **86**: 195209 (2012).

Hydrogen 1 1.0079																	Helium 2 4.0026
3 Li 6.941	4 Be 9.0122											5 B 10.811	6 C 12.011	7 N 14.007	8 O 15.999	9 F 18.998	10 Ne 20.180
11 Na 22.990	12 Mg 24.305											13 Al 26.982	14 Si 28.086	15 P 30.974	16 S 32.06	17 Cl 35.453	18 Ar 39.948
19 K 39.098	20 Ca 40.078	Scandium 21 44.956	Titanium 22 47.887	Vanadium 23 50.942	Chromium 24 51.996	Manganese 25 54.938	Iron 26 55.845	Cobalt 27 58.933	Nickel 28 58.693	Copper 29 63.546	Zinc 30 65.38	Gallium 31 69.723	Germanium 32 72.63	Arsenic 33 74.922	Selenium 34 78.96	Bromine 35 79.904	Krypton 36 83.80
37 Rb 85.468	38 Sr 87.62	Yttrium 39 88.906	Zirconium 40 91.224	Niobium 41 92.906	Molybdenum 42 95.94	Technetium 43 98	Ruthenium 44 101.07	Rhodium 45 102.91	Palladium 46 106.42	Silver 47 107.87	Cadmium 48 112.41	Indium 49 114.82	Sn 50 118.710	Sb 51 121.76	Te 52 127.60	Iodine 53 126.905	Xenon 54 131.29
55 Cs 132.91	56 Ba 137.33	57-79 * Lanthanum 57 138.905	Hafnium 72 178.49	Tantalum 73 180.948	Tungsten 74 183.84	Rhenium 75 186.21	Osmium 76 190.23	Iridium 77 192.22	Platinum 78 195.08	Gold 79 196.967	Mercury 80 200.59	Thallium 81 204.38	Lead 82 207.2	Bismuth 83 208.98	Polonium 84 209	Astatine 85 210	Rn 86 222
87 Fr 223	88 Ra 226	89-102 * * Actinium 89 227	Rutherfordium 104 261	Dubnium 105 262	Seaborgium 106 263	Bh 107 264	Hs 108 265	Mt 109 266	Uun 110 267	Uuu 111 268	Uub 112 269						

A

57 La 138.91	58 Ce 140.12	59 Pr 140.91	60 Nd 144.24	61 Pm (145)	62 Sm 150.36	63 Eu 151.96	64 Gd 157.25	65 Tb 158.93	66 Dy 162.50	67 Ho 164.93	68 Er 167.26	69 Tm 168.93	70 Yb 173.04
89 Ac 227	90 Th 232.04	91 Pa 231.04	92 U 238.03	93 Np 237	94 Pu 244	95 Am 243	96 Cm 247	97 Bk 247	98 Cf 251	99 Es 252	100 Fm 257	101 Md 258	102 No 259


## Skutterudite System Investigated

- Nd filled, Ge doped  $\text{Fe}_x\text{Co}_{4-x}\text{Sb}_{12}$  skutterudite,  $\text{Nd}_z\text{Fe}_x\text{Co}_{4-x}\text{Sb}_{12-y}\text{Ge}_y$ .
- Zhang *et al.* has previously investigated  $\text{Nd}_{0.6}\text{Fe}_2\text{Co}_2\text{Sb}_{12-y}\text{Ge}_y$  system.
  - Reported peak p-type ZT 1.1 for  $y=0.15$ .
  - Reported formation of a nano-structured precipitate, reported to lower thermal conductivity and cause high ZT.
- Interested to expand the parameter space of Zhang's work.
  - Nd level  $z = \{0 - 0.8\}$
  - Fe level  $x = \{1, 2, 3\}$
  - Ge level  $y = \{0, 0.15\}$

Zhang *et al.* J. Appl. Phys. **114** (2013).

## Objectives

- Focus on finding a p-type skutterudite with improved ZT.
- Study thermoelectric behavior of the skutterudite  $\text{Nd}_z\text{Fe}_x\text{Co}_{4-x}\text{Sb}_{12-y}\text{Ge}_y$ .
- Study processing conditions.
- Study effect of composition on properties.
- Samples created from a melt/mill/hot press procedure.

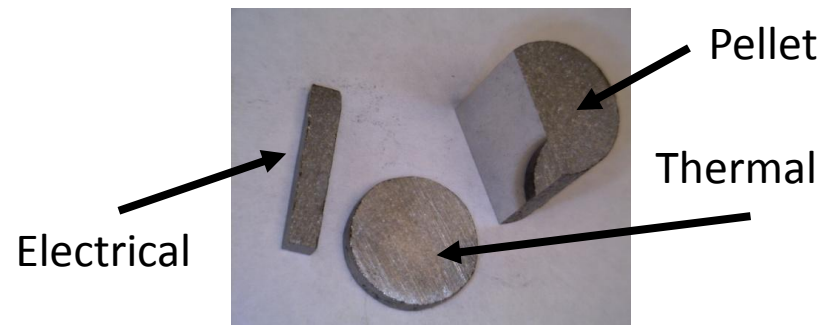


## Processing Conditions


- Ingots were fabricated by solidification.
  - 1100°C for 1 hour
  - 10°C/min cooling rate
  - Ingot dimensions 1" diameter, 2" height
  - He atmosphere
  - Carbon crucibles
- Ingots crushed in mortar and pestle then milled.
  - Planetary ball mill
  - WC milling jar and media
  - 500 rpm for 3-6 hours
- Powder was consolidated in a hot press.
  - 520-575°C with 62 MPa for ½ hour
  - 1.5°C/min cooling rate
  - ½" graphite die, lined with grafoil
- All compositions were processed with identical conditions.

### Solidified Ingot



### Hot Pressed Pellet

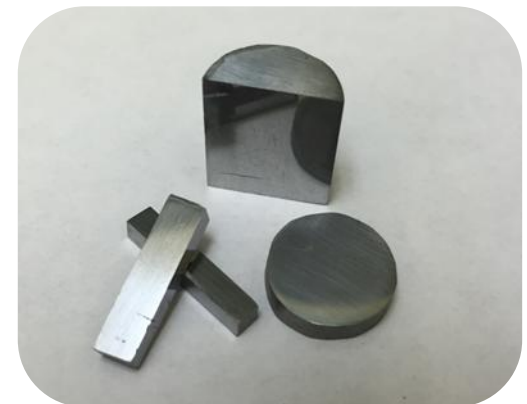




### X-Ray Diffraction







- Powder XRD of crushed pellets was evaluated with Rietveld refinement.
- Main phase is SKD structure, secondary phases include  $\text{FeSb}_2$  and Sb.
- SKD phase purity decreases significantly for  $\text{Nd} < 0.5$  and  $\text{Fe} > 2$ , no major impact from Ge.
- Filler occupancy increases with Nd level from 0 to 0.6 then levels off with maximum around 0.6.

### X-Ray Diffraction Summary

Nd Level (z)	Fe Level (x)	Ge Level (y)	SKD Phase (wt%)	Filler Occupancy
0.0	2	0.15	57	0.00
0.2	2	0.15	62	0.16
0.4	2	0.15	66	0.23
0.5	2	0.15	87	0.45
0.6	2	0.15	100	0.62
0.7	2	0.15	95	0.52
0.8	2	0.15	96	0.60
0.6	3	0.15	57	0.67
0.6	2	0.15	100	0.62
0.6	1	0.15	100	0.27
0.6	2	0.00	90	0.43
0.6	2	0.15	100	0.62








Nominal Composition

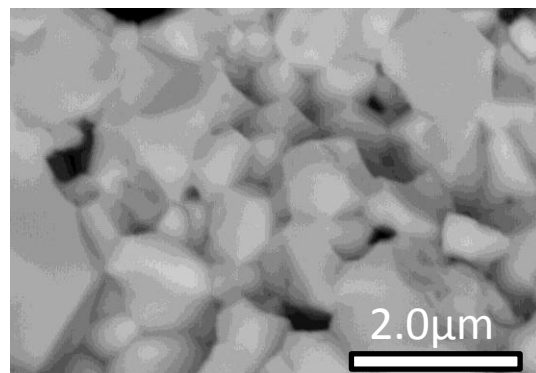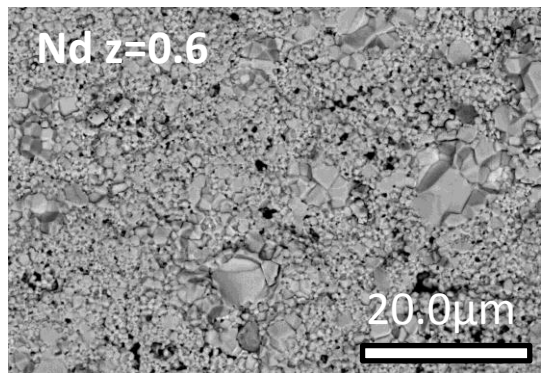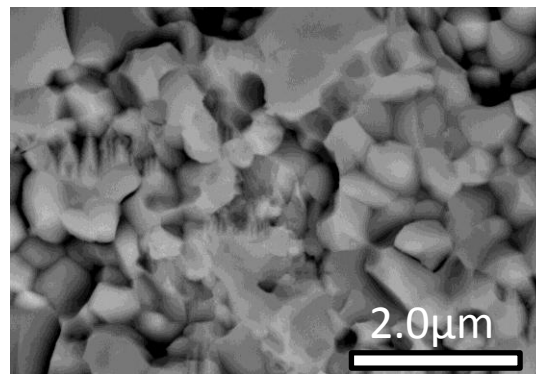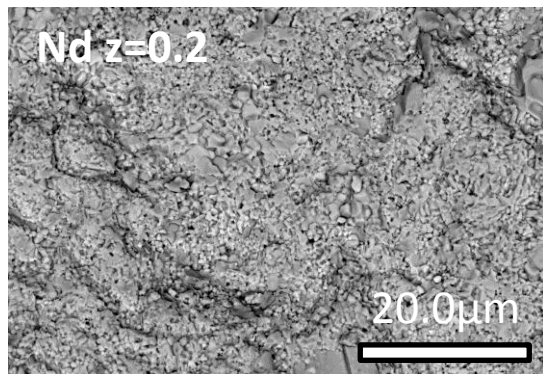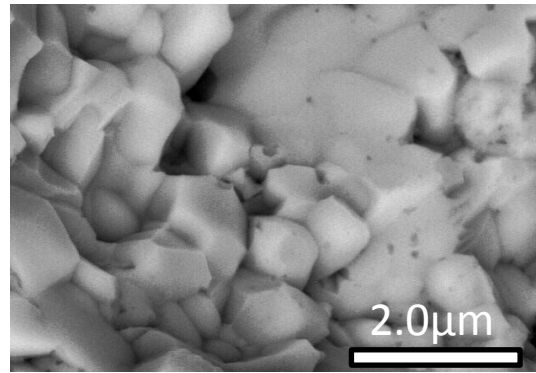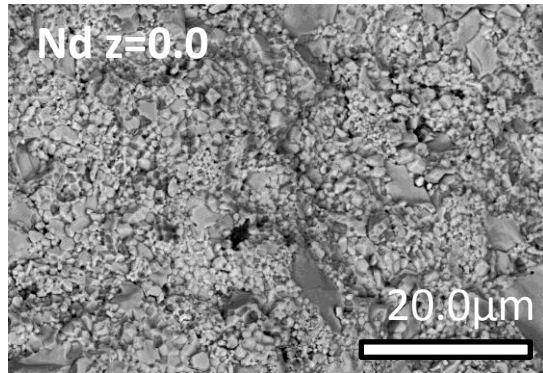

## Microstructure

- Similar microstructures for all hot pressed samples, no clear trends for composition.
- Grain size is bimodal with majority of grains 1-2μm, and others as large as 15μm.
- All samples had similar density (>96%) except for the sample with Fe content of 3 (90%).

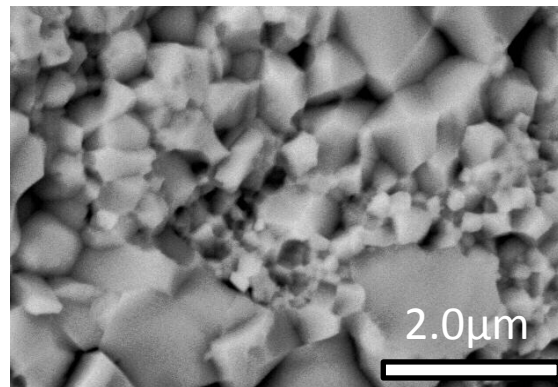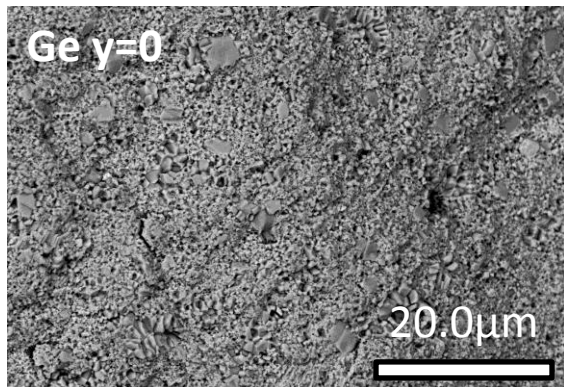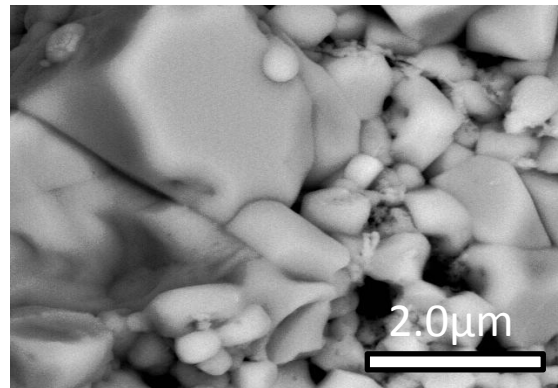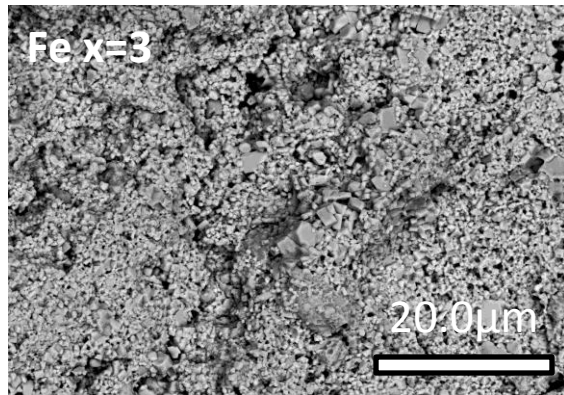


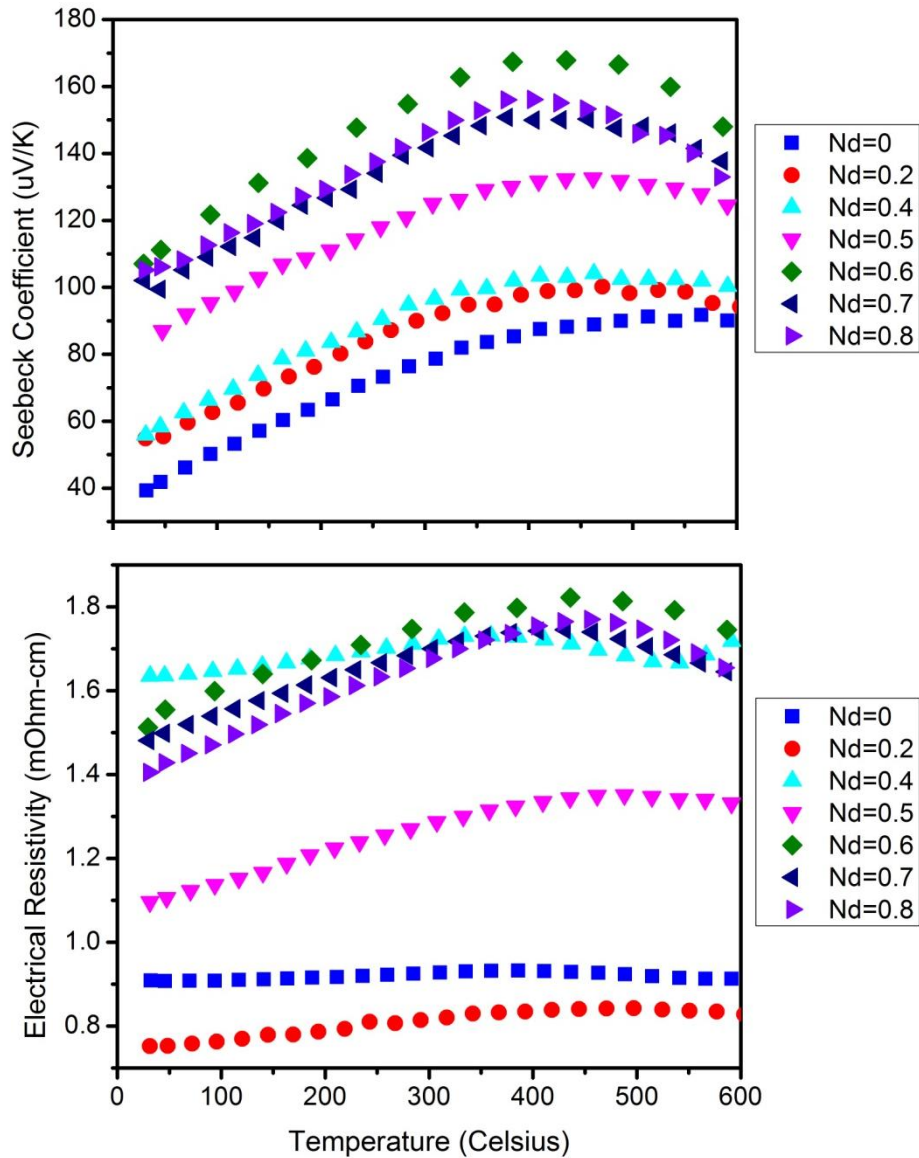

### Seebeck and Resistivity

- Seebeck coefficient trends well with Nd content. Increases with increasing Nd content from 0 to 0.6 then decreases.
- Electrical resistivity does not trend well with Nd content. It trends more with SKD phase purity than Nd content, secondary phases are metallic.
- More phase pure samples ( $0.5 < \text{Nd} < 0.8$ ) had higher electrical resistivity than the less phase pure samples.



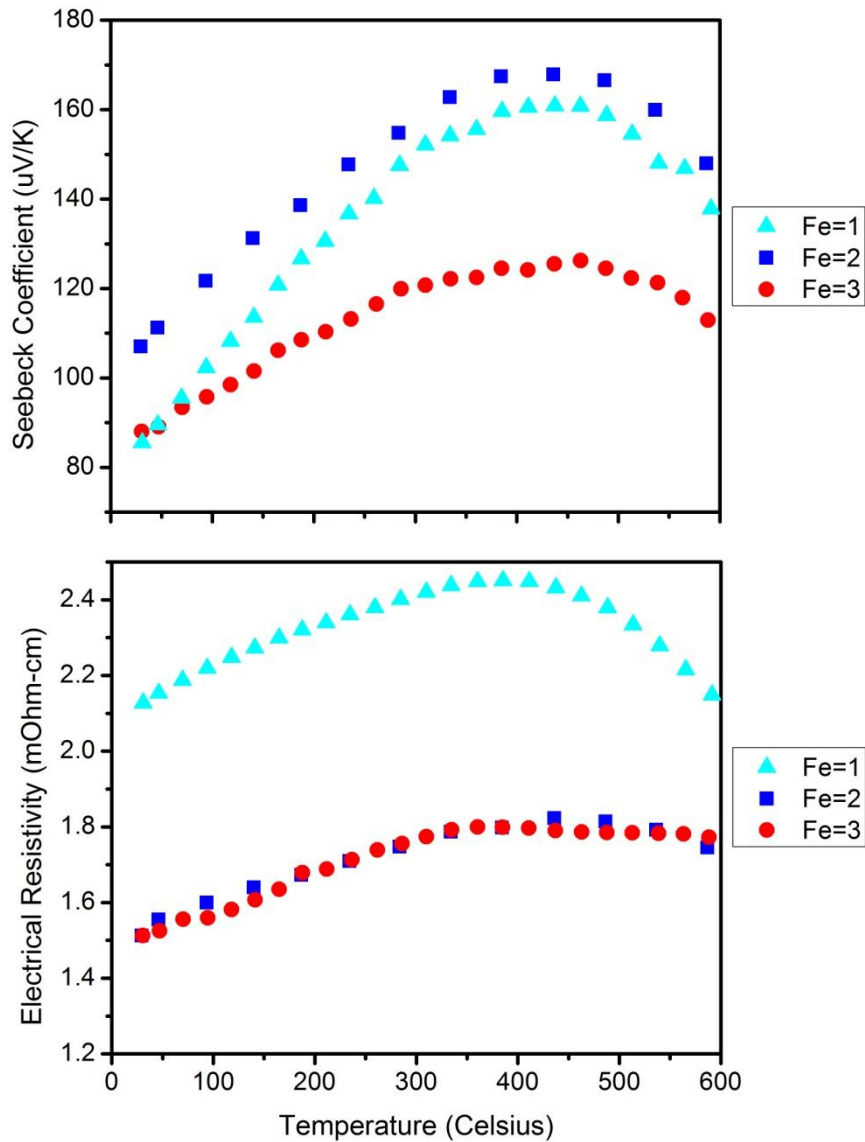


### Seebeck and Resistivity

- Seebeck coefficient is maximum for Fe content of 2, slightly lower for 1 and significantly lower for Fe 3.
- Electrical resistivity for Fe 1 is highest, with nearly identical resistivity for both Fe 2 and 3.
- In summary, Power factor is maximum for Fe content of 2 and lower for 1 and 3.



### Thermal and Figure of Merit

- Lattice thermal conductivity (open symbols) is calculated using a single parabolic band model.
- Only select samples are shown to avoid crowding the data.
- Lattice conductivity decreases with increasing Nd content up to 0.6.
- Highest ZT is obtained for the Nd 0.6 sample as a result of the low thermal conductivity.
  - The same composition in Zhang's paper reported ZT peak 1.1.

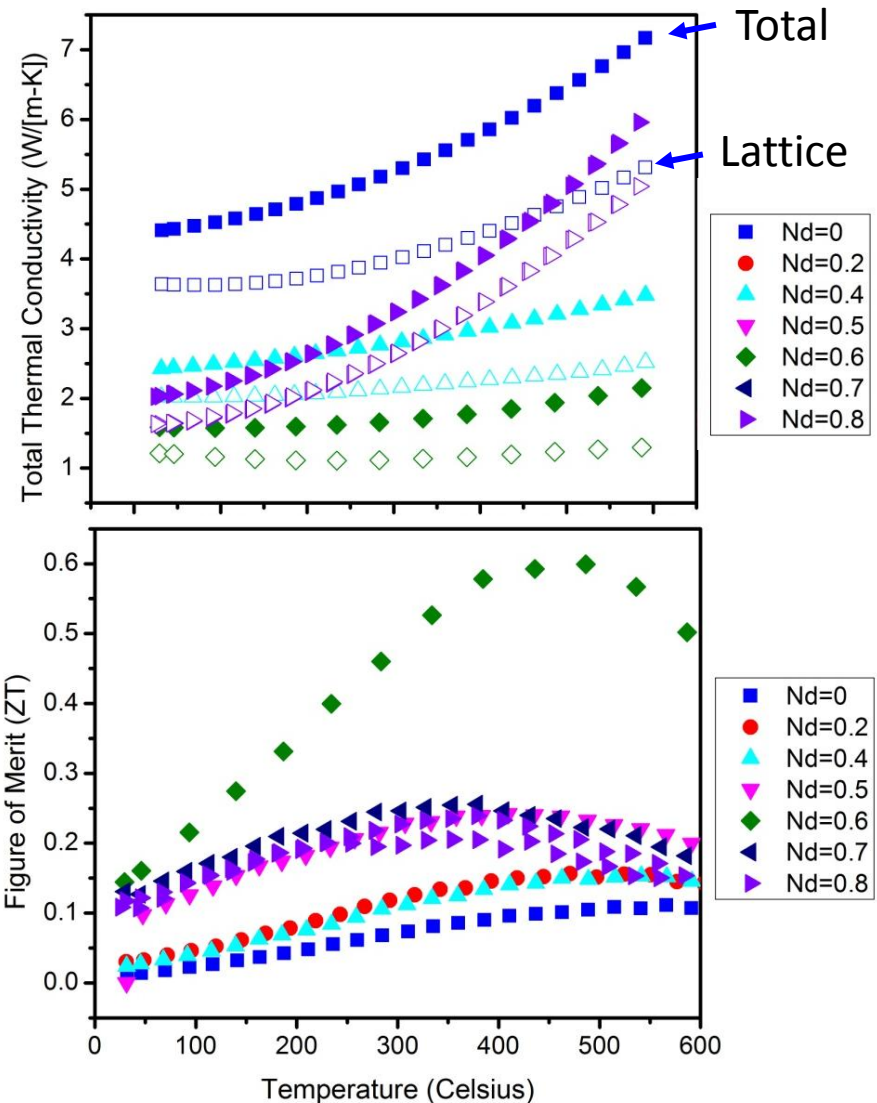





### Thermal Conductivity

- Lattice thermal conductivity is minimized for Fe content of 2.
- Fe content of 1 and 3 have similar thermal conductivity.
  - Suggests phonon scattering from Fe-Co bond. Maximized for Fe content of 2.
- Ge reduces lattice component of thermal conductivity.
  - Stronger scattering effect from Ge-Sb bond as Ge content is much lower than Fe content.

Chi *et al.* Phys. Rev. B **86**: 195209 (2012).

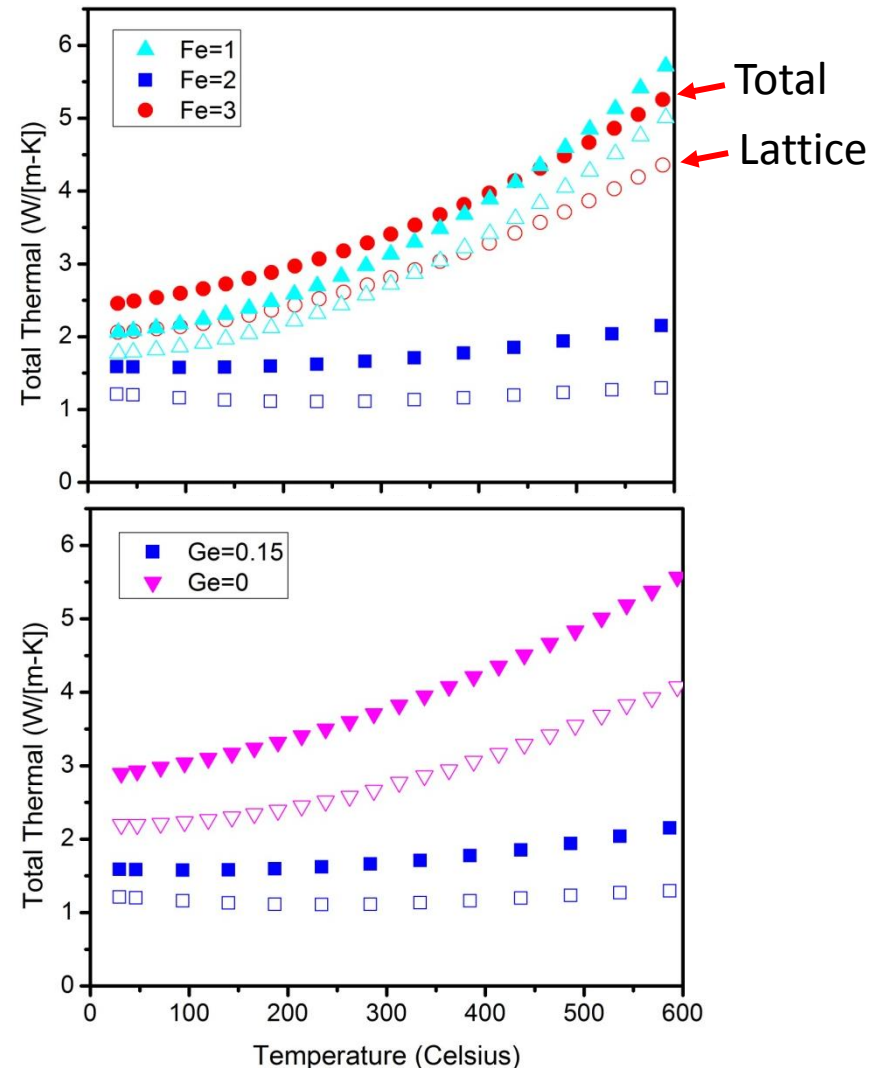


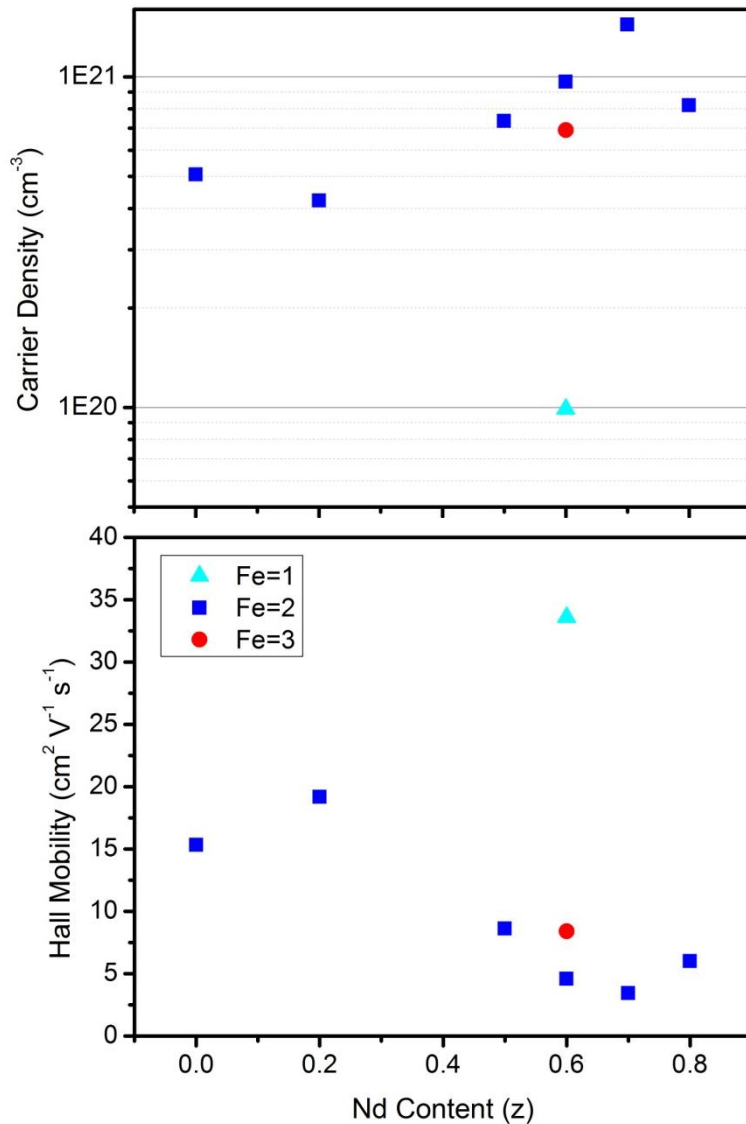

### Room Temperature Hall

- Carrier density increases with Nd content up to 0.7, while hall mobility decreases.
- Carrier density and hall mobility show strongest change as a result of Fe content.
  - Hall mobility is minimized and carrier density maximized for Fe content of 2.
  - Fe content of 1 produces the lowest carrier density and highest mobility.
- SPB modeling on the system shows optimal ZT around  $2 \times 10^{19} \text{ cm}^{-3}$ .

### Repeated Electrical Testing

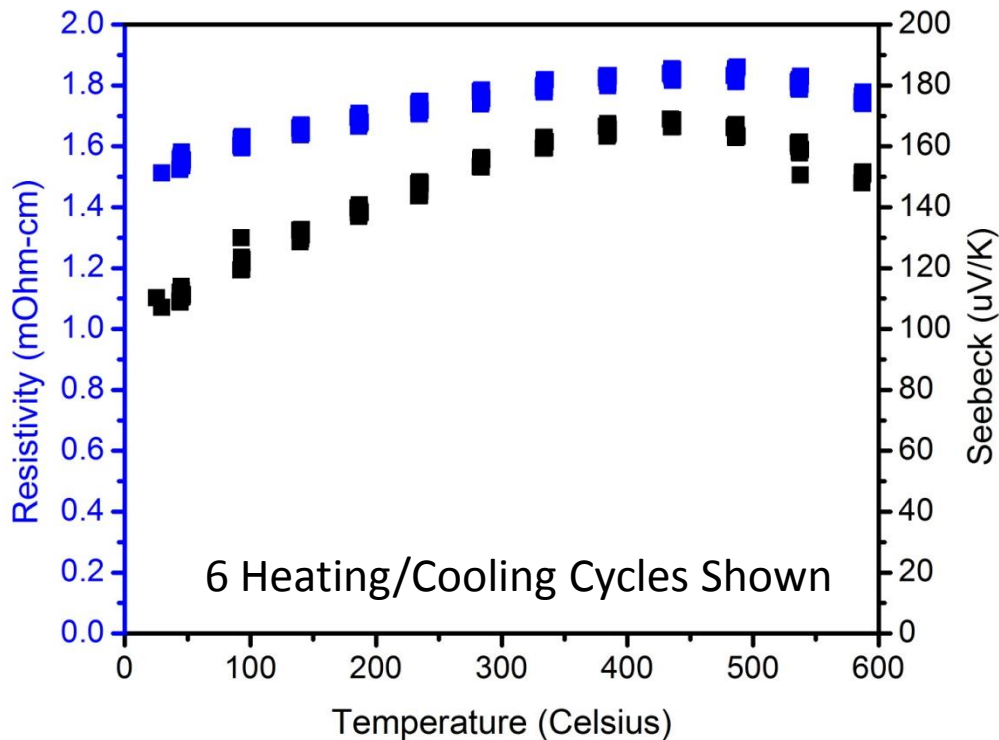

### Property Stability

- Electrical properties were tested on slow repeating loops, to investigate phase stability.
- Samples were measured from 25 to 600°C, on 18 hour loops.
- No change observed after 6 cycles.
- XRD of samples annealed at 650°C for 72 hours in N<sub>2</sub> atmosphere showed no change in phase content.

## Conclusions

- Fe and Nd content are critical in phase purity of the skutterudite phase, while Ge plays a lesser role.
- Microstructures of hot pressed samples are composed primarily of 1-2  $\mu\text{m}$  grains of SKD with  $\text{FeSb}_2$  and Sb phases.
- Electrical and thermal properties are dependant on Nd, Fe, and Ge level.
  - Highest figure of merit was achieved for  $\text{Nd}_{0.6}\text{Fe}_2\text{Co}_2\text{Sb}_{11.85}\text{Ge}_{0.15}$  peak ZT 0.6.
  - Published literature reported ZT 1.1 for the same composition.
  - 45% discrepancy may be partially attributed to experimental uncertainty, but not totally.
- Electrical properties and XRD phase are thermally stable.

## Acknowledgements

Tom Sabo, Ben Kowalski  
Case Western Reserve University  
Bethany Hudak, Dr. Beth Guiton  
University of Kentucky  
Dr. Sabah Bux, Dr. Jean-Pierre Fleurial  
NASA JPL

NASA Cooperative Agreement:  
NNX08AB43A

NASA/USRA Contract:  
04555-004

