

N95- 20528**FINAL RESULTS OF THE ADVANCED PHOTOVOLTAIC EXPERIMENT**

David J. Brinker
NASA Lewis Research Center
Cleveland, Ohio

and

John R. Hickey
The Eppley Laboratory, Inc.
Newport, Rhode Island

SUMMARY

The Advanced Photovoltaic Experiment was designed to generate laboratory reference standards as well as to explore the durability of a wide variety of space solar cells. In addition to the cells, it was equipped with an absolute cavity radiometer to measure solar intensity, a spectroradiometer to measure the spectral content of this radiation and a sun angle sensor. Data from the solar cells and various sensors was obtained on a daily basis during the first eleven months of the 69 month flight. In this paper we compare pre-flight and post-flight laboratory measurements with on-orbit calibration data. Pre-flight and post-flight calibration data of the cavity radiometer as well as on-orbit data demonstrated the accuracy and durability of the Eppley Labs. instrument flown on APEX.

INTRODUCTION AND EXPERIMENT DESCRIPTION

The Advanced Photovoltaic Experiment (APEX) is a space flight test designed to provide reference cell standards for laboratory photovoltaic performance measurements as well as to investigate the solar spectrum and the effect of long term exposure of solar cells to the space environment. Toward this end, 155 solar cells of the widest available variety of design and material were incorporated into the experiment along with sensors to measure total solar irradiance and sun angle. Experimental measurements were made on a daily basis, dependent upon the achievement of proper sun angles, and recorded on an on-board magnetic tape recorder. The experiment was designed around the original flight time of one year, with battery capacity the principal lifetime limiting factor. Useful data was in fact obtained for 325 days, at which time the voltage of the batteries supplying the data acquisition system fell below the threshold necessary for calibrated operation. Details of the design and operation of APEX have been previously published (ref. 1,2).

When the announcement of opportunity for LDEF experiments was released in 1976, a launch of about 1980 was envisioned. As a result, the solar cell samples prepared for APEX represented the state-of-the-art in space cell technology as of 1979, as well as samples of cells in use on a variety of satellites. A Shuttle-caused delay in the launch of LDEF by several years provided both the opportunity and necessity for updating the sample set, to one including the most recent advances in technology. The cell investigators were invited in mid-1982 to submit new cells. Of the 136 calibration cells (120 Isc and 16 IV cells), 69 were replaced. Many of those which were not replaced were either standards previously calibrated by other techniques or representative of cells in use on a variety of satellites.

These APEX solar cell investigators and the number of cells each supplied are:

A.F. Wright Aeronautical Laboratory	8
Applied Solar Energy Corporation	14
COMSAT Laboratories	7
European Space Agency	9
Jet Propulsion Laboratory	34
NASA Lewis Research Center	56 (Includes 19 sensor cells)
NASA Marshall Space Flight Center	11
Solarex Corporation	7
Spectrolab, Inc.	9

Each group provided cells representative of technologies which were either in development or production. The experiment was designed to accommodate a total of 155 such cells, including the silicon cells which were employed as sensors for the spectral radiometer portion of the experiment. All cells were permanently mounted on aluminum plates with a thermistor in contact with the rear of the cell. 139 cells were designated as Isc cells, 120 to be calibrated as reference standards and returned to the investigators, eighteen for use as spectral radiometer sensors and one as a night sensor to signal the data acquisition system that conditions were correct for the requisite periodic calibration of the cavity radiometer. For these cells, the short-circuit current was converted to a voltage through the use of a precision load resistor. In most cases a 0.1 Ω value was used. The remaining sixteen cells were designated IV cells, that is the entire current - voltage characteristic was measured through the loading of the cell by a series of five appropriately sized resistors.

At that time, Si cells were the only type in production, with the development of gallium arsenide in its early stages. This is reflected in the distribution of these semiconductor types in the APEX complement, which is summarized by cell type and size below:

Silicon: 105	2 x 2 cm	Gallium Arsenide: 10	2 x 2 cm
21	2 x 4 cm	<u>1</u>	1.3 x 1.6 cm
2	5 x 5 cm	11	
15	5.9 x 5.9 cm		
<u>1</u>	6 x 6 cm (module)		
144			

The cells were mounted on 127 aluminum plates of twelve different sizes and configurations. 28 of the mounts each held two 2 x 2 cm cells. Each mount was equipped with a Yellow Springs Instruments Type 16429 thermistor (10,000 Ω @ 25 °C). An additional thermistor monitored the Eppley absolute cavity radiometer.

SENSOR RESULTS

A detailed examination and recalibration of the various sensors and instruments on APEX was performed. The Eppley Type HF absolute cavity radiometer was of particular interest in that it is the only radiometer ever returned from an extended stay in space. It is identical to an instrument that has provided over 12 years of data as part of the Earth Radiation Budget experiment on Nimbus 7. After detailed examination at the Eppley

Laboratories, it was intercompared with standards at the World Radiation Center in Davos, Switzerland (ref. 3). As seen in Table I, the 69 months in-orbit had little effect on the radiometer. Its sensitivity was essentially unchanged, as was the its reflectance, in agreement with the results of visual inspections.

A spectroradiometer was included in APEX to measure the spectral content of the extraterrestrial sunlight. After return, it was intended that the instrument be used for calibration of laboratory solar simulators. The spectroradiometer consisted of sixteen identical silicon cells with narrow bandpass optical filters. The wavelength center of the filters ranged from 325 nm to 1100, with the last filter covering the infrared out to 2000 nm. Figure 1 compares values of solar irradiance from the APEX flight data with the World Meteorological Organization (WMO) standard. A comparison of pre-flight and post-flight transmittance of the first thirteen filters is seen in Figure 2. The drastic change in transmittance in many filter is clearly seen, although there was no major shift in wavelength band. This degradation was, of course, unexpected and has made the instrument unsuitable for further use in the laboratory. An explanation of the effect or its probable cause has not been forthcoming from the filter manufacturer (ref. 4).

The Digital Sun Angle Sensor (DSAS) was removed and returned to the manufacturer, Adcole Corporation, for recalibration. Its performance was unchanged due to the flight. One of the two graticules was cratered from a collision with a debris/micrometeoroid particle. Shadowing from the crater was evidence at the extreme angle limit of the DSAS (32°), but did not otherwise effect its performance. The instrument operated flawlessly during the data taking portion of the flight.

SOLAR CELL RESULTS

The overall condition of the cell sample set was excellent. A contaminating film seen over much of LDEF was present to a varying degree on APEX, the thickness of the layer dependent upon location. No loss of cell coverglass nor significant changes in color or appearance was observed. Several of the cells were cratered from micrometeoroid and/or debris impacts, with the range of damage spanning from microscopic craters in the coverglass surface to penetration of the coverglass and cell and cratering of the underlying aluminum mounting plate. However, even the few cells in which the cratering extended into the solar cell itself, or caused a crack in the coverglass and cell, electrical continuity was maintained. Loss in current proportional to the damage area and increase in fill factor due to cell cracking was observed. The electrical leads from the mounting plate feedthrough to the cell front and rear contacts were found to open in six cells. A silver ribbon of about 3 mil thickness was used for these cells. Where the flat portion of the ribbon faced the ram direction, the ribbon was severely eroded, creating an open circuit. In most cases the ribbon twisted through 90° at the feedthrough so that the narrow (3 mil) edge faced the ram direction; here the silver ribbon remained intact. Examination of the flight data indicates that the erosion did not occur to any extent that would affect cell performance during the data recording portion of the flight, the first eleven months. Post-flight performance testing of these cells was accomplished by direct probing of the cell contacts, no significant change from pre-flight performance was seen.

The first post-flight electrical test performed was measurement of the short-circuit

current utilizing the precision load resistor mounted on each cell for the flight. The resistors were soldered to the cell mounting plate electrical feedthroughs on the underside of the cell mounting plates. These measurements, as well as subsequent current-voltage (I-V) tests, were carried out in the Solar Cell Evaluation Laboratory at Lewis Research Center using a Spectrolab X-25L solar simulator. This simulator employs a short-arc xenon lamp as the light source and provides uniform, collimated illumination. The intensity of the simulator was set using an aircraft calibrated silicon standard which is identical to the standard used at Eppley Laboratory for pre-flight testing, where a xenon arc lamp simulator was also utilized. Cell temperature was monitored using the flight thermistors. One thermistor was found to be open. An examination of the flight data showed abnormal readings from it, indicating that the failure occurred before launch. With this sole exception, all of the thermistors functioned properly, providing values in close agreement with a temperature sensor used in controlling the laboratory test fixture. The short-circuit current values obtained in these test are useful in comparison with both pre-flight performance and flight data. The values obtained were in most cases in good agreement with pre-flight values, with the exception of those cells without a coverglass.

Upon completion of the measurement of short-circuit current, the load resistor was removed from the circuit by cutting one of its two leads. If LDEF had been retrieved on schedule and the value of the cells as calibration standards was retained, the load resistors could not have been removed. However, the absence of data from the last five years on-orbit negates their usefulness as standards. The complete I-V characteristic of all cells were then measured at 25 °C and recorded. Table II compares flight data with pre- and post-flight simulator data for a small representative sampling of the silicon cells. All data presented here is corrected to 25 °C and one AM0 sun (136.7 mW/cm²). All of these cells are n-p type, as were most of the silicon cells flown. Also included is the value of short-circuit current as measured on-orbit.

The loss in voltage and current in the unglassed cells (cells ISC 63 and ISC 83) was consistent with the proton radiation flux of the 250 nm, 28° inclination orbit. The variation in pre-flight to post-flight I_{sc} for the last four cells of Table II is typical of the entire cells set; the variation was within about ±2%. It is believed that this variation was due to inherent differences in the LeRC simulator and data acquisition system used for post-flight testing and those at Eppley Labs used for pre-flight testing. Pre-flight testing was not performed at LeRC as it was expected that the APEX cells would be used as calibrated reference cells; the evolution of the experiment into a long term durability test was neither expected nor ever contemplated. The I-V characteristic of 16 cells was measured by first recording the open-circuit voltage and then switching in five load resistors and recording cell current and voltage for each. The excellent agreement of the on-orbit I-V data (black squares) with the post-flight laboratory data of a Solar Maximum Mission cell is shown (Figure 3).

A summary of results from GaAs cells is shown in Table III. Of the eleven GaAs cells flown, ten were made by Hughes Research Laboratory using liquid phase epitaxy, the only type of GaAs cells then available. These cells had junction depths of either 0.35 μm or 0.50 μm and were flown with either a 12 mil fused silica coverglass or unglassed. The performance degradation, particularly in open-circuit voltage, of the uncovered cells is consistent with the known radiation characteristics of these cells and the mostly proton flux of the orbit. The eleventh GaAs cell was a metal-oxide-semiconductor design which was

under study at that time as a low fabrication cost alternative to epitaxial growth for III-V compounds. It has a very thick coverglass of unknown thickness and material and degraded significantly in short-circuit current. The accuracy of the preflight I_{sc} value is suspect.

Detailed discussion of other cells in the set, particularly those which sustained physical damage from micrometeoroids/debris, can be found in references 2 and 5.

CONCLUSION

The solar cells and sensors flown on APEX survived well their nearly six years in low earth orbit. Post-flight testing of the Eppley cavity radiometer shows that it is essentially unchanged from its pre-flight condition. The solar cell set survived equally well, with no evidence of electrical or physical changes except in those cases where debris or micrometeoroids cratered the cells. Pre-flight and post-flight performance measurements are in very good agreement.

REFERENCES

1. Brinker, D.J.; Hart, R.E. and Hickey, J.R.: Preliminary Results from the Advanced Photovoltaic Experiment Flight Test, 21st IEEE Photovoltaic Specialists Conference, 1990, pp 1213-1218.
2. Brinker, D.J.; Hickey, J.R. and Scheiman, D.A., Advanced Photovoltaic Experiment, S0014: Preliminary Flight Results and Post-Flight Findings, 1st LDEF Post-Retrieval Symposium, June 1991, NASA CP 3134, pp 1395-1404.
3. Hickey, J.R., Passive Exposure of Earth Radiation Budget Experiment Components, LDEF Experiment AO-147: Post-Flight Examinations and Tests, 1st LDEF Post-Retrieval Symposium, June 1991, NASA CP 3134, pp 1493-1510.
4. Hickey, J.R.; Brinker, D.J. and Jenkins, P.P., Studies of Effects on Optical Components and Sensors: LDEF Experiments AO-147 (ERB Components) and S-0014 (APEX), 2nd LDEF Post-Retrieval Symposium, June 1992, NASA CP-3194, pp. 1375-1388.
5. Brinker, D.J.; Hickey, J.R. and Scheiman, D.A., The Effect of the Low Earth Orbit Environment on Space Solar Cells: Results of the Advanced Photovoltaic Experiment (S0014), 2nd LDEF Post-Retrieval Symposium, June 1992, NASA CP-3194, pp. 1291-1302.

Table 1 - Cavity Radiometer Tests and Comparisons

	Pre-Flight	Post-Flight	% Change
Heater Resistance (Ω)	152.2	152.2	0.00
Thermopile Resistance (Ω)	354.4	354.7	0.08
Power Sensitivity Ratio (Vac/Atm)	1.2146	1.2126	-0.16
Intercomparison With World Radiation Reference			
APEX Instrument		1.00069	
EPLAB Reference Instrument		1.00002	
Reflectance Measurement (WRC)			
APEX Instrument		250 \pm 80 ppm	
New cavity		270 \pm 80 ppm	

Table 2 - Silicon Cell Data

Cell Number	Description	Coverglass	Isc (mA)		
			Pre-Flight	Flight	Post-Flight
ISC 63, NA-10	Solarex, BSF/R	No Cover	146.9	144.6	133.5 (Δ Voc=-65 mV)
ISC 83, B-21R	LeRC A/C AStand.	No cover	150.1	152	145.4 (Δ Voc=-46 mV)
ISC 86, B2SOF	COMSAT, Intsat 5	6 mil F.S.	288.2	300.9	292.3
ISC 95, M-5	ASEC, 6x6 W/A	6 mil F.S.	1199	881.3	1195
ISC 112, B-2R	COMSAT Blue	30 mil V-Groove	160	178.6	163.7
ISC 114, B-4R	COMSAT Non-Ref.	12 mil F.S.	193.1	202.7	189.3

Table III - Gallium Arsenide Cell Data

Cell Number	Description	Coverglass	Isc (mA)		
			Pre-Flight	Flight	Post-Flight
ISC 71, NB-15L	HRL, Dj=0.5 μm	12 mil F.S.	122.5	116.1	108 ($\Delta\text{Voc}=10\text{ mV}$)
ISC 76, NB-29R	HRL, Dj=0.5 μm	No cover	117.2	111.6	95.5 ($\Delta\text{Voc}=-65\text{ mV}$)
ISC 77, NB-29L	HRL, Dj=0.35 μm	No Cover	117.3	113.1	93.6 ($\Delta\text{Voc}=-85\text{ mV}$)
ISC 111, A-2	JPL, AMOS	Unknown	17.6	33.6	22

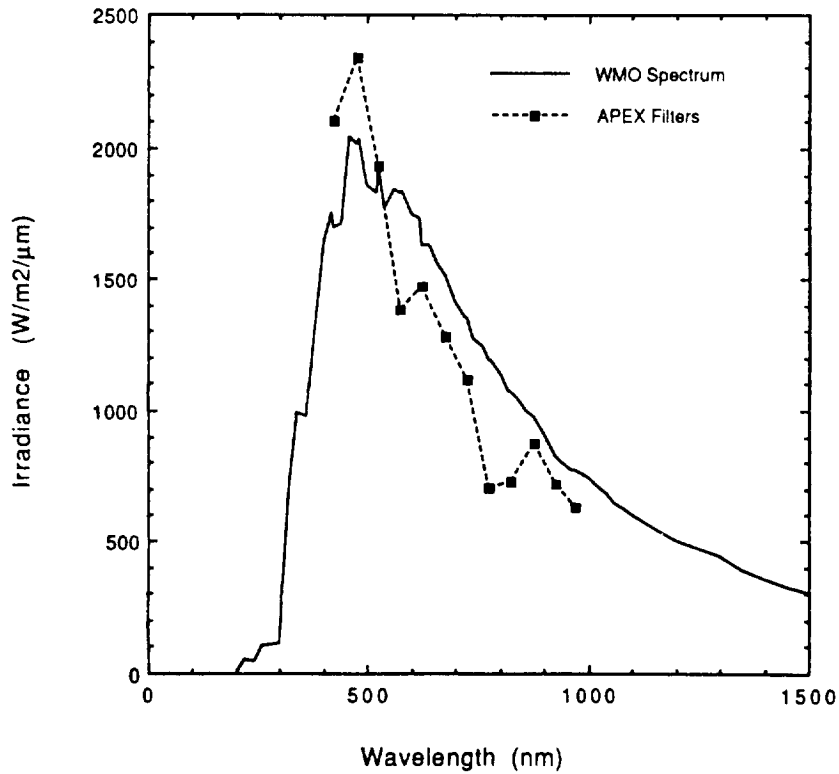


Figure 1 - APEX Filter Data Compared With WMO Spectrum

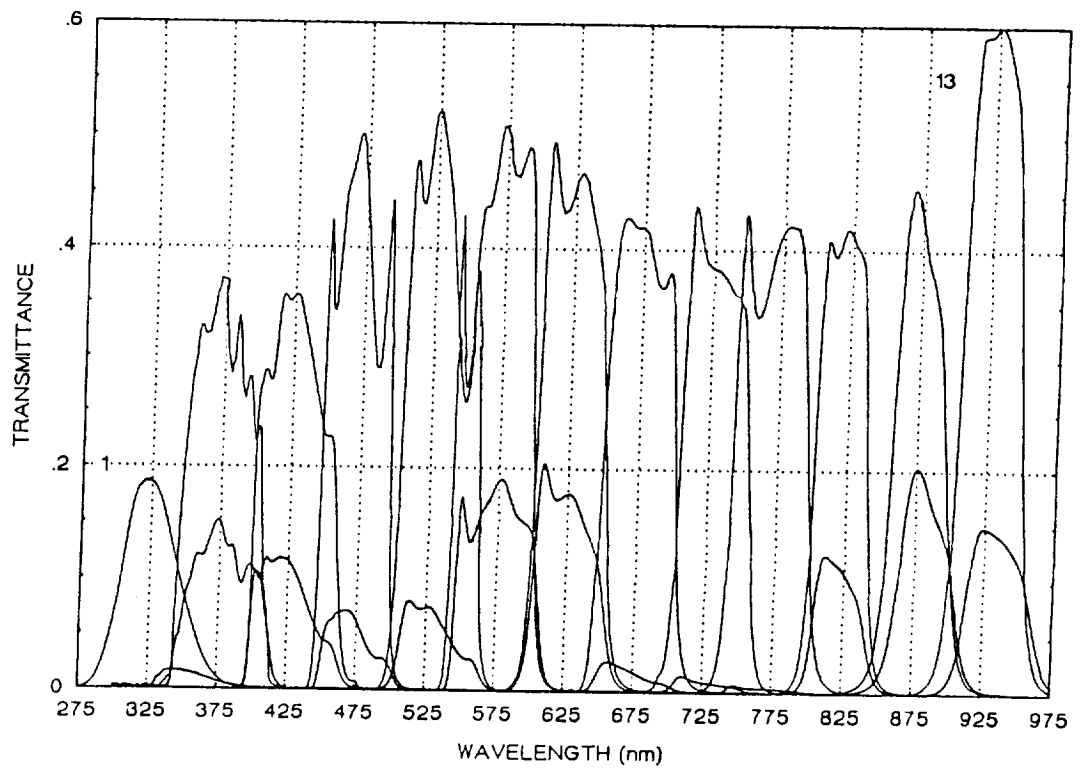


Figure 2 - Transmittance of APEX Filters 1 to 13

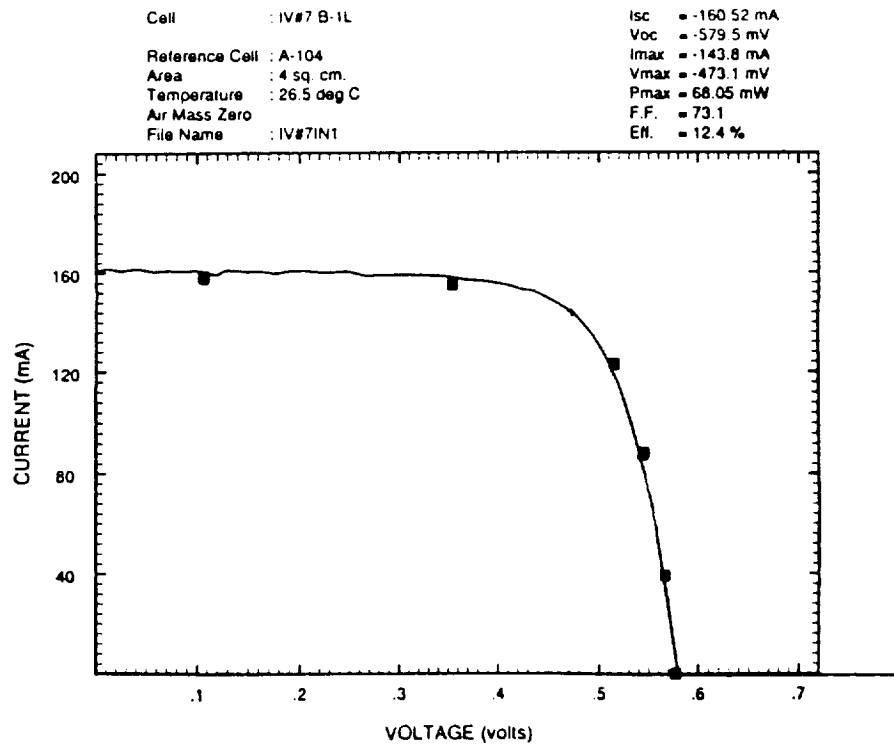


Figure 3 - I-V Curve of Solar Maximum Mission Cell