

11-5  
126275  
p-23

NASA Technical Memorandum 105885

# Parameterization of Solar Cells

J. Appelbaum, A. Chait, and  
D. Thompson  
*Lewis Research Center*  
*Cleveland, Ohio*

October 1992



(NASA-TM-105885) PARAMETERIZATION  
OF SOLAR CELLS (NASA) 23 p

N93-12301

Unclas

G3/33 0126275



## PARAMETERIZATION OF SOLAR CELLS :

J. Appelbaum,<sup>\*</sup> A. Chait, and D. Thompson  
National Aeronautics and Space Administration  
Lewis Research Center  
Cleveland, Ohio 44135

### SUMMARY

E-7188

The aggregation (sorting) of the individual solar cells into an array is commonly based on a single operating point on the I-V characteristic curve. An alternative approach for cell performance prediction and cell screening is provided by modeling the cell using an equivalent electrical circuit, in which the parameters involved are related to the physical phenomena in the device. These analytical models may be represented by a double exponential I-V characteristic with seven parameters, by a double exponential model with five parameters, or by a single exponential equation with four or five parameters. In this article we address issues concerning methodologies for the determination of solar cell parameters based on measured data points of the I-V characteristic, and introduce a procedure for screening of solar cells for arrays. We show that common curve fitting techniques, e.g., least squares, may produce many combinations of parameter values while maintaining a good fit between the fitted and measured I-V characteristics of the cell. Therefore, techniques relying on curve fitting criteria alone cannot be directly used for cell parameterization. We propose a consistent procedure which takes into account the entire set of parameter values for a batch of cells. This procedure is based on a definition of a mean cell representing the batch, and takes into account the relative contribution of each parameter to the overall goodness of fit. The procedure is demonstrated on a batch of 50 silicon cells for Space Station Freedom.

### INTRODUCTION

The analysis of the current-voltage (I-V) characteristic of a solar cell is one of the most important diagnostic methods that may be used to characterize the solar cell. The current-voltage equation which models the solar cell by an equivalent electrical circuit contains several parameters related to physical

---

<sup>\*</sup>National Research Council—NASA Research Associate at Lewis Research Center. Present address: Tel Aviv University, Faculty of Engineering, Tel Aviv, Israel.

phenomena occurring in the device. Changes in the parameter values may reveal important information about the effects of environmental conditions (e.g., radiation effects on space solar cells) or manufacturing processes on the performance of solar cell. Another application of the I-V equation of solar cells or arrays may be in the area of photovoltaic system design and performance analysis. In this paper we propose still another application of the I-V equation in the area of cell screening and arraying, i.e., the selection of compatible cells for an array from a production batch.

The methods for determination of solar cell equation parameters from experimental data may be grouped into two types: (1) methods which use selected points of the I-V characteristic;<sup>1,2</sup> (2) methods which use all the test points.<sup>3-7</sup> By using only selected points, the methods for calculating the cell parameters may be simpler and faster, however, the main deficiency of such procedures lies in the implicit assumption that the selected points are accurately measured and thus faithfully represent the entire characteristic. In practice, measurement errors may be introduced which may result in poor parameter estimation. This effect may be more pronounced for test data taken under uncontrolled conditions. Using all test points for the determination of the cell parameters provides greater accuracy through the increase in the statistical degrees of freedom in the process.

A common technique for cell screening is based on a single operating point. However the cells in the array may not match at other operating points. In addition, the single point matching may also be affected by variation in the measurement conditions. Therefore, the screening of cells based on the entire set of test points of the I-V characteristic may insure the selection of more "identical" cells for the array.

The solar cell may be modeled with different number of parameters and with either single or double exponents. A model with seven parameters is shown in Fig. 1 and its I-V equation is:

$$I = I_{ph} - I_{01} \left\{ \exp \left[ \frac{q(V + IR_s)}{n_1 kT} \right] - 1 \right\} - I_{02} \left\{ \exp \left[ \frac{q(V + IR_s)}{n_2 kT} \right] - 1 \right\} - \frac{V + IR_s}{R_{sh}} \quad (1)$$

where  $I$  and  $V$  are the cell terminal current and voltage, respectively, and  $I_{ph}$ ,  $I_{01}$ ,  $I_{02}$ ,  $n_1$ ,  $n_2$ ,  $R_s$ , and  $R_{sh}$  are seven model parameters related to physical phenomena;  $I_{ph}$  is the photogenerated current,  $I_{01}$  and  $I_{02}$  are reverse saturation currents,  $n_1$  and  $n_2$  are ideality factors,  $R_s$  is the series resistance and  $R_{sh}$  is the shunt resistance. Another model with a double exponent but with five parameters is obtained by setting  $n_1 = 1$  and  $n_2 = 2$ . When a single exponent is used for the cell model, the I-V characteristic is written with five parameters as:

$$I = I_{ph} - I_0 \left\{ \exp \left[ \frac{q(V + IR_s)}{nkT} \right] - 1 \right\} - \frac{V + IR_s}{R_{sh}} \quad (2)$$

A model with a single exponent but with four parameters is obtained for  $R_{sh} \rightarrow \infty$ . A single exponent model is mainly used for design calculation of photovoltaic systems.

The problem of determination of the solar cell equation parameters when considering all the experimental data points is an optimization problem (known also as a curve fitting problem). The basis for the solution of the problem relies on defining an appropriate error criterion (objective function, OF) for the difference between the experimental and the theoretical characteristic curve of the solar cell, and then minimizing this criterion using optimization algorithms.

An error criterion  $\sigma$  may be defined as:

$$\sigma = \left\{ \frac{1}{N} \sum_{j=1}^N \left[ \frac{(I_{th})_j - (I_{exp})_j}{(I_{exp})_j} \right]^2 \right\}^{1/2} \quad (3)$$

where  $N$  is the total number of data points,  $(I_{th})_j$  is the theoretical generated current at voltage  $V_j$ , and  $(I_{exp})_j$  is the experimentally measured current at the same voltage  $V_j$ . This criteria may give unreliable results, mainly because of the emphasis of the error in the low current part of the characteristic. This may be overcome by using the error criterion  $\epsilon$  (normalized chi-square, CHISQ):

$$\epsilon = \frac{\left\{ \frac{1}{N} \sum_{j=1}^N [(I_{th})_j - (I_{exp})_j]^2 \right\}^{1/2}}{I_{ph}} \quad (4)$$

Another criteria is based on the area difference between the experimental and the theoretical I-V characteristics<sup>5</sup>:

$$\Delta A = \sum_{j=1}^{N-1} \left| \frac{(\Delta I_j + \Delta I_{j+1}) [(V_{exp})_{j+1} - (V_{exp})_j]}{2} \right| + \left| \frac{[(V_{exp})_{m+1} - (V_{exp})_m]}{2} \frac{(\Delta I_m)^2 + (\Delta I_{m+1})^2}{|\Delta I_m| + |\Delta I_{m+1}|} \right|$$

where  $\Delta I_j = (I_{th})_j - (I_{exp})_j$  and  $(V_{exp})_j$  is the experimental measured voltage at the  $j^{th}$  point. The second term applies for current error  $\Delta I$  changing the sign between the  $m^{th}$  and  $(m+1)^{th}$  point. The parameters obtained by this criteria will be less dependent on the distribution of the experimental points along the I-V characteristic. Normalizing  $\Delta A$  will give the error of the fit in percentage, i.e.,

$$\frac{\Delta A}{A} = \frac{\Delta A \times 100}{\sum_{j=1}^N \frac{[(I_{exp})_j + (I_{exp})_{j+1}] [(V_{exp})_{j+1} - (V_{exp})_j]}{2}} \quad (5)$$

Several minimum seeking (optimization) algorithms were used in the present study. We report here only on results obtained by two algorithms: (1) A simplex-based procedure, E04CCF and (2) A quasi-Newton method E04JAF both in the NAG Library.<sup>8</sup> Because the I-V mathematical expression form an implicit relation between I and V, the optimization procedure must involve a root finder called iteratively by the minimum seeking algorithm for the actual curve fitting. A robust root finder used in this study is the Van Wijngaarden-Dekker-Brent algorithm.<sup>9</sup>

In this work it was found that different choices of initial conditions (i.e., the initial values of the parameters) may result in substantially different sets of parameter values for the same solar cell. This issue is related to the strong nonlinearity of the model equations of the solar cell. The two alternatives

for initial conditions examined in this study are based on: (1) the measured data points of the I-V characteristic, (2) the computed data of a "mean cell" for the batch. A "mean cell," which will be defined later, may be considered as a hypothetical cell best representing all the cells in the batch. In both cases, the initial parameter values of the cell were determined by the procedure outlined in Ref. 7.

A purpose of this study is to develop a reliable and a consistent method for the determination of the solar cell parameters from the measured data points of the I-V characteristics. Another purpose is to develop a method for screening solar cells for aggregation into arrays. The study was carried out on a batch of 50 8- by 8-cm silicon solar cells of the Space Station Freedom of the preliminary design (Fig. 2). Figure 3 shows the measured data for all 50 cells at 25 °C. Each individual I-V characteristic is composed from 100 measured data points. It is clear that there is some variation in the data that can be attributed to structural differences among the cells as well as measurement errors. It should be noted that these 50 cells were already pre-screened (for a desired current range) at 0.495 V.

### ISSUES IN PARAMETERS ESTIMATION

Once a model equation is selected, the problem becomes a mathematical task of finding a set of parameters that results in the least difference between the experimental and theoretical characteristic of the solar cell. As a result, the parameters may obtain values without physical significance, such as a negative series resistance. Negative values for the parameters are avoided by squaring the components of the vector  $\phi$  of the parameters in the I-V equation.

In this work we show that optimization methods for the determination of the cell parameters may give misleading or inconsistent results. The reasons for this are numerous: the incompleteness of the solar cell model and the nonlinearity of its equation; the optimization and root finding algorithms and error criteria; machine (computer) and compiler accuracy; measurement conditions; accuracy of instrumentation; and the number and distribution of the measured points along the I-V characteristic.

The I-V equation is described by an implicit function and is highly nonlinear. The parameter values are typically of different orders of magnitude. This leads to a solution with a very flat optimum (curve

fit error criterion) in most of the parameters and is therefore insensitive to large variations in certain parameter values. For the same reason, the solution may converge to different parameter sets starting from different initial conditions.

In spite of the above mentioned issues, it is possible to obtain a good fit between the theoretical I-V equation and the experimental I-V data with an arbitrary low fitting error using different fitting methods. However, different fitting methods with the same error tolerance, may lead to widely varying different sets of solar cell parameters. This general observation is referred to in this study as the consistency problem. To obtain a consistent solution to the solar cell parameters we developed a “consistent method” defined as a method which consistently converges to “similar” parameter values for “similar” cells obtained from the same batch. In other words, our proposed method is founded on the expectation that similar cells of the batch should produce similar parameter sets.

The issues discussed above are illustrated in the following graphs and tables for a randomly selected solar cell of the batch. Figure 4 shows a good visual agreement between the theoretical curve and the measured data which include some humps indicated by arrows. The particular method used combines a seven parameter double exponential model, a simplex based optimization algorithm, a normalized area error criterion, and the measured data as initial conditions. Figure 5 shows the variation of the objective function  $\Delta A/A$  (Eq. (5)) with the photocurrent  $I_{ph}$  and the reverse saturation current  $I_{02}$ . It is clear that the error criterion is insensitive to the parameter  $I_{02}$  and its optimal value is therefore poorly defined. A better defined optimum is shown in Fig. 6 for the series resistance  $R_s$  and the reverse saturation current  $I_{01}$ . Also in this case the optimum is flat indicating of the possibility for obtaining different parameter values.

The fact that acceptable curve fits may be obtained with different sets of parameter values for the same cell, using different optimization algorithms and initial conditions with the same objective function is shown in table I. The algorithms compared are Newton and simplex based techniques; the initial conditions are based on the experimental and the mean cell data (to be defined in the next section); and



the error criteria is less than 0.5 percent. The full range of the I-V characteristic was considered in this comparison.

The parameter values obtained from the fitting process may depend on the initial conditions for the reasons mentioned before. Table II lists the parameter values of cell number ss01 obtained using 10 randomly selected (different) initial conditions, designated as ss01.01 to ss01.10. The last row shows the standard deviation of each parameter. The largest deviations are observed in  $I_{01}$  and  $I_{02}$ , representing the two most insensitive parameters. All of the parameter sets produce good fits to the experimental data as shown in Fig. 7.

The variation of the parameter  $I_{01}$ , measured in standard deviations, for the batch of 50 cells is shown in Fig. 8. Similar distributions are obtained for other parameters.

#### A CONSISTENT METHOD FOR PARAMETERS ESTIMATION

As defined in the preceding section, a consistent method is defined as a method which consistently converges to "similar" parameter values for "similar" cells from the same production batch. But since the values obtained from various fitting algorithms are different, even for arbitrary small curve fit errors, an additional examination of the parameter values is required in order to select the best (or consistent) method for cell parameterization. The consistent method then defines the combination of an optimization algorithm, an error criterion, type of initial conditions and cell model equation. The procedure for selecting the consistent method requires the definition and determination of several new concepts: (1) mean cell, (2) parameter sensitivity, (3) cell frequency, and (4) figure of merit.

##### A Mean Cell

A mean cell is defined as a cell "best" representing all the cells in a batch from an overall performance viewpoint. The procedure for determining the mean cell is as follows:

(1) For a given optimization algorithm, error criterion and cell model equation, perform a curve fit for each cell to find the cell parameters.

(2) Compute the currents (for the given cell model equation) for each cell using its parameters at the same voltage. Repeat at other voltages covering the entire I-V curve at equal intervals.

(3) Compute the average for all currents (at each particular voltage) thereby generating new data points for the I-V characteristic of a hypothetical "mean cell."

(4) Perform a fit for the mean cell.

Note that if all the experimental data points were sampled at identical voltages, the step of dividing the voltage range may be omitted. As the mean cell represents all cells in the batch its characteristics may be used for cell and system performance analysis.

### Parameter Sensitivity (P.S.)

The values of certain parameters of different cells obtained from the fitting process by various methods may be widely dispersed. This observation applies to single cells for different starting conditions as well as for cells in a production batch. The implication of this observation is that these parameters are less sensitive to the fitting error criteria whereas other parameters are more sensitive. In other words, a large change in a particular parameter value may have only a small effect on the shape of the I-V characteristic (insensitive parameter) while a large change in another parameter value may considerably effect (a sensitive parameter) on the I-V characteristic. Therefore, the parameter sensitivity is important as a measure for selecting a consistent method. The "parameter sensitivity" is defined as the effect of change in parameter value on the cell performance:

$$(PS)_j = \frac{\partial(OF)}{\partial P_j} / \max \left[ \frac{\partial(OF)}{\partial P_j} \right] \quad (6)$$

i.e., the parameter sensitivity  $(PS)_j$  of each parameter  $j$  is defined as the normalized partial derivative of the objective function, OF, with respect to the parameter in question,  $j$ , having values between 0 and 1. The parameter sensitivity ranking was found to be slightly dependent on the fitting method. The ranking of the parameters, in terms of their relative effect on the I-V characteristic was found to be

$I_{ph}$ ,  $n_2$ ,  $n_1$ ,  $I_{02}$ ,  $R_{sh}$ ,  $I_{01}$ , and  $R_s$ , where  $I_{ph}$  and  $R_s$  are the most and least sensitive parameter, respectively.

### Cell Frequency (C.F.)

Other important information which may be used in determining a consistent method is provided by the dispersion of individual parameters. For some fitting methods, the parameter values are more dispersed, while for others the variation is small. The cell frequency is computed for each parameter and is the count of cells whose parameter value does not deviate from the mean cell parameter value by more than a predetermined amount (in terms of standard deviation S.D. of the parameter):

C.F. = Count of all cell  $i$  for parameter  $j$  such that:

$$m(\text{S.D.}) > |P_{ij} - P_{mj}| \quad (7)$$

where

$m$  is the desired number of standard deviation

$P_{ij}$  is the parameter  $j$  of cell  $i$

$P_{mj}$  is the parameter  $j$  of the mean cell

The standard deviation of parameter  $j$  of each cell is computed from all the  $N$  fitted cells, i.e.,

$$\text{S.D.} = \left\{ \frac{1}{N-1} \sum_{i=1}^N [P_{ij} - P_{mj}]^2 \right\}^{1/2} \quad (8)$$

### Figure of Merit (F.M.)

A Figure of Merit for a particular parameter must take into account the sensitivity of the characteristic to variation in that parameter together with its dispersion level. An overall Figure of Merit adds the partial contributions of all parameters:

$$\text{F.M.} = \sum_{j=1}^M (\text{P.S.})_j \times (\text{CF})_j \quad (9)$$

The best or most consistent fitting method is the method resulting in the highest Figure of Merit:

$$\max[\text{F.M.}] \quad (10)$$

An example of calculation of F.M. for the fitted 50 cells is provided in Table III for one method (quasi-Newton,  $\Delta A/A$  error criteria, and a two exponents seven parameters model). The most sensitive parameter is  $I_{ph}$ , whose normalized sensitivity is 1.00. The C.F. and the F.M. for predetermined levels of dispersion in terms of standard deviations around the mean cell are also computed. As an example, for one standard deviation, the cell frequency is 38 (out of 50) cells for the parameter  $I_{ph}$ , 34 cells for  $R_s$ , etc., and the Figure of Merit is 91.73. A comparison of different methods, using one standard deviation and initial conditions computed from the measured data, is shown in Table IV. The most consistent method (F.M. = 91.73) is provided by using a quasi-Newton procedure, with  $\Delta A/A$  error criteria and a two exponents seven parameter model.

#### CELL PARAMETERS

The determination of the cell parameters may be required for cells in a production batch and for individual cells. Even by using the method with the highest Figure of Merit a variation in parameter values is still obtained. Therefore, an alternative concept of a representative cell must be defined for cells in a production batch. Such a hypothetical cell, best representing the entire batch, was defined earlier as the "mean cell." Using the most consistent method, the values of the mean cell parameters for the batch of 50 silicon cells used in this paper and their variations, in one standard deviation, are tabulated in Table V.

The concept of a representative cell for a production batch may be used also for a single cell. By randomly varying  $N$  times the initial conditions during the fitting process and using a single cell experimental data, one obtains a batch of  $N$  fitted cells with  $N$  sets of parameter values. Since all the sets of parameters correspond to the same physical cell, a mean cell may be properly defined from these sets. The parameter values of this mean cell for  $N = 10$  are provided in Table II, and a composite plot of all 10 curve fits is shown in Fig. 7. As discussed earlier, no distinguishable differences can be found among the individual fits even though their individual parameter values are quite different.

## CELL SCREENING

The selection of compatible solar cells for an array from a production batch is commonly done on the basis of a single operating point, e.g., the maximum power point. To screen cells based on an approach more faithful to their entire performance characteristics necessitates the determination of model parameters. Because of the difficulties in obtaining unique parameter values, methods which explicitly screen cells by comparing parameter values are not warranted. However, the concept of the mean cell as the cell best representing the entire batch may be used for cell screening. The requirement of similar performance from the cells in the array can be expressed in terms of a similarity of the overall I-V characteristic of individual cells in the batch to the mean cell. A comparison of each cell to the mean cell may be computed by subtracting their respective total area under the I-V characteristic. When normalized, this  $\Delta A/A$  represents the overall deviation from performance view point of each cell from the average performance of the batch. Alternatively, one may compare each cell to the mean cell by computing the chi square error. Once a comparison is made, a ranking of the cells in terms of their similarity to the mean cell may be done, as shown in Table VI for the 50 cells used in the study. To chose K cells for an array from the given production batch, one simply selects the top K cells in the list. Table VI shows that the most similar cell to the mean cell is number 33, 14 cells deviate by less than 1 percent from the mean cell; 35 cells deviate by less than 2 percent, etc. The distribution of the measured I-V characteristics of the 50 cells for a given percent deviation from the mean cell is shown in Fig. 9. It is visually evident that the selection rule proposed results in cells whose characteristic curves are similar.

## DISCUSSION

The parameters of solar cell I-V equation are related to physical phenomena occurring in the device. Changes in the parameter values may reveal important information about the operating environment or manufacturing processes of the cell. The solar cell parameters are also needed for cell or PV system analysis. In this study we proposed another application of the cell parameters, namely, screening of solar

cells for aggregation into arrays. For all of these applications, the determination of the cell parameters may be based on a small number of selected points. However, ignoring the overall I-V characteristic may lead to erroneous values for the parameters and to a mismatch among the cells in the array at different operating points. Using test points representing the entire I-V characteristic for the determination of the cell parameters may give more reliable values for the parameters.

The estimation of cell parameters based on a set of test points resorts to optimization techniques where the difference between the experimental and the theoretical fitted characteristic of the cell is minimized. As such, the solution (i.e., the parameter values) is shown in this study to be nonunique and is subjected to nontrivial computational issues. To obtain a consistent solution to the cell parameters we proposed an additional requirement from the solution. We identified a "consistent method" which was defined as a method which consistently converges to "similar parameters" for "similar" cells. Identifying a consistent method necessitated the introduction of several new concepts: a mean cell; parameter sensitivity; cell frequency; and a Figure of Merit. These concepts were incorporated into a "Figure of Merit" resulting in a recommended fitting method and error criteria for the determination of the solar cell parameter values. The "mean cell" is defined as a hypothetical cell "best" representing all the cells in the batch from the total performance viewpoint. The mean cell concept may also be used for cell and array performance analysis. The "parameter sensitivity" which determines the effect of change in parameter value on the objective function (or cell performance) may be useful also for cell design and manufacturing. Finally, screening of cells for arrays in a consistent manner based on the entire I-V characteristic was also proposed in this study using the mean cell concept.

#### ACKNOWLEDGMENT

The authors would like to acknowledge Bernard L. Sater of NASA Lewis Research Center for supplying the measured data of the cells.

## REFERENCES

1. K.L. Kennerud, "Analysis of Performance Degradation in CdS Solar Cells," IEEE Transactions on Aerospace and Electronic Systems, AES-5, 912-917 (1969).
2. J.P. Charles, et al., "A Practical Method of Analysis of the Current-Voltage Characteristics of Solar Cells," Solar Cells, 169-178 (1981).
3. F.J. Bryant, and R.W. Glew, "Analysis of Current-Voltage Characteristics of Cadmium Sulphide Solar Cells Under Light Intensities," Energy Conversion, 14, 129-133 (1975).
4. A. Braunstein, J. Bany, and J. Appelbaum, "Determination of Solar Cell Equation Parameters From Empirical Data," Energy Conversion, 17, 1-6 (1977).
5. J.C.H. Phang, and D.S.H. Chan, "A Review of Curve Fitting Error Criteria for Solar Cell I-V Characteristics," Solar Cells, 18, 1-12 (1986).
6. J. Cabestany, and L. Castaner, "Evaluation of Solar Cell Parameters by Nonlinear Algorithms," Journal of Physics D: Applied Physics, 16, 2547-2558 (1986).
7. A. Polman, et al., "A New Method for the Evaluation of Solar Cell Parameters," Solar Cells, 17, 241-251 (1986).
8. NAG Inc., 1990, Downers Grove, IL, U.S.A.
9. R.P. Brent, Algorithms For Minimization Without Derivatives. Prentice-Hall, 1973.

TABLE I.—DIFFERENT SET OF PARAMETERS FOR THE SAME CELL

[Seven parameter model, error criteria  $\Delta A/A$ , full I-V range.]

Algorithm	Initial condition	$I_{ph}$ [A]	$R_s$ [ $\Omega$ ]	$R_{sh}$ [ $\Omega$ ]	$I_{01}$ [A]	$I_{02}$ [A]	$n_1$	$n_2$	$\Delta A/A$
Newton	Experimental data	2.61	$7.39 \times 10^{-3}$	2.98	$7.95 \times 10^{-11}$	$1.15 \times 10^{-5}$	1.00	2.00	$1.60 \times 10^{-3}$
Newton	Mean	2.61	$6.12 \times 10^{-3}$	3.24	$6.50 \times 10^{-11}$	$1.76 \times 10^{-5}$	1.00	2.06	$1.79 \times 10^{-3}$
Simplex	Experimental data	2.60	$8.24 \times 10^{-4}$	3.22	$3.64 \times 10^{-11}$	$1.33 \times 10^{-5}$	1.05	1.94	$2.17 \times 10^{-3}$
Simplex	Mean	2.60	$1.26 \times 10^{-5}$	3.33	$6.77 \times 10^{-11}$	$1.67 \times 10^{-5}$	.99	1.97	$2.35 \times 10^{-3}$

TABLE II.—DIFFERENT SET OF PARAMETERS FOR DIFFERENT INITIAL CONDITIONS

$I_{ph}$ [A]	$R_s$ [ $\Omega$ ]	$R_{sh}$ [ $\Omega$ ]	$I_{01}$ [A]	$I_{02}$ [A]	$n_1$	$n_2$	$\Delta A/A$	Cell
2.609	$7.59 \times 10^{-03}$	$3.10 \times 10^{00}$	$2.16 \times 10^{-10}$	$2.01 \times 10^{-05}$	1.04	2.13	$1.59 \times 10^{-03}$	ss01.01
2.610	$7.28 \times 10^{-03}$	$2.98 \times 10^{00}$	$8.29 \times 10^{-11}$	$1.18 \times 10^{-05}$	1.01	2.00	$1.59 \times 10^{-03}$	ss01.02
2.606	$4.18 \times 10^{-03}$	$3.04 \times 10^{00}$	$3.19 \times 10^{-11}$	$8.55 \times 10^{-06}$	.99	1.90	$1.91 \times 10^{-03}$	ss01.03
2.609	$7.76 \times 10^{-03}$	$3.12 \times 10^{00}$	$1.54 \times 10^{-10}$	$2.07 \times 10^{-05}$	1.03	2.13	$1.59 \times 10^{-03}$	ss01.04
2.609	$6.44 \times 10^{-03}$	$2.98 \times 10^{00}$	$2.86 \times 10^{-10}$	$1.14 \times 10^{-05}$	1.06	1.99	$1.81 \times 10^{-03}$	ss01.05
2.612	$8.27 \times 10^{-03}$	$3.04 \times 10^{00}$	$1.26 \times 10^{-10}$	$2.03 \times 10^{-05}$	1.02	2.14	$1.58 \times 10^{-03}$	ss01.06
2.607	$7.96 \times 10^{-03}$	$3.21 \times 10^{00}$	$3.05 \times 10^{-11}$	$1.60 \times 10^{-05}$	.96	2.06	$1.64 \times 10^{-03}$	ss01.07
2.610	$7.23 \times 10^{-03}$	$2.97 \times 10^{00}$	$3.65 \times 10^{-11}$	$1.01 \times 10^{-05}$	.97	1.97	$1.61 \times 10^{-03}$	ss01.08
2.605	$4.84 \times 10^{-03}$	$3.12 \times 10^{00}$	$1.45 \times 10^{-11}$	$1.18 \times 10^{-05}$	.95	1.96	$1.90 \times 10^{-03}$	ss01.09
2.609	$8.56 \times 10^{-03}$	$3.15 \times 10^{00}$	$8.05 \times 10^{-11}$	$2.23 \times 10^{-05}$	1.00	2.15	$1.60 \times 10^{-03}$	ss01.10
2.609	$7.04 \times 10^{-03}$	$3.07 \times 10^{00}$	$1.17 \times 10^{-10}$	$1.47 \times 10^{-05}$	1.02	2.04	$4.56 \times 10^{-06}$	ss01.mean
$2.03 \times 10^{-3}$	$1.45 \times 10^{-03}$	$8.36 \times 10^{-02}$	$9.06 \times 10^{-11}$	$5.20 \times 10^{-06}$	$3.95 \times 10^{-2}$	$2.19 \times 10^{-2}$	Standard deviation	

TABLE III.—PARAMETER SENSITIVITY AND CELL FREQUENCY

	$I_{ph}$	$R_s$	$R_{sh}$	$I_{01}$	$I_{02}$	$n_1$	$n_2$	S.D.	F.M.
P.S.	$1.00 \times 10^{00}$	$9.60 \times 10^{-03}$	$2.91 \times 10^{-02}$	$1.25 \times 10^{-02}$	$6.21 \times 10^{-02}$	$1.01 \times 10^{-02}$	$1.90 \times 10^{-02}$		
C.F.	24	27	23	30	45	33	32	0.50	64.76
	36	34	42	45	48	39	45	1.00	91.73
	44	42	44	49	48	42	48	1.50	101.32
	46	49	45	49	48	45	48	2.00	104.60
	48	49	48	49	48	48	48	2.50	107.87

TABLE IV.—ORDER OF METHODS FOR

FIGURE OF MERIT, max[F.M.]

[Measured points as initial conditions, one standard deviation.]

Optimization algorithm	Cell model equation	Error criteria	F.M.
Newton	7 parameters, 2 exponents	$\Delta A/A$	91.73
Simplex	7 parameters, 2 exponents	Chisq	78.94
Simplex	7 parameters, 2 exponents	$\Delta A/A$	72.52
Newton	7 parameters, 2 exponents	Chisq	42.20
Newton	5 parameters, 2 exponents	Chisq	37.87
Simplex	5 parameters, 2 exponents	$\Delta A/A$	32.48



TABLE V.—MEAN CELL  
PARAMETERS OF  
50 SOLAR CELL  
BATCH

$I_{ph} = 2.614 \text{ A}$
$R_s = 6.13 \times 10^{-3} \Omega$
$R_{sh} = 3.49 \times 10^0 \Omega$
$I_{01} = 4.09 \times 10^{-11} \text{ A}$
$I_{02} = 1.77 \times 10^{-5} \text{ A}$
$n_1 = 0.99$
$n_2 = 2.06$

TABLE VI.—CELL SCREENING

$\Delta A/A$	Cell number	Percent deviation	Number of cells
0.003515 .003626 .004049 .005013 .005042 .005342 .005488 .005907 .007099 .007243 .008173 .008818 .009260 .009412	ss33 ss40 ss04 ss34 ss37 ss10 ss32 ss44 ss24 ss25 ss07 ss08 ss20 ss27	1	14
0.010099 .010205 .010275 .010364 .010623 .010754 .011106 .011852 .011885 .011973 .012832 .013513 .014422 .014787 .015070 .015277 .016281 .017097 .017269 .018430 .018609	ss14 ss49 ss31 ss29 ss18 ss02 ss16 ss36 ss45 ss48 ss42 ss50 ss26 ss01 ss19 ss30 ss47 ss28 ss03 ss22 ss15	2	35
0.020316 .021644 .022172 .023247 .023364 .023542 .024410 .024429 .024841 .025179 .026600	ss09 ss06 ss41 ss39 ss38 ss11 ss12 ss35 ss17 ss13 ss46	3	46
0.030859 .032218 .034946 .035750	ss43 ss21 ss05 ss23	4	50

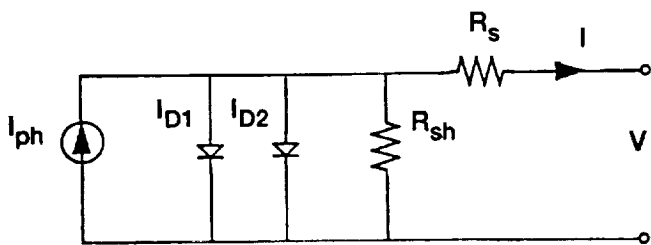


Figure 1.—Electrical equivalent circuit of a solar cell.

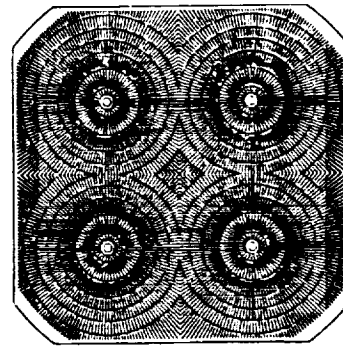


Figure 2.—8-by 8-cm silicon solar cell of Space Station Freedom.

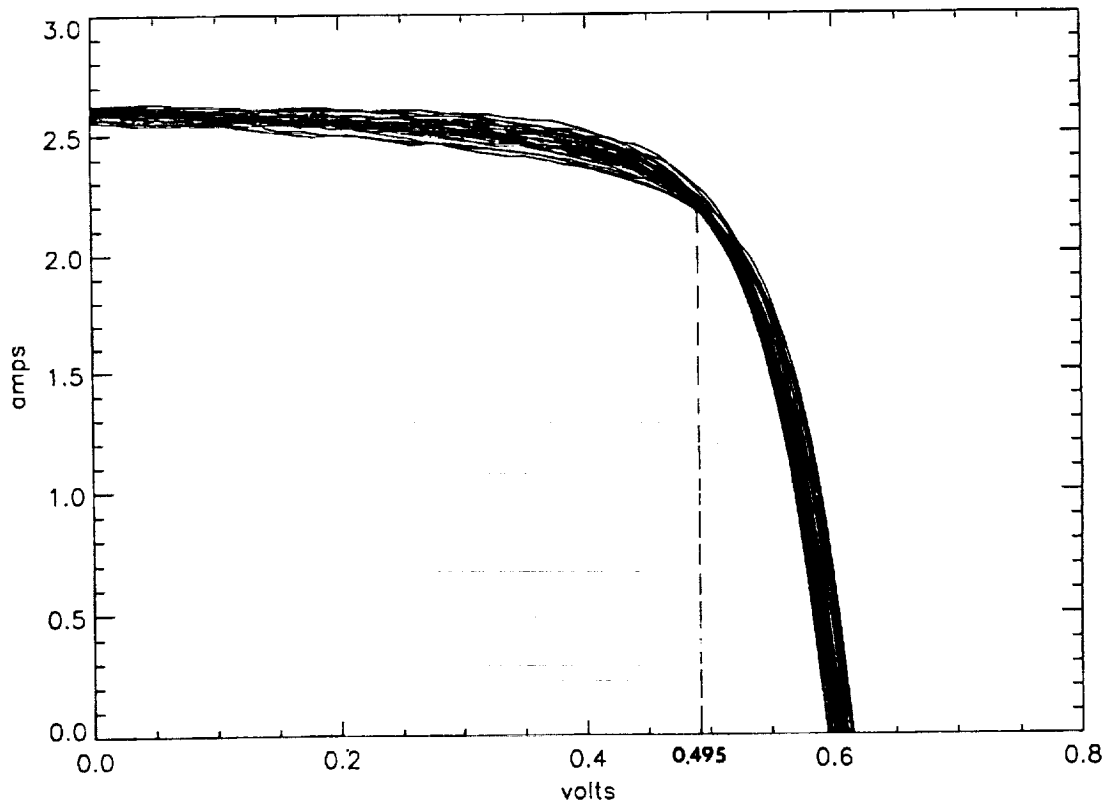


Figure 3.—Distribution of the measured I-V characteristics of 50 cells.

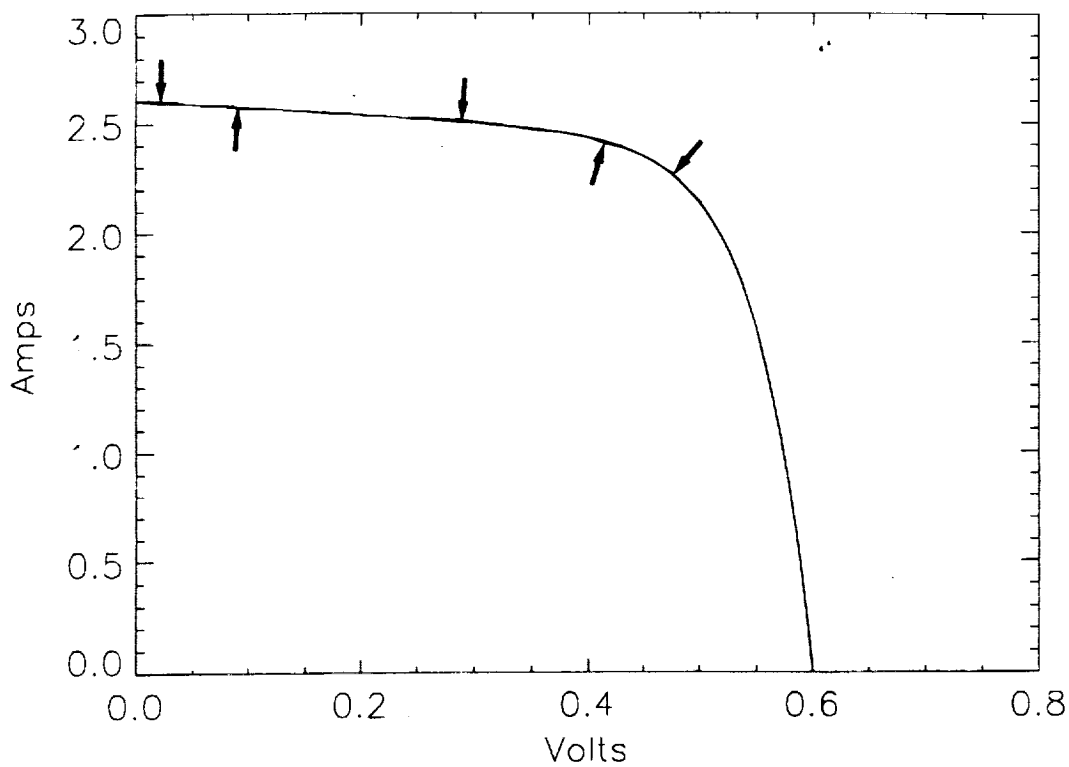


Figure 4.—Experimental and fitted I-V characteristics of cell ss01.

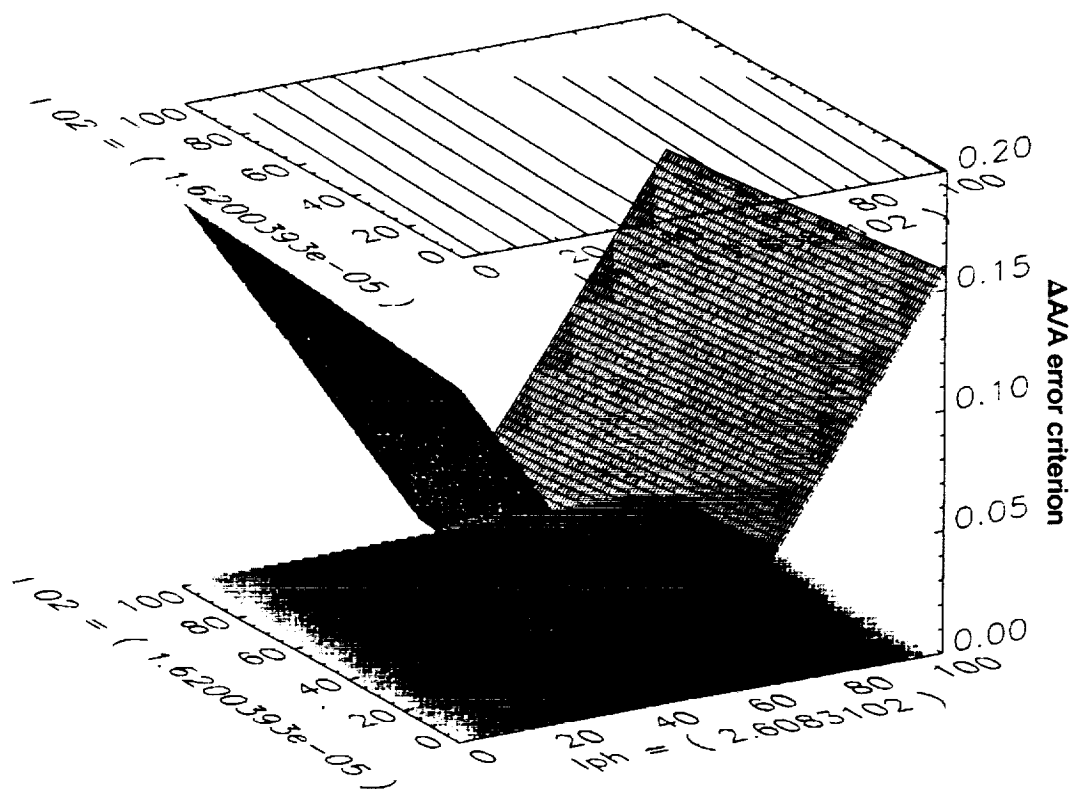


Figure 5.—Variation of the photocurrent  $I_{ph}$  and reverse saturation current  $I_{02}$  at the optimum ( $\pm 50$  percent variation around optimal  $I_{ph}$  and  $I_{02}$ ).

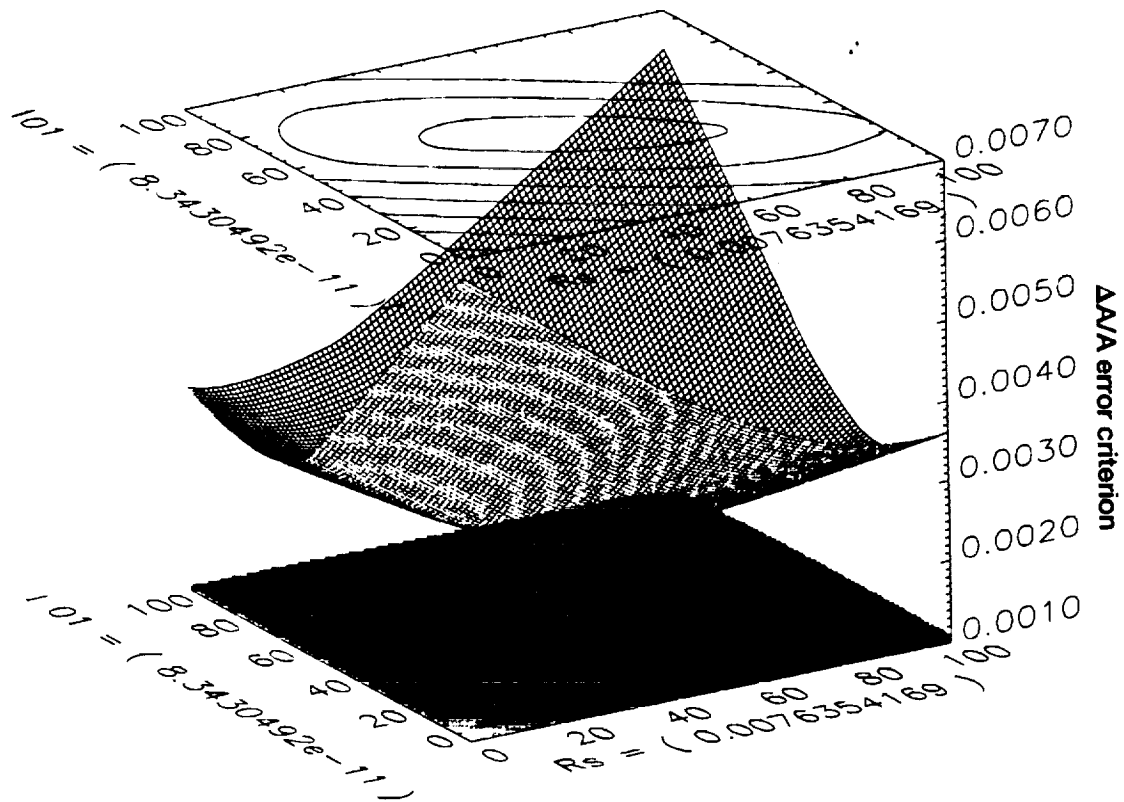


Figure 6.—Variation of the series resistance  $R_s$  and the reverse saturation current  $I_{01}$  at the optimum ( $\pm 50$  percent variation around optimal  $R_s$  and  $I_{01}$ ).

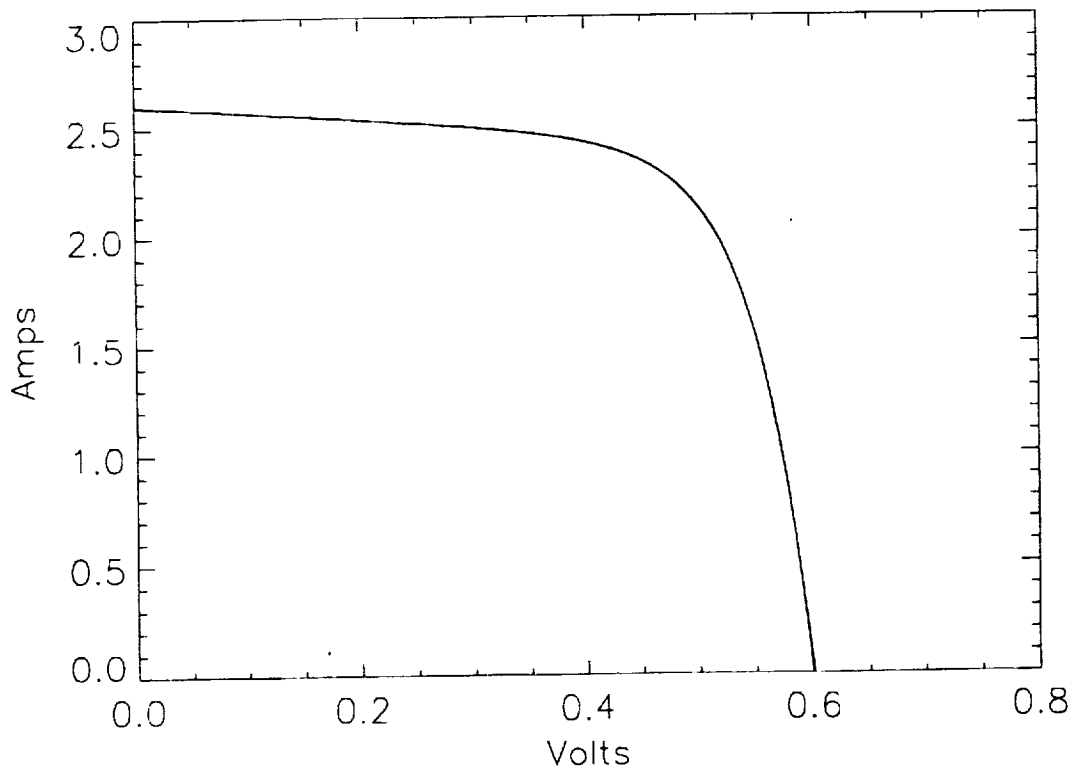


Figure 7.—I-V characteristics of 10 cells produced from cell ss01 by varying the initial conditions.

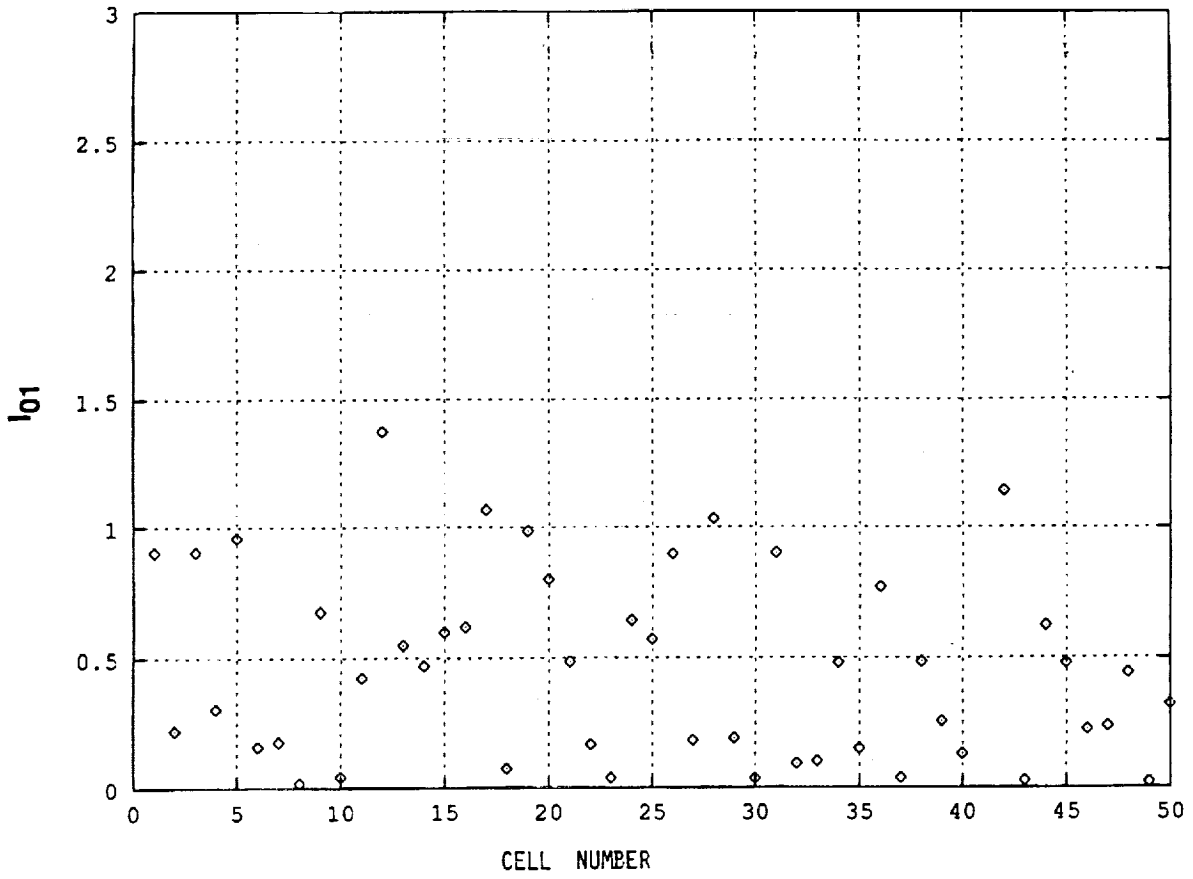
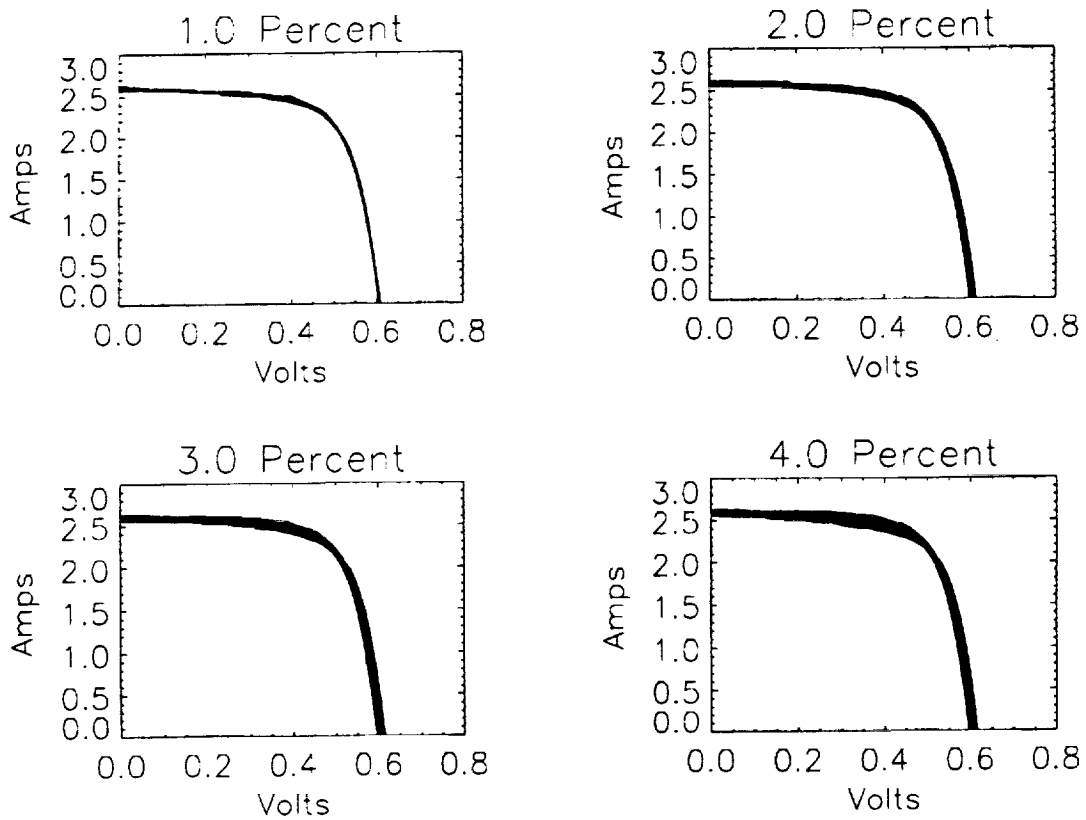


Figure 8.—Distribution of the reverse saturation current  $I_{01}$ , in standard deviation, for the 50 cells.



**Figure 9.—Cell screening according to percent deviation from the mean cell.**

# REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE October 1992	3. REPORT TYPE AND DATES COVERED Technical Memorandum	
4. TITLE AND SUBTITLE Parameterization of Solar Cells			5. FUNDING NUMBERS  WU-506-41-11	
6. AUTHOR(S) J. Appelbaum, A. Chait, and D. Thompson				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Lewis Research Center Cleveland, Ohio 44135-3191			8. PERFORMING ORGANIZATION REPORT NUMBER  E-7188	
9. SPONSORING/MONITORING AGENCY NAMES(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, D.C. 20546-0001			10. SPONSORING/MONITORING AGENCY REPORT NUMBER  NASA TM-105885	
11. SUPPLEMENTARY NOTES Joseph Appelbaum, NASA Lewis Research Council - NASA Research Associate, Lewis Research Center; A. Chait, and D. Thompson, NASA Lewis Research Center. Responsible person, Joseph Appelbaum, (216) 433-3852.				
12a. DISTRIBUTION/AVAILABILITY STATEMENT  Unclassified - Unlimited Subject Category 33			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) The aggregation (sorting) of the individual solar cells into an array is commonly based on a single operating point on the I-V characteristic curve. An alternative approach for cell performance prediction and cell screening is provided by modeling the cell using an equivalent electrical circuit, in which the parameters involved are related to the physical phenomena in the device. These analytical models may be represented by a double exponential I-V characteristic with seven parameters, by a double exponential model with five parameters, or by a single exponential equation with four or five parameters. In this article we address issues concerning methodologies for the determination of solar cell parameters based on measured data points of the I-V characteristic, and introduce a procedure for screening of solar cells for arrays. We show that common curve fitting techniques, e.g., least squares, may produce many combinations of parameter values while maintaining a good fit between the fitted and measured I-V characteristics of the cell. Therefore, techniques relying on curve fitting criteria alone cannot be directly used for cell parameterization. We propose a consistent procedure which takes into account the entire set of parameter values for a batch of cells. This procedure is based on a definition of a mean cell representing the batch, and takes into account the relative contribution of each parameter to the overall goodness of fit. The procedure is demonstrated on a batch of 50 silicon cells for Space Station Freedom.				
14. SUBJECT TERMS			15. NUMBER OF PAGES 22	
			16. PRICE CODE A03	
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT	