

0810  
E 5440

NASA  
Technical Memorandum 103116  
AIAA-90-2153

AVSCOM  
Technical Memorandum 90-C-008

# Surface Pitting Fatigue Life of Noninvolute, Low-Contact-Ratio Gears

Dennis P. Townsend  
*Lewis Research Center  
Cleveland, Ohio*

Prepared for the  
26th Joint Propulsion Conference  
cosponsored by the AIAA, SAE, ASME, and ASEE  
Orlando, Florida, July 16-18, 1990





# SURFACE PITTING FATIGUE LIFE OF NONINVOLUTE, LOW-CONTACT-RATIO GEARS

Dennis P. Townsend  
National Aeronautics and Space Administration  
Lewis Research Center  
Cleveland, Ohio 44135-3191

## Abstract

Spur gear endurance tests were conducted to investigate the surface pitting fatigue life of noninvolute gears with low numbers of teeth and low contact ratios for use in advanced applications. The results were compared with those for a standard involute design with a low number of teeth. The gear pitch diameter was 8.89 cm (3.50 in.) with 12 teeth on both gear designs. Test conditions were an oil inlet temperature of 320 K (116 °F), an oil outlet temperature of 350 K (170 °F), a maximum Hertz stress of 1.49 GPa (216 ksi), and a speed of 10 000 rpm. The following results were obtained: The noninvolute gear had a surface pitting fatigue life approximately 1.6 times that of the standard involute gear of a similar design. The surface pitting fatigue life of the 3.43-pitch AISI 8620 noninvolute gear was approximately equal to the surface pitting fatigue life of an 8-pitch, 28-tooth AISI 9310 gear at the same load but at a considerably higher maximum Hertz stress.

## Introduction

Many gears used in aircraft and other transmissions have size limitations based on the minimum number of teeth that can be cut on a pinion without undercutting the teeth.<sup>1</sup> If the number of teeth is made fewer than this minimum, a weaker tooth will be produced because of the undercutting. One method currently used to allow smaller minimum numbers of teeth on a pinion is to change the involute radius at both the dedendum and the addendum. Smaller numbers of teeth can be manufactured on a given pinion with a standard addendum by increasing the involute radius in the dedendum region, where it normally becomes very short, and decreasing the radius in the addendum region, where it normally increases rapidly. This can be seen on an involute chart as a positive modification in the dedendum region and a negative modification, similar to a large tip relief, in the addendum region. In addition to allowing smaller numbers of teeth without undercutting, this method, sometimes called new tooth form,<sup>2</sup> also reduces the maximum Hertz stress in the dedendum region, where the very short involute radius has been increased. This increased involute radius may also improve the gear tooth's surface fatigue life and possibly improve its scoring resistance. The new tooth form can be used for most spur or helical gears with either normal or high contact ratios to reduce the effect of undercutting on gears with fewer than the minimum number of teeth.

The objectives of the research reported herein were (1) to investigate the noninvolute modifications for use as a design method for gears with small numbers of teeth, (2) to determine the surface endurance characteristics of a spur gear with the new tooth form, and (3) to compare the results with those for a standard involute gear of similar design parameters. In order to accomplish these objectives, tests were conducted with one

lot each of spur gears made from a single heat of AISI 8620 AMS 6274 material in the noninvolute design and in the standard involute design. The gear pitch diameter was 8.89 cm (3.50 in.). Test conditions included an oil inlet temperature of 320 K (116 °F), which resulted in an oil outlet temperature of 350 K (170 °F), a maximum Hertz stress of 1.49 GPa (216 ksi), and a shaft speed of 10 000 rpm.

The work reported herein was conducted as a joint effort of NASA Lewis Research Center, General Electric Co. Ordinance Systems Division, and ITW Spiroid Division.

## Apparatus and Procedures

### Gear Test Apparatus

The gear fatigue tests were performed in the NASA Lewis gear fatigue test apparatus (Fig. 1). This test rig uses the four-square principle (recirculating power) of applying the test gear load so that the input drive needs to overcome only the frictional losses in the system. A schematic of the test rig is shown in Fig. 1(b). Oil pressure and leakage flow are supplied to the loading vanes through a shaft seal. As the oil pressure is increased on the loading vanes inside the slave gear, torque is applied to the shaft. This torque is transmitted through the test gears back to the slave gear, where an equal but opposite torque is maintained by the oil pressure. This torque on the test gears, which depends on the hydraulic pressure applied to the loading vanes, loads the gear teeth to the desired stress level. The two identical test gears can be started under no load, and the load can be applied gradually without changing the running track on the gear teeth.

Separate lubrication systems are provided for the test gears and the main gearbox. The two lubrication systems are separated at the gearbox shafts by nitrogen-gas-pressurized labyrinth seals. The test gear lubricant is filtered through a 5- $\mu$ m nominal fiberglass filter. The test lubricant can be heated electrically with an immersion heater. The skin temperature of the heater is controlled to prevent overheating the test lubricant.

A vibration transducer mounted on the gearbox is used to automatically shut off the test rig when gear surface fatigue occurs. The gearbox is also automatically shut off if there is a loss of oil flow to either the main gearbox or the test gears, if the test gear oil overheats, or if there is a loss of seal gas pressurization.

The belt-driven test rig can be operated at several fixed speeds by changing pulleys. The operating speed for the tests reported herein was 10 000 rpm.



## Test Gears

The test gears are shown in Fig. 2. Their dimensions are given in Table I. All the gears had a nominal surface finish on the tooth face of  $0.82 \mu\text{m}$  ( $32 \mu\text{in.}$ ) rms. The baseline gears had a standard involute profile; the noninvolute gear had a profile that deviated from a standard involute profile as shown in Fig. 3. The pressure angle for all the gears was  $20^\circ$  and the contact ratio was 1.15.

## Test Materials

The test gears were manufactured from one lot of AISI E8620 AQHR AMS 6274 material. The chemical composition of the gear material is shown in Table II. The heat treatment for the test gears is described in Table III. The case hardness was  $R_C60$  with a case depth of  $0.147 \text{ cm}$  ( $0.058 \text{ in.}$ ); the core hardness was  $R_C40$ . Photomicrographs of the case and core regions of the gear material are shown in Figs. 4(a) and (b).

## Lubricant

All the gears were lubricated with a single batch of synthetic paraffinic oil. The physical properties of this lubricant are summarized in Table IV. Five volume percent of an extreme-pressure additive, designated Lubrizol 5002 (partial chemical analysis given in Table IV), was added to the lubricant.

## Test Procedure

After the test gears were cleaned to remove their protective coating, they were assembled on the test rig. The test gears ran in an offset condition with a  $0.30\text{-cm}$  ( $0.120\text{-in.}$ ) tooth-surface overlap to give a  $0.28\text{-cm}$  ( $0.110\text{-in.}$ ) load surface on the gear face after allowing for the edge radius on the gear teeth. If both faces of the gears were tested, four fatigue tests could be run for each set of gears. All tests were run-in at a load per unit length of  $1230 \text{ N/cm}$  ( $700 \text{ lb/in.}$ ) for 1 hr. The load was then increased to  $5800 \text{ N/cm}$  ( $3300 \text{ lb/in.}$ ), which resulted in a  $1.49\text{-GPa}$  ( $216\text{-ksi}$ ) pitch-line maximum Hertz stress. The tooth bending stress at the worst load point was calculated to be  $0.10 \text{ GPa}$  ( $15 \text{ ksi}$ ).

Operating the test gears at  $10\,000 \text{ rpm}$  gave a pitch-line velocity of  $46.55 \text{ m/sec}$  ( $9163 \text{ ft/min}$ ). Lubricant was supplied to the inlet mesh at  $800 \text{ cm}^3/\text{min}$  ( $49 \text{ in.}^3/\text{min}$ ) and  $320 \pm 6 \text{ K}$  ( $116 \pm 10 \text{ }^\circ\text{F}$ ). The lubricant outlet temperature was nearly constant at  $350 \pm 3 \text{ K}$  ( $170 \pm 5 \text{ }^\circ\text{F}$ ). The tests ran continuously ( $24 \text{ hr/day}$ ) until the rig was automatically shut down by the vibration detection transducer (located on the gearbox adjacent to the test gears) or until  $500 \text{ hr}$  of operation without failure were completed. The lubricant circulated through a  $5\text{-}\mu\text{m}$  fiberglass filter to remove wear particles. For each test,  $3.8 \text{ liters}$  ( $1 \text{ gal}$ ) of lubricant was used. At the end of each test, the lubricant and the filter element were discarded. Oil inlet and outlet temperatures were continuously recorded on a strip-chart recorder.

The pitch-line elastohydrodynamic (EHD) film thickness was calculated by the method of Dowson and Higginson.<sup>3</sup> It was assumed, for this film thickness calculation, that the gear temperature

at the pitch line was equal to the oil outlet temperature and that the oil inlet temperature to the contact zone was equal to the gear temperature, even though the oil inlet temperature was considerably lower. It is possible that the gear surface temperature was even higher than the oil outlet temperature, especially at the end points of sliding contact. The EHD film thickness for these conditions was computed to be  $0.94 \mu\text{m}$  ( $37 \mu\text{in.}$ ), which gave an initial ratio of film thickness to composite surface roughness  $h/\sigma$  of  $0.82$  at the  $1.49\text{-GPa}$  ( $216\text{-ksi}$ ) pitch-line maximum Hertz stress.

Each test conducted with a pair of gears was considered as a system and, hence, a single test. A maximum of four tests were conducted with each pair of gears. Test results were evaluated by using Weibull plots calculated by the method of Johnson.<sup>4</sup> (A Weibull plot is the number of stress cycles versus the statistical percentage of gear systems failed.)

## Results and Discussion

One lot each of AISI 8620 standard involute gears and noninvolute gears with the modified involute profile was endurance tested. Test conditions included a tangential tooth load of  $5800 \text{ N/cm}$  ( $3300 \text{ lb/in.}$ ), which produced a maximum Hertz stress of  $1.49 \text{ GPa}$  ( $216 \text{ ksi}$ ), and a speed of  $10\,000 \text{ rpm}$ . The gears failed by classical subsurface pitting fatigue. The surface pitting fatigue life results of these tests are shown in the Weibull plots of Fig. 5 and are summarized in Table V. Surface pitting fatigue life results for the standard involute gears are shown in Fig. 5(a). The 10- and 50-percent lives were  $14.6 \times 10^6$  and  $45.8 \times 10^6$  stress cycles ( $24.3$  and  $76.3 \text{ hr}$ ), respectively. The failure index (i.e., the number of fatigue failures out of the number of sets tested) was 20 out of 20. A typical fatigue spall that occurs near the pitch line on a standard involute gear is shown in Fig. 6(a). This spall is similar to those observed in rolling-element fatigue tests. The pitch-line pitting is the result of a high subsurface shearing stress, which develops subsurface cracks. The subsurface cracks propagate into a crack network that results in a fatigue spall slightly below the pitch line, where the sliding condition is more severe.

Surface pitting fatigue life results for the noninvolute gear systems are shown in Fig. 5(b). The 10- and 50-percent surface pitting fatigue lives were  $23.2 \times 10^6$  and  $62.5 \times 10^6$  stress cycles ( $38.1$  and  $104.2 \text{ hr}$ ), respectively. The failure index was 18 out of 18. Figure 6(b) shows a typical fatigue spall for a noninvolute gear. The fatigue spalls and tooth wear were very similar for both types of gears. The 10-percent life of the noninvolute gear was approximately 1.6 times that of the standard involute gears. The confidence number was 77 percent, which indicates that the difference in surface fatigue life is statistically significant. (The confidence number indicates the percentage of time that the relative lives of the two types of gears will occur in the same order.)

The gear life data are summarized in Fig. 5(c). The surface pitting fatigue test data show the noninvolute gear to be superior in surface pitting fatigue life to the standard involute gear



for the gear sets tested. It is not clear why there was an improvement in surface pitting fatigue life for the noninvolute gear, since the fatigue failures occurred near the pitch line, where the load, Hertz stress, and involute radius are the same for both types of gears. Since the gears had a very low contact ratio of only 1.15 because of the low number of teeth, it is possible that the dynamic load for the noninvolute gear was less than that for the standard involute gear. Data from Lin et al.<sup>5</sup> indicate that certain types (or length) of profile modification give reduced dynamic loads. Since the noninvolute gear is a special form of profile modification, it may have a reduced dynamic load.

The 10-percent pitting fatigue life of the noninvolute gear (23.3 million cycles) at the 1.49-GPa (216-ksi) maximum Hertz stress was approximately equivalent to that of a standard AISI 9310 8-pitch gear (19 million cycles) at the same load but with a much higher maximum Hertz stress of 1.71 GPa (248 ksi).<sup>6</sup> The 8-pitch gears had a contact ratio of 1.638, in contrast to 1.15 for the 3.43-diametral-pitch gears used in these tests. Normally, the gear life is inversely proportional to the stress to the ninth power.<sup>7</sup> In these tests the low contact ratio may have resulted in higher dynamic loads on the teeth and therefore in a higher dynamic maximum Hertz stress and a reduced life. Results from the NASA gear dynamic analysis program show the 12-tooth gear to have a dynamic load factor of 1.5, in contrast to 1.04 for the 8-pitch, 28-tooth gear. In addition, the AISI 8620 material may have a lower fatigue life at the same stress than the AISI 9310 material.

#### Summary of Results

Spur gear endurance tests were conducted to investigate the effect of the noninvolute tooth form on the surface pitting fatigue life of gears with low numbers of teeth. The results were compared with those for a standard involute design with the same number of teeth. The gear pitch diameter was 8.89 cm (3.50 in.) with 12 teeth on both gear designs. Test conditions were on oil

TABLE I. DESCRIPTION OF TEST GEARS<sup>a</sup>

Pitch diameter, cm (in.) . . . . .	8.89 (3.50)
Number of teeth . . . . .	12
Module (diametral pitch) . . . . .	7.4083 (3.4286)
Pressure angle, deg . . . . .	20
Face width, cm (in.) . . . . .	0.635 (0.250)
Outside diameter, cm (in.) . . . . .	10.2558 (4.0377)
Root diameter, cm (in.) . . . . .	7.248 (2.854)
Tooth thickness (arc), cm (in.) . . . . .	1.3528 (0.5326)
Fillet radius, cm (in.) . . . . .	0.198 (0.078)
Surface finish (min.), $\mu\text{m}$ ( $\mu\text{in.}$ ) . . . . .	0.8 (32)

<sup>a</sup>Gears were identical except for the tooth form, which was involute for the standard gear and noninvolute for the other gear.

inlet temperature of 320 K (116 °F), an oil outlet temperature of 350 K (170 °F), a maximum Hertz stress of 1.49 GPa (216 ksi), and a speed of 10 000 rpm. The following results were obtained:

1. The noninvolute gear had a surface pitting fatigue life approximately 1.6 times that of a standard involute gear of a similar design.

2. The surface pitting fatigue life of the 3.43-pitch, 12-tooth AISI 8620 noninvolute gear was approximately equal to the surface pitting fatigue life of an 8-pitch, 28-tooth AISI 9310 gear at the same load but at a considerably higher maximum Hertz stress.

#### References

1. Dudley, D.W., Handbook of Practical Gear Design, McGraw Hill, New York, 1984.
2. Townsend, D.P., Baber, B.B., and Nagy, A., "Evaluation of High Contact Ratio Spur Gears With Profile Modification," NASA TP-1458, 1979.
3. Dowson, D., and Higginson, G.R., "Elasto-Hydrodynamic Lubrication," Pergamon Press, New York, 1966.
4. Johnson, L.G., The Statistical Treatment of Fatigue Experiments, Elsevier, New York, 1964.
5. Lin, H.H., Townsend, D.P., and Oswald, F.B., "Profile Modification to Minimize Spur Gear Dynamic Loading," NASA TM-89901, 1987.
6. Townsend, D.P., "Surface Fatigue Life and Failure Characteristics of EX-53, CBS 1000M and AISI 9310 Gear Materials," NASA TP-2513, 1985.
7. Townsend, D.P., Coy, J.J., and Zaretsky, E.V., "Experimental and Analytical Load-Life Relation for AISI 9310 Steel Spur Gears," Journal of Mechanical Design, Vol. 100, Jan. 1978, pp. 54-60.

TABLE II. CHEMICAL COMPOSITION OF AISI 8620 GEAR MATERIAL

Element	Content, wt %
Carbon (core)	0.22
Manganese	.82
Phosphorus	.013
Sulfur	.01
Silicon	.27
Copper	.10
Chromium	.49
Molybdenum	.16
Nickel	.54
Iron	Balance

TABLE III. HEAT TREATMENT PROCEDURE  
[Material, AISI 8620.]

Step	Process
1	Carburize at 1200 K (1700 °F) for 8 hr
2	Temper at 922 K (1200 °F) for 1 hr
3	Austenize or harden at 1118 K (1550 °F) for 2.5 hr
4	Oil quench
5	Deep freeze at 190 K (-120 °F) for 3.5 hr
6	Temper at 436 K (325 °F) for 2 hr

TABLE IV. - LUBRICANT PROPERTIES

[Lubricant, synthetic paraffinic oil plus additive<sup>a</sup>.]

Kinematic viscosity, cm <sup>2</sup> /sec (cS) at:	
244 K (-20 °F)	2500×10 <sup>-2</sup> (2500)
311 K (100 °F)	31.6×10 <sup>-2</sup> (31.6)
372 K (210 °F)	5.5×10 <sup>-2</sup> (5.5)
477 K (400 °F)	2.0×10 <sup>-2</sup> (2.0)
Flash point, K (°F)	508 (455)
Fire point, K (°F)	533 (500)
Pour point, K (°F)	219 (-65)
Specific gravity	0.8285
Vapor pressure at 311 K (100 °F), torr	0.1
Specific heat at 311 K (100 °F), J/kg K (Btu/lb °F)	2190 (0.523)

<sup>a</sup>Additive, 5 vol % Lubrizol 5002 (phosphorus, 0.03 vol %; sulfur, 0.93 vol %).

TABLE V. RESULTS OF SPUR GEAR FATIGUE LIFE TESTS


[Pitch diameter, 8.2542 cm (3.2497 in.); maximum Hertz stress, 1.49 GPa (216 ksi); speed, 10 000 rpm; lubricant, synthetic paraffinic oil; gear temperature, 350 K (170 °F).]

Tooth form	10-percent life	50-percent life	Weibull slope	Failure index <sup>a</sup>	Confidence number at 10-percent level <sup>b</sup>
	Gear system life, revolutions				
Involute	14.6×10 <sup>6</sup>	45.8×10 <sup>6</sup>	1.64	20 out of 20	--
Noninvolute	23.2	62.5	1.9	18 out of 18	77


<sup>a</sup>Number of surface fatigue failures out of number of gears tested.

<sup>b</sup>Percentage of time that 10-percent life obtained with involute gears will have the same relation to 10-percent life obtained with noninvolute gears.



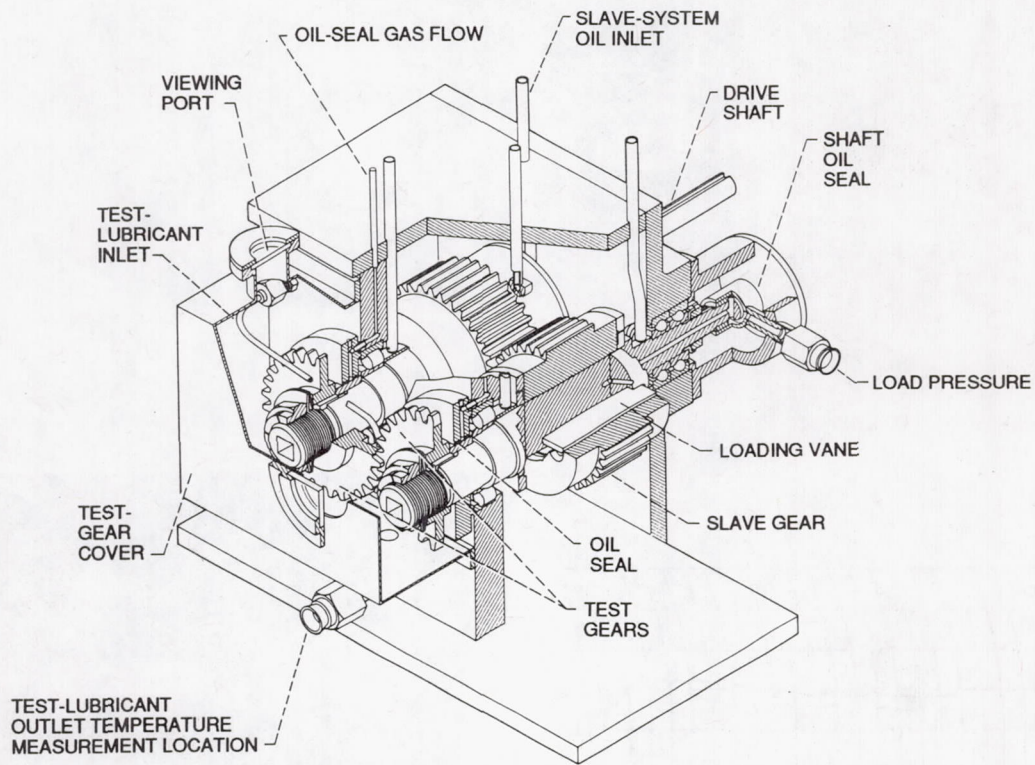


(a) Cutaway view.

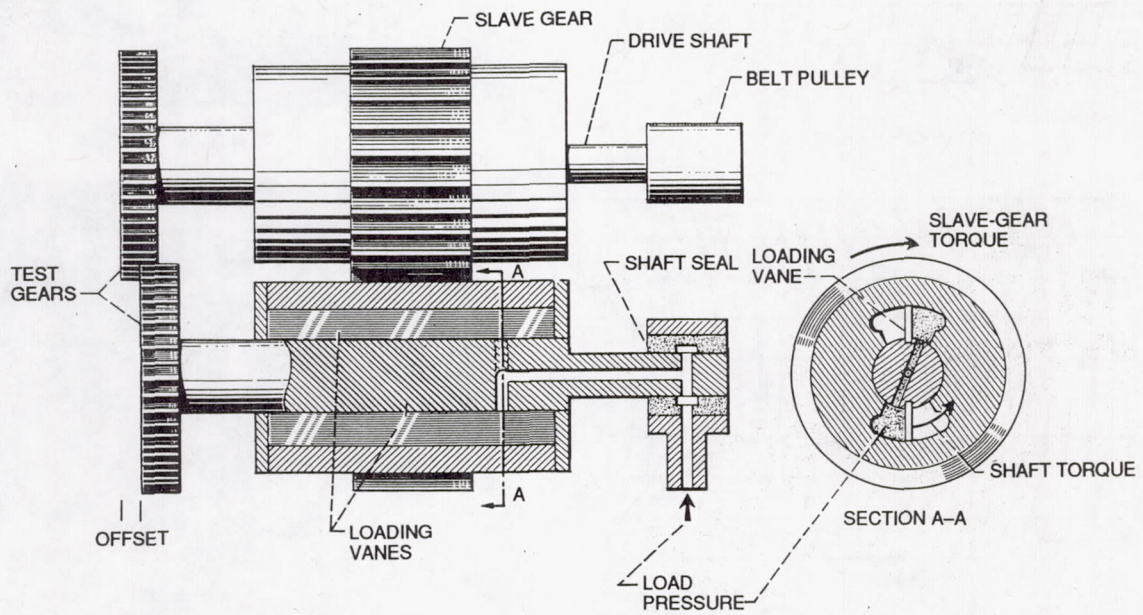

(b) Schematic diagram.

Fig. 1. NASA Lewis Research Center's gear fatigue test apparatus.





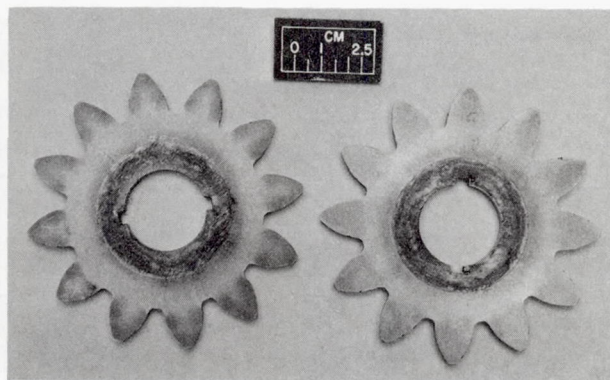



(a) Standard involute.

(b) Noninvolute.

Fig. 2. Test gear configurations.

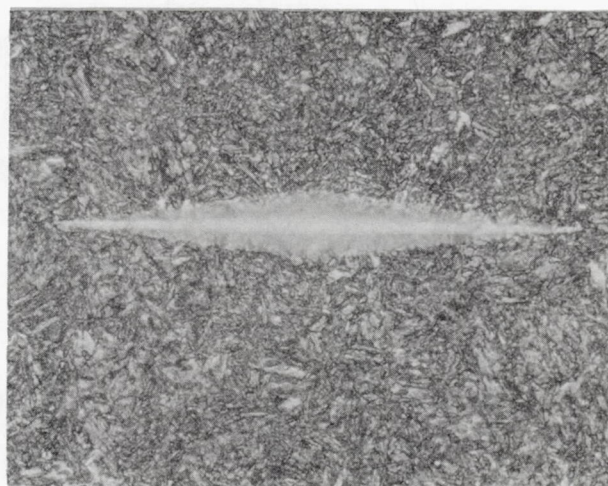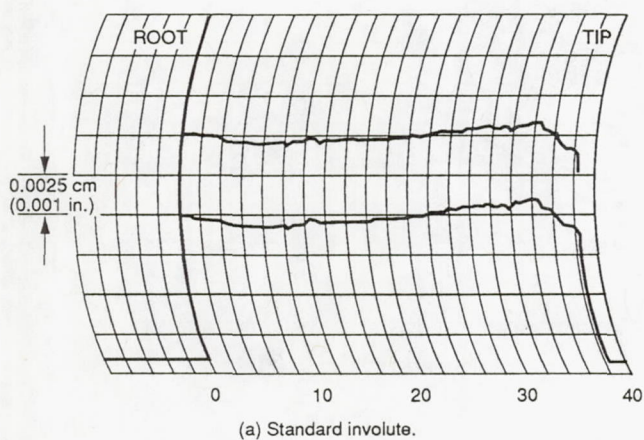

(a) Case.

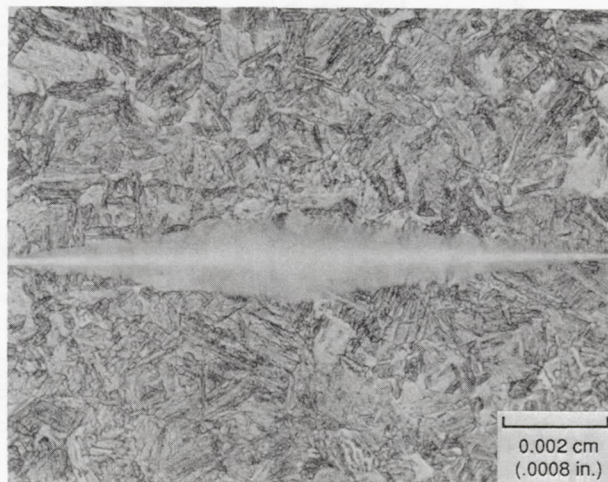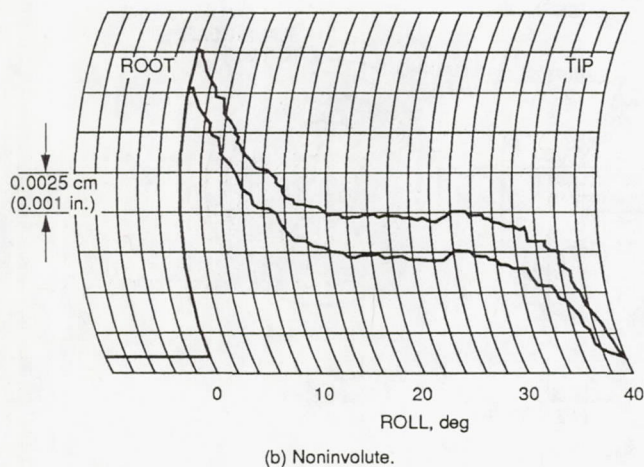

(b) Core.

Fig. 3. Tooth profile traces of standard involute and noninvolute gears.

Fig. 4. Photomicrographs of case and core of AISI 8620 test gear material.


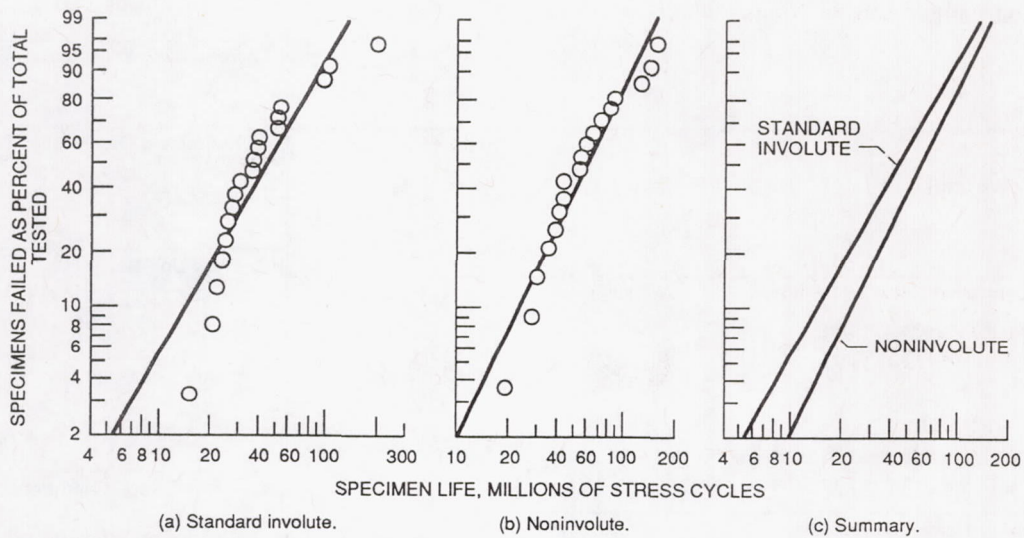


Fig. 5. Pitting fatigue lives of carburized and hardened AISI 8620 AMS 6274 standard involute and noninvolute gears. Speed, 10 000 rpm; lubricant, synthetic paraffinic oil with 5 vol % extreme-pressure additive; maximum Hertz stress, 1.49 GPa (216 ksi); temperature, 350 K (170 °F).



(a) Standard gear. (b) Noninvolute gear.

Fig. 6. Typical fatigue spall.

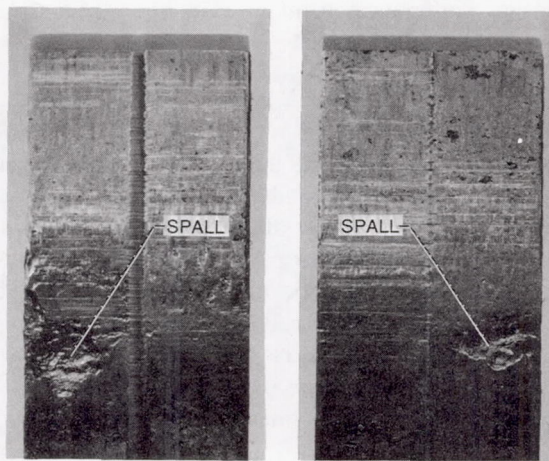

1. Report No. NASA TM-103116 AVSCOM TM-90-C-008		2. Government Accession No.		3. Recipient's Catalog No.	
4. Title and Subtitle Surface Pitting Fatigue Life of Noninvolute, Low-Contact-Ratio Gears				5. Report Date	
				6. Performing Organization Code	
7. Author(s) Dennis P. Townsend				8. Performing Organization Report No. E-5440	
9. Performing Organization Name and Address NASA Lewis Research Center Cleveland, Ohio 44135-3191 and Propulsion Directorate U.S. Army Aviation Research and Technology Activity—AVSCOM Cleveland, Ohio 44135-3127				10. Work Unit No. 505-63-51 1L162209A47A	
				11. Contract or Grant No.	
12. Sponsoring Agency Name and Address National Aeronautics and Space Administration Washington, D.C. 20546-0001 and U.S. Army Aviation Systems Command St. Louis, Mo. 63120-1798				13. Type of Report and Period Covered Technical Memorandum	
				14. Sponsoring Agency Code	
15. Supplementary Notes Prepared for the 26th Joint Propulsion Conference cosponsored by the AIAA, SAE, ASME, and ASEE, Orlando, Florida, July 16-18, 1990.					
16. Abstract Spur gear endurance tests were conducted to investigate the surface pitting fatigue life of noninvolute gears with low numbers of teeth and low contact ratios for use in advanced applications. The results were compared with those for a standard involute design with a low number of teeth. The gear pitch diameter was 8.89 cm (3.50 in.) with 12 teeth on both gear designs. Test conditions were an oil inlet temperature of 320 K (116 °F), an oil outlet temperature of 350 K (170 °F), a maximum Hertz stress of 1.49 GPa (216 ksi), and a speed of 10 000 rpm. The following results were obtained: The noninvolute gear had a surface pitting fatigue life approximately 1.6 times that of the standard involute gear of a similar design. The surface pitting fatigue life of the 3.43-pitch AISI 8620 noninvolute gear was approximately equal to the surface pitting fatigue life of an 8-pitch, 28-tooth AISI 9310 gear at the same load but at a considerably higher maximum Hertz stress.					
17. Key Words (Suggested by Author(s)) Spur gears Noninvolute gears Surface fatigue life Surface fatigue			18. Distribution Statement Unclassified—Unlimited Subject Category 37		
19. Security Classif. (of this report) Unclassified		20. Security Classif. (of this page) Unclassified		21. No. of pages 8	22. Price* A02