

NASA
TP
1781
c.1

NASA Technical Paper 1781

LOAN COPY: RI
AFWL TECHNIC
KIRTLAND AFB

0067679



TECH LIBRARY KAFB, NM

Creep and Residual Mechanical Properties of Cast Superalloys and Oxide Dispersion Strengthened Alloys

J. Daniel Whittenberger

FEBRUARY 1981

NASA



NASA Technical Paper 1781

Creep and Residual Mechanical Properties of Cast Superalloys and Oxide Dispersion Strengthened Alloys

J. Daniel Whittenberger
Lewis Research Center
Cleveland, Ohio



National Aeronautics
and Space Administration

**Scientific and Technical
Information Branch**

Trade names or manufacturer's names are used in this report for identification only. This usage does not constitute an official endorsement, either expressed or implied, by the National Aeronautics and Space Administration.

Summary

A study of the creep behavior and residual mechanical properties of two cast superalloys and several wrought bar oxide dispersion strengthened (ODS) alloys reveals that the tensile properties of the nickel-base superalloy B-1900 and cobalt-base superalloy MAR-M509 are not degraded by prior elevated temperature creep (at least up to 1 percent) straining between 1144 and 1366 K. On the other hand, the room temperature tensile properties of ODS nickel-base alloys can be reduced by prior creep strains of 0.5 percent or less between 1144 and 1477 K, with the long transverse direction being more susceptible to degradation than the longitudinal direction. The room temperature tensile properties of the ODS iron-base alloy MA-956 tested in the longitudinal direction are apparently not degraded by prior creep strains up to about 0.25 percent.

While not subject to creep degradation, the ODS alloy MA-956 is unusual in the manner in which it appears to deform at elevated temperature. Basically, MA-956 creep strained in the longitudinal direction appears to undergo slow plastic deformation by the nucleation and slow growth of cracks. On the other hand, the creep behavior of the ODS nickel-base alloys in this study is quite similar to that of previously studied ODS nickel alloys. In general, the longitudinal direction is stronger than the long transverse direction, and creep is at least partially due to a diffusional creep mechanism as dispersoid-free zones were observed after creep-rupture testing.

Introduction

Oxide dispersion strengthened (ODS) nickel- and iron-base alloys are of interest for use in gas turbine engines because of their mechanical strength and environmental resistance at high homologous temperatures. However, recent studies (refs. 1 to 3) of mechanical properties of several nickel-base ODS alloys have indicated that in some instances prior elevated temperature creep straining can severely affect subsequent room temperature tensile properties, particularly ductility. Reductions in ductility are apparently due to diffusional creep, which causes formation of dispersoid-free regions around grain boundaries. Such regions are weak in comparison to the adjacent dispersion strengthened material. Additionally, the dispersoid-free regions can act as sites for cavitation and internal oxidation during subsequent creep; these effects further weaken the alloy.

While creep degradation effects have been documented for many nickel-base ODS alloys, the behavior of iron-base ODS alloys is not clear. A recent study (ref. 4) of mechanical properties of the ODS iron-base sheet alloy MA-956E indicated that room temperature tensile properties are not affected by very small amounts of prior creep strain (less than 0.2 percent) at 1365 K. Attempts to introduce greater amounts of creep strain were unsuccessful because of the rather unique way in which this alloy deforms under conditions designed to promote slow plastic deformation. It appears that beyond transient creep (about 0.1 percent strain), the alloy does not undergo uniform plastic deformation but rather deforms by the nucleation and slow growth of cracks which eventually lead to tensile overload conditions and rapid failure.

In current gas turbine engines, most high temperature parts are manufactured from either nickel- or cobalt-base alloys. Degradation of 1033 K stress-rupture and room temperature tensile properties as a result of 1-percent creep straining at 1089 to 1366 K has been reported for the wrought nickel-base alloy Udimet 700 (ref. 5) and the cast nickel-base alloy Inco 713 (ref. 6). Unfortunately, degradation effects due to aging and/or creep-straining could not be well differentiated in these studies. A study by Tien and Gamble (ref. 7) on a simple gamma-prime strengthened nickel-base alloy (Ni-16Cr-5Al-4Ta) revealed the formation of gamma-prime-free regions during creep straining at 1255 K, which are similar to the dispersoid-free regions observed in creep-strained ODS alloys. Similar results were observed by Gibbons (ref. 8) in a study of creep at 1023 to 1123 K in high-purity Ni-20Cr-2.5Ti-1.5Al alloy and a commercial Nimonic 80A alloy. In these alloys, the gamma-prime-free regions are likely sites for premature failure during subsequent straining. No studies of creep degradation effects on the properties of cobalt-base superalloys have been reported.

The present study was conducted to determine the effects of similar thermal/creep exposures on the residual mechanical properties of cast superalloys and advanced wrought ODS alloys. In addition to the required creep testing, tensile properties and, where possible, stress rupture properties were measured in order to more fully characterize the elevated temperature properties of the alloys. The superalloys studied included the cast nickel-base alloy B-1900 and the cast cobalt-base alloy MAR-M509; both of these alloys are vane materials in current gas turbine engines. While creep degradation effects would not

be expected in MAR-M509, as it is basically a solid solution-strengthened alloy, creep degradation effects are possible in the gamma-prime strengthened B-1900. The advanced ODS alloys examined included nickel-base alloys (nominally Ni-16Cr-5Al) from three manufacturers and an iron-base alloy. All of the ODS alloys evaluated have been under consideration for or actually used as vanes in gas turbine engines (ref. 9).

The results of all the mechanical property testing are presented in appendix A, and typical microstructures of as-received and tested alloys are shown in appendix B. The results of a linear regression analysis of the stress rupture and steady state creep rate data for the tested alloys are given in appendix C.

Experimental Procedure

Materials

Cast bars 16 mm in diameter by 150 mm in length of MAR-M509 and B-1900 were procured from the Metals Division of TRW. Bars of each composition were cast from a single master heat, and each bar was radiographically inspected. All bars containing defects were rejected. The compositions of these two superalloys are shown in table I. Prior to being machined into test specimens, all B-1900 cast bars were heat treated as follows: 4 hours at 1350 K, air cool to room temperature, then 10 hours at 1170 K, and air cool to room temperature. MAR-M509 bars were not heat treated.

The ODS alloys evaluated included both commercial and experimental alloys. The nickel-base alloy MA-757 and iron-base alloy MA-956 were obtained from Huntington Alloys, Inc. Four pieces of hot-finished flat bar, nominally 8 by 3 cm in cross section and 80 cm in length, of each alloy in the heat-treated condition were obtained; the compositions are given in table I.

Three experimental aluminum-modified Ni-16Cr-type ODS alloys developed under NASA contract (ref. 10) at the Stellite Division of Cabot Corporation were also examined. These alloys are designated by STCA plus heat numbers and their compositions are given in table I. Extruded bar stock nominally 6.7 by 2.0 cm in cross section of each alloy composition was obtained from the contractor. In order to develop a low modulus texture, these alloys were thermomechanically processed and heat treated at the Lewis Research Center. The three alloys were canned in mild steel and rolled parallel to the extrusion direction at 1310 K in a single pass to reductions of 14 percent (262/264 and 266) or 24

percent (265). After rolling, the cans were removed and the alloys were heat treated in air. The heat treatment consisted of placing the materials in a furnace at 1475 K, raising the temperature over a 4-hour period to 1535 K, holding 1 hour at 1535 K, raising the temperature over a 2-hour period to 1590 K, holding 1 hour at 1590 K, lowering the temperature to 1475 K, and removing from the furnace and air cooling. The STCA heats given only this standard heat treatment are identified by the suffix "S". Heat numbers 265SC and 266SC were given the standard heat treatment followed by an additional 24-hour anneal at 1115 K to precipitate carbides.

In addition to the above ODS alloys, a limited amount of testing was conducted on the Special Metals experimental alloy YD-NiCrAl. One piece of heat treated bar stock approximately 3.8 by 1.3 cm in cross section and 28 cm long was obtained from the manufacturer; the nominal composition of this alloy is also listed in table I.

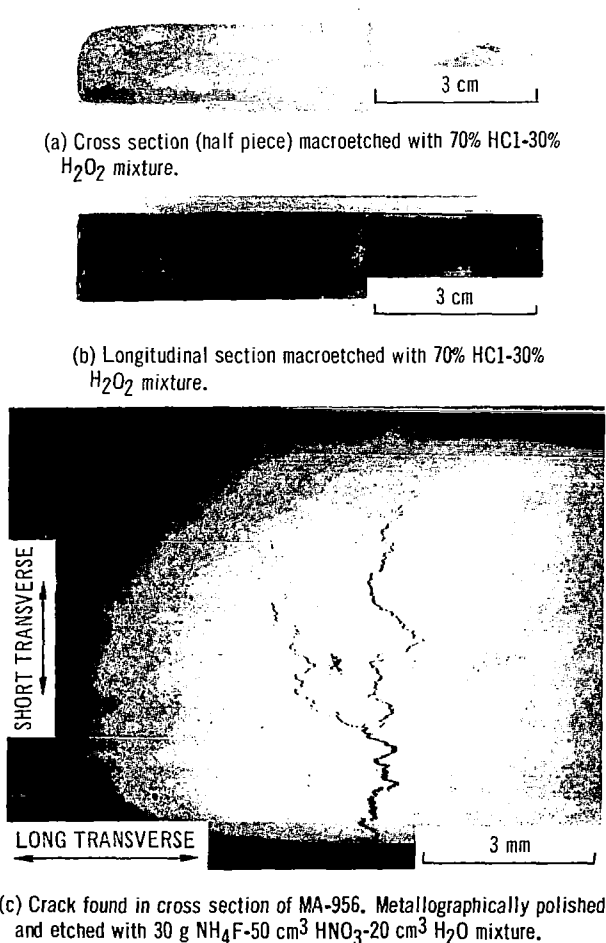


Figure 1. - Structure of as-received MA-956.

The crystallographic textures and grain sizes of all alloys were determined. Both superalloys possessed a very large as-cast grain structure with a basically random texture. B-1900 exhibited a minor texture where the [100] direction was parallel to the length of the as-cast bars. Additionally, it was noted that both superalloys contained very few grains with the [111] direction parallel to the bar length; the number found was less than expected for a truly "random" orientation.

Textures and grain sizes for the ODS alloys are reported in table II. The grain sizes are arithmetic averages; wide variation about the reported sizes exists. In particular, MA-757 and STCA-262/264 exhibited diameters in the long transverse-short transverse plane as small as 8 microns and as large as 500 microns. Of the nickel-base ODS alloys, only STCA-266S had a grain aspect ratio greater than 10 in the longitudinal direction. MA-956 possessed an extremely large grain structure as shown in figure 1. The "grains" are cigar-shaped, on the order of a cm in diameter by tens of cm long in the extrusion direction. Based on the [100] texture, all of the nickel-base ODS alloys have low elastic moduli in the direction parallel to the extrusion axis of the bar; unfortunately neither the long transverse nor short transverse bar directions are low modulus directions. On the basis of crystallography, all three bar directions for MA-956 will have high elastic moduli. In general for gas turbine applications, low modulus orientations are desirable (ref. 9) to reduce thermal stresses.

Testing Procedure

Specimen geometry and machining.—All machining of test bars was done by Metcut Research Associates, Inc. Threaded grip end round bar tensile-type specimens with a 0.635-cm-diameter reduced section were machined from each alloy. While it is normal practice to utilize cast test specimens for B-1900 and MAR-M509, specimens of both alloys were machined from the as-cast bars. This procedure was followed so that both the superalloy and ODS alloy specimens possessed similar surface finishes. All superalloy specimens and many MA-956 specimens in the longitudinal direction possessed a 5.7-cm-long reduced section. All other specimens had either a 3.2- or 2.5-cm-long reduced section. Since the emphasis of this program was on the measurement of residual properties after small amounts of prior creep strain, specimens with 5.7-cm reduced sections were desired in order to more accurately measure the creep strains. However, due to limitations on the size of the bar stock (particularly for the long transverse direction) and the availability of material, shorter reduced sections

had to be used for many material-test direction combinations. The reduced sections of all test specimens possessed a 16 rms or better surface finish and were free of defects as determined by dye penetrant inspection.

Generally, no difficulties were encountered in machining the alloys. However, a large fraction (about 60 percent) of MA-956 specimens with gage length parallel to the long transverse direction had to be discarded because of flaws (as revealed by dye penetrant techniques) in the reduced section. The source of the flaws has not been identified; however, several cracks were found in the as-received cross section of MA-956. These cracks start at the bar surfaces and generally follow the "grain" boundaries, as shown in figure 1.

Tensile testing.—Room temperature and elevated temperature tensile testing were conducted by Metcut Research Associates, Inc. All tensile testing followed the procedures outlined in ASTM Specifications E8-69 and E21-70. Elevated temperature tensile testing was conducted in air at 1144, 1255, 1366, and 1477 K except for the STCA alloys and YD-NiCrAl. The latter alloy was not tensile tested because only eleven specimens were available; only 1366 K tensile tests were run for the STCA alloys since the number of specimens for each composition-direction-heat treatment combination was also limited. The measured tensile properties included 0.02 and 0.2 percent yield stresses, ultimate tensile strength, elongation, and reduction in area.

Creep testing.—Elevated temperature creep testing was conducted at Metcut Research Associates, Inc., following the procedures outlined in ASTM Specification E139-70. For test temperatures below 1260 K an electromechanical extensometry system (LVDT which measures differential motion of extensometer arms attached to the gage sections) was generally used to determine creep strain. For temperatures exceeding 1260 K, an optical creep measuring system (creep cathetometer used in conjunction with platinum strip extensometers attached to the specimens) was used. A few 1255 K creep tests were conducted with the optical extensometry system. Tests were conducted in air at various stress levels at 1144, 1255, and 1366 K. MA-757 and MA-956 were also tested at 1477 K whereas the STCA alloys and YD-NiCrAl were only tested at 1366 K. Creep tests were conducted to rupture or were terminated after about 150 hours. The creep properties reported include plastic strain on loading; plastic strains after 0.1, 5, 10, 25, 50, 100, and 150 hours of testing; plastic strain at the end of test; minimum creep rate; and time to rupture if the specimen failed. Unfailed creep specimens were utilized in the determination of residual tensile properties.

Residual property testing.—In this study, creep tests were designed to introduce various amounts of strain into each alloy in order to determine if slow plastic deformation at elevated temperatures affects subsequent mechanical properties. Following creep testing specimens were tensile tested at room temperature. Due to the low ductility of MAR-M509 at room temperature, a few MAR-M509 specimens which had been creep tested at 1255 K were also tensile tested at 1144 K. In all cases, the measured residual tensile properties included 0.02 and 0.2 percent yield stresses, ultimate tensile stress, elongation, and reduction in area. The residual strength properties were calculated on the basis of the original (prior to creep testing) specimen diameter. Residual ductility measurements for specimens with less than 1 percent creep strain were based on the original gage dimensions while ductilities for specimens crept to more than 1 percent strain were based on gage dimensions after creep. The latter procedure was necessary since specimens with more than 1 percent creep strain had usually necked in the gage section.

Most residual property tests were conducted at Metcut Research Associates, Inc., following test procedures previously outlined for room temperature and elevated temperature tensile testing. A few interrupted creep specimens which possessed damaged grip ends were tensile tested at the Lewis Research Center; only ultimate tensile strength and ductility data were obtained from these residual property tests.

Stress-rupture testing.—Stress-rupture testing of the superalloys and ODS alloys MA-757 and MA-956 was conducted at the Lewis Research Center. Tests were designed to produce rupture at times ranging from 10 to about 500 hours at 1144, 1255, and 1366 K; in addition, the two ODS alloys were tested at 1477 K. All testing was conducted in air and followed the procedures outlines in ASTM Specification E139-70. Several MA-757 and MA-956 stress-rupture specimens which had not failed after about 1000 hours of testing were unloaded and tensile tested at room temperature in order to assess the effects of long-term stress-temperature exposure on mechanical properties.

Following mechanical property testing, selected specimens were examined by standard metallographic and scanning electron microscopy (SEM) techniques.

Results and Discussion

Superalloys

A complete tabular presentation of all the

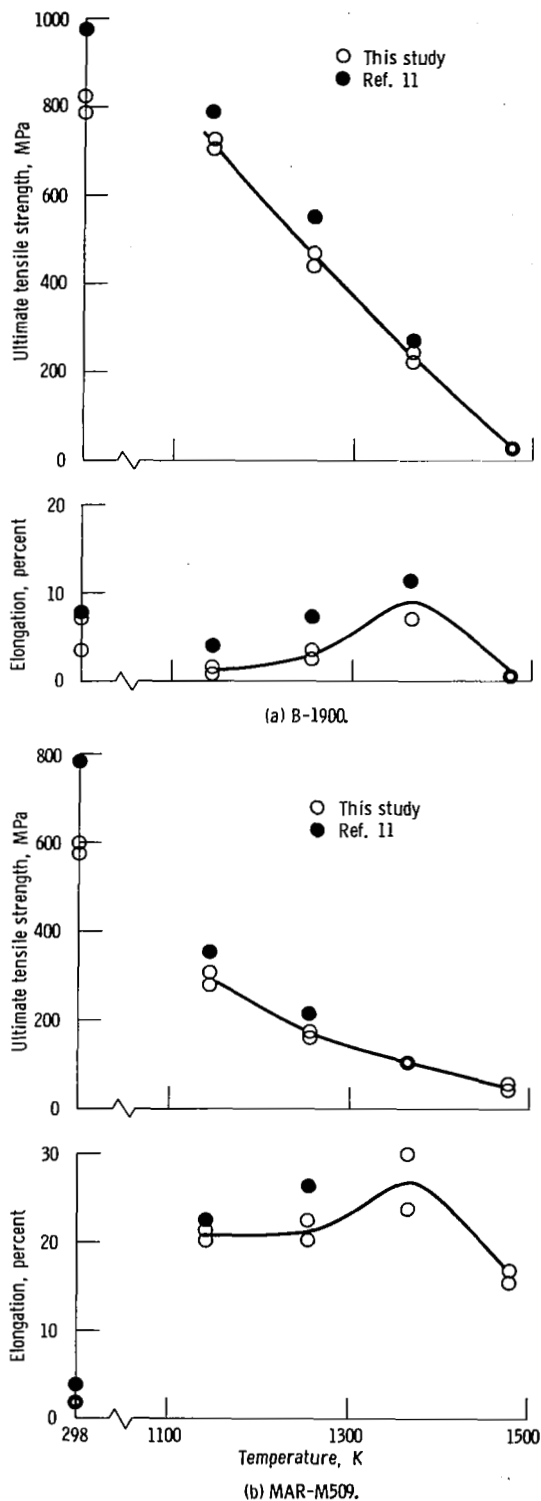


Figure 2. - Tensile properties as a function of temperature.

mechanical properties for B-1900 and MAR-M509 determined in this study is given in appendix A. Figure 2 shows the ultimate tensile strength and elongation data as a function of temperature, and figure 3 shows the stress-rupture data determined at 1255 K for both alloys. In addition, typical literature data (ref. 11) are included. The literature data for B-1900 in these two figures were determined for specimens in the as-cast condition, while the B-1900 specimens in this study had been subjected to a heat treatment. According to reference 11, it is usual practice to employ a heat treatment in order to improve the rupture life and ductility at 1033 K. Unfortunately, neither the tensile nor stress-rupture data for B-1900 bar reported in reference 11 are for the heat-treated condition. The tensile data in figures 2(a) and (b) indicate that both alloys tested in this program are weaker than typical heats of material. Also, figure 3 illustrates that the rupture strength of MAR-M509 at 1255 K is less than the typical strength while the rupture strength of B-1900 at 1255 K is equivalent to the typical strength levels. The exact reasons why the tested heats of B-1900 and

MAR-M509 are weaker than normal is not known; one possible cause is the use of test specimens machined from cylindrical castings rather than cast specimens.

Comparison of the stress-rupture data in appendix A for B-1900 and MAR-M509 at 1144 and 1366 K to literature data reveals that the material behavior at these temperatures is also similar to that seen at 1255 K. That is, the B-1900 alloy tested in this study possesses stress-rupture strengths equivalent to those previously reported in the literature while the MAR-M509 material is weaker than previously reported strengths. Typical photomicrographs of the as-received microstructures and the microstructures of selected stress-rupture specimens are presented in appendix B.

Typical creep curves and minimum creep rate data as a function of applied stress for B-1900 and MAR-M509 tested at 1255 K are presented in figures 4 and 5, respectively. The data in these figures demonstrate that creep in these alloys is generally well-behaved. The degree of scatter in minimum creep rates for MAR-M509 tested at the two lowest stresses (55.3 and 41.4 MPa) was unusually high (fig. 5); multiple testing for either alloy at other stresses and temperatures almost always resulted in minimum creep rates within a factor of two. Creep at 1144 and 1366 K for these two alloys was also well-behaved.

Typical residual tensile properties for the two superalloys after creep testing at 1255 K are presented in figure 6. For purposes of comparison, this figure also contains tensile data from as-received specimens and from specimens which had been thermally exposed for 150 hours in air at 1255 K. Knowledge of the effects of thermal exposure alone is important for the superalloys because their complex chemistries can induce precipitation reactions.

The residual property data for B-1900 in figure 6(a) indicate that thermal exposure alone at 1255 K slightly decreases the ultimate tensile strength and elongation. Furthermore, it appears that creep strains up to 1.25 percent do not unduly affect the residual properties. On the other hand, the test specimen which was creep strained to 1.91 percent did exhibit much lower residual properties. In fact, this specimen failed before the 0.02 percent yield strength was reached. Examination of the fracture surface revealed a large region of oxide which formed during creep testing. The clean fracture surface shown in figure 7(a) is typical for most of the B-1900 specimens; while the nodular fracture surface in figure 7(b) is the only example of a partially oxidized superalloy residual property fracture surface seen in this study.

A review of the residual property data in appendix A for B-1900 after creep testing at either 1144 or 1366 K indicates that creep at these temperatures also

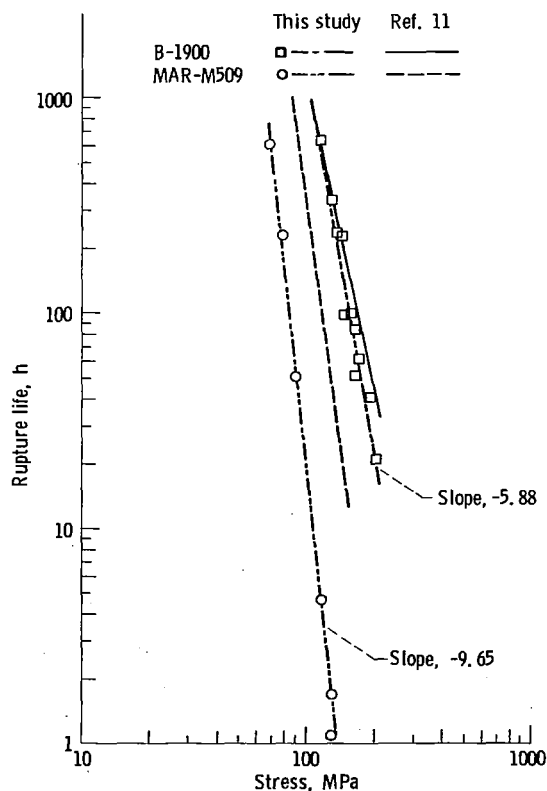


Figure 3 - Rupture life as a function of stress for B-1900 and MAR-M509 at 1255 K.

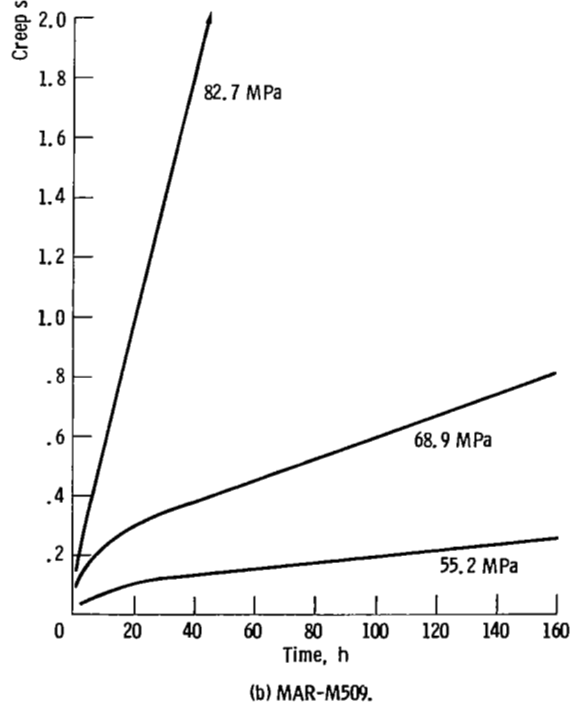
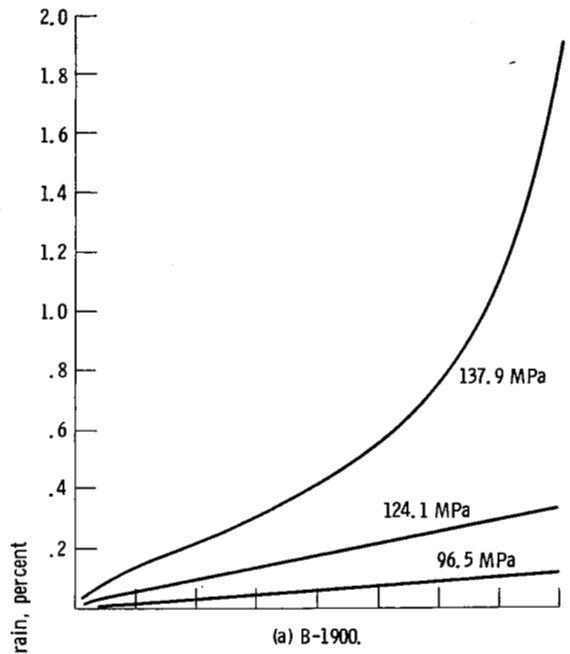


Figure 4 - Typical creep curves for B-1900 and MAR-M509 at 1255 K.

has little influence beyond that due to thermal exposure alone on residual room temperature tensile properties. For example, neither prior creep strains up to about 4 percent at 1144 K nor creep strains up to 0.7 percent at 1366 K affected the residual tensile properties.


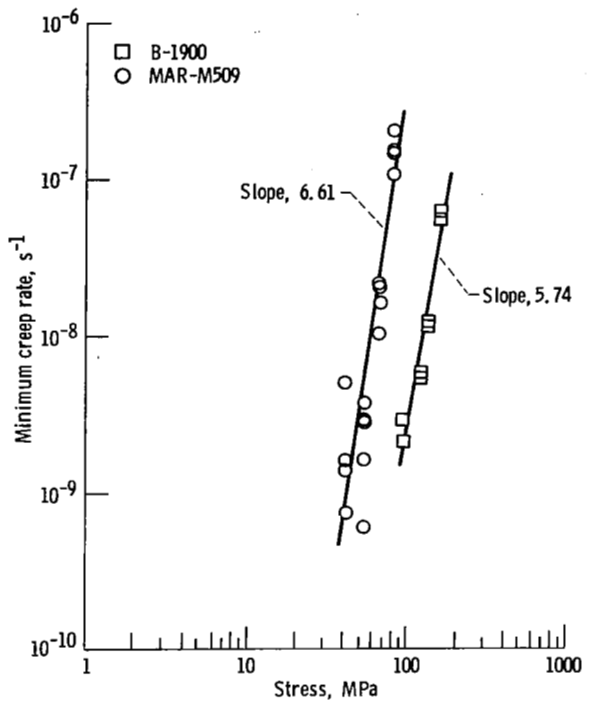


Figure 5 - Minimum creep rate as a function of stress for B-1900 and MAR-M509 at 1255 K.


Examination of the microstructures of selected residual property specimens did not reveal gamma-prime-free regions similar to those reported by Tien and Gamble (ref. 7) or Gibbons (ref. 8). The absence of gamma-prime-free regions is probably due to the much larger grain size (greater than a factor of ten) in the present B-1900 as compared to the alloys discussed in references 7 and 8. Thus it appears that nickel-base alloys with large grain size cast microstructures will not be subject to creep degradation effects.

The room temperature residual property data for MAR-M509 after being creep tested for about 150 hours at 1255 K are presented in figure 6(b). This figure also contains tensile properties for as-received specimens and specimens which had been exposed 150 hours in air at 1255 K. Thermal exposure alone slightly increases the strength and decreases the ductility. Creep strains up to about 1.8 percent do not appear to further reduce tensile properties by any significant amount. The SEM fractograph shown in figure 7(c) is typical of both heat treated and creep strained residual property specimens.


Because of the rather low room temperature ductility of MAR-M509, residual tensile property tests were also conducted at 1144 K following creep testing for about 150 hours at 1255 K. The 1144 K residual tensile property data are shown in figure

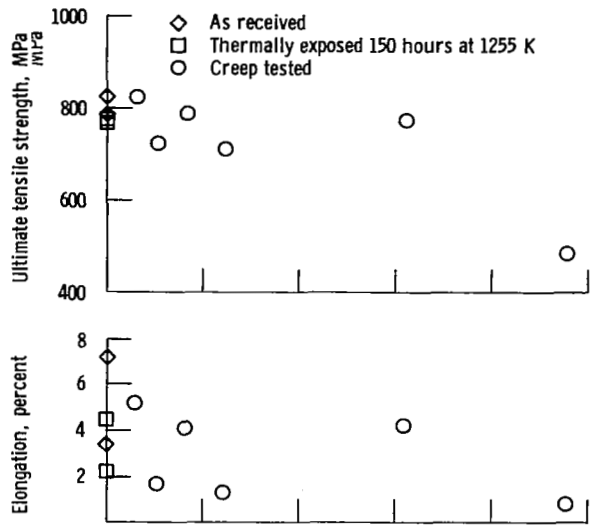

(a) B-1900 tensile tested at room temperature.

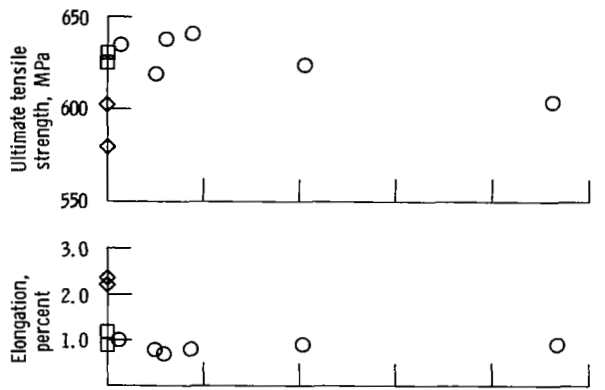


(b) MAR-M509 tensile tested at room temperature.

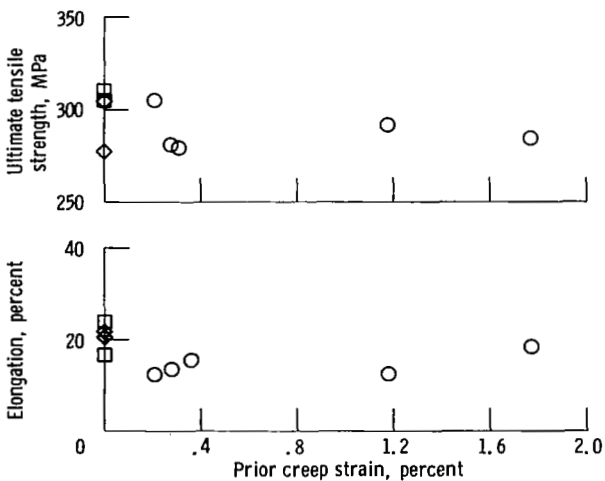


(c) MAR-M509 tensile tested at 1144 K.


Figure 6. - Residual tensile properties as a function of prior creep strain for B-1900 and MAR-M509 creep tested at 1255 K for approximately 150 hours.

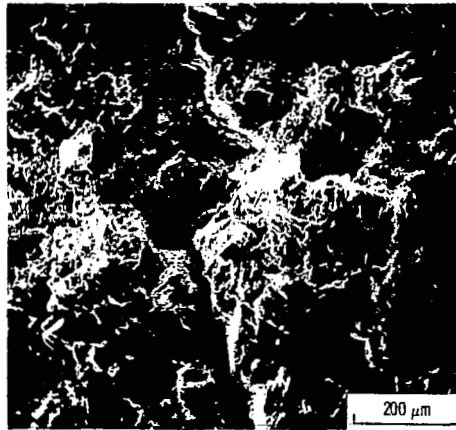

(a) B-1900 strained 0.12 percent at 96.5 MPa before tensile testing.

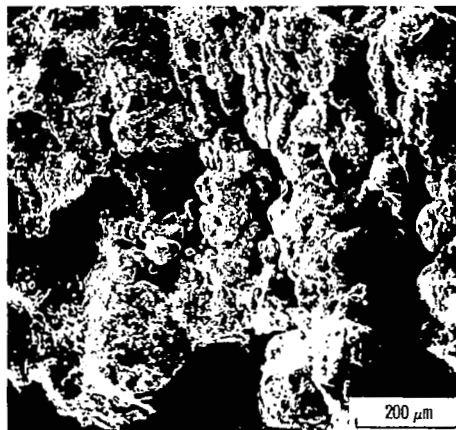

(b) B-1900 strained 1.91 percent at 137.9 MPa before tensile testing.

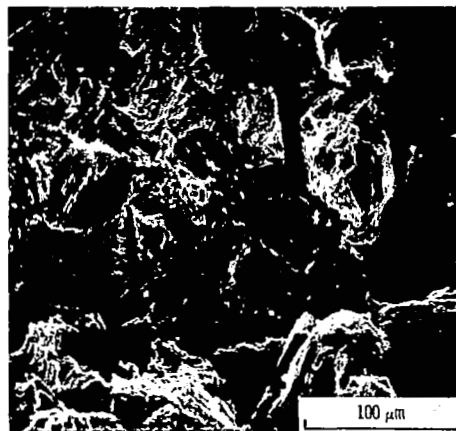

(c) MAR-M509 strained 0.82 percent at 68.9 MPa before tensile testing.

Figure 7. - SEM fractographs of B-1900 and MAR-M509 residual property specimens strained in creep at 1255 K for approximately 150 hours and tensile tested at room temperature.

6(c). At this temperature, prior thermal exposure alone has little effect on the tensile properties. While prior creep up to approximately 1.8 percent strain does not greatly influence the ultimate tensile strength, the tensile elongation was reduced from about 20 percent for as-received and thermally exposed to about 13 percent after creep straining. However, the ductility of as-crept specimens is still reasonable.

A review of the room temperature residual property data for MAR-M509 in appendix A indicates that 1144 K creep straining has no effect while the effect at 1366 K is not clear. In comparison to as-received properties, thermal exposure at 1144 K increases ultimate tensile strength by 15 percent and reduces the tensile elongation from about 2 percent to about 1 percent; these changes are maintained even after 6.83 percent creep strain at 1144 K. Compared to as-received properties, thermal exposure at 1366 K has little effect on ultimate tensile strength, while elongation is decreased to about 1 percent. Of the six possible 1366 K residual property specimens, two (with 0.08 and 0.31 percent creep strain) failed while being removed from the test fixtures, one (with 0.09 percent strain) failed before reaching the 0.2 percent yield stress, and the remaining three (0.17, 0.18, and 0.53 percent strain) possessed tensile properties similar to the thermally exposed specimens. Thus, while it appears that creep strains up to at least 0.53 percent can be tolerated at 1366 K, the large number of questionable failures is disquieting.

Summary of superalloy behavior.—In summary for the superalloys B-1900 and MAR-M509, prior creep at temperatures ranging from 1144 to 1366 K to strains on the order of 1 percent generally have little effect on subsequent tensile properties beyond those changes in tensile properties ascribed to thermal exposure alone.

Oxide Dispersion Strengthened Alloys

A complete tabular presentation of all the mechanical properties determined for the ODS alloys is given in appendix A. For simplicity, typical mechanical properties for each ODS alloy are presented in the following sections.

MA-757.—Typical elevated temperature tensile properties are presented in figure 8 and stress-rupture properties at 1366 K in the longitudinal and long transverse bar directions are presented in figure 9. While the elevated temperature tensile strength is not dependent on testing direction, both tensile ductility and rupture strengths are directionally dependent. In rupture testing, the longitudinal direction was always stronger than the long transverse direction, irrespective of test temperature (appendix A).

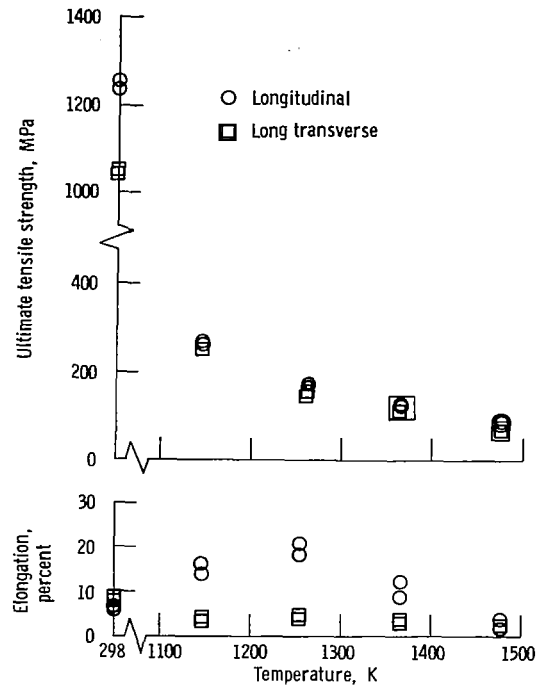


Figure 8. - Tensile properties as function of temperature and test direction for MA-757.

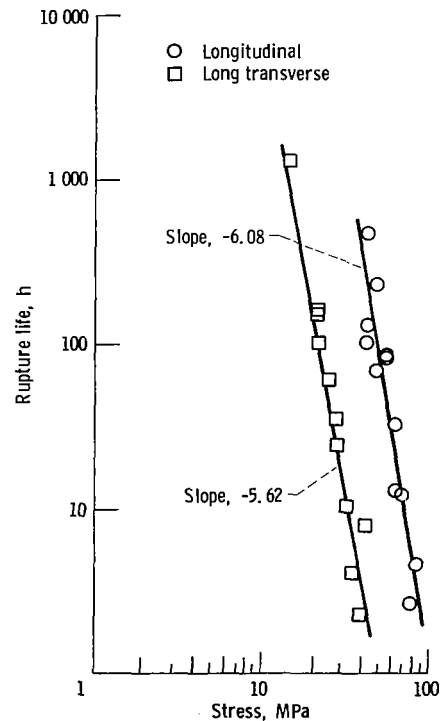


Figure 9. - Rupture life as a function of stress for MA-757 at 1366 K.

Photomicrographs of representative stress-rupture specimens are presented in appendix B. Of particular importance are the presence of dispersoid-free regions, extensive grain boundary cavitation and cracking, and massive internal oxidation (which leads to extended stress-rupture life and high rupture ductilities). All of these effects reduce the usefulness of stress-rupture data for design purposes (ref. 1).

Typical 1366 K creep curves and minimum creep rates as a function of stress are shown in figures 10 and 11, respectively. As is the case for most ODS bar alloys, the longitudinal direction is stronger than the long transverse direction. Also it should be noted that very small changes in stress (about 3.5 MPa) can produce very large changes in creep strain. Thus it proved difficult to induce moderate amounts of creep strain (from about 0.4 to about 1.0 percent) under the testing conditions (strain after 150 h of testing) used in this study.

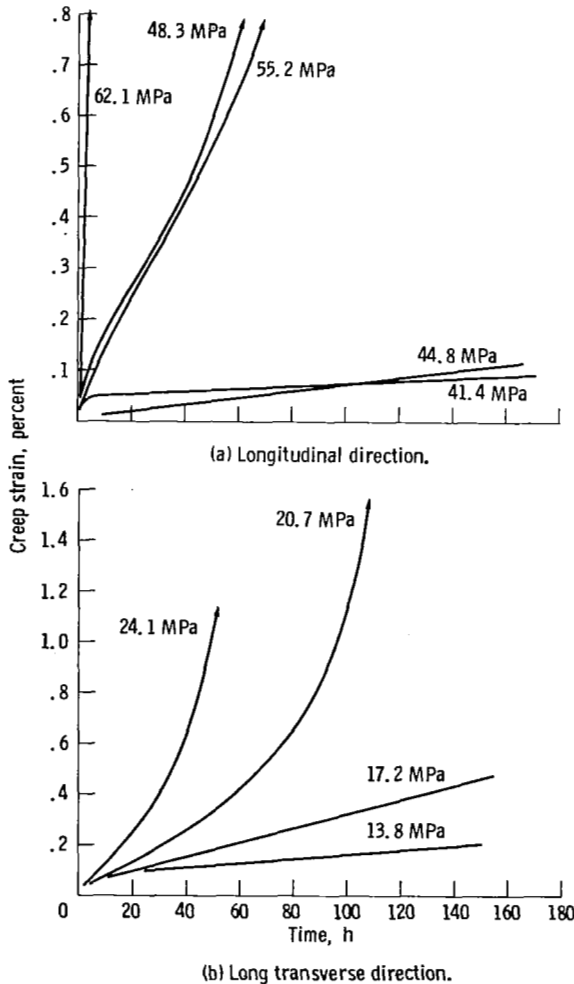


Figure 10. - Typical creep curves for MA-757 at 1366 K.

The creep data in appendix A for MA-757 reveals that creep behavior at 1144, 1255, and 1477 K is similar to that at 1366 K; the longitudinal direction is stronger than the long transverse direction and small changes in stress can result in large changes in creep strain.

Residual tensile properties after prior elevated temperature creep straining are presented in figure 12. Previous residual property studies of ODS alloys (refs. 2 and 3) have indicated that tensile ductility and fractography are the most sensitive indicators of creep damage; in general, rather severe creep damage (very large scale dispersoid-free bands, cavitation, and internal oxidation) must take place before significant changes in residual strengths are noted.

The residual mechanical property data in figure 12(a) indicate that both the ultimate tensile strength and ductility in the longitudinal direction can be affected by prior creep. In general, the ultimate tensile strengths are not greatly reduced (maximum reduction observed was 25 percent) by creep strains up to about 0.55 percent. The behavior of the residual ductility shown in figure 12(a) is erratic; both increases and decreases as compared to as-received ductility are observed. Thus, while prior



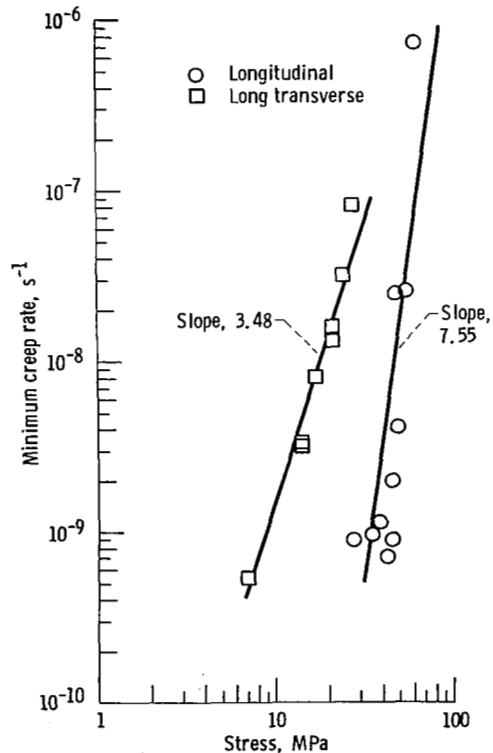


Figure 11. - Minimum creep rate as a function of stress for MA-757 at 1366 K.

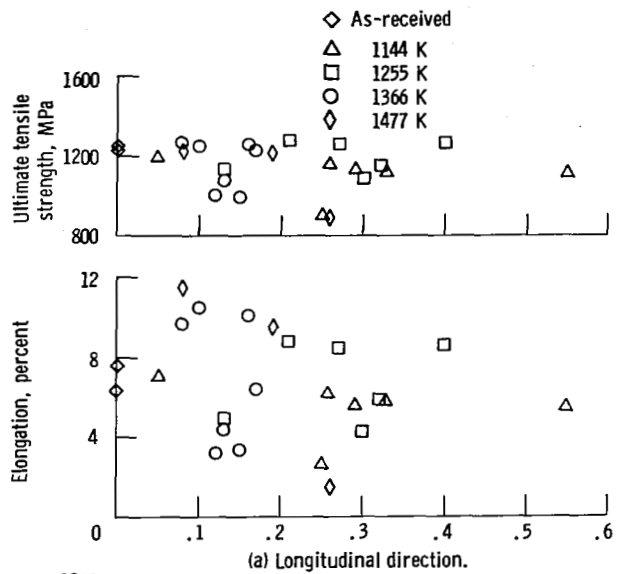

(a) Longitudinal direction.

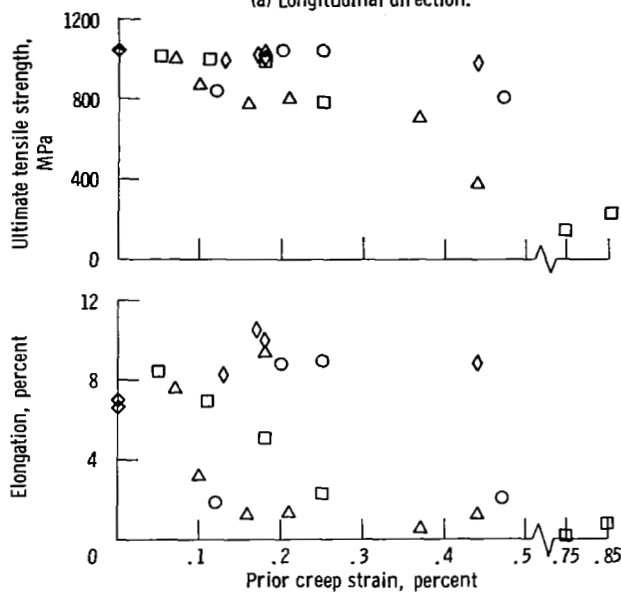


(b) Long transverse direction.


Figure 12. - Residual room temperature tensile properties as a function of prior creep strain for MA-757 strained at 1144 to 1477 K for approximately 150 hours.

creep straining apparently does not produce creep degradation in every instance, the mechanical property data illustrate that creep degradation can occur in the longitudinal direction.

Fractographs of residual property specimens (fig. 13) and microstructures of stress-rupture tested specimens (appendix B) indicate that microstructural changes (refs. 2 and 3) which lead to degradation of mechanical properties are occurring during creep. In particular, pock-marked fracture surfaces are considered indicative of damage associated with the

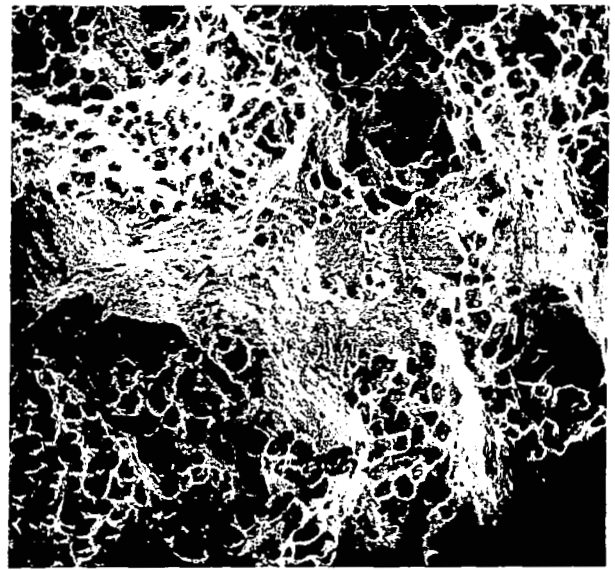

(a) Longitudinal specimen strained 0.32 percent at 68.9 MPa before tensile testing.

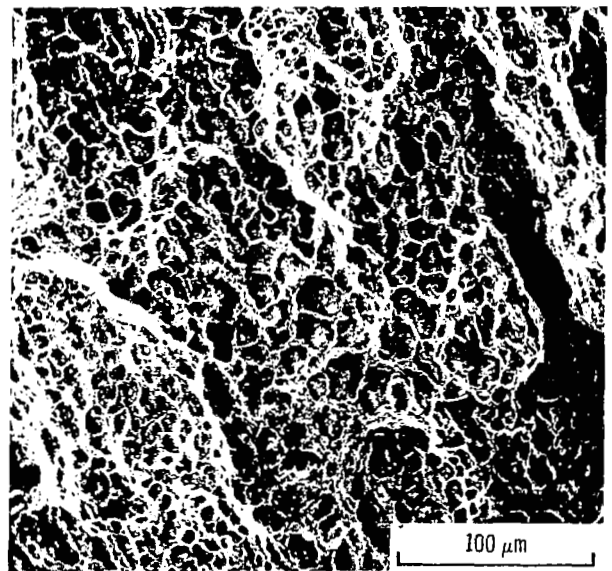

(b) Long transverse specimen strained 0.25 percent at 34.5 MPa before tensile testing.

Figure 13. - SEM fractographs of MA-757 residual property specimens strained in creep at 1255 K for approximately 150 hours and tensile tested at room temperature.

formation of weakened, dispersoid-free regions during prior creep straining. Thus, the eventual reduction of mechanical properties in the longitudinal direction after long term elevated temperature creep straining should be expected.

The residual mechanical property data in figure 12(b) also indicate that creep damage has occurred for tests conducted in the long transverse direction. In general, for prior creep exposures between 1144 and 1366 K, creep damage occurs at about 0.1 percent strain while prior creep at 1477 K to about 0.44 percent strain does not appear to affect residual properties. Fractography of residual property specimens which had previously been creep strained at 1255 K (fig. 13) and metallography of failed stress-rupture specimens tested at 1144 and 1477 K (appendix B) reveal microstructural features intimately connected with creep degradation.

MA-956.—Of the alloys tested in this program, MA-956 is by far the most unusual and interesting. Because of this, the majority of the MA-956 data on longitudinal properties will be graphically presented. In general, data for MA-956 in the long transverse direction will be only summarily presented. Only a few tests in the long transverse direction were conducted due to difficulties in obtaining sound specimens. All mechanical property data obtained for MA-956 are presented in appendix A.

Typical elevated temperature tensile properties for MA-956 tested in the longitudinal and long transverse bar directions are shown in figure 14. In general, the longitudinal direction was stronger and more ductile than the long transverse direction. The strength data in the long transverse direction at 1144 and 1255 K exhibited considerable scatter, possibly due to internal defects (see fig. 1). Except at room temperature, the strength and ductility results in the longitudinal direction were consistent. At room temperature the long transverse specimen and one longitudinal specimen failed by cleavage at low elongations; the other longitudinal specimen also failed by cleavage but only after considerable deformation.

The stress-rupture characteristics of MA-956 tested in the longitudinal direction are shown in figure 15. These data reveal that the stresses to produce rupture in times ranging from 0.1 to greater than 1000 hours for temperatures ranging from 1144 to 1477 K lie in a band about 30 MPa in width. Rupture life is thus highly dependent on stress.

Typical creep curves for longitudinal MA-956 tested at 1255 K are shown in figure 16 and steady state creep rate data as a function of stress and temperature are presented in figure 17. Examination of the creep curves in figure 16 illustrates an important characteristic concerning creep failure of MA-956. When failure occurs, there is almost an instantaneous transition from an apparently slowly deforming specimen to a failed specimen. The process or processes which control the final few moments of life must be very rapid and allow

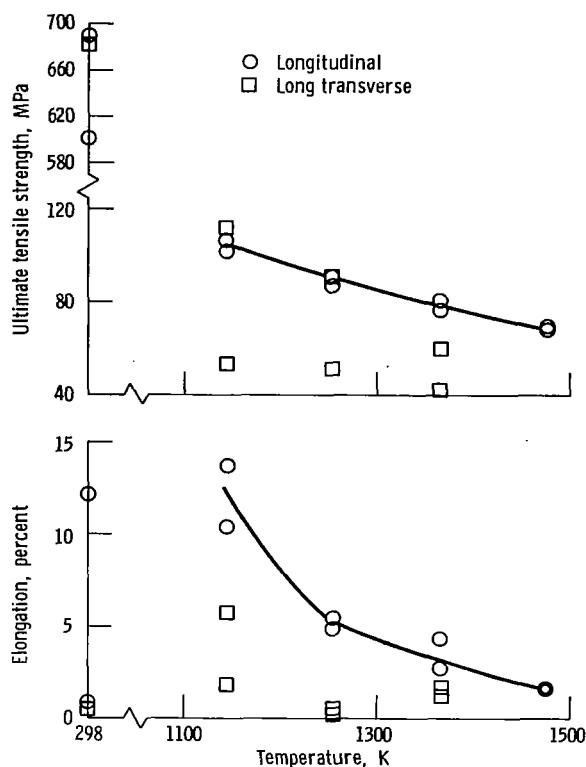


Figure 14. - Tensile properties as a function of temperature and test direction for MA-956.

considerable deformation to occur as indicated by the final elongation and reduction-in-area data for the failed specimens (appendix A). Except for the short life tests (failure times less than 10 h), MA-956 does not exhibit third stage creep. This behavior was noted at all four test temperatures.

A macrograph of a typical failed MA-956 specimen is shown in figure 18. As can be seen, considerable localized deformation (reduction in area) has occurred. Note, however, that the observed deformation has apparently taken place only on one side of the test specimen while the other side has remained essentially parallel to the stress axis.

Typical SEM fractographs of the fracture surface of the same MA-956 specimen shown in figure 18 are presented in figure 19. Figure 19(a) shows a flat crack-like surface which is perpendicular to the applied stress, and figure 19(b) illustrates a region, ahead of the crack-like surface, which is composed of small flat areas on many different levels. Similar fracture surfaces have been seen on specimens of MA-956E after stress-rupture testing at 1365 K (ref. 4) and on MA-956 bar after slow tension testing at 1366 K (ref. 12). The latter work presents evidence that the flat regions found on the fracture surfaces of

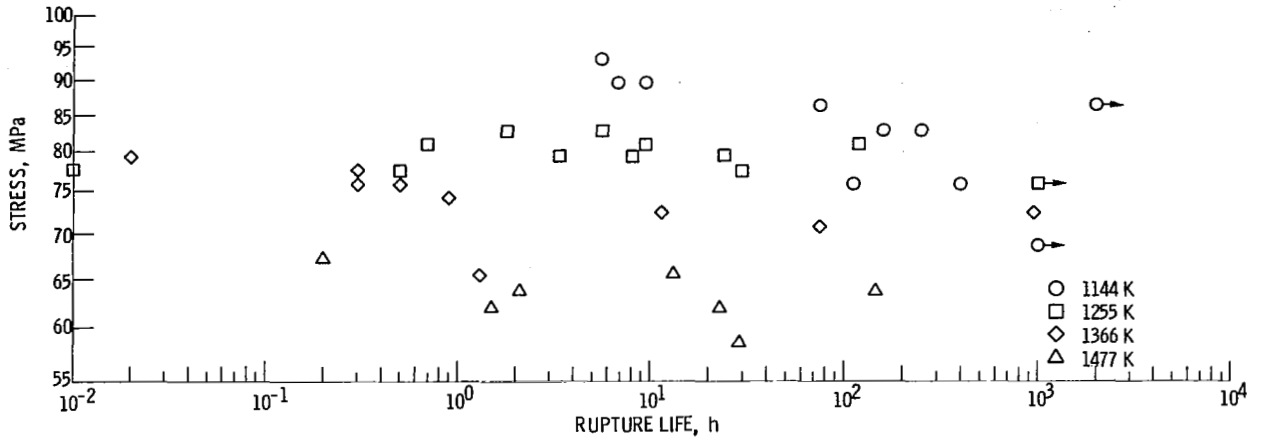


Figure 15. - Rupture life as a function of stress in longitudinal direction for MA-956 at 1144 to 1477 K.

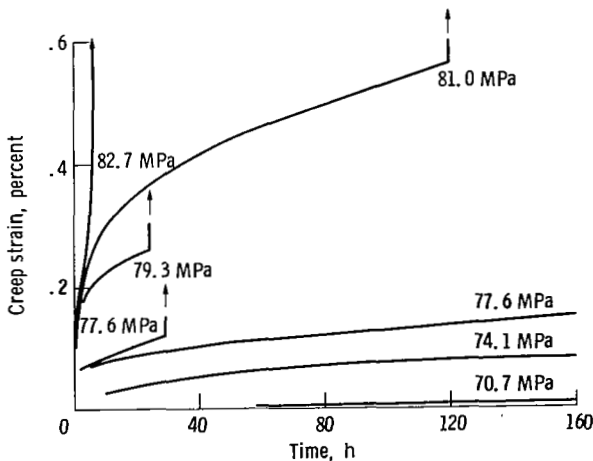


Figure 16. - Typical creep curves in longitudinal direction for MA-956 at 1255 K.

MA-956 are indeed the result of slow growth of a crack and that the multilevel region ahead of the crack occurs when the running crack is undergoing the transformation from slow to fast growth. Crack growth processes apparently take place in MA-956 until the remaining load-bearing area is reduced to the point where fast ductile deformation can occur. Since the running crack starts at or near the surface of the test specimen and slowly grows until overload conditions occur, metallographic sections parallel to the stress axis should reveal a structure which has a deformed and undeformed appearance on opposite sides of the specimen. This is consistent with the structure shown in figure 18.

Because of the slow crack growth mechanism by which MA-956 apparently undergoes slow plastic

deformation, the measurement and reporting of minimum creep rates may not be meaningful. However, for completeness, these data were characterized and are graphically presented in figure 17. This figure contains approximate minimum creep rate data for two tests which underwent no deformation after about 150 hours of testing (points plotted at rate = 10^{-10} s⁻¹ and five tests which underwent considerable deformation in a short time. The minimum creep rate data in figure 17 are very similar to the stress-rupture data in figure 15 in that both deformation rates and rupture lives are highly dependent on stress.

The creep data in figure 17 also illustrate the very strong dependency of creep rate on stress, where small changes in stress produce dramatic differences in behavior. Although many attempts were made, it proved impossible to induce moderate amounts of creep strain into MA-956 specimens. There were only 12 unfailed creep specimens out of a total of 34 creep tests; of these specimens, one had 0.25 percent strain, two had about 0.15 percent strain, and the remaining had 0.1 percent or less strain. Except for the short life tests, very little creep deformation was observed. The maximum amount of creep strain seen in any test (prior to the rapid failure processes, if failure occurred) is shown in figure 16 by the test conducted at 81 MPa.

Typical room temperature residual tensile properties of MA-956 in the longitudinal direction are presented in figure 20. These data indicate that for prior elevated temperature creep strains of less than 0.25 percent, MA-956 is not subject to creep degradation. Attempts to introduce larger creep strains were not successful. No evidence of creep damage was seen during SEM examination of selected fracture surfaces. Only cleavage type

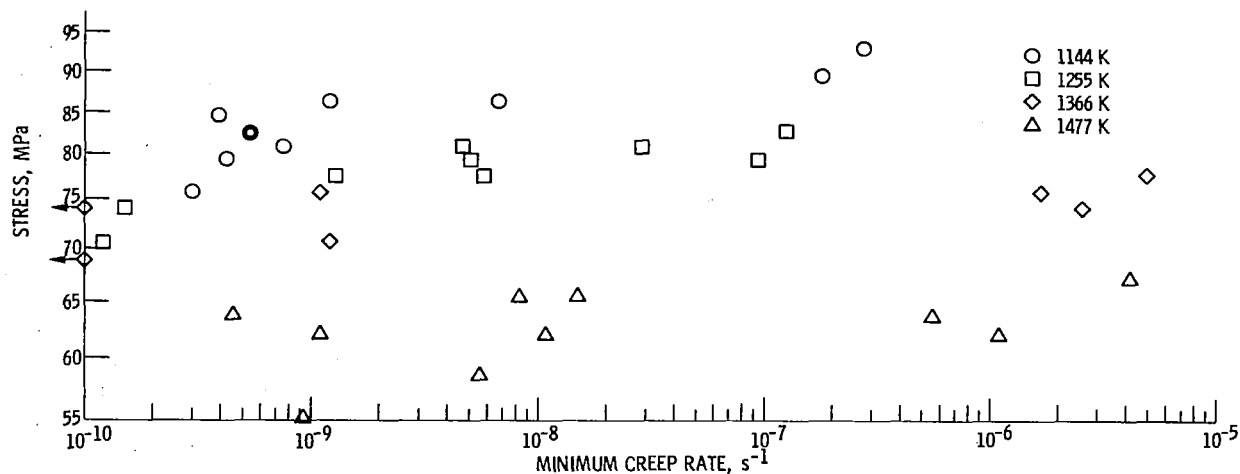


Figure 17. - Minimum creep rate at a function of stress for MA-956 tested in longitudinal direction at 1144 to 1477 K.



Figure 18. - Macrograph of failure region of MA-956 rupture tested in longitudinal direction for 943.1 hours at 72.4 MPa and 1366 K.


features were seen on the fracture surface of as-received room temperature test specimens, whereas regions of ductile failure as well as cleavage failure were seen on the residual property test specimens. Typical examples of residual fracture surfaces are presented in figure 21.

In summary, the elevated temperature deformation characteristics of MA-956 tested in the longitudinal direction are unusual. Under test conditions designed to promote slow plastic flow, the alloy apparently deforms by the growth of cracks. This process is rather insensitive to test temperature but extremely sensitive to stress. With regard to residual properties, MA-956 is not subject to creep degradation in the longitudinal direction at least up to prior creep strains on the order of 0.25 percent.


STCA alloys.—Only room temperature and 1366 K tensile testing, 1366 K creep testing, and room temperature residual property testing were conducted on STCA alloys; all test results are tabulated in appendix A.

The 1366 K tensile data (appendix A) reveal that the tensile strength of STCA alloys is independent of chemistry and test direction. While tensile elongation appears to vary with chemistry, the reduction-in-area ductility data do not indicate significant differences based on chemistry. Both ductility indicators reveal, however, that the longitudinal direction is more ductile than the long transverse direction at 1366 K.

Typical creep curves and minimum creep rates as a function of stress, testing direction, and heat treatment are presented in figures 22 and 23, respectively, for STCA-266 tested at 1366 K. This alloy contains about 1.2 weight percent Ta in addition to nominally 16Cr and 4.5Al (table I); STCA-266SC was given a carbide precipitation heat treatment following the standard heat treatment. The creep rate data in figure 23 indicate that the alloy in the longitudinal direction is more creep resistant than in the long transverse direction; additionally, it appears that the carbide heat treatment lowers the creep strength of heat STCA-266 in the long transverse direction. As is the case for most ODS alloys, small changes in stress can produce large changes in creep strain. Thus, it proved difficult to induce moderate creep strains in specimens for residual property testing. Whereas the creep behavior in figures 22 and 23 is typical, discrepancies in behavior were observed; for example, the carbide precipitation heat treatment lowered the creep strength of STCA-266 but did not affect the strength of STCA-265 (appendix A). Also in the longitudinal

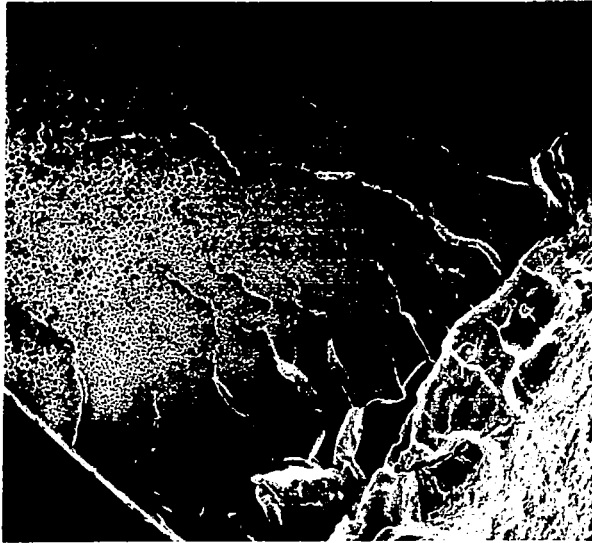

(a) Fracture surface in crack-like region.

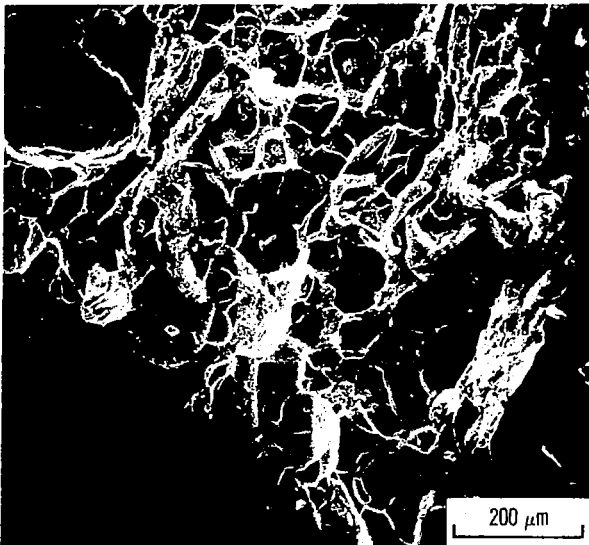

(b) Fracture surface ahead of crack.

Figure 19. - SEM fractographs of MA-956 specimen ruptured tested in longitudinal direction for 943.1 hours at 72.4 MPa and 1366 K.

testing direction the Ta-free alloy (STCA-262/264S) and the Ta-rich alloy (STCA-265S) are stronger than the intermediate Ta level alloy (STCA-266S); however in the long transverse direction the Ta-free and the intermediate level Ta alloys are stronger than

the Ta-rich alloy. The reasons for this behavior are not known. Photomicrographs of representative failed creep specimens are presented in appendix B. As was the case for MA-757, these photomicrographs reveal the presence of extensive grain boundary cavitation and cracking. Dispersoid-free regions and massive internal oxidation were also noted on some specimens.

Room temperature residual tensile properties for STCA alloys after 1366 K creep straining are compared to as-received properties in figure 24. The as-received room temperature strength properties are dependent on test direction and essentially independent of chemistry. The ultimate tensile strengths are about 1300 and 1100 MPa in the longitudinal and long transverse directions, respectively, and both testing directions and all chemistries exhibit from 5 to 6 percent elongation. In the longitudinal test direction, prior creep straining up to 0.11 percent had no effect on residual properties except for the STCA-265SC specimen pre-crept 0.09 percent (fig. 24(a)); SEM examination of this specimen revealed an internal defect on the fracture surface which produced the premature failure. Prior creep exposure involving creep strains between 0.13 and 0.55 percent in the longitudinal



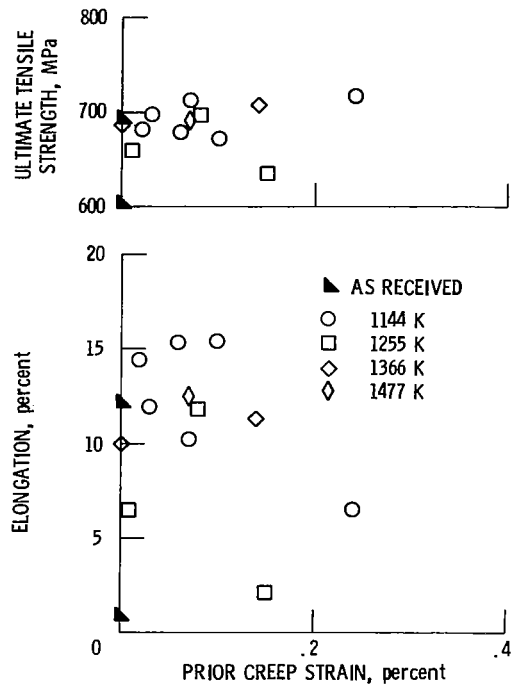


Figure 20. - Residual room temperature tensile properties as a function of prior creep strain for MA-956 strained in longitudinal direction at 1144 to 1477 K.

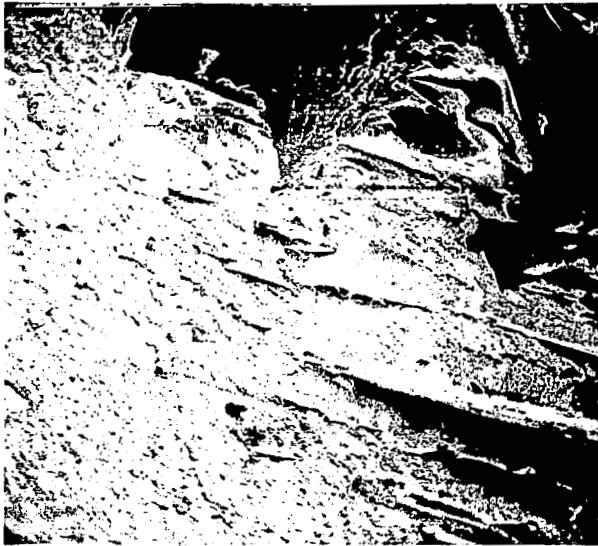


(a) Strained 0.08 percent at 74.1 MPa before tensile testing. Ductile plus cleavage fracture.

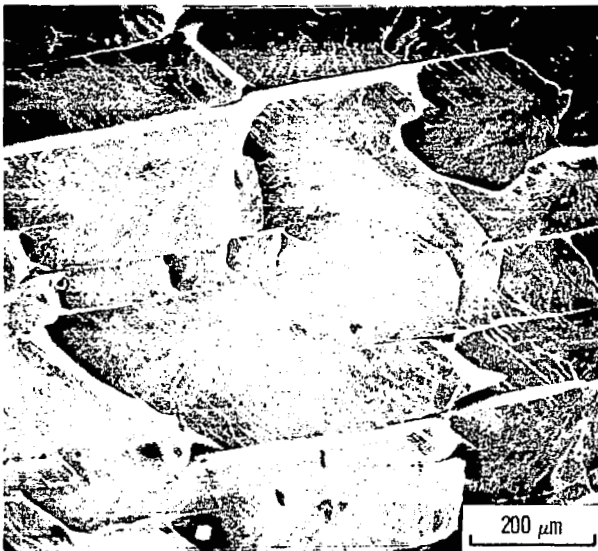


(b) Strained 0.15 percent at 77.6 MPa before tensile testing. Cleavage fracture.

Figure 21. - SEM fractographs of longitudinal MA-956 residual property specimens strained in creep for approximately 150 hours at 1255 K and tensile tested at room temperature.


direction lowered the tensile strength about 15 percent to nominally 1000 MPa, whereas the tensile elongation was progressively lowered from 6 percent to about 1 percent as the prior creep strain increased.

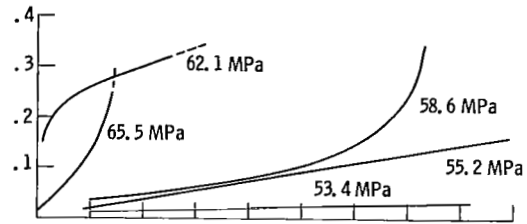

(a) STCA-266S in longitudinal direction.

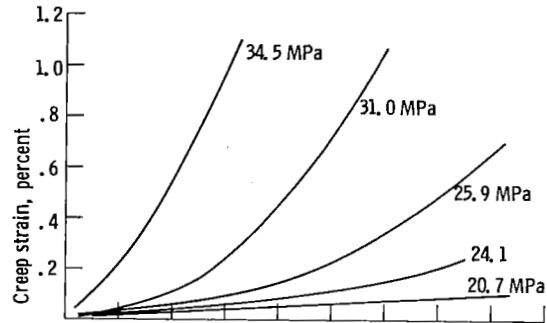

(b) STCA-266S in long transverse direction.

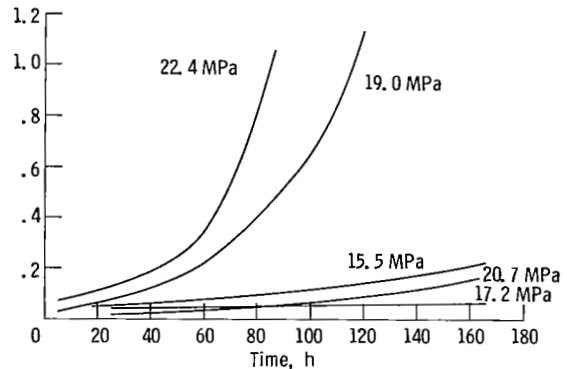

(c) STCA-266SC in long transverse direction.

Figure 22. - Typical creep curves for STCA-266S and STCA-266SC at 1366 K.

The residual property data in figure 24(b) for the long transverse direction indicate that prior creep strain up to about 0.1 percent has no effect on room temperature properties. However, at greater than 0.1 percent strain the residual tensile properties are severely degraded. In many cases tensile failure occurred before the 0.2 percent offset yield strength was reached. Two typical SEM fractographs illustrating creep-damaged areas on STCA residual property fracture surfaces are presented in figure 25.

YD-NiCrAl.—As only a few *YD-NiCrAl* specimens were available for testing, only 1366 K creep and residual property tests were conducted.


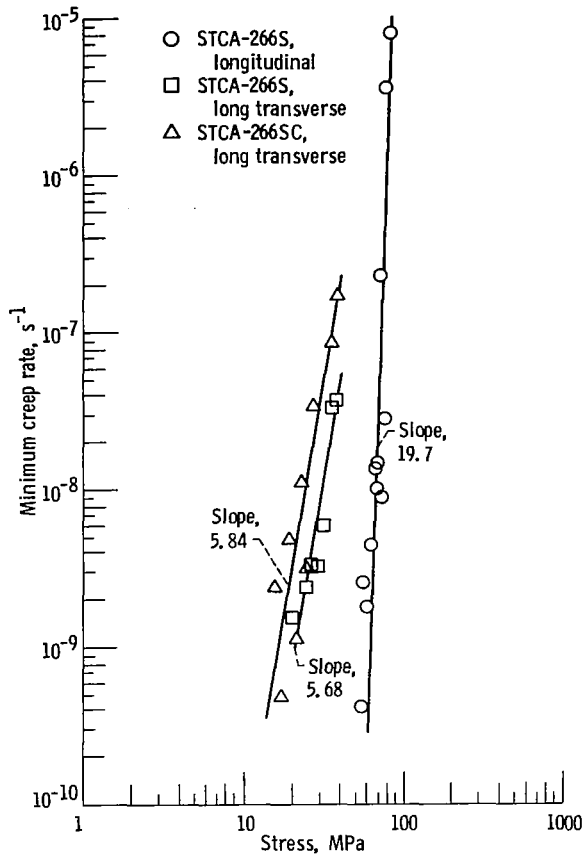



Figure 23. - Minimum creep rate as a function of stress for STCA-266S and STCA-266SC at 1366 K.

Typical creep curves are shown in figure 26 and minimum creep rates as a function of stress are shown in figure 27. This alloy was reasonably ductile in creep because strains up to about 0.7 percent after about 150 hours of testing could be readily induced (fig. 26). Figure 27 also indicates that creep rates in YD-NiCrAl are highly dependent on stress.

Figure 28 presents residual tensile property data for YD-NiCrAl after creep straining at 1366 K. Unfortunately, as-received tensile properties are not available for comparison; however, the residual property data indicate that YD-NiCrAl is not severely affected by prior creep straining in the longitudinal direction. In general, the ductility is good (8 percent elongation or greater) and tensile strength is high (about 1050 MPa) even after 0.72 percent prior creep strain. While the residual mechanical properties are excellent in terms of resistance to creep degradation, SEM fractography (fig. 29) of residual property specimens did reveal areas which were creep-damaged. Thus, long term application under slow strain rate conditions might

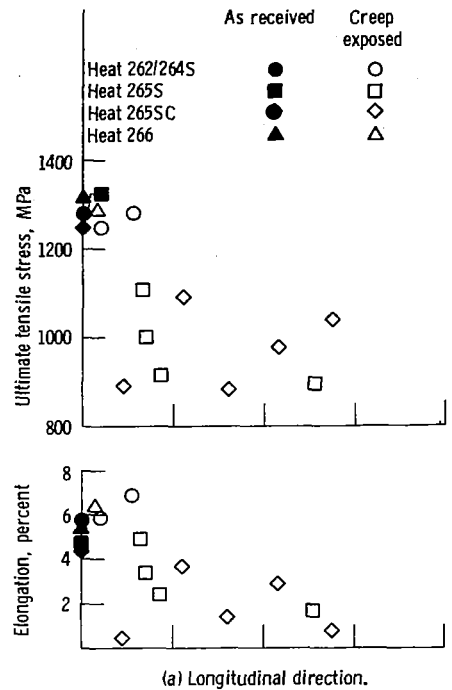


(a) Longitudinal direction.

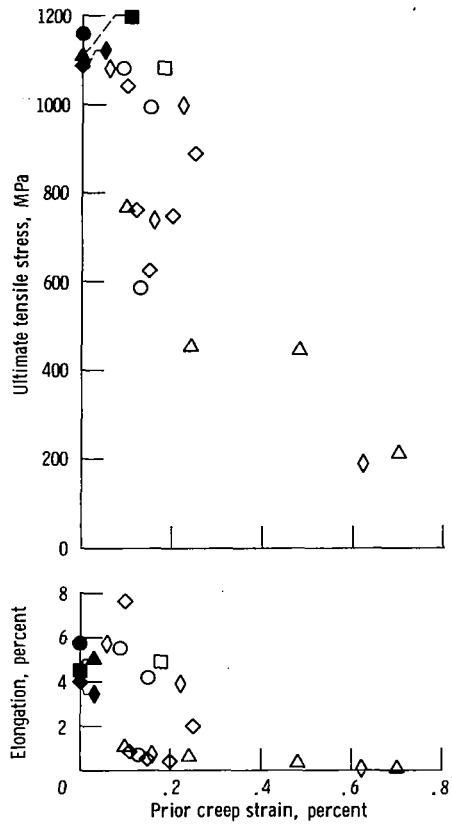


(b) Long transverse direction.

Figure 24. - Residual room temperature tensile properties as a function of prior creep strain for STCA alloys strained at 1366 K for approximately 150 hours.

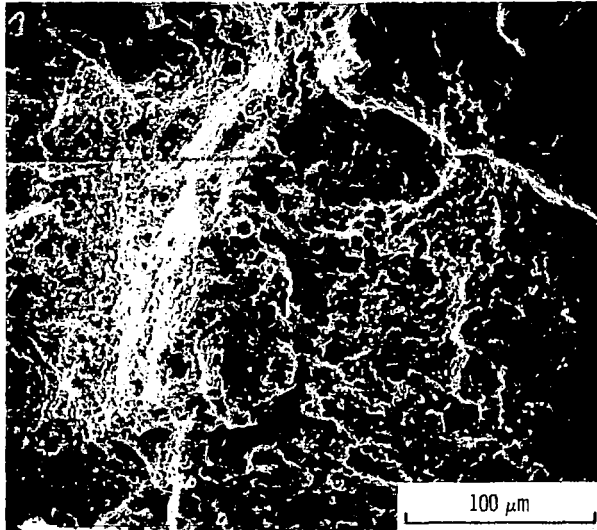

(a) STCA-265SC longitudinal specimen strained 0.32 percent at 68.9 MPa before tensile testing.

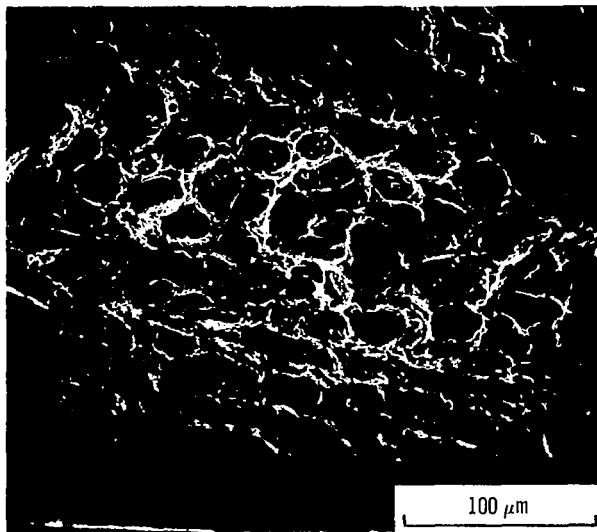

(b) STCA-266S long transverse specimen strained 0.10 percent at 20.7 MPa before tensile testing.

Figure 25. - SEM fractographs of STCA residual property specimens strained in creep for approximately 150 hours at 1366 K and tensile tested at room temperature.

lead to severe degradation of subsequent tensile properties in YD-NiCrAl as damaged regions increase in size during creep.

Summary and comparison of ODS alloy behavior.—All of the nickel-base ODS alloys examined in this study revealed signs of creep

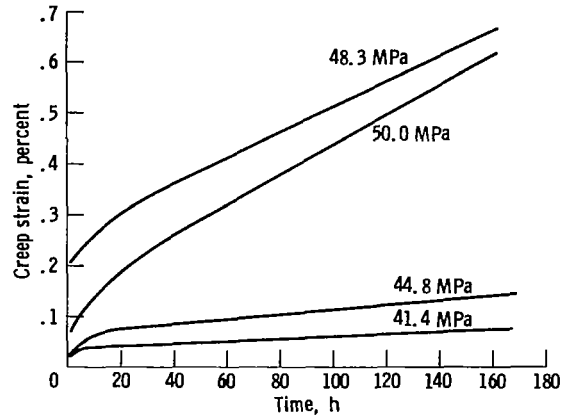


Figure 26. - Typical creep curves for YD-NiCrAl in longitudinal direction at 1366 K.

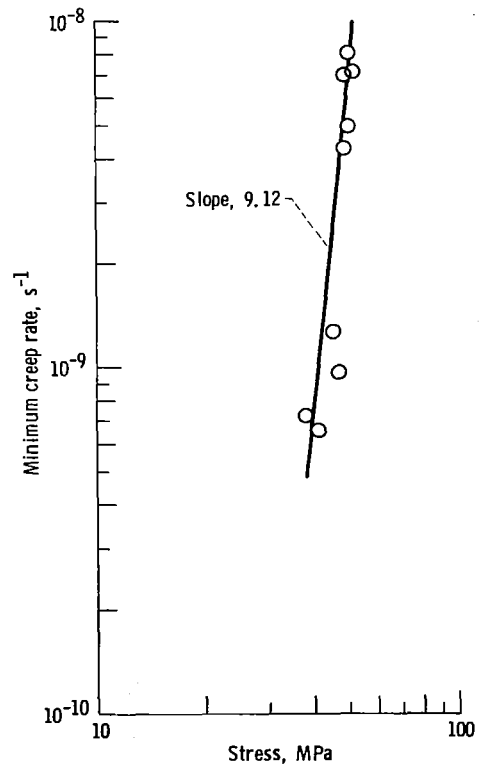


Figure 27. - Minimum creep rate as a function of stress for YD-NiCrAl tested in longitudinal direction at 1366 K.

degradation. The longitudinal bar direction is more resistant to degradation than the long transverse bar direction. In the longitudinal direction, creep strains up to about 0.5 percent in 150 hours do not significantly reduce residual room temperature


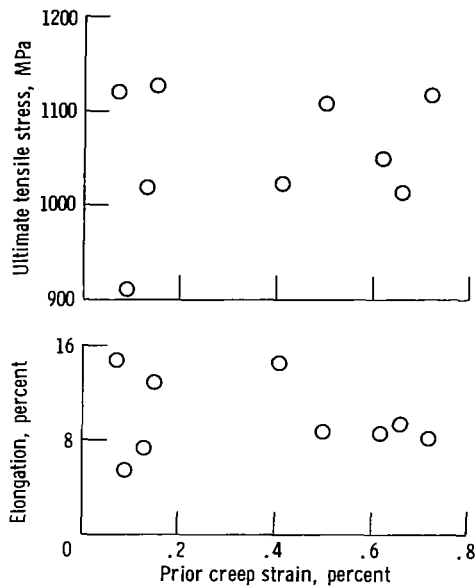


Figure 28. - Residual room temperature tensile properties as a function of prior creep strain for YD-NiCrAl strained in longitudinal direction at 1366 K for approximately 150 hours.


tensile properties. However, the observation of microstructural artifacts thought to be connected to creep degradation on longitudinal test specimens indicates that severe damage is possible for very long time creep exposures even if they involve only small strains. In the long transverse direction, prior creep exposures involving as little as 0.1 percent strain can produce significant reduction in residual properties. Overall, the residual property behavior of nickel-base ODS alloys in this study is similar to that of MA-754 (ref. 3), where the degree of creep damage was dependent on testing direction as well as the amount of prior creep strain. Finally, on the basis of MA-757 testing and previous results for TD-NiCr (ref 2), it appears that creep degradation will occur in practically all nickel-base ODS alloys when creep strained between 1144 and 1477 K.

The ODS iron-base alloy MA-956 is apparently not subject to creep degradation for prior creep strains up to 0.25 percent in the longitudinal bar direction. It should be noted, however, that it was not possible to induce larger creep strains into this alloy because of the unusual manner in which MA-956 deforms at elevated temperatures.

With regards to long term elevated temperature creep strength of ODS alloys, the longitudinal bar direction was always stronger than the long transverse bar direction. Comparison of the long

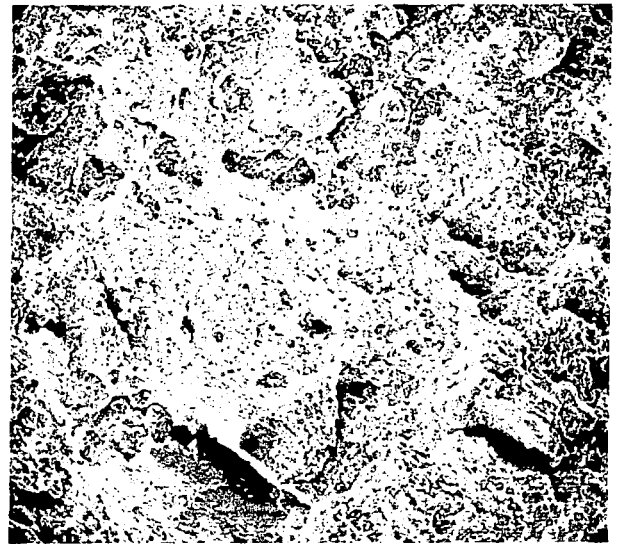

(a) Strained 0.07 percent at 41.4 MPa before tensile testing.

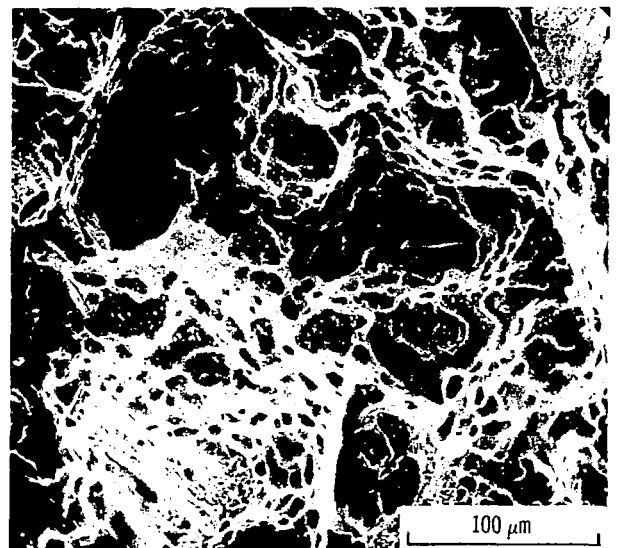

(b) Strained 0.66 percent at 48.3 MPa before tensile testing.

Figure 29. - SEM fractographs of YD-NiCrAl residual property specimens strained in creep at 1366 K for approximately 150 hours and tensile tested at room temperature.

term creep strength at 1366 K in the longitudinal direction of iron-base MA-956 (fig. 17) to those of nickel-base alloys (figs. 9, 23, and 27) reveals that MA-956 is more creep resistant than the nickel-base alloys. The data in appendix A reveal that the long term creep strength of MA-757 at 1144 K in the

longitudinal direction is greater than that of MA-956; however, between 1255 and 1477 K the opposite behavior is observed, with MA-956 being the stronger alloy.

Conclusions

The following conclusions are drawn from this study of creep and residual mechanical properties of high temperature superalloys and advanced ODS alloys:

1. The tensile properties of the large grain size cast superalloys B-1900 (nickel-base) and MAR-509 (cobalt-base) are not degraded by creep at least up to about one percent strain at 1144 to 1366 K.

2. The room temperature properties of the wrought Ni-Cr-Al ODS alloys MA-757, STCA, and

YD-NiCrAl can be degraded by prior creep strains of 0.5 percent or less at 1144 to 1477 K. The longitudinal direction is less susceptible to creep damage than the long transverse direction.

3. The residual room temperature tensile properties of the iron-base ODS alloy MA-956 are apparently not degraded by prior creep straining up to 0.25 percent at 1144 to 1477 K. However, MA-956 exhibits unusual creep behavior which apparently involves nucleation and slow growth of cracks.

Lewis Research Center
National Aeronautics and Space Administration
Cleveland, Ohio, August 21, 1980

Appendix A

Mechanical Properties of Test Alloys

This appendix presents a tabular summary of all mechanical property data generated during this study. Each alloy and its pertinent tables are listed here:

| | |
|-----------|-------------------------|
| B-1900 | Tables III(a) to (d) |
| MAR-M509 | Tables IV (a) to (e) |
| MA-757 | Tables V (a) to (d) |
| MA-956 | Tables VI (a) to (d) |
| STCA | Tables VII (a) to (c) |
| YD-NiCrAl | Tables VIII (a) and (b) |


Appendix B

Microstructure of Several Tested Alloys


The following appendix contains typical photomicrographs of the alloys which were extensively studied. Where meaningful, photomicrographs of both as-received and test alloys are presented.

Figure 30 contains photomicrographs of as-received and stress-rupture tested B-1900. As can be most easily seen in figure 30(a), the as-received B-1900 contains porosity due to the casting process.

Figure 30(b) shows a typical microstructure for long term B-1900 stress-rupture specimens. Comparison of figures 30(a) and (b) indicates that the gamma-prime phase grows during rupture testing. Also figure 30(b) shows oxide penetration along grain boundaries. Both specimens were etched with a mixed acid solution containing 33 parts by volume HCl, 33 parts acetic acid, 33 parts HNO₃, and 1 part HF.

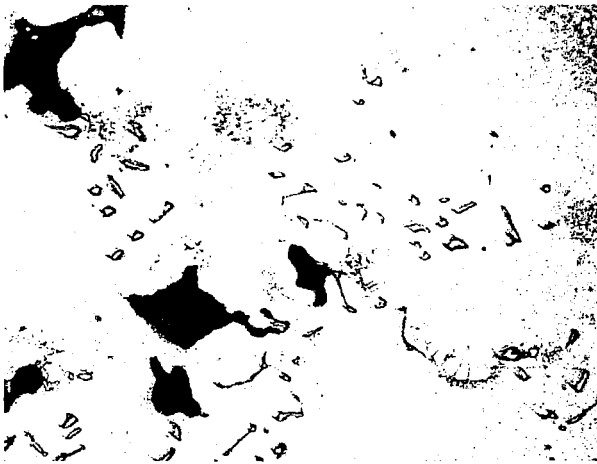


(a) As-received.

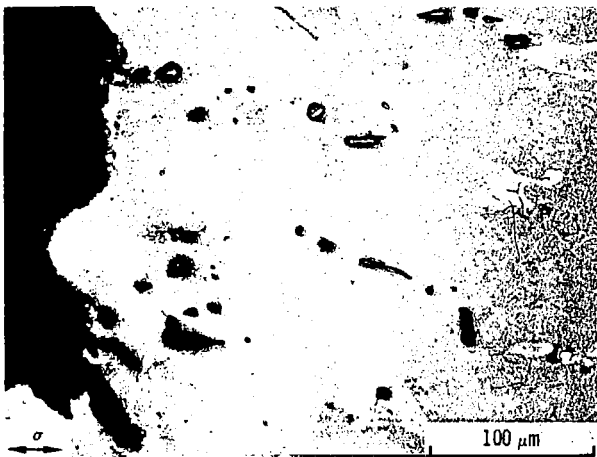


(b) Stress rupture tested for 624.6 hours at 117.1 MPa and 1255 K.

Figure 30. - Microstructures of B-1900.

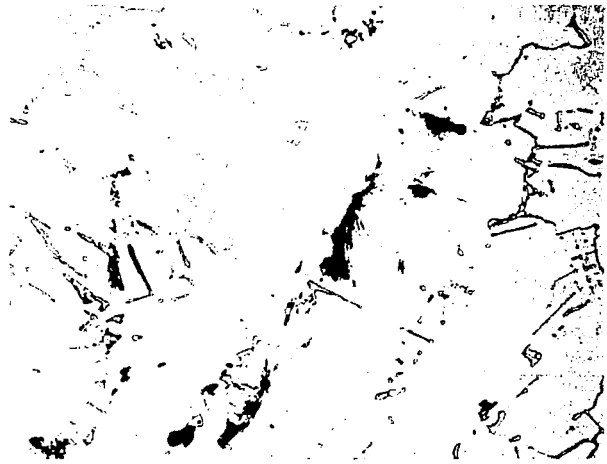

(a) As-received.

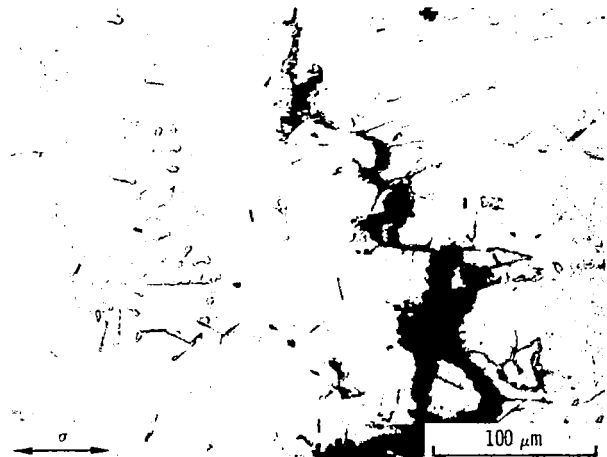

(b) Stress rupture tested for 606.2 hours at 68.9 MPa and 1255 K.


Figure 31. - Microstructures of MAR-M509.

The microstructure of as-received MAR-M509 is shown in figure 31(a) where the Chinese script pattern of the carbides can be easily seen. A typical microstructure of long time stress-rupture tested MAR-M509 is presented in figure 31(b). Carbides and oxide penetration along grain boundaries are evident in this figure. All MAR-M509 specimens were etched with the mixed acid solution.


Examples of the microstructure found in stress-rupture tested MA-757 are shown in figure 32. Extensive intergranular cracking is evident in specimens tested at 1144 K, while intergranular void formation is seen in specimens tested at 1477 K.

Dispersoid-free zones are also visible after testing at both temperatures. These microstructures are similar to those observed in other nickel-base ODS alloys (refs. 1 to 3). All specimens were electrolytically stain etched with a chromic acid mixture (100 ml H₂O, 10 ml H₂SO₄, and 2 g chromic acid).


Finally, typical examples of the microstructure of failed STCA creep test specimens are shown in figure 33. The microstructures shown are similar to those presented for MA-757, and contain dispersoid-free bands, grain boundary cracking and cavitation, and massive internal oxide. All alloys were electrolytically etched with a buffered aqua regia solution containing 33 percent glycerine by volume.

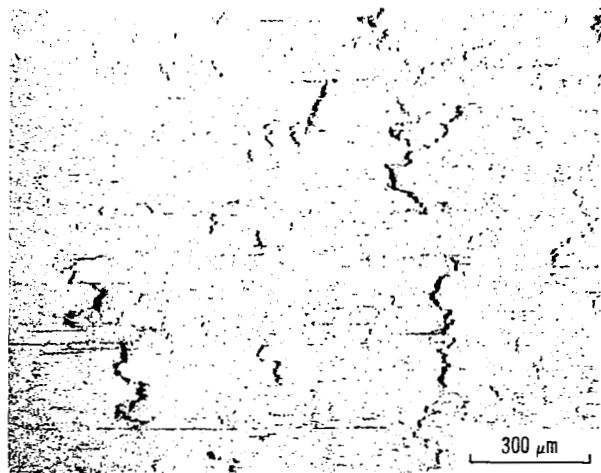


(a) Longitudinal specimen stress rupture tested for 160.8 hours at 130.9 MPa and 1144 K.

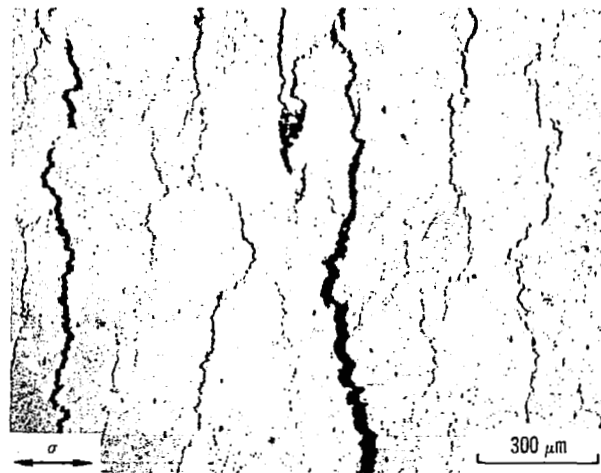

(b) Long transverse specimen stress rupture tested for 110.4 hours at 82.7 MPa and 1144 K.

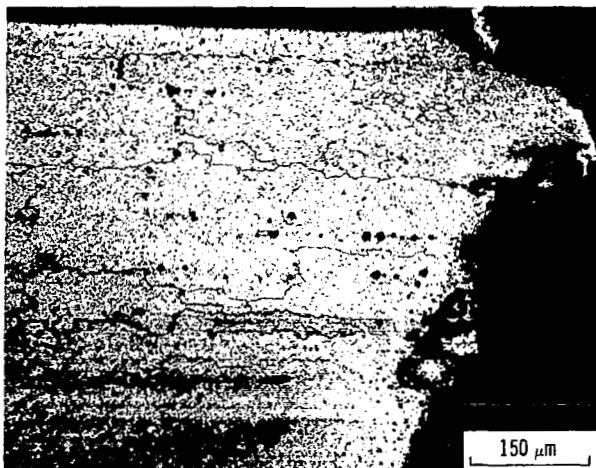


(c) Longitudinal specimen stress rupture tested 200.6 hours at 31.0 MPa and 1477 K.

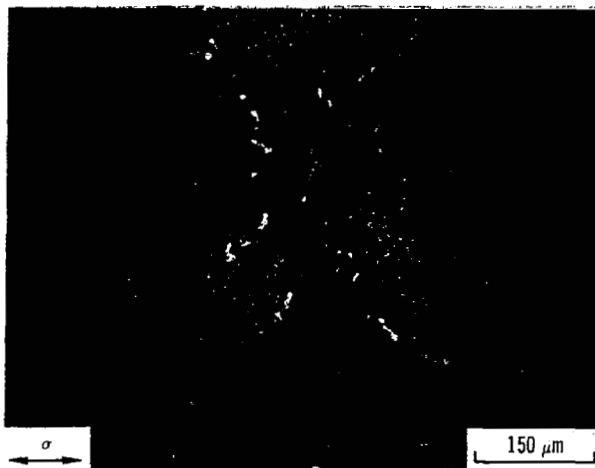


(d) Long transverse specimen stress rupture tested for 124.1 hours at 3.4 MPa and 1477 K.


Figure 32. - Microstructures of MA-757.

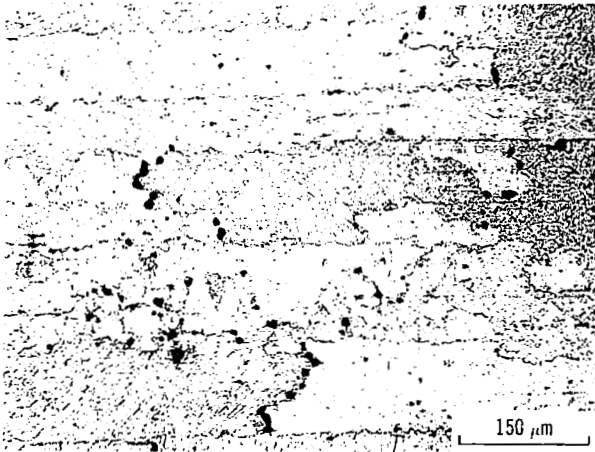


(a) Longitudinal specimen of STCA-265SC creep rupture tested for 116.2 hours at 72.4 MPa and 1366 K.

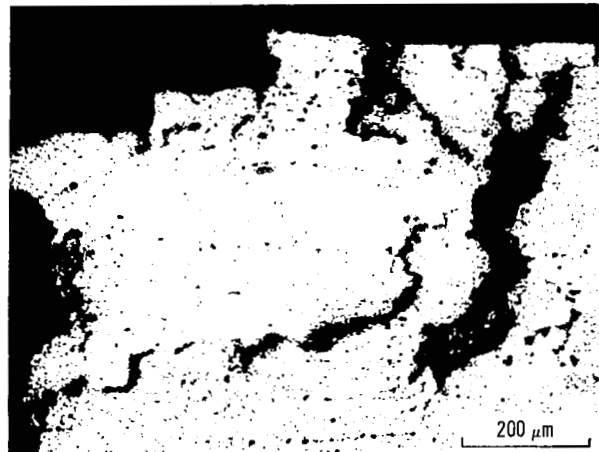

(b) Longitudinal specimen of STCA-266S creep rupture tested for 146.6 hours at 58.6 MPa and 1366 K.

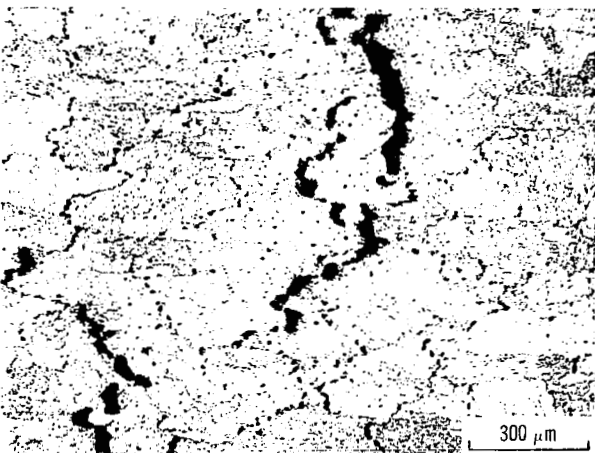

(c) Long transverse specimen of STCA-265S creep rupture tested for 165.4 hours at 19.0 MPa and 1366 K.

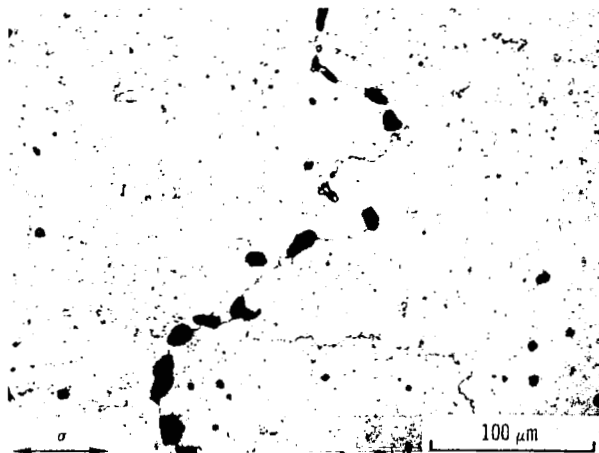

(d) Long transverse specimen of STCA 262/264S creep tested for 166.5 hours at 31.0 MPa and 1366 K.

Figure 33. - Microstructures of STCA alloys.

Appendix C

Regression Analysis of Stress Rupture and Creep Data

As part of this study, a considerable amount of creep and stress-rupture data were generated. In order to develop equations which could be used for prediction and comparison to theoretical models, the time to rupture and steady state creep rate data from appendix A were fitted to the standard semi-empirical stress-temperature equations by means of a computerized linear regression program. The equations used in this work are:

$$\left. \begin{array}{l} \ln tr \\ \ln e' \end{array} \right\} = A + n(\ln s) \quad (C-1)$$

$$\left. \begin{array}{l} \ln tr \\ \ln e' \end{array} \right\} = B + \frac{Q}{RT} + n(\ln s) \quad (C-2)$$

where tr is the time to rupture in hours, e' is the steady state creep rate in reciprocal seconds, A and B are constants, n is a stress exponent, s is the applied stress in MPa, Q is an activation energy in joules/g-mol-K, R is the gas constant (8.314 joules/g-mol-K), and T is the absolute temperature in Kelvin.

Whereas equations (C-1) and (C-2) can be independently applied to the experimental data, the activation energy(s) determined by equation (C-2) is (are) only theoretically meaningful when the stress exponents calculated at different temperatures via equation (C-1) are equal. Due to the limited testing at each temperature, it would be fortuitous if the stress exponents at each temperature were determined to be exactly equal. However confidence limits for the stress exponents can be calculated and examined to see if a common overlap region exists. When an overlap exists and the stress exponents determined from equation (C-2) fall within this overlap, a statistically meaningful activation energy has been calculated, and it can be used in theoretical models of deformation. If these two conditions are not met, the "activation energy" and "stress exponent" data reported in table IX to XIX are simply coefficients which best describe the behavior of the material in question.

Where possible all the experimental data were used in the regression analysis; however, in some

instances, particularly for the ODS alloys, editing of the data was necessary to develop reasonable equations. The pertinent regression equations as well as the regression coefficient, R^{*2} , for each alloy system are presented in tables IX to XIX.

Applicability of equations (C-2) to determine a meaningful activation energy(s) was based on 95 percent confidence limits on the stress exponents calculated from equations (C-1). In this work only stress-temperature fits of the data obtained at 1144 K and progressively higher temperatures were determined.

Each alloy and its pertinent tables are listed here:

| | |
|-----------|-----------------------|
| B-1900 | Table IX |
| MAR-M509 | Table X |
| MA-757 | Tables XI to XIV |
| MA-956 | Tables XV and XVI |
| STCA | Tables XVII and XVIII |
| YD-NiCrAl | Table XIX |

B-1900

The data presented in table XI indicates that equations (C-1) well describe the rupture and creep data at each test temperature. While the stress-temperature fits are good for the 1144-1255 K interval, fits based on equations (C-2) for the larger temperature intervals are not as good. Only the activation energies calculated for the 1144-1255 K interval satisfy the previously stated requirements on stress exponents, and both the activation energy for creep and activation energy for rupture are higher than that for diffusion in nickel or nickel-base superalloys ($Q \approx 280\text{kJ/g-mol-K}$, ref. 13).

Since the stress exponents calculated from equations (C-1) have common overlap regions (-5.24 to -6.00 for rupture data and 4.63 to 6.28 for creep data), it is possible that the stress dependency is independent of temperature. Thus, it appears that the inability of equations (C-2) to successfully predict behavior at the larger temperature intervals is due to changes in the thermally activated processes. For example the amount, distribution, size and shape of gamma-prime are functions of time at temperature, and such changes in gamma-prime will most certainly affect deformation processes. While such reasoning is appealing, it can not be proven because of the statistical correlation between stress and

temperature. This correlation is the result of the decreasing strength with increasing temperature and the limitations placed on testing (e.g., time to rupture less than 500 and measureable creep strain after 150 h of testing). For B-1900 the following equations relate the stresses for creep testing se and the stresses for rupture testing sr to the absolute temperature:

$$\ln se = -5.24 + \frac{12\,427}{T} \quad (R^{**2} = 0.92)$$

$$\ln sr = -5.52 + \frac{13\,106}{T} \quad (R^{**2} = 0.92)$$

Because of the high correlation, it is difficult to separate effects due solely to temperature or stress.

MAR-M509

Only the activation energy for rupture in table X calculated from the 1144-1255 K temperature interval is statistically sound. This activation energy (510.6 kJ) compares unfavorably with the activation energy measured for diffusion in Co-Ni alloys containing 10 to 25 percent nickel ($Q \approx 250$ kJ/g-mol-K, ref. 14).

MA-757

Some editing of the raw data was required to produce reasonable fits. The results for both the unedited and edited data are shown in tables IX to XIV. Only the activation energies for rupture and creep for testing in the longitudinal direction (590 kJ/g-mol-K) and the activation energy for rupture in the long transverse direction (518 kJ/g-mol-K) calculated from the 1144-1255 K interval are statistically significant for theoretical purposes. These activation energies are higher than that for diffusion in nickel or nickel-base alloys (280 kJ/g-mol-K). Both high activation energies and high stress exponents have been observed during creep and rupture (ref 15).

MA-956

As can be seen from the regression coefficients in tables XV and XVI, editing of the MA-956 data was required. In addition to deletion, data was added: for example, ultimate tensile strength data from table VI was used as 0.1 hour rupture life strength and ultimate tensile strength-strain rate data at 1366 K from slow tensile testing (ref. 12) was used in the 1366 K creep rate regression fit. While editing significantly improved the fits of the stress rupture data, the fits of the creep data at 1366 and 1477 K are poor.

Although the stress exponents in tables XV and XVI are quite high, they were not unexpected since similar high values were observed during slow tensile testing (ref. 12). None of the activation energies calculated for rupture are meaningful for theoretical work, whereas all the activation energies for creep satisfy the stress exponent criteria. The latter is true because the permissible confidence interval is large extending from 29 to 67 due to the poorness of fit. Hence the activation energies for creep are of questionable value other than for best description of material behavior.

STCA Alloys

While editing of the creep data for the STCA alloys was not necessary for the longitudinal direction (table XVII), minor editing was required for the long transverse direction (table XVIII). Application of "F" tests to the longitudinal data in table XVII permitted comparisons of the various alloy chemistries (table I) and heat treatments (see the section Materials under Experimental Procedures). Such testing indicated that (1) the carbide heat treatment had no effect on the creep strength of STCA-265, (2) the creep strengths of heats STCA-262/264S and -265S are similar, and (3) there is a strength difference between STCA-262/264S (-265S) and -266S where heat STCA-266S is weaker. Because of these observations, the data from STCA-262/264S and -265S and STCA-265S and -265SC were pooled and fitted; the results of this procedure are also given in table XVII.

In a like manner, the edited data fits in table XVIII for the long transverse direction can be tested for differences in chemistry and heat treatment. The results of the "F" tests are as follows:

(1) The creep strengths of STCA-265S and -265SC are similar, but STCA-266S is stronger than STCA-266SC.

(2) STCA-262/264S and -266S possess similar strength while STCA-262/264S is stronger than STCA-265S.

(3) The strengths of STCA-265S and -266SC are similar. "F" tests conducted on unedited data yielded the same behavior. For completeness the results of regression fits of the pooled data from heats of similar strength are also presented in table XVIII.

Examination of the results for both test directions with regard to the effects of chemistry and heat treatment reveals several discrepancies. A carbide heat treatment has no effect on the strength of STCA-265 but apparently reduces the strength of the low tantalum alloy STCA-266. While the Ta-free

alloy (STCA-262/264S) and the Ta-rich alloy (STCA-265S) are stronger than the intermediate Ta alloy (STCA-266S) in the longitudinal direction, for the long transverse testing direction the Ta-free and intermediate Ta level alloys are stronger than the Ta-

rich alloy. This paradox with respect to the chemistry cannot be explained on the basis of grain size or grain aspect ratio (table II) as one would expect the largest grain size, highest grain aspect ratio alloy to possess the best strength.

References

1. Whittenberger, John D.: Diffusional Creep and Creep-Degradation in Dispersion-Strengthened Ni-Cr Base Alloys. Metall. Trans., vol. 4 no. 6, June 1973, pp. 1475-1483.
2. Whittenberger, John D.: Observations on the Relationship of Structure to the Mechanical Properties of Thin TD-NiCr Sheet. Metall. Trans. A; vol. 7A, no. 5, May 1976, pp. 611-619.
3. Whittenberger, J. Daniel: Effect of Prior Creep at 1365 K on the Room Temperature Tensile Properties of Several Oxide Dispersion Strengthened Alloys. Metall. Trans. A; vol. 8A, no. 12, Dec. 1977, pp. 1863-1870.
4. Whittenberger, J. Daniel: Tensile and Creep Properties of the Experimental Oxide Dispersion Strengthened Iron-Base Sheet Alloy MA-956E at 1365 K. Metall. Trans A; vol. 9A, no. 1, Jan. 1978, pp. 101-110.
5. Smith, W. E.; Donachie, M. J., Jr.; and Johnson, J. L.: Relationship of Prior Creep Exposure to Strength of Wrought Udimet 700 Nickel-Base Alloy. J. Basic Eng., vol. 88, no. 1, Mar. 1966, pp. 4-6.
6. Jensen, D. E.; Pinkowish, A. A.; and Donachie, M. J., Jr.: Effects of Prior Creep Exposure on 1400° F Strength of Inco 713 Cast Nickel-Base Alloy. J Basic Eng., vol. 88, no. 1, March 1966, pp. 109-110.
7. Tien, J. K.; and Gamble, R. P.: The Influence of Applied Stress and Stress Sense on Grain Boundary Precipitate Morphology in a Nickel-Base Superalloy During Creep. Metall. Trans., vol. 2, no. 6, June 1971, pp. 1663-1667.
8. Gibbons, T. B.: The Influence of Diffusion Creep on Precipitate-Free Zone Formation in Ni-20% Cr-Base Alloys. Met. Sci. J., Vol. 6, no. 1, Jan. 1972, pp. 13-16.
9. Bailey, P. G.: Manufacture and Engine Test of Advanced Oxide Dispersion Strengthened Alloy Turbine Vanes. (R77AEG569, General Electric Co.; NASA Contract NAS3-18915) NASA CR-135269, 1977.
10. Klarstrom, D. L. and Grierson, R.: Optimization of an Oxide Dispersion Strengthened Ni-Cr-Al Alloy for Gas Turbine Engine Vanes. (Cabot Corp.; NASA Contract NAS3-17806) NASA CR-134901, 1975.
11. Manson, S. S.: Nonferrous Alloys. Aerospace Structural Metals Handbook Vol. 5, D. J. Maykuth, ed., Mechanical Properties Data Center, Battelle Memorial Labs., 1980, Sections 4213 and 4311.
12. Whittenberger, J. Daniel: Effect of Strain Rate on the Fracture Behavior at 1366 K of the bcc Iron Base Oxide Dispersion Strengthened Alloy MA956. Metall. Trans. A, vol. 10A, no. 9, Sep. 1979, pp. 1285-1295.
13. Feller-Kniepmeier, M.; Gruendler, M.; and Helfmeier, H.: Self-diffusion in High Purity Nickel and Nickel-0.02 at.% Gold Single Crystals. Z. Metallkd., vol. 67, no. 8, 1976, pp. 533-537; or Pruthi, D. D.; Anand, M. S.; and Agarwala, R. P.: Diffusion of Chromium in Inconel 600. J. Nucl. Mater., vol. 64, no. 1-2 1977, pp. 206-210.
14. Kucera, J.; Ciha, K.; and Stransky, K.: Interdiffusion in Co-Ni System. I-Concentration Penetration Curves and Interdiffusion Coefficients. II-Kirkendall Effect. III-Intrinsic Diffusion-Coefficient. Czech. J. Phys., vol. 27, no. 7, 1977, pp. 758-768, 935-942, 1049-1059.
15. Wilcox, B. A.; and Clauer, A. H.: Creep of Thoriated Nickel Above and Below 0.5 T_m . Trans. AIME, vol. 236, no. 4, Apr. 1966, pp. 570-580; and Wilcox, B. A.; Clauer, A. H.; and McCain, W. S.: Creep and Creep Fracture of Ni-20Cr-2ThO₂ Alloy. Trans. AIME, vol. 239, no. 11, Nov. 1967, pp. 1791-1796.

TABLE I. - COMPOSITION OF EXPERIMENTAL MATERIALS AS PROVIDED BY VENDORS

| ALLOY | HEAT NUMBER | COMPOSITION, WT PCT | | | | | | | | | | | | | | | | | |
|--------------------------------------|----------------|---------------------|-------|------|------|------|-----|-----|------|------|-----|-------|------|------|------|------|------|-------------------------------|-----|
| | | AL | B | C | CO | CR | FE | HF | MO | NI | O | S | SI | TA | TI | W | Y | Y ₂ O ₃ | ZR |
| SUPERALLOYS | | | | | | | | | | | | | | | | | | | |
| B-1900 | FP5255 | 6.15 | .016 | .098 | 10.1 | 7.74 | .21 | 1.2 | 5.98 | BAL | - | .006 | *.05 | 4.22 | 1.09 | *.05 | - | - | .08 |
| MAR-M509 | CJ5098 | - | *.005 | .62 | BAL | 23.6 | .26 | - | - | 10.5 | - | .007 | .18 | 3.41 | .23 | 6.90 | - | - | .31 |
| OXIDE DISPERSION STRENGTHENED ALLOYS | | | | | | | | | | | | | | | | | | | |
| MA-757 | DT01ABD | 4.04 | - | .06 | - | 15.7 | .91 | - | - | BAL | .63 | .005 | - | - | .60 | - | - | .59 | - |
| MA-956 | DH0001F3 | 5.09 | - | .02 | - | 20.7 | BAL | - | - | - | - | .017 | - | - | - | - | - | .76 | - |
| STCA | **262/264 | 4.61 | - | .05 | 1.1 | 15.7 | .40 | - | - | BAL | .54 | *.002 | - | *.01 | - | - | 1.52 | - | - |
| STCA | 265 | 4.69 | - | .05 | .7 | 15.8 | .24 | - | - | BAL | .52 | *.002 | - | 1.76 | - | - | 1.50 | - | - |
| STCA | 266 | 4.77 | - | .05 | .4 | 15.9 | .23 | - | - | BAL | .53 | *.002 | - | 1.25 | - | - | 1.52 | - | - |
| YD-NiCrAl | 173 | 4. | - | - | - | 16. | - | - | - | BAL | - | - | - | - | - | - | - | 1. | - |

* LESS THAN AMOUNT INDICATED.

** AVERAGE OF TWO HEATS.

TABLE II. - GRAIN SIZE PARAMETERS AND CRYSTALLOGRAPHIC ORIENTATIONS FOR ODS ALLOYS

| ALLOY | CHARACTERISTIC LENGTH, MICRONS | | | AVERAGE GRAIN SIZE, MICRONS | GRAIN ASPECT RATIO | | CRYSTALLOGRAPHIC ORIENTATION | | |
|-----------------|-----------------------------------|-----------------------------|------------------------------|--------------------------------|------------------------------|--|--|-------------------|---------------------|
| | EXTRUSION AXIS L_1 | LONG TRANSVERSE L_2 | SHORT TRANSVERSE L_3 | | $0.85 \sqrt[3]{L_1 L_2 L_3}$ | LONGITUDINAL $L_1 / \sqrt{L_2 L_3}$ | LONG TRANSVERSE $L_2 / \sqrt{L_1 L_3}$ | EXTRUSION AXIS | LONG TRANSVERSE |
| MA-757 | 265 | 130 | 70 | 110 | 2.8 | .95 | [100] | [011] | $[0\bar{1}1]$ |
| MA-956 | * | * | * | - | - | - | $[\bar{1}13]$ | [110] | $[\bar{3}3\bar{2}]$ |
| STCA 262/264 | 810 | 330 | 145 | 290 | 3.7 | .96 | **[100] | - | - |
| STCA 265 | 1500 | 440 | 160 | 400 | 5.7 | .90 | **[100] | - | - |
| STCA 266 | >6500 | 660 | 275 | >900 | >15 | <.5 | **[100] | - | - |
| YD-NiCrAl | 2500 | 520 | 310 | 630 | 6.2 | .6 | [100] | [011] | $[0\bar{1}1]$ |

* GREATER THAN 1 CM.

** WIRE TEXTURE.

TABLE III. - MECHANICAL PROPERTIES OF B-1900

(a) Elevated temperature tensile properties.

| TEMPERATURE, K | 0.02 PERCENT YIELD STRESS, MEGAPASCALS | 0.2 PERCENT YIELD STRESS, MEGAPASCALS | ULTIMATE TENSILE STRESS, MEGAPASCALS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
|-------------------|--|---|--|------------------------|----------------------------------|
| 298 | 560.5 | 636.7 | 828.1 | 7.2 | 11.7 |
| 298 | 535.0 | 707.4 | 739.5 | 3.6 | 8.1 |
| 1144 | 428.9 | 586.1 | 729.5 | 1.6 | 3.2 |
| 1144 | 413.0 | 599.2 | 707.4 | 1.3 | 2.4 |
| 1255 | 204.1 | 341.3 | 439.9 | 2.8 | 7.4 |
| 1255 | 194.4 | 326.1 | 468.8 | 3.5 | 6.0 |
| 1366 | 97.2 | 151.7 | 242.0 | 7.0 | 11.6 |
| 1366 | 98.6 | 162.7 | 221.3 | 11.7 | 15.3 |
| 1477 | 29.0 | (A) | 29.0 | .6 | NIL |
| 1477 | 26.2 | (A) | 27.6 | .9 | .4 |

(b) Stress-rupture behavior.

| TEMPERATURE, K | STRESS, MEGAPASCALS | LIFE, HOURS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
|-------------------|------------------------|----------------|------------------------|----------------------------------|
| 1144 | 241.2 | 958.9 | 3.5 | 4.7 |
| 1144 | 275.6 | 392.6 | 2.8 | 4.7 |
| 1144 | 303.2 | 108.7 | 6.0 | 13.8 |
| 1144 | 323.8 | 212.8 | 7.0 | 10.6 |
| 1144 | 344.7 | 47.4 | 1.0 | 3.2 |
| 1144 | 344.7 | 136.9 | 6.9 | 10.5 |
| 1144 | 358.3 | 54.7 | 3.3 | 7.0 |
| 1144 | 385.8 | 49.8 | 4.7 | 6.8 |
| 1144 | 434.1 | 21.0 | 5.6 | 6.7 |
| 1144 | 482.3 | 6.1 | 2.5 | 2.4 |
| 1255 | 117.2 | 624.1 | 6.0 | 12.3 |
| 1255 | 130.9 | 340.9 | 5.1 | 11.0 |
| 1255 | 137.8 | 236.8 | 4.2 | 7.6 |
| 1255 | 144.7 | 228.8 | 6.5 | 11.3 |
| 1255 | 148.1 | 98.5 | 4.2 | 11.6 |
| 1255 | 158.5 | 100.5 | 6.0 | 7.8 |
| 1255 | 165.5 | 83.5 | 6.1 | 12.2 |
| 1255 | 165.5 | 51.5 | 2.4 | 7.0 |
| 1255 | 172.3 | 62.4 | 3.0 | 6.3 |
| 1255 | 192.9 | 41.3 | 5.0 | 7.0 |
| 1255 | 206.7 | 20.8 | 5.5 | 10.1 |
| 1366 | 41.3 | 626.4 | 10.2 | 11.0 |
| 1366 | 48.2 | 362.6 | 10.2 | 18.8 |
| 1366 | 51.7 | 317.4 | 3.7 | 3.2 |
| 1366 | 55.1 | 151.5 | 4.7 | 6.2 |
| 1366 | 58.6 | 123.6 | 9.0 | 17.0 |
| 1366 | 58.6 | 103.0 | 3.8 | 9.9 |
| 1366 | 62.0 | 116.8 | 5.6 | 13.1 |
| 1366 | 68.9 | 35.8 | 3.7 | 7.8 |
| 1366 | 82.7 | 23.6 | 11.0 | 25.2 |
| 1366 | 96.5 | 7.8 | 2.6 | 15.2 |
| 1477 | 13.8 | 77.4 | 3.7 | 24.0 |
| 1477 | 20.7 | 7.7 | 9.3 | 38.4 |
| 1477 | 27.6 | 1.9 | 8.8 | 24.5 |
| 1477 | 37.9 | .1 | 1.9 | 4.6 |

(A) SPECIMEN FAILED BEFORE DATA OBTAINED.

TABLE III. - Continued.

(c) Elevated temperature creep behavior.

| TEMPERATURE, K | STRESS, MEGAPASCALS | PLASTIC STRAIN ON LOADING, PERCENT | PLASTIC STRAIN (PERCENT) AT HOURS | | | | | | | STEADY STATE CREEP RATE, S ⁻¹ | TEST DURATION, HOURS | FINAL STRAIN, PERCENT |
|-------------------|------------------------|---|-----------------------------------|-----|------|---------------|------|-------|-------|--|----------------------------|-----------------------------|
| | | | 0.1 | 5.0 | 10.0 | 25.0 SHOWN | 50.0 | 100.0 | 150.0 | | | |
| 1144 | 206.8 | NIL | .05 | .08 | .09 | .11 | .15 | .20 | .24 | 2.22E-09 | 160.5 | .25 |
| 1144 | 206.8 | NIL | NIL | .03 | .05 | .10 | .17 | .22 | .29 | 2.78E-09 | 158.6 | .30 |
| 1144 | 241.3 | NIL | .02 | .08 | .11 | .17 | .25 | .40 | ---- | 7.81E-09 | 147.3 | .52 |
| 1144 | 241.3 | NIL | .01 | .08 | .10 | .15 | .22 | .32 | .45 | 5.56E-09 | 162.4 | .49 |
| 1144 | 275.8 | NIL | NIL | .08 | .10 | .17 | .23 | .38 | .56 | 7.64E-09 | 159.4 | .60 |
| 1144 | 275.8 | NIL | .02 | .07 | .09 | .14 | .22 | .37 | .53 | 7.46E-09 | 186.5 | .71 |
| 1144 | 310.3 | NIL | .04 | .20 | .25 | .40 | .70 | 1.47 | 2.65 | 3.16E-08 | 165.8 | 3.22 |
| 1144 | 310.3 | .02 | .05 | .14 | .22 | .39 | .73 | 1.73 | 3.12 | 3.28E-08 | 159.2 | 3.82 |
| 1144 | 344.7 | NIL | .04 | .20 | .28 | .54 | ---- | ---- | ---- | 5.36E-08 | 47.4 (A) | 1.0 |
| 1144 | 344.7 | NIL | .01 | .09 | .17 | .42 | .9 | 2.78 | ---- | 4.63E-08 | 136.9 (A) | 6.9 |
| 1255 | 96.5 | NIL | NIL | .04 | .04 | .06 | .10 | .15 | .20 | 2.86E-09 | 161.5 | .21 |
| 1255 | 96.5 | NIL | NIL | .01 | .01 | .02 | .03 | .07 | .11 | 2.15E-09 | 160.0 | .12 |
| 1255 | 124.1 | NIL | .01 | .02 | .03 | .05 | .11 | .22 | .32 | 5.73E-09 | 158.5 | .33 |
| 1255 | 124.1 | NIL | NIL | .11 | .13 | .18 | .25 | .34 | .45 | 5.00E-09 | 162.2 | .49 |
| 1255 | 137.9 | NIL | NIL | .05 | .08 | .14 | .25 | .55 | 1.04 | 1.22E-08 | 164.0 | 1.24 |
| 1255 | 137.9 | NIL | NIL | .05 | .08 | .16 | .25 | .58 | 1.46 | 1.15E-08 | 159.5 | 1.91 |
| 1255 | 165.5 | NIL | .02 | .18 | .25 | .58 | 1.40 | ---- | ---- | 5.40E-08 | 83.5 (A) | 6.1 |
| 1255 | 165.5 | NIL | .02 | .18 | .30 | .67 | 1.72 | ---- | ---- | 6.17E-08 | 51.5 (A) | 2.4 |
| 1366 | 34.5 | NIL | .01 | .03 | .05 | .08 | .12 | .17 | .20 | 1.69E-09 | 166.1 | .20 |
| 1366 | 34.5 | NIL | .01 | .04 | .06 | .10 | .16 | .24 | .30 | 2.72E-09 | 165.6 | .31 |
| 1366 | 41.4 | NIL | .01 | .06 | .09 | .14 | .20 | .29 | .35 | 2.78E-09 | 167.8 | .37 |
| 1366 | 41.4 | NIL | .02 | .04 | .06 | .10 | .15 | .22 | .31 | 3.82E-09 | 166.0 | .34 |
| 1366 | 48.3 | NIL | NIL | .09 | .12 | .19 | .29 | .45 | .60 | 8.33E-09 | 163.2 | .65 |
| 1366 | 48.3 | NIL | NIL | .07 | .09 | .16 | .25 | .42 | .61 | 9.54E-09 | 167.9 | .69 |
| 1366 | 58.6 | NIL | .01 | .11 | .18 | .32 | .59 | 2.15 | ---- | 2.96E-08 | 123.6 (A) | 9.0 |
| 1366 | 58.6 | NIL | .01 | .10 | .15 | .29 | .55 | ---- | ---- | 2.73E-08 | 103.0 (A) | 3.8 |

(A) FAILED AT TIME SHOWN.

TABLE III - Concluded.

(d) Residual room temperature properties.

| PRIOR CREEP HISTORY | | | | RESIDUAL TENSILE PROPERTIES | | | | |
|---------------------|------------------------|----------------|-------------------------------------|--|---|--|------------------------|----------------------------------|
| TEMPERATURE, K | STRESS, MEGAPASCALS | TIME, HOURS | PLASTIC CREEP STRAIN, PERCENT | 0.02 PERCENT YIELD STRESS, MEGAPASCALS | 0.2 PERCENT YIELD STRESS, MEGAPASCALS | ULTIMATE TENSILE STRESS, MEGAPASCALS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
| | AS RECEIVED | | | 560.5 | 686.7 | 928.1 | 7.2 | 11.7 |
| | AS RECEIVED | | | 535.0 | 707.4 | 789.5 | 3.6 | 6.1 |
| | THERMALLY EXPOSED | | | 660.5 | 686.7 | 766.0 | 1.2 | 4.2 |
| | 150 H AT 1144K | | | 575.7 | 646.1 | 777.0 | 5.5 | 17.8 |
| 1144 | 206.8 | 160.5 | .25 | 615.0 | 679.1 | 726.7 | 2.7 | 9.3 |
| 1144 | 206.8 | 156.6 | .30 | 627.4 | 686.0 | 755.0 | 2.9 | 11.6 |
| 1144 | 241.3 | 147.3 | .52 | 632.3 | 704.6 | 777.0 | 4.5 | 12.0 (A) |
| 1144 | 241.3 | 162.1 | .49 | 606.1 | 683.3 | 751.5 | 3.7 | 11.3 |
| 1144 | 275.8 | 159.4 | .60 | 649.5 | 697.8 | 732.9 | 1.6 | 7.6 |
| 1144 | 275.8 | 186.5 | .71 | 637.8 | 695.7 | 725.3 | 1.5 | 7.0 |
| 1144 | 310.3 | 165.8 | 3.22 | 599.8 | 681.9 | 717.1 | 1.1 | 6.0 |
| 1144 | 310.3 | 159.2 | 3.92 | 597.8 | 664.0 | 708.1 | 1.5 | 11.5 |
| | THERMALLY EXPOSED | | | 562.6 | 701.9 | 775.0 | 2.2 | 12.0 |
| | 150 H AT 1255K | | | 585.4 | 672.9 | 769.5 | 4.5 | 9.3 |
| 1255 | 96.5 | 161.5 | .21 | 593.0 | 677.0 | 724.0 | 1.7 | 13.7 |
| 1255 | 96.5 | 160.0 | .12 | 617.1 | 692.9 | 826.0 | 5.2 | 6.9 |
| 1255 | 124.1 | 156.5 | .33 | 591.6 | 677.1 | 788.1 | 4.1 | 14.5 |
| 1255 | 124.1 | 162.2 | .49 | 568.1 | 662.6 | 711.5 | 1.3 | 8.8 |
| 1255 | 137.9 | 164.0 | 1.24 | 545.4 | 652.9 | 775.0 | 4.2 | 7.9 |
| 1255 | 137.9 | 159.5 | 1.91 | (B) | | 486.8 | .8 | 4.1 |
| | THERMALLY EXPOSED | | | 621.2 | 732.9 | 803.0 | 3.4 | 11.8 |
| | 150 H AT 1366K | | | 653.6 | 730.2 | 848.7 | 4.3 | 10.8 |
| 1366 | 34.5 | 166.1 | .20 | 555.7 | 660.5 | 768.8 | 4.9 | 8.6 |
| 1366 | 36.5 | 165.6 | .31 | 559.9 | 652.2 | 752.2 | 5.1 | 12.0 |
| 1366 | 41.4 | 167.9 | .37 | 548.1 | 667.4 | 801.9 | 6.1 | 8.6 |
| 1366 | 41.4 | 166.0 | .34 | 546.1 | 636.4 | 755.0 | 5.5 | 5.3 |
| 1366 | 48.3 | 163.2 | .65 | 543.3 | 641.2 | 668.8 | 1.4 | 7.8 |
| 1366 | 48.3 | 167.0 | .69 | 539.2 | 653.6 | 776.4 | 4.5 | 7.0 |
| | THERMALLY EXPOSED | | | 786.0 | 840.5 | 917.0 | 4.4 | 10.5 |
| | 150 H AT 1477K | | | 668.8 | 819.1 | 933.6 | 5.0 | 9.3 |

(A) SPECIMEN FAILED NEAR GAGE LENGTH.

(B) SPECIMEN FAILED BEFORE DATA WAS OBTAINED.

TABLE IV. - MECHANICAL PROPERTIES OF MAR-509

(a) Elevated temperature tensile properties.

| TEMPERATURE, K | 0.02 PERCENT YIELD STRESS, MEGAPASCALS | 0.2 PERCENT YIELD STRESS, MEGAPASCALS | ULTIMATE TENSILE STRESS, MEGAPASCALS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
|-------------------|--|---|--|------------------------|----------------------------------|
| 298 | 320.6 | 427.5 | 603.3 | 2.3 | 1.0 |
| 298 | 291.7 | 402.0 | 580.5 | 2.2 | 2.2 |
| 1144 | 180.0 | 220.6 | 305.4 | 21.0 | 31.6 |
| 1144 | 163.4 | 208.9 | 278.5 | 22.4 | 38.1 |
| 1255 | 114.5 | 139.3 | 168.9 | 20.0 | 34.2 |
| 1255 | 113.1 | 148.2 | 175.8 | 22.2 | 33.9 |
| 1366 | 62.1 | 84.1 | 105.5 | 23.3 | 41.5 |
| 1366 | 53.8 | 72.4 | 107.6 | 29.4 | 42.6 |
| 1477 | 42.7 | 47.6 | 57.9 | 16.5 | 19.2 |
| 1477 | 35.9 | 40.7 | 49.6 | 14.9 | 18.6 |

(b) Stress-rupture behavior.

| TEMPERATURE, K | STRESS, MEGAPASCALS | LIFE, HOURS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
|-------------------|------------------------|----------------|------------------------|----------------------------------|
| 1144 | 131.9 | 582.5 | 12.0 | 36.0 |
| 1144 | 137.8 | >142.1 | (A) | ---- |
| 1144 | 144.7 | 70.3 | 16.3 | 48.9 |
| 1144 | 155.0 | 61.8 | 15.8 | 23.7 |
| 1144 | 158.6 | 80.3 | 14.9 | 34.9 |
| 1144 | 158.6 | 134.9 | 21.5 | 36.2 |
| 1144 | 165.4 | 77.6 | 26.0 | 35.7 |
| 1144 | 165.4 | 68.2 | 15.3 | 36.7 |
| 1144 | 172.3 | 19.4 | 20.9 | 45.5 |
| 1144 | 186.0 | 54.1 | 11.1 | 24.5 |
| 1144 | 206.7 | 2.3 | 20.5 | 38.6 |
| 1255 | 68.9 | 612.3 | 14.0 | 14.6 |
| 1255 | 79.2 | 228.7 | 16.7 | 45.2 |
| 1255 | 89.6 | 50.7 | 19.5 | 24.4 |
| 1255 | 117.1 | 4.7 | 25.6 | 28.5 |
| 1255 | 130.9 | 1.7 | 24.1 | 37.0 |
| 1255 | 130.9 | 1.1 | 12.1 | 41.5 |
| 1366 | 27.6 | 950.0 | 5.6 | 7.0 |
| 1366 | 34.5 | 326.2 | 6.5 | 6.1 |
| 1366 | 41.3 | 117.5 | 7.4 | 11.0 |
| 1366 | 41.3 | 179.3 | 13.6 | 9.0 |
| 1366 | 44.8 | 45.3 | 13.4 | 15.9 |
| 1366 | 51.7 | 27.8 | 16.2 | 19.6 |
| 1366 | 51.7 | 32.1 | 11.1 | 16.5 |
| 1366 | 55.1 | 21.2 | 17.2 | 29.3 |
| 1366 | 62.0 | 9.3 | 14.8 | 40.6 |
| 1477 | 10.3 | 0.1 | 11.0 | 14.6 |
| 1477 | 13.8 | 76.4 | 7.4 | ---- |
| 1477 | 18.6 | 10.8 | 6.5 | ---- |
| 1477 | 24.1 | 43.2 | 7.0 | 22.3 |
| 1477 | 24.1 | 0.1 | 15.5 | 32.6 |
| 1477 | 27.6 | 3.4 | 11.1 | 21.7 |

(A) SPECIMEN DID NOT FAIL DUE TO CONTROLLER MALFUNCTION.

TABLE IV. - Continued.

(c) Elevated temperature creep behavior.

| TEMPERATURE, K | STRESS, MEGAPASCALS | PLASTIC STRAIN ON LOADING, PERCENT | PLASTIC STRAIN (PERCENT) AT HOURS | | | | | | | STEADY STATE CREEP RATE, S**-1 | TEST DURATION, HOURS | FINAL STRAIN, PERCENT |
|-------------------|------------------------|---|-----------------------------------|------|------|------|------|-------|-------|--------------------------------------|----------------------------|-----------------------------|
| | | | 0.1 | 5.0 | 10.0 | 25.0 | 50.0 | 100.0 | 150.0 | | | |
| 1144 | 96.5 | NIL | NIL | .06 | .09 | .15 | .20 | .25 | .27 | 1.21E-09 | 159.4 | .28 |
| 1144 | 96.5 | NIL | .09 | .31 | .40 | .60 | .74 | .83 | .88 | 1.91E-09 | 159.3 | .88 |
| 1144 | 117.2 | NIL | NIL | .38 | .57 | .98 | 1.27 | 1.57 | 1.77 | 1.04E-08 | 159.3 | 1.80 |
| 1144 | 117.2 | NIL | .02 | .24 | .35 | .59 | .79 | .98 | 1.10 | 5.56E-09 | 158.9 | 1.12 |
| 1144 | 117.2 | NIL | .04 | .38 | .55 | .82 | 1.03 | 1.25 | 1.40 | 5.43E-09 | 163.7 | 1.44 |
| 1144 | 137.9 | NIL | .05 | .95 | 1.30 | 1.95 | 2.85 | 4.36 | 6.37 | 8.60E-08 | 161.2 | 6.63 |
| 1144 | 137.9 | NIL | .03 | .68 | .98 | 1.66 | 2.33 | 3.47 | 4.78 | 6.90E-08 | 161.6 | 5.10 |
| 1144 | 158.6 | NIL | .26 | 2.43 | 3.35 | 5.27 | 9.17 | ---- | ---- | 3.62E-07 | 80.3 (A) | 14.9 |
| 1144 | 158.6 | NIL | .13 | 1.38 | 1.82 | 3.30 | 5.80 | 11.51 | ---- | 3.07E-07 | 134.9 (A) | 21.5 |
| 1255 | 41.4 | NIL | NIL | .05 | .07 | .10 | .14 | .17 | .19 | 1.57E-09 | 160.3 | .20 |
| 1255 | 41.4 | NIL | NIL | .01 | .11 | .15 | .19 | .25 | .33 | 7.25E-10 | 159.7 | .65 |
| 1255 | 41.4 | NIL | NIL | .03 | .05 | .10 | .14 | .20 | .21 | 4.95E-09 | 158.2 | .43 |
| 1255 | 55.2 | NIL | .01 | .04 | .07 | .12 | .14 | .20 | .24 | 1.33E-09 | 159.6 | .21 |
| 1255 | 55.2 | NIL | .02 | .11 | .14 | .20 | .25 | .31 | .35 | 2.77E-09 | 159.0 | .24 |
| 1255 | 55.2 | NIL | .01 | .06 | .09 | .16 | .23 | .30 | .35 | 1.63E-09 | 159.0 | .35 |
| 1255 | 55.2 | NIL | .01 | .11 | .14 | .18 | .22 | .25 | .28 | 2.83E-09 | 158.8 | .36 |
| 1255 | 55.2 | NIL | .01 | .06 | .07 | .09 | .13 | .19 | .26 | 6.04E-10 | 158.4 | .28 |
| 1255 | 68.9 | NIL | .02 | .17 | .23 | .31 | .41 | .59 | .78 | 3.68E-09 | 160.2 | .27 |
| 1255 | 68.9 | NIL | .04 | .22 | .35 | .59 | .87 | 1.35 | 1.77 | 1.06E-08 | 160.0 | .82 |
| 1255 (B) | 68.9 | NIL | .03 | .21 | .28 | .39 | .60 | 1.23 | 1.72 | 2.18E-08 | 160.1 | 1.85 |
| 1255 | 68.9 | NIL | .01 | .11 | .16 | .27 | .45 | .74 | 1.10 | 2.53E-08 | 159.0 | 1.77 |
| 1255 | 82.7 | NIL | .04 | .38 | .60 | 1.22 | 2.33 | 5.16 | 8.10 | 1.62E-08 | 160.3 | 1.18 |
| 1255 | 82.7 | NIL | .04 | .38 | .74 | 1.88 | 3.62 | 6.85 | 12.16 | 1.08E-07 | 161.9 | 8.87 |
| 1255 | 82.7 | NIL | .04 | .66 | .95 | 1.67 | 3.08 | 6.35 | 11.25 | 2.02E-07 | 160.6 | 14.25 |
| 1255 | 82.7 | NIL | .03 | .59 | .81 | 1.70 | 3.02 | 6.07 | 10.18 | 1.50E-07 | 161.5 | 13.14 |
| 1366 | 17.2 | NIL | NIL | .01 | .02 | .03 | .04 | .06 | .09 | 1.50E-07 | 162.2 | 11.36 |
| 1366 | 17.2 | NIL | NIL | .01 | .01 | .02 | .03 | .05 | .07 | 1.43E-09 | 150.0 | .09 |
| 1366 | 24.1 | NIL | .02 | .04 | .04 | .06 | .08 | .12 | .16 | 1.21E-09 | 166.3 | .08 |
| 1366 | 24.1 | NIL | .03 | .04 | .05 | .06 | .09 | .14 | .17 | 2.34E-09 | 166.3 | .18 |
| 1366 | 31.0 | NIL | .02 | .04 | .05 | .08 | .13 | .25 | .42 | 1.57E-09 | 150.0 | .17 |
| 1366 | 31.0 | NIL | NIL | .01 | .02 | .04 | .08 | .16 | .26 | 5.56E-09 | 166.6 | .53 |
| 1366 | 41.4 | NIL | .01 | .07 | .10 | .21 | .43 | 1.56 | 5.72 | 4.34E-09 | 167.5 | .31 |
| 1366 | 41.4 | NIL | .24 | 1.32 | 2.43 | 7.65 | ---- | ---- | ---- | 2.26E-08 | 179.3 (A) | 13.6 |
| | | | | | | | | | | 6.06E-07 | 32.1 (A) | 11.1 |

(A) FAILED AT TIME SHOWN.

(B) SPECIMEN OVER TEMPERATURE 7 TO 20 K BETWEEN 90 AND 140 HOURS.

TABLE IV. - Continued.

(d) Residual room temperature properties.

| PRIOR CREEP HISTORY | | | | RESIDUAL TENSILE PROPERTIES | | | | |
|---------------------|------------------------|----------------|-------------------------------------|--|---|--|------------------------|----------------------------------|
| TEMPERATURE, K | STRESS, MEGAPASCALS | TIME, HOURS | PLASTIC CREEP STRAIN, PERCENT | 0.02 PERCENT YIELD STRESS, MEGAPASCALS | 0.2 PERCENT YIELD STRESS, MEGAPASCALS | ULTIMATE TENSILE STRESS, MEGAPASCALS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
| | AS RECEIVED | | | 320.6 | 427.5 | 603.3 | 2.3 | 1.0 |
| | AS RECEIVED | | | 291.7 | 402.0 | 580.5 | 2.2 | 2.2 |
| | THERMALLY EXPOSED | | | 376.5 | 548.8 | 692.2 | .8 | .4 |
| | 150 H AT 1144K | | | 368.2 | 536.4 | 672.9 | .7 | .5 |
| 1144 | 96.5 | 159.4 | .28 | 390.9 | 558.5 | 674.3 | .8 | .6 |
| 1144 | 96.5 | 159.9 | .88 | 381.3 | 547.4 | 683.3 | .6 | 1.0 |
| 1144 | 117.2 | 159.3 | 1.80 | 396.5 | 555.7 | 677.1 | 1.0 | .8 |
| 1144 | 137.9 | 161.2 | 6.83 | 369.6 | 544.7 | 660.5 | .8 | 11.8 |
| 1144 | 137.9 | 161.6 | 5.10 | 417.8 | 553.0 | 664.0 | .6 | 6.0 |
| | THERMALLY EXPOSED | | | 318.5 | 494.4 | 631.6 | 1.0 | .2 |
| | 150 H AT 1255K | | | 322.0 | 484.0 | 626.7 | 1.2 | .2 (A) |
| 1255 | 41.4 | 160.3 | .20 | 295.1 | 477.1 | 619.2 | .8 | .6 |
| 1255 | 41.4 | 159.7 | .05 | 333.7 | 504.7 | 635.7 | 1.0 | .2 |
| 1255 | 55.2 | 159.0 | .24 | 342.0 | 506.1 | 638.5 | .7 | .6 |
| 1255 | 55.2 | 159.0 | .35 | 331.6 | 489.5 | 641.2 | .6 | 1.2 |
| 1255 | 68.9 | 160.0 | .82 | 328.9 | 488.2 | 624.0 | .9 | .6 |
| 1255 | 68.9 | 160.1 | 1.85 | 322.0 | 469.5 | 604.0 | .9 | .9 |
| 1255 | 82.7 | 161.9 | 3.87 | 326.1 | 468.8 | 541.2 | .5 | 12.3 |
| 1255 | 82.7 | 160.6 | 14.25 | 343.4 | (B) | 400.6 | .3 | 21.9 |
| | THERMALLY EXPOSED | | | 442.0 | 507.5 | 585.4 | 1.3 | 1.2 |
| | 150 H AT 1366K | | | 328.9 | 455.7 | 578.5 | 1.3 | NIL |
| 1366 | 17.2 | 150.0 | .09 | 407.5 | (B) | 489.5 | 1.6 | NIL |
| 1366 | 17.2 | 166.3 | .08 | (C) | | | | |
| 1366 | 24.1 | 166.3 | .18 | 338.5 | 455.1 | 571.6 | 1.2 | .8 |
| 1366 | 24.1 | 150.0 | .17 | 359.9 | 480.0 | 585.4 | 1.0 | 2.4 |
| 1366 | 31.0 | 166.6 | .53 | 292.3 | 425.4 | 521.2 | 1.0 | .8 |
| 1366 | 31.0 | 167.5 | .31 | (C) | | | | |
| | THERMALLY EXPOSED | | | 271.0 | 365.4 | 494.4 | 3.1 | 6.1 |
| | 150 H AT 1477K | | | 278.5 | 393.0 | 546.1 | 3.8 | 8.2 |

(A) FAILED NEAR RADIUS.

(B) SPECIMEN FAILED BEFORE DATA OBTAINED.

(C) SPECIMEN FAILED WHILE BEING REMOVED FROM CREEP TEST.

TABLE IV. - Concluded.

(e) Residual 1255 K properties.

| PRIOR CREEP HISTORY | | | | RESIDUAL TENSILE PROPERTIES | | | | |
|---------------------|------------------------|----------------|-------------------------------------|--|---|--|------------------------|----------------------------------|
| TEMPERATURE, K | STRESS, MEGAPASCALS | TIME, HOURS | PLASTIC CREEP STRAIN, PERCENT | 0.02 PERCENT YIELD STRESS, MEGAPASCALS | 0.2 PERCENT YIELD STRESS, MEGAPASCALS | ULTIMATE TENSILE STRESS, MEGAPASCALS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
| | AS RECEIVED | | | 180.0 | 220.6 | 305.4 | 21.0 | 31.6 |
| | AS RECEIVED | | | 163.4 | 208.9 | 278.5 | 22.4 | 38.1 |
| | THERMALLY EXPOSED | | | 184.8 | 222.0 | 311.0 | 15.9 | 32.3 |
| | 150 H AT 1255K | | | 175.1 | 213.0 | 305.4 | 24.0 | 31.8 |
| 1255 | 41.4 | 158.2 | .43 | 195.8 | 240.6 | (A) | 14.8 | 26.0 |
| 1255 | 41.4 | 159.6 | .21 | 210.3 | 245.5 | 310.3 | 12.3 | 22.1 |
| 1255 | 55.2 | 158.6 | .36 | 196.5 | 213.7 | 279.2 | 15.5 | 22.8 |
| 1255 | 55.2 | 158.4 | .28 | 194.4 | 233.7 | 281.3 | 13.6 | 19.6 |
| 1255(B) | 68.9 | 159.0 | 1.77 | 197.2 | 235.8 | 284.8 | 18.3 | 33.8 |
| 1255 | 68.9 | 160.3 | 1.18 | 208.9 | 245.5 | 291.0 | 12.5 | 22.0 |
| 1255 | 82.9 | 161.5 | 13.14 | 182.7 | 233.7 | 259.9 | 8.0 | 18.0 |
| 1255 | 82.9 | 162.2 | 11.36 | 172.4 | 217.2 | 242.7 | 7.4 | 17.9 |

(A) TEST MACHINE MALFUNCTION, UTS NOT MEASURED.

(B) SPECIMEN OVER TEMPERATURE 7 TO 20 K BETWEEN 90 AND 140 HOURS.

TABLE V. - MECHANICAL PROPERTIES OF MA-757

(a) Elevated temperature tensile properties.

| TEMPERATURE, K | 0.02 PERCENT YIELD STRESS, MEGAPASCALS | 0.2 PERCENT YIELD STRESS, MEGAPASCALS | ULTIMATE TENSILE STRESS, MEGAPASCALS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
|-------------------|--|---|--|------------------------|----------------------------------|
| LONGITUDINAL | | | | | |
| 298 | 696.4 | 899.1 | 1236.2 | 5.4 | 7.4 |
| 298 | 790.1 | 895.6 | 1252.8 | 6.6 | 7.8 |
| 1144 | 189.2 | 242.7 | 253.7 | 14.1 | 16.8 |
| 1144 | 177.9 | 248.9 | 266.8 | 16.7 | 25.8 |
| 1255 | 113.1 | 128.9 | 153.1 | 18.2 | 28.0 |
| 1255 | 102.0 | 130.3 | 153.1 | 21.0 | 33.8 |
| 1366 | 93.1 | 104.8 | 115.1 | 9.0 | 18.0 |
| 1366 | 99.3 | 113.8 | 120.7 | 12.2 | 18.6 |
| 1477 | 79.3 | 84.1 | 86.2 | 3.5 | 4.7 |
| 1477 | 81.4 | 84.8 | 85.5 | 1.6 | 3.2 |
| LONG TRANSVERSE | | | | | |
| 298 | 745.3 | 820.5 | 1049.4 | 6.6 | 8.6 |
| 298 | 759.1 | 815.0 | 1052.1 | 7.0 | 7.4 |
| 1144 | 208.2 | 249.6 | 259.2 | 3.9 | 10.4 |
| 1144 | 206.2 | 239.9 | 248.2 | 4.5 | 4.7 |
| 1255 | 103.9 | 122.0 | 134.4 | 4.5 | 3.5 |
| 1255 | 100.0 | 126.2 | 140.0 | 3.7 | 3.1 |
| 1366 | 99.3 | 113.1 | 113.8 | 3.1 | .4 (A) |
| 1366 | 106.9 | 114.5 | 115.8 | 2.5 | 1.0 |
| 1477 | 66.9 | 71.7 | 71.7 | 2.0 | .2 |
| 1477 | 66.9 | (B) | 71.0 | 1.6 | .4 |

(A) SPECIMEN FAILED AT RADIUS.

(B) SPECIMEN FAILED BEFORE DATA POINT OBTAINED.

TABLE V. - Continued.

(b) Stress-rupture behavior.

| TEMPERATURE, K | STRESS, MEGAPASCALS | LIFE, HOURS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
|-------------------|------------------------|----------------|------------------------|----------------------------------|
| LONGITUDINAL | | | | |
| 1144 | 103.4 | 3603.6 | 4.0 | 0.8 |
| 1144 | 110.3 | 1419.5 (A) | ---- | ---- |
| 1144 | 117.1 | 278.3 | 5.0 | 3.0 |
| 1144 | 130.9 | 160.8 | 6.0 | 2.2 |
| 1144 | 137.8 | 76.1 | 3.8 | 6.7 |
| 1144 | 144.7 | 34.6 | 5.0 | 4.6 |
| 1144 | 158.5 | 9.2 | 7.0 | 10.7 |
| 1255 | 62.0 | 4522.9 (A) | ---- | ---- |
| 1255 | 68.9 | 653.4 | 2.4 | 0.5 |
| 1255 | 75.8 | 285.2 | 8.0 | 18.8 |
| 1255 | 82.7 | 104.8 | 2.9 | 4.8 |
| 1255 | 89.6 | 15.4 | 3.2 | 7.8 |
| 1255 | 89.6 | 164.5 | 5.0 | 2.4 |
| 1255 | 96.5 | 34.8 | 7.0 | 10.1 |
| 1255 | 103.4 | 14.0 | 3.0 | 3.8 |
| 1255 | 117.1 | 1.5 | 9.8 | 14.0 |
| 1366 | 41.4 | 106.1 | 0.8 | NIL (B) |
| 1366 | 41.4 | 134.1 | 2.0 | NIL |
| 1366 | 41.4 | 482.1 | 0.8 | NIL (B) |
| 1366 | 48.2 | 71.5 | 1.8 | NIL |
| 1366 | 48.2 | 238.9 | 0.8 | NIL (B) |
| 1366 | 55.1 | 87.6 | 3.0 | NIL (B) |
| 1366 | 55.1 | 85.1 | 2.3 | NIL |
| 1366 | 62.0 | 33.1 | 2.5 | NIL (B) |
| 1366 | 62.0 | 12.9 | 1.8 | 0.9 |
| 1366 | 68.9 | 12.3 | 4.0 | 2.1 |
| 1366 | 75.8 | 2.7 | 5.0 | NIL (B) |
| 1366 | 82.7 | 4.8 | 6.0 | 8.0 |
| 1477 | 27.6 | 183.3 | 2.4 | NIL |
| 1477 | 31.0 | 200.6 | 1.5 | NIL |
| 1477 | 31.0 | 39.7 | 5.8 | NIL |
| 1477 | 34.5 | 18.1 | 3.0 | NIL |
| 1477 | 34.5 | 79.8 | 1.4 | 0.4 |
| 1477 | 34.5 | 131.2 | 1.3 | NIL |
| 1477 | 37.9 | 13.4 | 4.0 | NIL (B) |
| 1477 | 37.9 | 1.4 | 3.0 | NIL |
| 1477 | 41.3 | 14.0 | 1.0 | NIL |
| 1477 | 41.3 | 3.4 | 1.0 | NIL |
| 1477 | 55.1 | 2.3 | 3.0 | NIL (B) |

TABLE V. - Continued.

(b) Concluded.

| TEMPERATURE, K | STRESS, MEGAPASCALS | LIFE, HOURS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
|-------------------|------------------------|----------------|------------------------|----------------------------------|
| LONG TRANSVERSE | | | | |
| 1144 | 55.1 | 1773.6 | 2.0 | 0.8 |
| 1144 | 68.9 | 501.0 | 2.0 | NIL |
| 1144 | 79.3 | 141.4 | 2.6 | 0.6 |
| 1144 | 79.3 | 141.4 | 2.6 | 0.6 |
| 1144 | 82.7 | 110.4 | 1.0 | NIL |
| 1144 | 96.5 | 27.3 | NIL | NIL |
| 1144 | 110.3 | 12.8 | 2.4 | 1.0 |
| 1255 | 34.5 | 406.2 | 2.0 | NIL |
| 1255 | 37.9 | 157.7 | 1.7 | NIL |
| 1255 | 41.3 | 127.5 | NIL | NIL |
| 1255 | 48.2 | 123.0 | 7.6 | 2.0 |
| 1255 | 48.2 | 30.2 | (C) | NIL |
| 1255 | 55.1 | 21.6 | 1.0 | NIL |
| 1255 | 62.0 | 0.8 | 0.8 | NIL |
| 1366 | 13.8 | 1340.4 | 4.8 | NIL |
| 1366 | 20.7 | 163.2 | 6.7 | NIL |
| 1366 | 20.7 | 103.9 | 2.0 | NIL |
| 1366 | 20.7 | 154.0 | 9.0 | NIL |
| 1366 | 24.1 | 62.1 | 3.6 | NIL |
| 1366 | 27.6 | 35.7 | 6.0 | NIL |
| 1366 | 27.6 | 24.4 | (C) | NIL (B) |
| 1366 | 31.0 | 10.4 | 3.0 | NIL (B) |
| 1366 | 34.5 | 4.2 | (C) | NIL (B) |
| 1366 | 37.9 | 2.3 | 2.5 | NIL (B) |
| 1366 | 41.3 | 8.1 | (C) | NIL (B) |
| 1477 | 3.4 | 724.4 | 3.0 | NIL |
| 1477 | 6.9 | 187.3 | 0.8 | NIL |
| 1477 | 10.3 | 73.5 | 2.0 | NIL |
| 1477 | 10.3 | 87.4 | 3.1 | NIL |
| 1477 | 13.8 | 29.6 | 4.0 | NIL |
| 1477 | 13.8 | 38.2 | 2.6 | NIL |
| 1477 | 20.7 | 10.9 | 2.4 | 1.0 |

(A) UNLOADED AT TIME SHOWN.

(B) FAILED NEAR SHOULDER.

(C) COULD NOT BE MEASURED.

TABLE V. - Continued.

(c) Elevated temperature creep behavior.

| TEMPERATURE, K | STRESS, MEGAPASCALS | PLASTIC STRAIN ON LOADING, PERCENT | PLASTIC STRAIN (PERCENT) SHOWN | | | | | | | STEADY STATE CREEP RATE, S ⁻¹ | TEST DURATION, HOURS | FINAL STRAIN, PERCENT |
|-------------------|------------------------|---|--------------------------------|------|------|------|------|-------|---------|--|----------------------------|-----------------------------|
| | | | 0.1 | 5.0 | 10.0 | 25.0 | 50.0 | 100.0 | 150.0 | | | |
| LONGITUDINAL | | | | | | | | | | | | |
| 1144 | 58.7 | NIL | NIL | .03 | .04 | .05 | .06 | .06 | .10 | 1.09E-09 | 161.1 | .10 |
| 1144 | 56.5 | NIL | NIL | .01 | .01 | .02 | .03 | .04 | .05 (A) | 6.88E-10 | 160.1 | .05 (A) |
| 1144 | 103.4 | NIL | NIL | .05 | .10 | .15 | .21 | .28 | .32 | 2.53E-09 | 159.0 | .33 |
| 1144 | 110.3 | NIL | NIL | .06 | .08 | .10 | .13 | .19 | .25 | 3.99E-09 | 162.6 | .26 |
| 1144 | 117.2 | NIL | .03 | .15 | .19 | .27 | .33 | .43 | .53 | 5.79E-09 | 159.9 | .55 |
| 1144 | 124.1 | NIL | NIL | .02 | .04 | .07 | .11 | .19 | .27 | 3.86E-09 | 162.7 | .29 |
| 1144 | 131.0 | NIL | NIL | .03 | .04 | .08 | .12 | .19 | .25 | 3.14E-09 | 150.0 | .25 |
| 1144 | 137.8 | NIL | .01 | .10 | .18 | .50 | 1.16 | ---- | ---- | 5.14E-08 | 76.1 (B) | 3.8 |
| 1255 | 48.3 | NIL | .01 | .05 | .12 | .16 | .20 | .24 | .27 | 1.87E-09 | 159.5 | .27 |
| 1255 | 55.2 | NIL | .01 | .06 | .08 | .11 | .14 | .17 | .20 | 1.81E-09 | 161.3 | .21 |
| 1255 | 62.1 | NIL | .04 | .07 | .10 | .14 | .19 | .29 | .39 | 5.50E-09 | 159.5 | .40 |
| 1255 | 69.9 | NIL | .01 | .06 | .08 | .12 | .16 | .24 | .31 | 4.35E-09 | 162.5 | .32 |
| 1255 | 75.9 | NIL | .01 | .03 | .04 | .07 | .11 | .19 | .28 | 4.70E-09 | 162.3 | .30 |
| 1255 | 82.7 | NIL | .01 | .13 | .19 | .31 | .52 | 1.15 | ---- | 2.36E-08 | 104.8 (B) | 2.9 |
| 1255 | 92.7 | NIL | .02 | .07 | .08 | .09 | .10 | .11 | .13 | 9.06E-10 | 165.0 | .13 |
| 1255 | 99.7 | NIL | .06 | 1.11 | ---- | ---- | ---- | ---- | ---- | 5.91E-07 | 15.4 (B) | 3.2 |
| 1366 | 27.6 | NIL | .04 | .07 | .09 | .11 | .12 | .14 | .16 | 9.06E-10 | 164.7 | .16 |
| 1366 | 34.5 | NIL | .03 | .07 | .09 | .11 | .13 | .15 | .16 | 5.66E-10 | 166.6 | .17 |
| 1366 | 37.9 | NIL | .06 | .08 | .08 | .09 | .10 | .12 | .14 | 1.15E-09 | 164.9 | .15 |
| 1366 | 41.4 | NIL | .03 | .05 | .05 | .06 | .07 | .07 | .08 | 7.25E-10 | 166.4 | .08 |
| 1366 | 44.8 | NIL | NIL | .01 | .01 | .02 | .04 | .08 | .11 | 2.05E-09 | 165.8 | .13 |
| 1366 | 44.8 | NIL | .02 | .05 | .06 | .07 | .08 | .10 | .11 | 9.06E-10 | 172.4 | .12 |
| 1366 | 48.3 | NIL | .03 | .12 | .17 | .31 | .58 | ---- | ---- | 2.48E-08 | 71.5 (B) | 1.8 |
| 1366 | 48.3 | NIL | NIL | .01 | .02 | .04 | .07 | ---- | ---- | 4.10E-09 | 67.5 (C) | ---- |
| 1366 | 55.2 | NIL | .01 | .09 | .14 | .29 | .53 | ---- | ---- | 2.57E-08 | 85.1 (B) | 2.3 |
| 1366 | 62.1 | NIL | .02 | .08 | ---- | ---- | ---- | ---- | ---- | 7.41E-07 | 12.9 (B) | 1.8 |
| 1477 | 20.7 | NIL | .02 | .04 | .05 | .05 | .06 | .07 | .08 | 6.04E-10 | 164.7 | .08 |
| 1477 | 24.1 | NIL | .10 | .16 | .18 | .20 | .22 | .24 | .25 | 1.09E-09 | 164.0 | .26 |
| 1477 | 27.6 | NIL | .02 | .05 | .06 | .07 | .08 | .12 | .16 | 1.75E-09 | 163.9 | .19 |
| 1477 | 31.0 | NIL | .01 | .02 | .02 | .03 | .05 | .10 | ---- | 2.17E-09 | 128.2 (C) | .13 |
| 1477 | 31.0 | NIL | NIL | .20 | .34 | .58 | ---- | ---- | ---- | 1.03E-07 | 39.7 (B) | 5.8 |
| 1477 | 34.5 | NIL | .01 | .08 | .10 | .12 | .17 | .25 | ---- | 4.71E-09 | 131.2 (B) | 1.3 |
| 1477 | 34.5 | NIL | .04 | .06 | .08 | .15 | .39 | ---- | ---- | 1.26E-08 | 79.8 (B) | 1.4 |

TABLE V. - Continued.

(c) Concluded.

| TEMPERATURE, K | STRESS, MEGAPASCALS | PLASTIC STRAIN ON LOADING, PERCENT | PLASTIC STRAIN (PERCENT) AT HOURS | | | | | | | STEADY STATE CREEP RATE, S***-1 | TEST DURATION, HOURS | FINAL STRAIN, PERCENT |
|-------------------|------------------------|---|-----------------------------------|-----|------|------|------|-------|-------|---------------------------------------|----------------------------|-----------------------------|
| | | | 0.1 | 5.0 | 10.0 | 25.0 | 50.0 | 100.0 | 150.0 | | | |
| LONG TRANSVERSE | | | | | | | | | | | | |
| 1144 | 41.4 | NIL | .02 | .03 | .04 | .05 | .05 | .06 | .07 | 5.80E-10 | 160.6 | .07 |
| 1144 | 48.3 | NIL | NIL | .03 | .04 | .05 | .05 | .06 | .09 | 1.09E-09 | 161.9 | .10 |
| 1144 | 55.2 | NIL | NIL | .07 | .09 | .12 | .14 | .17 | .20 | 1.75E-09 | 164.2 | .21 |
| 1144 | 55.2 | NIL | .03 | .08 | .10 | .12 | .14 | .16 | .19 | 1.45E-09 | 160.8 | .19 |
| 1144 | 62.1 | NIL | NIL | .02 | .03 | .05 | .07 | .11 | .15 | 2.17E-09 | 162.0 | .16 |
| 1144 | 68.9 | NIL | .03 | .16 | .19 | .23 | .25 | .30 | .36 | 2.95E-09 | 161.8 | .37 |
| 1144 | 75.8 | NIL | .02 | .06 | .07 | .08 | .13 | .23 | .38 | 4.59E-09 | 159.9 | .44 |
| 1144 | 79.3 | NIL | .01 | .04 | .06 | .10 | .17 | .38 | ---- | 6.34E-09 | 141.4 (B) | 2.6 |
| 1255 | 24.1 | NIL | .03 | .06 | .06 | .08 | .09 | .10 | .11 | 9.30E-10 | 164.2 | .11 |
| 1255 | 27.6 | NIL | NIL | .01 | .01 | .01 | .02 | .03 | .04 | 7.25E-10 | 160.2 | .05 |
| 1255 | 31.0 | NIL | NIL | .04 | .05 | .07 | .09 | .13 | .17 | 2.11E-09 | 160.6 | .18 |
| 1255 | 34.5 | NIL | NIL | .02 | .03 | .06 | .09 | .17 | .24 | 3.86E-09 | 160.3 | .25 |
| 1255 | 36.2 | NIL | .03 | .08 | .11 | .15 | .21 | .32 | .43 | 6.22E-09 | 172.0 | .48 |
| 1255 | 37.9 | NIL | .01 | .05 | .08 | .14 | .23 | .44 | 1.02 | 8.94E-09 | 157.7 (B) | 1.7 |
| 1255 | 37.9 | NIL | NIL | .05 | .10 | .18 | .29 | .44 | .66 | 7.81E-09 | 162.6 | .75 |
| 1255 | 41.3 | NIL | NIL | .05 | .08 | .16 | .23 | .37 | .73 | 7.25E-09 | 161.2 | .86 |
| 1255 | 48.2 | NIL | NIL | .03 | .07 | .23 | .79 | 3.80 | ---- | 1.99E-08 | 123.0 (B) | 7.6 |
| 1366 | 6.9 | NIL | .06 | .08 | .09 | .10 | .10 | .11 | .12 | 5.43E-10 | 162.3 | .12 |
| 1366 | 10.3 (D) | | | | | | | | | | 163.8 | |
| 1366 | 13.8 | NIL | .01 | .04 | .05 | .08 | .11 | .17 | .23 | 3.44E-09 | 167.2 | .25 |
| 1366 | 13.8 | NIL | .01 | .06 | .08 | .10 | .12 | .16 | .20 | 3.26E-09 | 151.1 | .20 |
| 1366 | 17.2 | NIL | .01 | .06 | .08 | .11 | .18 | .32 | .47 | 8.21E-09 | 150.5 | .47 |
| 1366 | 20.7 | NIL | .01 | .06 | .09 | .17 | .34 | 1.10 | ---- | 1.33E-08 | 154.0 (B) | 9.0 |
| 1366 | 20.7 | NIL | .02 | .06 | .08 | .15 | .35 | 1.08 | 6.05 | 1.63E-08 | 163.2 (B) | 6.7 |
| 1366 | 24.1 | NIL | .01 | .08 | .14 | .33 | 1.03 | ---- | ---- | 3.22E-08 | 62.1 (B) | 3.6 |
| 1366 | 27.6 | NIL | .01 | .23 | .74 | 4.82 | ---- | ---- | ---- | 8.23E-08 | 35.7 (B) | 6.0 |
| 1477 | 3.5 | NIL | .01 | .01 | .02 | .03 | .06 | .11 | .16 | 2.90E-09 | 164.3 | .18 |
| 1477 | 5.2 | NIL | .06 | .11 | .12 | .13 | .15 | .16 | .17 | 9.66E-10 | 163.3 | .17 |
| 1477 | 6.9 | NIL | .03 | .06 | .07 | .08 | .09 | .11 | .12 | 1.09E-09 | 162.7 | .13 |
| 1477 | 6.9 | NIL | .03 | .11 | .15 | .22 | .29 | .38 | .44 | 3.14E-09 | 154.2 | .44 |
| 1477 | 10.3 | NIL | .01 | .06 | .11 | .21 | .41 | ---- | ---- | 2.02E-08 | 87.4 (B) | 3.1 |
| 1477 | 13.8 | NIL | .01 | .11 | .20 | .63 | ---- | ---- | ---- | 5.63E-08 | 38.2 (B) | 2.6 |

(A) EXTRAPOLATED VALUE, CREEP RECORDER MALFUNCTION AT APPROXIMATELY 130 HOURS.

(B) SPECIMEN FAILED AT TIME SHOWN.

(C) PULL ROD FAILED AT TIME SHOWN.

(D) DEFECTIVE EXTENSOMETER; NO VALID CREEP DATA.

TABLE V. - Continued.

(d) Residual room temperature properties.

| PRIME CREEP HISTORY | | | | RESIDUAL TENSILE PROPERTIES | | | | |
|---------------------|------------------------|----------------|-------------------------------------|--|---|--|------------------------|----------------------------------|
| TEMPERATURE, K | STRESS, MEGAPASCALS | TIME, HOURS | PLASTIC CREEP STRAIN, PERCENT | 0.02 PERCENT YIELD STRESS, MEGAPASCALS | 0.2 PERCENT YIELD STRESS, MEGAPASCALS | ULTIMATE TENSILE STRESS, MEGAPASCALS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
| LONGITUDINAL | | | | | | | | |
| 1144 | 39.7 | 151.1 | .10 | 732.9 | 797.0 | 1244.5 | 10.5 | 12.0 |
| 1144 | 46.5 | 150.1 | .05 | 773.6 | 930.8 | 1192.8 | 7.0 | 5.2 (A) |
| 1144 | 103.4 | 159.0 | .33 | 766.0 | 820.5 | 1110.1 | 5.8 | 4.1 (A) |
| 1144 | 110.3 | 162.6 | .26 | 749.5 | 809.4 | 1156.3 | 6.2 | 4.8 (A) |
| 1144 | 110.3 | 1413.5 | ---- | 514.4 | (B) | 718.4 | 0.9 | 0.2 |
| 1144 | 117.2 | 159.9 | .55 | 752.2 | 817.7 | 1104.5 | 5.5 | 4.7 (A) |
| 1144 | 124.1 | 152.7 | .29 | 735.8 | 805.3 | 1127.3 | 5.6 | 6.3 |
| 1144 | 131.0 | 150.0 | .25 | 758.4 | 818.7 | 997.0 | 2.6 | 3.5 |
| 1255 | 43.3 | 159.5 | .27 | 758.4 | 852.3 | 1259.0 | 8.5 | 11.3 |
| 1255 | 55.2 | 151.3 | .21 | 752.2 | 876.2 | 1279.0 | 8.8 | 7.8 |
| 1255 | 62.0 | 1522.9 | ---- | 655.0 | 835.0 | 1170.7 | 5.1 | 6.3 (A) |
| 1255 | 62.1 | 159.5 | .40 | 779.1 | 856.3 | 1261.1 | 8.6 | 6.5 (A) |
| 1255 | 58.9 | 162.5 | .32 | 764.6 | 850.1 | 1149.4 | 5.9 | 4.4 (A) |
| 1255 | 75.8 | 162.3 | .30 | 768.8 | 854.3 | 1094.9 | 4.3 | 3.5 (A) |
| 1255 | 57.7 | 155.0 | .13 | 721.5 | 795.7 | 1130.7 | 4.9 | 3.8 (A) |
| 1366 | 27.6 | 164.7 | .16 | 702.6 | 812.2 | 1251.4 | 10.1 | 13.1 |
| 1366 | 34.5 | 166.6 | .17 | 662.6 | 766.0 | 1220.4 | 6.4 | 12.4 |
| 1366 | 37.5 | 154.9 | .15 | 738.4 | 802.6 | 990.8 | 3.4 | 0.1 |
| 1365 | 41.4 | 150.4 | .08 | 706.7 | 910.1 | 1259.0 | 9.7 | 12.0 |
| 1365 | 44.6 | 155.8 | .13 | 720.5 | 796.3 | 1075.6 | 4.4 | 6.0 |
| 1365 | 44.6 | 172.4 | .12 | 694.3 | 794.3 | 1012.8 | 3.2 | 5.0 |
| 1477 | 20.7 | 164.7 | .08 | 617.1 | 752.9 | 1225.9 | 11.5 | 12.5 |
| 1477 | 24.1 | 159.0 | .26 | 641.2 | 761.9 | 894.3 | 1.5 | 0.6 (A) |
| 1477 | 24.1 | 153.0 | .19 | 692.2 | 766.7 | 1212.1 | 9.5 | 6.7 (A) |

TABLE V. - Concluded.

(d) Concluded.

| PRIOR CREEP HISTORY | | | | RESIDUAL TENSILE PROPERTIES | | | | |
|---------------------|------------------------|----------------|-------------------------------------|--|---|--|------------------------|----------------------------------|
| TEMPERATURE, K | STRESS, MEGAPASCALS | TIME, HOURS | PLASTIC CREEP STRAIN, PERCENT | 0.02 PERCENT YIELD STRESS, MEGAPASCALS | 0.2 PERCENT YIELD STRESS, MEGAPASCALS | ULTIMATE TENSILE STRESS, MEGAPASCALS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
| LONG TRANSVERSE | | | | | | | | |
| 1144 | 41.4 | 160.6 | .07 | 704.0 | 750.8 | 1003.2 | 7.6 | 11.6 |
| 1144 | 48.3 | 161.9 | .10 | 682.6 | 741.9 | 873.6 | 3.3 | 1.3 (A) |
| 1144 | 55.2 | 164.2 | .21 | 687.4 | 751.5 | 805.3 | 1.4 | 1.5 |
| 1144 | 55.2 | 160.8 | .19 | 677.1 | 752.2 | 1046.6 | 9.4 | 10.8 |
| 1144 | 62.1 | 162.0 | .16 | 708.1 | 775.0 | 781.9 | 1.3 | 2.5 (A) |
| 1144 | 68.9 | 161.8 | .37 | 700.5 | (B) | 712.9 | .6 | 2.1 (A) |
| 1144 | 75.8 | 159.9 | .44 | (C) | ---- | 373.0 | 1.3 | .1 (A) |
| 1255 | 24.1 | 164.2 | .11 | 559.0 | 741.9 | 1003.9 | 7.0 | 12.3 |
| 1255 | 27.6 | 160.2 | .05 | 685.3 | 732.9 | 1012.2 | 8.5 | 11.6 |
| 1255 | 31.0 | 160.6 | .18 | 616.4 | 802.6 | 970.1 | 5.1 | 1.3 (A) |
| 1255 | 34.5 | 160.3 | .25 | 674.3 | 728.1 | 787.4 | 2.3 | 2.8 (A) |
| 1255 | 37.9 | 162.6 | .75 | (C) | | 153.1 | 0.2 | NIL |
| 1255 | 41.3 | 161.2 | .86 | (C) | | 233.0 | 0.8 | NIL (A) |
| 1366 | 4.9 | 162.3 | .12 | 614.3 | 739.8 | 848.7 | 2.0 | 3.8 |
| 1366 | 13.8 | 167.2 | .25 | 660.5 | 742.6 | 1048.0 | 9.0 | 7.0 |
| 1366 | 13.8 | 151.1 | .20 | 676.4 | 751.5 | 1052.8 | 8.8 | 9.7 |
| 1366 | 17.2 | 150.5 | .47 | 522.6 | 743.9 | 802.6 | 2.1 | 1.0 |
| 1477 | 3.5 | 164.3 | .18 | 626.7 | 698.4 | 999.1 | 10.0 | 8.6 |
| 1477 | 5.2 | 163.3 | .17 | 622.6 | 711.5 | 1021.8 | 10.5 | 10.3 |
| 1477 | 6.9 | 162.7 | .13 | 627.4 | 712.2 | 993.5 | 8.3 | 14.0 |
| 1477 | 6.9 | 154.2 | .44 | 628.1 | 708.1 | 983.2 | 8.9 | 11.9 |

(A) SPECIMEN FAILED NEAR RADIUS.

(B) FAILED BEFORE 0.2 PERCENT YIELD STRESS REACHED.

(C) FAILED BEFORE 0.02 PERCENT YIELD STRESS REACHED.

TABLE VI. - MECHANICAL PROPERTIES OF MA-956

(a) Elevated temperature tensile properties.

| TEMPERATURE, K | 0.02 PERCENT YIELD STRESS, MEGAPASCALS | 0.2 PERCENT YIELD STRESS, MEGAPASCALS | ULTIMATE TENSILE STRESS, MEGAPASCALS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
|-------------------|--|---|--|------------------------|----------------------------------|
| LONGITUDINAL | | | | | |
| 298 | 557.1 | 586.7 | 689.5 | 12.1 | 20.4 |
| 298 | 553.7 | 591.6 | 601.2 | 0.9 | 1.2 |
| 1144 | 82.0 | 97.9 | 102.0 | 13.7 | 53.7 |
| 1144 | 93.8 | 104.8 | 106.9 | 10.6 | 44.0 |
| 1255 | 82.7 | 89.6 | 91.0 | 4.7 | 40.3 |
| 1255 | 83.4 | 85.5 | 87.6 | 5.8 | 33.2 |
| 1366 | 77.2 | 80.0 | 81.4 | 4.3 | 17.2 |
| 1366 | 66.9 | 73.1 | 77.2 | 2.4 | 9.4 |
| 1477 | 66.2 | 69.6 | 69.6 | 1.6 | 2.8 |
| 1477 | 66.2 | 68.3 | 68.9 | 1.5 | 4.0 |
| LONG TRANSVERSE | | | | | |
| 298 | 652.9 | 669.5 | 670.9 | 0.7 | 0.2 |
| 1144 | 48.3 | 53.1 | 53.1 | 1.8 | 1.2 |
| 1144 | 88.3 | 110.3 | 112.4 | 5.7 | 8.2 |
| 1255 | 51.7 | 51.7 | 51.7 | 0.6 | NIL |
| 1255 | 85.5 | (A) | 91.0 | 0.4 | 0.2 |
| 1366 | 40.7 | (A) | 42.1 | 1.8 | 0.2 |
| 1366 | 57.9 | (A) | 60.0 | 1.2 | 0.6 |

(A) SPECIMEN FAILED BEFORE 0.2 PERCENT YIELD STRESS OBTAINED.

TABLE VI. - Continued.

(b) Stress-rupture behavior.

| TEMPERATURE, K | STRESS, MEGAPASCALS | LIFE, HOURS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
|-------------------|------------------------|----------------|------------------------|----------------------------------|
| LONGITUDINAL | | | | |
| 1144 | 68.9 | 1005.4 (A) | ---- | ---- |
| 1144 | 75.8 | 111.4 | 6.0 | (B) |
| 1144 | 75.8 | 393.1 | 3.7 | (B) |
| 1144 | 82.7 | 157.6 | 6.0 | (B) |
| 1144 | 82.7 | 248.3 | 4.7 | (B) |
| 1144 | 86.2 | 2061.5 (A) | ---- | ---- |
| 1144 | 86.2 | 75.1 | 6.2 | 32.1 |
| 1144 | 89.6 | 9.5 | 7.4 | 36.9 |
| 1144 | 89.6 | 6.8 | 4.7 | 26.8 |
| 1144 | 93.1 | 5.6 | 7.1 | 17.9 |
| 1255 | 75.8 | 1005.4 (A) | ---- | ---- |
| 1255 | 77.6 | .01 | 20.0 | >97. |
| 1255 | 77.6 | .5 | 7.4 | (B) |
| 1255 | 77.6 | 29.7 | 5.5 | 35.5 |
| 1255 | 79.3 | 8.1 | 9.3 | 50.5 |
| 1255 | 79.3 | 3.4 | 5.9 | 41.6 |
| 1255 | 79.3 | 24.2 | 4.4 | 10.2 |
| 1255 | 81.0 | .7 | 10.7 | 45.4 |
| 1255 | 81.0 | 9.5 | 6.5 | 32.0 |
| 1255 | 81.0 | 119.7 | 5.5 | 33.0 |
| 1255 | 82.7 | 5.7 | 5.6 | 30.4 |
| 1255 | 82.7 | 1.8 | 6.5 | 16.4 |
| 1366 | 65.4 | 1.3 | 3.2 | (B) |
| 1366 | 70.7 | 75.3 | 6.3 | 19.0 |
| 1366 | 72.4 | 11.4 | ---- | (B) |
| 1366 | 72.4 | 943.1 | 6.0 | 36.1 |
| 1366 | 74.1 | .9 | 5.6 | 31.0 |
| 1366 | 75.8 | .3 | 5.6 | 55.0 |
| 1366 | 75.8 | .5 | 3.5 | 26.8 |
| 1366 | 77.6 | .3 | 8.7 | 42.1 |
| 1366 | 79.2 | .02 | 8.3 | 38.0 |
| 1477 | 58.6 | 28.8 | 3.9 | 32.2 |
| 1477 | 62.1 | 1.5 | 5.4 | (B) |
| 1477 | 62.1 | 23.0 | 4.4 | 40.3 |
| 1477 | 63.8 | 144.8 | 5.4 | 25.5 |
| 1477 | 63.8 | 2.1 | 3.6 | 31.8 |
| 1477 | 65.5 | 13.1 | 4.5 | 30.1 |
| 1477 | 67.2 | .2 | 5.2 | 47.5 |

(A) SPECIMEN UNLOADED AT TIME SHOWN.

(B) FRACTURE NEAR RADIUS; RA COULD NOT BE MEASURED.

TABLE VI. - Continued.

(c) Elevated temperature creep behavior.

| TEMPERATURE, K | STRESS, MEGAPASCALS | PLASTIC STRAIN ON LOADING, PERCENT | PLASTIC STRAIN (PERCENT) AT HOURS SHOWN | | | | | | | STEADY STATE CREEP RATE, %/HR-1 | TEST DURATION, HOURS | FINAL STRAIN, PERCENT | |
|-------------------|------------------------|---|--|------|------|------|------|-------|-------|---------------------------------------|----------------------------|-----------------------------|------|
| | | | 0.1 | 5.0 | 10.0 | 25.0 | 50.0 | 100.0 | 150.0 | | | | |
| LONGITUDINAL | | | | | | | | | | | | | |
| 1144 | 75.8 | NIL | NIL | NIL | NIL | NIL | NIL | NIL | .01 | .01 | 3.02E-10 | 160.6 | .02 |
| 1144 | 79.3 | NIL | .01 | .01 | .01 | .01 | .02 | .03 | ---- | ---- | 4.22E-10 | 128.5 (A) | ---- |
| 1144 | 81.0 | .013 | .02 | .04 | .05 | .06 | .07 | .08 | .09 | ---- | 7.55E-10 | 161.4 | .10 |
| 1144 | 82.7 | NIL | NIL | NIL | .01 | .01 | .02 | .02 | .03 | ---- | 5.43E-10 | 163.1 | .03 |
| 1144 | 82.7 | NIL | NIL | .02 | .03 | .05 | .05 | .06 | .07 | ---- | 5.44E-10 | 153.4 | .07 |
| 1144 | 84.5 | NIL | .01 | .03 | .04 | .04 | .05 | .05 | .06 | ---- | 3.93E-10 | 161.0 | .06 |
| 1144 | 86.2 | .009 | .02 | .09 | .12 | .15 | .18 | .21 | .24 | ---- | 1.21E-09 | 161.7 | .24 |
| 1144 | 86.2 | .04 | .04 | .05 | .07 | .11 | .19 | ---- | ---- | ---- | 6.76E-09 | 75.1 (B) | 6.2 |
| 1144 | 89.6 | .03 | .09 | .40 | ---- | ---- | ---- | ---- | ---- | ---- | 1.81E-07 | 6.8 (B) | 4.7 |
| 1144 | 93.1 | .08 | .13 | .70 | ---- | ---- | ---- | ---- | ---- | ---- | 2.78E-07 | 5.6 (B) | 7.1 |
| 1255 | 70.7 | NIL | NIL | NIL | NIL | NIL | .01 | .01 | .01 | ---- | 1.20E-10 | 160.0 | .01 |
| 1255 | 74.1 | NIL | NIL | .01 | .02 | .04 | .06 | .07 | .08 | ---- | 1.51E-10 | 160.4 | .08 |
| 1255 | 77.6 | NIL | .02 | .07 | .08 | .09 | .10 | .13 | .15 | ---- | 1.27E-09 | 159.6 | .15 |
| 1255 | 77.6 | .04 | .04 | .05 | .08 | .11 | ---- | ---- | ---- | ---- | 5.74E-09 | 29.7 (B) | 5.5 |
| 1255 | 79.3 | .035 | .05 | ---- | ---- | ---- | ---- | ---- | ---- | ---- | 9.49E-08 | 3.4 (B) | 5.9 |
| 1255 | 79.3 | .09 | .10 | .20 | .22 | ---- | ---- | ---- | ---- | ---- | 5.09E-09 | 24.2 (B) | 4.4 |
| 1255 | 81.0 | .025 | .05 | .13 | ---- | ---- | ---- | ---- | ---- | ---- | 2.87E-09 | 9.5 (B) | 6.5 |
| 1255 | 81.0 | .06 | .08 | .25 | .30 | .37 | .44 | .53 | ---- | ---- | 4.63E-09 | 119.7 (B) | 5.5 |
| 1255 | 82.7 | .05 | .08 | .35 | ---- | ---- | ---- | ---- | ---- | ---- | 1.25E-07 | 5.7 (B) | 5.6 |
| 1366 | 68.9 | NIL | NIL | NIL | NIL | NIL | NIL | NIL | NIL | ---- | NIL | 150.1 | NIL |
| 1366 | 70.7 | NIL | .01 | .05 | .06 | .08 | .10 | ---- | ---- | ---- | 1.21E-09 | 75.3 (B) | 6.1 |
| 1366 | 74.1 | NIL | NIL | NIL | NIL | NIL | NIL | NIL | NIL | ---- | NIL | 163.5 | NIL |
| 1366 | 74.1 | .035 | .13 | ---- | ---- | ---- | ---- | ---- | ---- | ---- | 2.60E-06 (C) | .9 (B) | 5.6 |
| 1366 | 75.8 | NIL | NIL | .01 | .02 | .04 | .05 | .06 | .10 | ---- | 1.06E-09 | 168.2 | .14 |
| 1366 | 75.8 | .06 | .12 | ---- | ---- | ---- | ---- | ---- | ---- | ---- | 1.70E-06 (C) | .5 (B) | 3.5 |
| 1366 | 77.6 | .04 | .22 | ---- | ---- | ---- | ---- | ---- | ---- | ---- | 5.00E-06 (C) | .3 (B) | 6.7 |
| 1477 | 55.1 | NIL | NIL | NIL | .01 | .01 | .02 | .04 | .09 | ---- | 9.25E-10 | 162.6 | .12 |
| 1477 | 58.6 | NIL | NIL | .03 | .04 | .07 | ---- | ---- | ---- | ---- | 5.56E-09 | 28.8 (B) | 3.9 |
| 1477 | 62.1 | NIL | .04 | ---- | ---- | ---- | ---- | ---- | ---- | ---- | 1.10E-06 (C) | 1.5 (B) | 5.4 |
| 1477 | 62.1 | NIL | NIL | NIL | .01 | .01 | .02 | .04 | .06 | ---- | 1.09E-09 | 165.6 | .07 |
| 1477 | 62.1 | NIL | NIL | .03 | .05 | ---- | ---- | ---- | ---- | ---- | 1.09E-08 | 23.0 (B) | 4.4 |
| 1477 | 63.8 | NIL | .01 | .02 | .02 | .02 | .03 | .03 | ---- | ---- | 4.53E-10 | 144.8 (B) | 5.4 |
| 1477 | 63.8 | NIL | .02 | ---- | ---- | ---- | ---- | ---- | ---- | ---- | 5.56E-07 | 2.1 (B) | 3.6 |
| 1477 | 65.5 | NIL | .01 | .03 | .05 | ---- | ---- | ---- | ---- | ---- | 8.33E-09 | 13.1 (B) | 4.5 |
| 1477 | 65.5 | .04 | .05 | .11 | .15 | ---- | ---- | ---- | ---- | ---- | 2.02E-08 | 14.8 (A) | ---- |
| 1477 | 67.2 | NIL | .15 | ---- | ---- | ---- | ---- | ---- | ---- | ---- | 4.20E-06 (C) | .2 (B) | 5.2 |

TABLE VI. - Continued.

(c) Concluded.

| TEMPERATURE, K | STRESS, MEGAPASCALS | PLASTIC STRAIN ON LOADING, PERCENT | PLASTIC STRAIN (PERCENT) AT HOURS SHOWN | | | | | | | STEADY STATE CREEP RATE, S**-1 | TEST DURATION, HOURS | FINAL STRAIN, PERCENT | |
|-------------------|------------------------|---|--|-----|------|------|------|-------|-------|--------------------------------------|----------------------------|-----------------------------|-----|
| | | | 0.1 | 5.0 | 10.0 | 25.0 | 50.0 | 100.0 | 150.0 | | | | |
| LONG TRANSVERSE | | | | | | | | | | | | | |
| 1144 | 72.4 | | | | | | | | | | | .9 (B) | 1.6 |
| 1144 | 75.8 | | | | | | | | | | | FOL (D) | 1.9 |
| 1144 | 79.3 | | | | | | | | | | | .1 (B) | 1.9 |
| 1144 | 82.7 | | | | | | | | | | | FOL | 2.3 |
| 1255 | 65.5 | | | | | | | | | | | FOL | 4.2 |
| 1255 | 68.9 | | | | | | | | | | | FOL | .7 |
| 1255 | 72.4 | | | | | | | | | | | FOL | 1.0 |
| 1255 | 75.8 | | | | | | | | | | | FOL | (E) |
| 1366 | 10.3 | NIL | .02 | .04 | .05 | .06 | .07 | .09 | .10 | 9.06E-10 | 163.4 | | .11 |
| 1366 | 13.8 | NIL | NIL | .01 | .01 | .02 | .03 | .06 | .09 | 1.63E-09 | 149.4 | | .09 |
| 1366 | 15.5 | NIL | (F) | | | | | | | | 118.2 (B) | | (E) |
| 1366 | 17.2 | NIL | NIL | .01 | .01 | .02 | .04 | .08 | .12 | 2.17E-09 | 163.6 | | .13 |
| 1366 | 17.2 | NIL | NIL | | | | | | | | 1.0 (B) | | 1.8 |
| 1366 | 18.9 | NIL | .01 | | | | | | | | 1.7 (B) | | .5 |
| 1366 | 24.1 | NIL | .01 | | | | | | | | 2.9 (B) | | 1.5 |
| 1366 | 27.6 | NIL | NIL | | | | | | | | .7 (B) | | 1.7 |
| 1366 | 31.0 | | | | | | | | | | (G) | | 1.8 |

- (A) TEST INTERRUPTED DUE TO TESTING MACHINE FAILURE.
- (B) FAILED AT TIME SHOWN.
- (C) NO CREEP CURVE AVAILABLE; CREEP RATE ESTIMATED FROM STRAINS ON LOADING AND 0.1 HOUR.
- (D) FAILED ON LOADING.
- (E) MULTIPLE FRACTURE.
- (F) ALL CREEP READINGS WERE NEGATIVE.
- (G) SPECIMEN FAILED WHILE BEING STEP LOADED.

TABLE VI. - Concluded.

(d) Residual room temperature properties.

| PRIOR CREEP HISTORY | | | | RESIDUAL TENSILE PROPERTIES | | | | |
|---------------------|------------------------|----------------|-------------------------------------|--|---|--|------------------------|----------------------------------|
| TEMPERATURE, K | STRESS, MEGAPASCALS | TIME, HOURS | ELASTIC CREEP STRAIN, PERCENT | 0.02 PERCENT YIELD STRESS, MEGAPASCALS | 0.2 PERCENT YIELD STRESS, MEGAPASCALS | ULTIMATE TENSILE STRESS, MEGAPASCALS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
| LONGITUDINAL | | | | | | | | |
| 1144 | 68.9 | 1005.4 (A) | ---- | 596.4 | 597.8 | 664.0 | 13.6 | 39.6 |
| 1144 | 75.8 | 160.6 | .02 | 561.9 | 579.9 | 682.6 | 14.4 | 46.2 |
| 1144 | 81.0 | 161.4 | .10 | 584.7 | 586.8 | 672.9 | 15.6 | 39.3 |
| 1144 | 82.7 | 163.1 | .03 | 598.5 | 604.0 | 697.6 | 11.7 | 43.4 |
| 1144 | 82.7 | 150.4 | .07 | 566.1 | 619.2 | 712.2 | 10.4 | 27.8 |
| 1144 | 84.5 | 161.0 | .06 | 590.2 | 597.1 | 679.8 | 15.5 | 43.0 |
| 1144 | 86.2 | 161.7 | .24 | 577.8 | 590.2 | 718.4 | 6.5 | 4.0 (B) |
| 1144 | 86.2 | 2061.5 (A) | ---- | 598.5 | 604.0 | 653.6 | 15.0 | 42.6 |
| 1255 | 70.7 | 160.0 | .01 | 581.2 | 588.1 | 659.8 | 6.5 | 3.3 (B) |
| 1255 | 74.1 | 160.4 | .08 | 620.5 | 632.3 | 692.2 | 11.6 | 40.7 |
| 1255 | 75.8 | 1005.4 (A) | ---- | 592.3 | 595.0 | 650.9 | 13.5 | 41.5 |
| 1255 | 77.6 | 159.8 | .15 | 564.7 | 598.8 | 635.0 | 2.1 | 1.4 (B) |
| 1366 | 74.1 | 163.5 | NIL | 608.8 | 631.2 | 688.1 | 9.9 | 47.3 |
| 1366 | 75.8 | 168.2 | .14 | 593.6 | 639.1 | 713.6 | 11.3 | 43.8 |
| 1477 | 62.1 | 165.6 | .07 | 590.2 | 593.0 | 691.5 | 12.5 | 41.3 |
| 1477 | 65.5 | 14.8 (C) | .18 | (D) | | 659.7 | 11.8 | 42.6 |
| LONG TRANSVERSE | | | | | | | | |
| 1366 | 10.3 | 163.4 | .11 | 637.1 | 652.2 | 657.6 | 12.5 | 32.8 |
| 1366 | 13.6 | 149.4 | .09 | (E) | | 467.5 | 1.0 (F) | .3 |
| 1366 | 17.2 | 163.6 | .13 | 607.4 | 628.1 | 641.2 | 2.3 (F) | 3.6 |

(A) STRESS RUPTURE SPECIMEN UNLOADED AT TIME SHOWN; NO MEASUREABLE DEFORMATION.

(B) CLEAVAGE FAILURE.

(C) TEST FIXTURE FAILED AT TIME SHOWN.

(D) THREADED GRIP END DESTROYED; SPECIMEN TESTED AT LEWIS RESEARCH CENTER ; YIELD STRENGTHS COULD NOT BE DETERMINED.

(E) FAILED BEFORE 0.02 PERCENT STRESS REACHED.

(F) FAILED IN SHOULDER.

TABLE VII. - MECHANICAL PROPERTIES OF STCA ALLOYS

| (a) Tensile properties. | | | | | |
|-------------------------|--|---|--|------------------------|----------------------------------|
| HEAT | 0.92 PERCENT YIELD STRESS, MEGAPASCALS | 3.2 PERCENT YIELD STRESS, MEGAPASCALS | ULTIMATE TENSILE STRESS, MEGAPASCALS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
| 298 K | | | | | |
| LONGITUDINAL | | | | | |
| 262/264S | 815.7 | 923.2 | 1280.4 | 5.8 | 4.3 (A) |
| 265S | 850.8 | 954.9 | 1261.1 | 4.7 | 6.6 |
| 265SC | 801.2 | 958.4 | 1252.1 | 4.5 | 3.9 (A) |
| 266S | 866.7 | 946.7 | 1316.9 | 5.4 | 5.5 |
| LONG TRANSVERSE | | | | | |
| 262/264S | 777.0 | 971.5 | 1160.4 | 5.7 | 2.4 (A) |
| 265S | 810.8 | 886.7 | 1096.3 | 4.7 | 7.4 |
| 265SC | 843.9 | 941.1 | 1090.8 | 4.0 | 4.3 |
| 266S | 788.8 | 881.2 | 1109.4 | 4.8 | 9.3 |
| 266SC | 834.3 | 927.4 | 1081.1 | 4.0 | 6.6 |
| 1366K | | | | | |
| LONGITUDINAL | | | | | |
| 262/264S | 79.3 | 37.9 | 105.5 | 9.8 | 19.3 |
| 265S | 75.5 | 37.9 | 105.1 | 14.1 | 19.8 |
| 265SC | 75.8 | 95.8 | 102.0 | 9.7 | 16.8 |
| 266S | 65.5 | 100.0 | 104.0 | 6.8 | 15.0 |
| LONG TRANSVERSE | | | | | |
| 262/264S | 84.8 | 35.8 | 97.2 | 2.1 | 1.3 |
| 265S | 82.7 | 95.1 | 95.8 | 1.0 | .6 |
| 265SC | 64.8 | 97.2 | 97.9 | 5.4 | 1.2 |
| 266S | 81.4 | 101.4 | 101.4 | 1.2 | .6 |
| 266SC | 78.6 | 95.1 | 95.8 | 1.7 | .4 |

(A) SPECIMEN FAILED AT RADIUS.

TABLE VII - Continued.

(b) Creep behavior at 1366 K.

| STRESS, MEGAPASCALS | PLASTIC STRAIN ON LOADING, PERCENT | PLASTIC STRAIN (PERCENT) AT HOURS SHOWN | | | | | | | STEADY STATE CREEP RATE, S ⁻¹ | TEST DURATION, HOURS | FINAL STRAIN, PERCENT | REDUCTION OF AREA, PERCENT |
|------------------------|---|--|------|------|------|------|-------|-------|--|----------------------------|-----------------------------|----------------------------------|
| | | 0.1 | 5.0 | 10.0 | 25.0 | 50.0 | 100.0 | 150.0 | | | | |
| LONGITUDINAL | | | | | | | | | | | | |
| HEAT 262/264S | | | | | | | | | | | | |
| 65.5 | NIL | NIL | .01 | .01 | .02 | .02 | .03 | .04 | 4.91E-10 | 163.5 | .04 | ---- |
| 68.9 | NIL | .02 | .06 | .07 | .08 | .09 | .10 | .11 | 6.00E-10 | 163.5 | .11 | ---- |
| 72.4 | NIL | .04 | .13 | .19 | .30 | .44 | ---- | ---- | 1.50E-08 | 62.2 (A) | 1.4 | 11.0 |
| 75.8 | NIL | .02 | .11 | .16 | .29 | .52 | ---- | ---- | 2.46E-08 | 111.9 (A) | 8.6 | 12.8 |
| 79.3 | NIL | .08 | .49 | .85 | ---- | ---- | ---- | ---- | 1.90E-07 | 24.3 (A) | 9.3 | 10.6 |
| 82.7 | NIL | .12 | ---- | ---- | ---- | ---- | ---- | ---- | 7.20E-07 | 4.8 (A) | 5.8 | 15.2 |
| HEAT 265S | | | | | | | | | | | | |
| 65.5 | NIL | .02 | .03 | .04 | .05 | .07 | .10 | .12 | 1.39E-09 | 168.1 | .14 | ---- |
| 67.2 | NIL | .02 | .03 | .04 | .05 | .07 | .10 | .15 | 1.57E-09 | 161.0 | .17 | ---- |
| 70.7 | NIL | .03 | .07 | .09 | .15 | .22 | ---- | ---- | 5.86E-09 | 87.3 (A) | 4.3 | 8.8 |
| 72.4 | NIL | .01 | .04 | .05 | .06 | .08 | .11 | .13 | 1.81E-09 | 149.7 | .13 | ---- |
| 74.1 | NIL | .02 | .09 | .13 | .24 | .41 | ---- | ---- | 1.86E-08 | 82.5 (A) | 7.9 | .9 |
| 75.8 | NIL | .01 | .04 | .06 | .10 | .16 | .30 | .51 | 6.40E-09 | 149.9 | .51 | ---- |
| 79.3 | NIL | .03 | .41 | .68 | ---- | ---- | ---- | ---- | 1.40E-07 | 26.7 (A) | 5.7 | 16.1 |
| 82.7 | NIL | .15 | ---- | ---- | ---- | ---- | ---- | ---- | 4.10E-06 | 3.0 (A) | 8.1 | 12.5 |
| HEAT 265SC | | | | | | | | | | | | |
| 63.8 | NIL | .04 | .15 | .20 | .26 | .36 | .46 | .53 | 3.44E-09 | 165.3 | .55 | ---- |
| 65.5 | NIL | .08 | .12 | .14 | .17 | .18 | .20 | .22 | 1.09E-09 | 165.3 | .22 | ---- |
| 65.5 | NIL | .01 | .01 | .01 | .02 | .03 | .05 | .07 | 1.21E-09 | 190.0 | .09 | (B) |
| 67.2 | NIL | .01 | .02 | .02 | .03 | .04 | .06 | .08 | 1.27E-09 | 163.4 | .09 | ---- |
| 68.9 | NIL | .04 | .06 | .10 | .14 | .18 | .22 | .28 | 2.78E-09 | 164.8 | .32 | ---- |
| 70.7 | NIL | .01 | .06 | .08 | .12 | .16 | .21 | .31 | 1.93E-09 | 173.9 | .43 | ---- |
| 72.4 | NIL | NIL | .06 | .10 | .22 | .37 | .64 | ---- | 1.45E-08 | 116.2 (A) | 4.0 | 4.4 |
| 75.8 | NIL | .02 | .28 | .43 | .90 | ---- | ---- | ---- | 8.06E-08 | 45.2 (A) | 6.6 | 13.0 |
| 79.3 | .02 | .11 | .87 | ---- | ---- | ---- | ---- | ---- | 4.30E-07 | 10.0 (A) | 5.9 | 2.4 |
| 82.7 | NIL | .09 | 1.55 | ---- | ---- | ---- | ---- | ---- | 6.00E-07 | 5.5 (A) | 4.2 | 6.3 |

TABLE VII. - Continued.

(b) Continued.

| STRESS, MEGAPASCALS | PLASTIC STRAIN ON LOADING, PERCENT | PLASTIC STRAIN (PERCENT) AT HOURS SHOWN | | | | | | | STEADY STATE CREEP RATE, S**-1 | TEST DURATION, HOURS | FINAL STRAIN, PERCENT | REDUCTION OF AREA, PERCENT |
|------------------------|---|--|------|------|------|------|-------|-------|--------------------------------------|----------------------------|-----------------------------|----------------------------------|
| | | 0.1 | 5.0 | 10.0 | 25.0 | 50.0 | 100.0 | 150.0 | | | | |
| LONGITUDINAL | | | | | | | | | | | | |
| HEAT 266S | | | | | | | | | | | | |
| 53.4 | NIL | .01 | .01 | .01 | .02 | .02 | .03 | .03 | 4.23E-10 | 163.3 | .03 | ---- |
| 55.2 | NIL | NIL | .01 | .01 | .02 | .05 | .09 | .14 | 2.57E-09 | 178.2 | .16 (E) | ---- |
| 55.2 | NIL | (C) | | | | | | | | 165.5 | ---- | ---- |
| 56.9 | NIL | -.02 | -.02 | -.03 | -.04 | -.05 | -.06 | -.04 | | 166.1 | -.02 | ---- |
| 58.6 | NIL | .01 | .02 | .02 | .04 | .05 | .11 | ---- | 1.81E-09 | 146.3 (A) | 1.2 | (D) |
| 62.1 | NIL | .03 | .20 | .23 | .27 | .32 | ---- | ---- | 4.43E-09 | 63.3 (A) | 2.1 | .3 |
| 65.5 | NIL | .01 | .04 | .06 | .20 | ---- | ---- | ---- | 1.35E-08 | 29.0 (A) | 2.2 | 4.3 |
| 67.2 | NIL | .02 | .05 | .08 | .13 | ---- | ---- | ---- | 1.00E-08 | 48.5 (A) | 3.2 | 4.2 |
| 68.9 | NIL | .01 | .06 | .09 | .17 | .30 | ---- | ---- | 1.48E-08 | 64.7 (A) | 2.7 | 5.1 |
| 70.7 | NIL | .09 | .40 | ---- | ---- | ---- | ---- | ---- | 2.30E-07 | 7.7 (A) | 1.6 | 2.8 |
| 72.4 | .02 | .01 | .05 | .07 | .12 | .20 | ---- | ---- | 8.94E-09 | 89.1 (A) | 2.7 | 8.3 |
| 75.8 | NIL | .04 | .16 | .22 | .38 | .71 | ---- | ---- | 2.78E-08 | 73.2 (A) | 9.5 | 22.0 |
| 79.3 | .04 | .17 | ---- | ---- | ---- | ---- | ---- | ---- | 3.60E-06 | 1.6 (A) | 2.3 | 10.8 |
| 82.7 | .06 | .84 | ---- | ---- | ---- | ---- | ---- | ---- | 2.16E-05 | .2 (A) | 3.8 | 3.0 |
| LONG TRANSVERSE | | | | | | | | | | | | |
| HEAT 262/264S | | | | | | | | | | | | |
| 22.4 | NIL | NIL | .04 | .04 | .05 | .06 | .08 | .09 | 9.66E-10 | 149.3 | .09 | ---- |
| 25.9 | NIL | NIL | .04 | .05 | .06 | .08 | .10 | .14 | 1.93E-09 | 166.7 | .15 | ---- |
| 27.6 | NIL | NIL | .01 | .01 | .02 | .04 | .07 | .11 | 2.17E-09 | 164.7 | .13 | ---- |
| 29.3 | NIL | .01 | .03 | .04 | .06 | .11 | .23 | .44 | 4.89E-09 | 163.2 | .54 | (B) |
| 31.0 | NIL | NIL | .03 | .04 | .07 | .15 | .61 | 1.66 | 7.49E-09 | 166.5 | 2.14 | (E) |
| 34.5 | NIL | NIL | .08 | .19 | 1.01 | 4.53 | ---- | ---- | 4.83E-08 | 65.9 (A) | 7.6 | NIL |
| 37.9 | NIL | NIL | .08 | .15 | .59 | ---- | ---- | ---- | 3.14E-08 | 51.1 (A) | 3.9 | NIL (D) |
| HEAT 265S | | | | | | | | | | | | |
| 15.5 | NIL | .01 | .02 | .02 | .03 | .04 | .09 | .15 | 1.81E-09 | 164.7 | .18 | ---- |
| 19.0 | NIL | .02 | .03 | .05 | .09 | .18 | .46 | 1.09 | 8.21E-09 | 165.4 | 1.46 | (B) |
| 22.4 | NIL | .01 | .03 | .05 | .08 | .21 | 1.06 | (P) | 7.00E-09 | 188.1 | 6.7 | ---- |
| 25.9 | NIL | .01 | .11 | .15 | .27 | .92 | ---- | ---- | 1.98E-08 | 96.4 (A) | 4.3 | .3 |
| 27.6 | NIL | NIL | .03 | .05 | .09 | .19 | .54 | 1.14 | 6.28E-09 | 165.5 | 1.31 | ---- |
| 29.3 | NIL | .45 | .70 | ---- | ---- | ---- | ---- | ---- | 3.20E-07 | 21.1 (A) | 2.6 | .4 |
| 34.5 | NIL | .01 | .12 | .19 | ---- | ---- | ---- | ---- | 4.03E-08 | 21.8 (A) | (G) | ---- |
| 37.9 | NIL | .02 | .20 | .37 | ---- | ---- | ---- | ---- | 9.44E-08 | 19.9 (A) | 2.1 | NIL (D) |

TABLE VII. - Continued.

(b) Concluded.

| STRESS, MEGAPASCALS | PLASTIC STRAIN ON LOADING, PERCENT | PLASTIC STRAIN (PERCENT) AT HOURS SHOWN | | | | | | | STEADY STATE CREEP RATE, S** ⁻¹ | TEST DURATION, HOURS | FINAL STRAIN, PERCENT | REDUCTION OF AREA, PERCENT |
|------------------------|---|--|-----|------|------|------|-------|-------|--|----------------------------|-----------------------------|----------------------------------|
| | | 0.1 | 5.0 | 10.0 | 25.0 | 50.0 | 100.0 | 150.0 | | | | |
| LONG TRANSVERSE | | | | | | | | | | | | |
| HEAT 265SC | | | | | | | | | | | | |
| 15.5 | NIL | NIL | .01 | .01 | .02 | .03 | .05 | .06 | 9.92E-10 | 162.6 | .10 | ---- |
| 17.2 | NIL | NIL | .01 | .01 | .02 | .03 | .06 | .10 | 1.30E-09 | 163.5 | .12 | ---- |
| 19.0 | NIL | .02 | .04 | .06 | .09 | .13 | .18 | .23 | 2.70E-09 | 165.2 | .25 | ---- |
| 20.7 | NIL | NIL | .04 | .05 | .06 | .08 | .11 | .15 | 1.97E-09 | 164.2 | .15 | ---- |
| 22.4 | NIL | .01 | .03 | .04 | .05 | .06 | .09 | .12 | 1.54E-09 | 215.3 | .20 | ---- |
| 24.1 | NIL | NIL | .03 | .05 | .12 | .33 | 2.35 | 5.02 | 1.44E-08 | 151.1 | 5.3 | (B) |
| 25.9 | NIL | .02 | .06 | .08 | .14 | .30 | 1.05 | 3.07 | 1.11E-08 | 150.0 | 4.6 | (E) |
| 27.6 | NIL | NIL | .01 | .01 | .03 | .09 | .45 | 1.29 | 2.90E-09 | 166.9 | 1.66 | ---- |
| 31.0 | NIL | .01 | .01 | .02 | .05 | .21 | 2.12 | 4.52 | 8.45E-09 | 167.1 | 5.35 | (B) |
| 34.5 | NIL | .01 | .07 | .17 | .76 | 3.41 | ---- | ---- | 5.79E-08 | 64.2(A) | 5.2 | NIL(D) |
| 37.9 | NIL | NIL | .12 | ---- | ---- | ---- | ---- | ---- | 4.03E-08 | 9.2(A) | 1.0 | NIL(D) |
| HEAT 266S | | | | | | | | | | | | |
| 20.7 | NIL | .01 | .02 | .02 | .03 | .04 | .06 | .09 | 1.53E-09 | 166.9 | .10 | ---- |
| 24.1 | NIL | .01 | .02 | .02 | .03 | .04 | .12 | .24 | 2.42E-09 | 149.8 | .24 | ---- |
| 25.9 | NIL | .01 | .01 | .02 | .04 | .07 | .23 | .57 | 3.44E-09 | 164.2 | .70 | ---- |
| 27.6 | NIL | NIL | NIL | .01 | .03 | .06 | .18 | .48 | 3.26E-09 | 150.0 | .48 | ---- |
| 31.0 | NIL | NIL | .01 | .02 | .05 | .16 | .74 | 1.65 | 5.92E-09 | 151.5 | 1.68 | ---- |
| 34.5 | NIL | .02 | .06 | .11 | .29 | .76 | 2.30 | 4.63 | 3.32E-08 | 150.0 | 4.63 | ---- |
| 37.9 | NIL | NIL | .05 | .14 | .66 | 1.97 | 5.00 | 8.70 | 3.70E-08 | 166.1 | 10.4 | NIL(B) |
| HEAT 266SC | | | | | | | | | | | | |
| 15.5 | NIL | .01 | .03 | .04 | .05 | .07 | .12 | .19 | 2.39E-09 | 165.3 | .22 | ---- |
| 17.2 | NIL | .01 | .02 | .03 | .04 | .04 | .05 | .06 | 4.83E-10 | 163.3 | .06 | ---- |
| 19.0 | NIL | .01 | .03 | .04 | .08 | .17 | .65 | 2.44 | 4.83E-09 | 167.3 | 3.49 | ---- |
| 20.7 | NIL | NIL | .01 | .02 | .02 | .03 | .06 | .13 | 1.14E-09 | 163.0 | .16 | ---- |
| 22.4 | NIL | .02 | .07 | .09 | .13 | .24 | 1.98 | 5.77 | 1.09E-08 | 162.6 | 6.69 | ---- |
| 24.1 | NIL | .01 | .03 | .04 | .06 | .09 | .19 | .44 | 3.20E-09 | 163.3 | .62 | ---- |
| 27.6 | NIL | NIL | .03 | .04 | .35 | 3.42 | ---- | ---- | 3.32E-08 | 103.2(A) | 10.4 | .2 |
| 31.0 | NIL | NIL | .02 | .08 | .11 | ---- | ---- | ---- | ---- | 24.1(H) | ---- | ---- |
| 34.5 | NIL | NIL | .02 | .19 | .43 | 2.25 | 5.88 | ---- | 8.57E-08 | 67.4(A) | 9.0 | .6 |
| 37.9 | NIL | NIL | .42 | ---- | ---- | ---- | ---- | ---- | 1.71E-07 | 8.4(A) | .8 | .2 |

- (A) FAILED AT TIME SHOWN.
- (B) SPECIMEN FAILED WHILE BEING REMOVED FROM THE ADAPTER.
- (C) ERRATIC CREEP READINGS - NO MEASUREABLE DEFORMATION AFTER TESTING.
- (D) FAILED AT RADIUS.
- (E) FAILED WHILE COOLING
- (F) EXTENSOMETER SLIPPED; STRAIN COULD NOT BE DETERMINED.
- (G) SPECIMEN COULD NOT BE FITTED TOGETHER.
- (H) SPECIMEN WAS c5 K OVER TEMPERATURE WHEN FAILED AT TIME SHOWN.

TABLE VII. - Continued.

(c) Residual room temperature properties.

| PRIOR CREEP HISTORY | | | | RESIDUAL TENSILE PROPERTIES | | | | |
|---------------------|------------------------|----------------|-------------------------------------|--|---|--|------------------------|----------------------------------|
| TEMPERATURE, K | STRESS, MEGAPASCALS | TIME, HOURS | PLASTIC CREEP STRAIN, PERCENT | 0.02 PERCENT YIELD STRESS, MEGAPASCALS | 0.2 PERCENT YIELD STRESS, MEGAPASCALS | ULTIMATE TENSILE STRESS, MEGAPASCALS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
| LONGITUDINAL | | | | | | | | |
| HEAT 262/264S | | | | | | | | |
| 1366 | 65.5 | 163.5 | .04 | 733.6 | 823.9 | 1248.6 | 5.9 | 4.9 |
| 1366 | 68.9 | 163.5 | .11 | 731.5 | 814.3 | 1282.4 | 6.9 | 5.2 |
| HEAT 265S | | | | | | | | |
| 1366 | 65.5 | 168.1 | .14 | 760.5 | 805.3 | 1001.8 | 3.4 | 4.7 |
| 1366 | 67.2 | 161.0 | .17 | 695.0 | 800.5 | 916.3 | 2.4 | 4.0 |
| 1366 | 72.3 | 149.2 | .13 | 686.7 | 828.1 | 1107.3 | 4.9 | 5.9 |
| 1366 | 75.8 | 149.9 | .51 | 727.4 | 840.5 | 895.6 | 1.7 | 2.1 |
| HEAT 265SC | | | | | | | | |
| 1366 | 63.8 | 165.3 | .55 | (A) | ----- | 1040.4 | .8 | 2.4 |
| 1366 | 65.5 | 165.3 | .22 | 706.0 | 869.4 | 1093.5 | 3.7 | 2.2 |
| 1366 | 67.2 | 163.4 | .09 | 732.9 | 870.8 | 891.5 (B) | .4 | 2.4 |
| 1366 | 68.9 | 164.8 | .32 | 745.3 | 817.0 | 886.0 | 1.4 | 2.4 |
| 1366 | 70.6 | 173.9 | .43 | 651.6 | 808.1 | 979.8 | 2.9 | 3.3 (C) |
| HEAT 266S | | | | | | | | |
| 1366 | 53.4 | 163.3 | .03 | 817.7 | 868.7 | 1288.6 | 6.4 | 5.0 (C) |
| 1366 | 55.1 | 165.5 | (D) | 733.6 | 812.9 | 1199.0 | 5.8 | 4.9 (C) |
| 1366 | 56.9 | 166.1 | -.02 | 772.2 | 870.8 | 1039.0 | 3.2 | 3.3 |

TABLE VII - Continued.

(c) Continued.

| PRIOR CREEP HISTORY | | | | RESIDUAL TENSILE PROPERTIES | | | | |
|---------------------|------------------------|----------------|-------------------------------------|--|---|--|------------------------|----------------------------------|
| TEMPERATURE, K | STRESS, MEGAPASCALS | TIME, HOURS | PLASTIC CREEP STRAIN, PERCENT | 0.02 PERCENT YIELD STRESS, MEGAPASCALS | 0.2 PERCENT YIELD STRESS, MEGAPASCALS | ULTIMATE TENSILE STRESS, MEGAPASCALS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
| LONG TRANSVERSE | | | | | | | | |
| HEAT 262/264S | | | | | | | | |
| 1366 | 22.4 | 149.3 | .09 | 644.0 | 788.1 | 1081.1 | 5.5 | 8.8 |
| 1366 | 25.8 | 166.7 | .15 | 700.5 | 788.8 | 992.9 | 4.2 | 3.6 |
| 1366 | 27.6 | 164.7 | .13 | 586.1 | (E) | 586.1 | .7 | .4 |
| HEAT 265S | | | | | | | | |
| 1366 | 15.5 | 164.7 | .18 | 728.1 | 842.5 | 1031.1 | 4.9 | 3.5 |
| 1366 | 22.4 | 188.1 | 6.7 | (F) | ----- | 55.2 | 3.6 | NIL (C) |
| HEAT 265SC | | | | | | | | |
| 1366 | 15.5 | 162.6 | .10 | 679.8 | 761.9 | 1041.1 | 7.6 | 5.5 |
| 1366 | 17.2 | 163.5 | .12 | 667.4 | 748.8 | 761.2 | .8 | .6 (C) |
| 1366 | 19.0 | 165.2 | .22 | 602.6 | 801.9 | 886.0 | 2.0 | 3.8 |
| 1366 | 20.7 | 164.2 | .15 | 566.1 | (E) | 623.3 | .5 | .5 |
| 1366 | 22.4 | 215.3 | .20 | 553.0 | 748.1 | 748.1 | .4 | .8 (C) |
| 1366 | 27.6 | 166.9 | 1.66 | 121.3 | (E) | 137.9 | .2 | .2 |



TABLE VII - Concluded.

(c) Concluded.

| PART OF CREEP HISTORY | | | | RESIDUAL TENSILE PROPERTIES | | | | |
|-----------------------|------------------------|----------------|-------------------------------------|--|---|--|------------------------|----------------------------------|
| TEMPERATURE, K | STRESS, MEGAPASCALS | TIME, HOURS | ELASTIC CREEP STRAIN, PERCENT | 0.02 PERCENT YIELD STRESS, MEGAPASCALS | 0.2 PERCENT YIELD STRESS, MEGAPASCALS | ULTIMATE TENSILE STRESS, MEGAPASCALS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
| LONG TRANSVERSE | | | | | | | | |
| HEAT 266S | | | | | | | | |
| 1365 | 20.7 | 166.9 | .10 | 653.6 | (E) | 767.4 | 1.0 | .2 (C) |
| 1366 | 20.1 | 189.0 | .24 | (F) | ----- | 452.3 | .6 | NIL (C) |
| 1366 | 25.8 | 164.2 | .70 | (F) | ----- | 212.4 | NIL | NIL (C) |
| 1366 | 27.6 | 150.0 | .48 | 302.0 | (E) | 346.1 | .3 | .3 |
| 1366 | 31.0 | 151.5 | 1.68 | 41.4 | 44.1 | 44.1 | NIL | NIL |
| 1368 | 34.5 | 150.0 | 4.63 | 41.4 | (E) | 41.4 | .6 | .2 |
| HEAT 266SC | | | | | | | | |
| 1367 | 15.5 | 165.3 | .22 | 674.0 | 814.3 | 996.4 | 3.9 | 2.2 |
| 1368 | 17.2 | 163.3 | .06 | 661.9 | 786.0 | 1081.1 | 5.7 | 6.3 |
| 1367 | 19.0 | 167.3 | 3.49 | (F), (G) | ----- | 82.0 | 1.4 | NIL |
| 1368 | 20.7 | 163.0 | .10 | 675.8 | (E) | 738.4 | .5 | .8 (C) |
| 1368 | 22.0 | 162.6 | 6.69 | (F), (G) | ----- | 6.9 | .4 | NIL |
| 1368 | 24.1 | 163.3 | .62 | 181.3 | (E) | 191.0 | .1 | .2 |

- (A) THREADED GRIP ENDS DESTROYED; SPECIMEN TESTED AT LEWIS RESEARCH CENTER; YIELD STRENGTHS COULD NOT BE DETERMINED.
- (B) DEFECT FOUND ON FRACTURE SURFACE.
- (C) SPECIMEN FAILED NEAR RADIUS.
- (D) NO MEASUREABLE DEFORMATION AFTER TESTING; ERRATIC CREEP READINGS.
- (E) FAILED BEFORE 0.2 PERCENT YIELD STRESS WAS OBTAINED.
- (F) FAILED BEFORE 0.02 PERCENT YIELD STRESS WAS OBTAINED.
- (G) CRACKS IN GAGE SECTION PRIOR TO TENSILE TESTING.

TABLE VIII. - MECHANICAL PROPERTIES OF YD-NiCrAl

(a) Creep behavior at 1366 K.

| STRESS, MEGAPASCALS | PLASTIC STRAIN ON LOADING, PERCENT | PLASTIC STRAIN (PERCENT) AT HOURS SHOWN | | | | | | | STEADY STATE CREEP RATE, S***-1 | TEST DURATION, HOURS | FINAL STRAIN, PERCENT |
|------------------------|---|--|------|------|------|------|-------|-------|---------------------------------------|----------------------------|-----------------------------|
| | | 0.1 | 5.0 | 10.0 | 25.0 | 50.0 | 100.0 | 150.0 | | | |
| LONGITUDINAL | | | | | | | | | | | |
| 37.9 | NIL | .01 | .04 | .04 | .05 | .06 | .07 | .08 | 7.25E-10 | 173.8 | .09 |
| 41.4 | NIL | .02 | .04 | .04 | .05 | .05 | .06 | .07 | 6.64E-10 | 163.6 | .07 |
| 44.8 | NIL | .02 | .05 | .06 | .08 | .09 | .11 | .13 | 1.27E-09 | 163.7 | .15 |
| 46.5 | NIL | .01 | .04 | .05 | .07 | .09 | .11 | .12 | 9.66E-10 | 172.7 | .13 |
| 48.3 | NIL | .04 | .11 | .13 | .18 | .23 | .31 | .39 | 4.29E-09 | 165.3 | .41 |
| 48.3 | NIL | .13 | .22 | .26 | .32 | .39 | .51 | .63 | 6.98E-09 | 162.7 | .66 |
| 50.0 | NIL | .02 | .10 | .14 | .20 | .29 | .44 | .58 | 8.10E-09 | 162.8 | .62 |
| 50.0 | NIL | .04 | .09 | .12 | .16 | .22 | .32 | .44 | 5.00E-09 | 164.0 | .50 |
| 51.7 | NIL | .02 | .14 | .19 | .30 | .41 | .55 | .66 | 7.23E-09 | 164.8 | .72 |
| 53.4 | NIL | .22 | 2.23 | --- | --- | --- | --- | --- | --- | 10.8 (A) | |

(b) Residual room temperature properties.

| PRIOR CREEP HISTORY | | | | RESIDUAL TENSILE PROPERTIES | | | | |
|---------------------|------------------------|----------------|-------------------------------------|--|---|--|------------------------|----------------------------------|
| TEMPERATURE, K | STRESS, MEGAPASCALS | TIME, HOURS | PLASTIC CREEP STRAIN, PERCENT | 0.02 PERCENT YIELD STRESS, MEGAPASCALS | 0.2 PERCENT YIELD STRESS, MEGAPASCALS | ULTIMATE TENSILE STRESS, MEGAPASCALS | ELONGATION, PERCENT | REDUCTION OF AREA, PERCENT |
| 1366 | 37.9 | 173.8 | .09 | 597.1 | 686.0 | 922.5 | 5.5 | 9.6 |
| 1366 | 41.4 | 163.6 | .07 | 666.7 | 695.7 | 1139.0 | 14.8 | 19.2 |
| 1366 | 44.8 | 163.7 | .15 | 677.1 | 706.0 | 1152.1 | 12.9 | 16.6 |
| 1366 | 46.5 | 172.7 | .13 | 667.4 | 710.2 | 1038.4 | 7.4 | 8.0 |
| 1366 | 48.3 | 165.3 | .41 | 642.6 | 655.0 | 1045.9 | 14.6 | 16.9 |
| 1366 | 48.3 | 162.7 | .66 | 661.9 | 699.1 | 1028.7 | 9.4 | 7.3 |
| 1366 | 50.0 | 152.8 | .62 | 662.6 | 699.1 | 1098.3 | 8.6 | 15.7 |
| 1366 | 50.0 | 164.0 | .50 | 659.1 | 716.4 | 1115.6 | 8.8 | 14.7 |
| 1366 | 51.7 | 164.8 | .72 | 726.7 | 737.7 | 1131.4 | 8.1 | 13.1 |

(A) FAILED AT TIME SHOWN; 29.5 % ELONGATION; 62.6% RA.

TABLE IX. - REGRESSION ANALYSIS OF B-1900

| CONSTANT | STRESS EXPONENT | TEMPERATURE, K | ACTIVATION ENERGY, kJ/g-mol-K | TEMPERATURE RANGE, K | REGRESSION COEFFICIENT, R**2 |
|-------------------------|-----------------|-------------------|-------------------------------------|----------------------------|------------------------------------|
| TIME TO RUPTURE | | | | | |
| 44.32 | -6.83 | 1144 | - | - | 0.93 |
| 34.41 | -5.88 | 1255 | - | - | 0.95 |
| 26.31 | -5.29 | 1366 | - | - | 0.97 |
| 21.38 | -6.41 | 1477 | - | - | 0.98 |
| -12.35 | -6.43 | - | 516.6 | 1144-1255 | 0.93 |
| -18.16 | -5.04 | - | 497.5 | 1144-1366 | 0.78 |
| -21.96 | -3.48 | - | 452.7 | 1144-1477 | 0.35 |
| STEADY STATE CREEP RATE | | | | | |
| -51.41 | 5.91 | 1144 | - | - | 0.93 |
| -46.33 | 5.74 | 1255 | - | - | 0.93 |
| -37.97 | 5.03 | 1366 | - | - | 0.94 |
| -3.58 | 5.83 | - | -450.5 | 1144-1255 | 0.93 |
| 1.30 | 4.38 | - | -421.7 | 1144-1366 | 0.76 |

TABLE X. - REGRESSION ANALYSIS OF MAR-M509

| CONSTANT | STRESS EXPONENT | TEMPERATURE, K | ACTIVATION ENERGY, kJ/g-mol-K | TEMPERATURE RANGE, K | REGRESSION COEFFICIENT, R**2 |
|-------------------------|-----------------|-------------------|-------------------------------------|----------------------------|------------------------------------|
| TIME TO RUPTURE | | | | | |
| 54.00 | -9.80 | 1144 | - | - | 0.75 |
| 47.39 | -9.65 | 1255 | - | - | 0.99 |
| 26.28 | -5.80 | 1366 | - | - | 0.97 |
| -12.51 | -4.69 | - | 627.1 | 1144-1255 | 0.92 |
| -15.80 | -7.37 | - | 546.7 | 1144-1366 | 0.87 |
| STEADY STATE CREEP RATE | | | | | |
| -72.16 | 11.28 | 1144 | - | - | 0.97 |
| -45.62 | 8.61 | 1255 | - | - | 0.77 |
| -34.86 | 4.80 | 1366 | - | - | 0.81 |
| -0.68 | 7.59 | - | -510.6 | 1144-1255 | 0.80 |
| 1.35 | 6.17 | - | -457.4 | 1144-1366 | 0.74 |

TABLE XI - REGRESSION ANALYSIS OF TIME TO RUPTURE FOR MA-757 TESTED
IN THE LONGITUDINAL DIRECTION

| CONSTANT | STRESS EXPONENT | TEMPERATURE, K | ACTIVATION ENERGY, kJ/mol-K | TEMPERATURE RANGE, K | REGRESSION COEFFICIENT, R**2 |
|---------------|-----------------|-------------------|-----------------------------------|----------------------------|------------------------------------|
| UNEDITED DATA | | | | | |
| 68.59 | -13.08 | 1144 | - | - | 0.97 |
| 52.48 | -10.81 | 1255 | - | - | 0.87 |
| 28.19 | - 6.08 | 1366 | - | - | 0.83 |
| 29.75 | - 7.42 | 1477 | - | - | 0.61 |
| 0.83 | -11.65 | - | 578.1 | 1144-1255 | 0.91 |
| - 4.99 | - 7.81 | - | 456.5 | 1144-1366 | 0.80 |
| - 8.76 | - 7.42 | - | 477.0 | 1144-1477 | 0.73 |
| EDITED DATA * | | | | | |
| 68.57 | -13.08 | 1144 | - | - | 0.97 |
| 52.48 | -10.81 | 1255 | - | - | 0.87 |
| 28.19 | - 6.08 | 1366 | - | - | 0.83 |
| 32.07 | - 7.95 | 1477 | - | - | 0.74 |
| 0.83 | -11.65 | - | 578.1 | 1144-1255 | 0.91 |
| - 4.99 | - 7.81 | - | 456.5 | 1144-1366 | 0.80 |
| - 7.24 | - 7.74 | - | 476.2 | 1144-1477 | 0.79 |

* FOLLOWING DATA DELETED FROM ANALYSIS

| TEMPERATURE, K | STRESS, MEGAPASCALS | LIFE, HOURS |
|-------------------|------------------------|----------------|
| 1477 | 27.6 | 183.3 |
| 1477 | 31.0 | 39.7 |
| 1477 | 37.9 | 1.4 |

TABLE XII. - REGRESSION ANALYSIS OF STEADY STATE CREEP RATE DATA FOR MA-757

TESTED IN THE LONGITUDINAL DIRECTION

| CONSTANT | STRESS EXPONENT | TEMPERATURE, K | ACTIVATION ENERGY, kJ/g-mol-K | TEMPERATURE RANGE, K | REGRESSION COEFFICIENT, R**2 |
|----------|-----------------|-------------------|-------------------------------------|----------------------------|------------------------------------|
|----------|-----------------|-------------------|-------------------------------------|----------------------------|------------------------------------|

UNEDITED DATA

| | | | | | |
|--------|------|------|---|---|------|
| -52.26 | 6.94 | 1144 | - | - | 0.66 |
| -41.49 | 5.35 | 1255 | - | - | 0.32 |
| -47.73 | 7.55 | 1366 | - | - | 0.62 |
| -39.64 | 6.05 | 1477 | - | - | 0.44 |

EDITED DATA *

| | | | | | |
|--------|-------|------|--------|-----------|------|
| -64.52 | 9.63 | 1144 | - | - | 0.93 |
| -97.68 | 18.34 | 1255 | - | - | 0.81 |
| -83.72 | 16.74 | 1366 | - | - | 0.90 |
| -36.02 | 4.83 | 1477 | - | - | 0.84 |
| -11.70 | 11.80 | - | -599.1 | 1144-1255 | 0.93 |
| -11.65 | 13.66 | - | -682.8 | 1144-1366 | 0.84 |
| -10.36 | 9.41 | - | -505.8 | 1144-1477 | 0.72 |

* FOLLOWING DATA DELETED FROM ANALYSIS

| TEMPERATURE, K | STRESS, MEGAPASCALS | STEADY STATE CREEP RATE, S**-1 |
|-------------------|------------------------|--------------------------------------|
| 1144 | 124.1 | 3.86E-09 |
| 1144 | 131.0 | 3.14E-09 |
| 1255 | 48.3 | 1.87E-09 |
| 1255 | 55.2 | 1.81E-09 |
| 1255 | 62.1 | 5.50E-09 |
| 1255 | 82.7 | 3.06E-10 |
| 1366 | 27.6 | 9.06E-10 |
| 1366 | 34.5 | 9.66E-10 |
| 1366 | 37.9 | 1.15E-09 |
| 1477 | 31.0 | 1.03E-07 |

TABLE XIII. - REGRESSION ANALYSIS OF TIME TO RUPTURE DATA FOR MA-757 TESTED
IN THE LONG TRANSVERSE DIRECTION

| CONSTANT | STRESS EXPONENT | TEMPERATURE, K | ACTIVATION ENERGY, kJ/mol-K | TEMPERATURE RANGE, K | REGRESSION COEFFICIENT, R**2 |
|---------------|-----------------|-------------------|-----------------------------------|----------------------------|------------------------------------|
| UNEDITED DATA | | | | | |
| 37.21 | -7.33 | 1144 | - | - | 0.99 |
| 37.89 | -8.90 | 1255 | - | - | 0.80 |
| 21.92 | -5.62 | 1366 | - | - | 0.94 |
| 9.59 | -2.31 | 1477 | - | - | 0.98 |
| -22.10 | -8.03 | - | 593.3 | 1144-1255 | 0.33 |
| -19.34 | -6.43 | - | 500.3 | 1144-1366 | 0.89 |
| -15.16 | -3.80 | - | 350.0 | 1144-1477 | 0.70 |
| EDITED DATA * | | | | | |
| 37.21 | -7.38 | 1144 | - | - | 0.99 |
| 28.43 | -6.38 | 1255 | - | - | 0.96 |
| 21.92 | -5.62 | 1366 | - | - | 0.94 |
| 9.59 | -2.31 | 1477 | - | - | 0.99 |
| -18.67 | -7.06 | - | 513.2 | 1144-1255 | 0.93 |
| -18.34 | -6.06 | - | 473.9 | 1144-1366 | 0.95 |
| -14.46 | -3.56 | - | 334.6 | 1144-1477 | 0.77 |

* FOLLOWING DATA DELETED FROM ANALYSIS

| TEMPERATURE, K | STRESS, MEGAPASCALS | LIFE, HOURS |
|-------------------|------------------------|----------------|
| 1255 | 48.2 | 123.0 |
| 1255 | 62.0 | 0.8 |

TABLE XIV. - REGRESSION ANALYSIS OF STEADY STATE CREEP RATE FOR MA-757

TESTED IN THE LONG TRANSVERSE DIRECTION

| CONSTANT | STRESS EXPONENT | TEMPERATURE, K | ACTIVATION ENERGY, kJ/g-mol-K | TEMPERATURE RANGE, K | REGRESSION COEFFICIENT, R**2 |
|---------------|-----------------|-------------------|-------------------------------------|----------------------------|------------------------------------|
| UNEDITED DATA | | | | | |
| -34.02 | 3.43 | 1144 | - | - | 0.93 |
| -37.10 | 5.02 | 1255 | - | - | 0.92 |
| -28.42 | 3.48 | 1366 | - | - | 0.96 |
| -24.28 | 2.61 | 1477 | - | - | 0.60 |
| - 3.61 | 4.23 | - | -320.1 | 1144-1255 | 0.92 |
| 1.24 | 3.49 | - | -339.7 | 1144-1366 | 0.89 |
| 0.66 | 3.10 | - | -318.9 | 1144-1477 | 0.80 |
| EDITED DATA * | | | | | |
| -34.02 | 3.43 | 1144 | - | - | 0.98 |
| -37.10 | 5.02 | 1255 | - | - | 0.92 |
| -28.42 | 3.48 | 1366 | - | - | 0.96 |
| -27.72 | 4.23 | 1477 | - | - | 0.99 |
| - 3.61 | 4.23 | - | -320.1 | 1144-1255 | 0.92 |
| 1.24 | 3.49 | - | -339.7 | 1144-1366 | 0.89 |
| 2.37 | 3.58 | - | -354.4 | 1144-1477 | 0.90 |

* FOLLOWING DATA DELETED FROM ANALYSIS

| TEMPERATURE, K | STRESS, MEGAPASCALS | STEADY STATE CREEP RATE, S**-1 |
|-------------------|------------------------|--------------------------------------|
| 1477 | 3.5 | 2.90E-09 |
| 1477 | 6.9 | 1.09E-09 |

TABLE XV. - REGRESSION ANALYSIS OF TIME TO RUPTURE DATA FOR MA-956 TESTED
IN THE LONGITUDINAL DIRECTION

| CONSTANT | STRESS EXPONENT | TEMPERATURE, K | ACTIVATION ENERGY, kJ/g-mol-K | TEMPERATURE RANGE, K | REGRESSION COEFFICIENT, R**2 |
|----------------|-----------------|-------------------|-------------------------------------|----------------------------|------------------------------------|
| UNEDITED DATA | | | | | |
| 90.27 | -17.11 | 1144 * | - | - | 0.37 |
| 52.56 | -11.62 | 1255 | - | - | 0.01 |
| 126.91 | -29.35 | 1366 | - | - | 0.26 |
| 102.24 | -24.19 | 1477 | - | - | 0.23 |
| EDITED DATA ** | | | | | |
| 115.73 | -25.25 | 1144 | - | - | 0.90 |
| 212.31 | -47.76 | 1255 | - | - | 0.83 |
| 280.08 | -64.71 | 1366 | - | - | 0.73 |
| 271.29 | -64.54 | 1477 | - | - | 0.81 |
| 102.81 | -29.49 | - | 303.4 | 1144-1255 | 0.80 |
| 104.85 | -32.95 | - | 434.2 | 1144-1366 | 0.70 |
| 101.23 | -33.03 | - | 473.7 | 1144-1477 | 0.68 |

* 86.2 MPA - 2061.5 H (UNFAILED) INCLUDED;
68.9 MPA - 1005.4 H (UNFAILED) NOT INCLUDED.

** FOLLOWING DATA DELETED FROM OR ADDED TO ANALYSIS

TEMPERATURE, STRESS, LIFE,
K MEGAPASCALS HOURS

DELETED DATA

| | | |
|------|------|-------------------|
| 1144 | 68.9 | 1005.4 (UNFAILED) |
| 1144 | 86.2 | 2061.5 (UNFAILED) |
| 1255 | 77.6 | 0.01 |
| 1255 | 77.6 | 0.5 |
| 1255 | 79.3 | 3.4 |
| 1255 | 81.0 | 0.7 |
| 1366 | 65.4 | 1.3 |
| 1477 | 58.1 | 28.8 |
| 1477 | 62.1 | 1.5 |
| 1477 | 63.8 | 2.1 |

ADDITIONAL DATA

| | | |
|------|-------|-------------------|
| 1144 | 106.9 | 0.1 |
| 1144 | 102.0 | 0.1 |
| 1255 | 87.6 | 0.1 |
| 1255 | 91.0 | 0.1 |
| 1366 | 77.2 | 0.1 |
| 1366 | 81.4 | 0.1 |
| 1366 | 68.9 | 1005.4 (UNFAILED) |
| 1477 | 69.6 | 0.1 |
| 1477 | 68.9 | 0.1 |

TABLE XVI. - REGRESSION ANALYSIS OF STEADY STATE CREEP RATE OF MA-956 TESTED
IN THE LONGITUDINAL DIRECTION

| CONSTANT | STRESS EXPONENT | TEMPERATURE, K | ACTIVATION ENERGY, kJ/g-mol-K | TEMPERATURE RANGE, K | REGRESSION COEFFICIENT, R**2 |
|---------------|-----------------|-------------------|-------------------------------------|----------------------------|------------------------------------|
| UNEDITED DATA | | | | | |
| -182.57 | 36.72 | 1144 | - | - | 0.72 |
| -213.29 | 44.55 | 1255 | - | - | 0.76 |
| -405.74 | 90.00 | 1366 | - | - | 0.43 |
| -126.20 | 26.24 | 1477 | - | - | 0.23 |
| -154.97 | 39.66 | - | -386.5 | 1144-1255 | 0.74 |
| EDITED DATA * | | | | | |
| -225.98 | 46.45 | 1144 | - | - | 0.80 |
| -213.29 | 44.55 | 1255 | - | - | 0.76 |
| -355.91 | 78.89 | 1366 | - | - | 0.58 |
| -184.42 | 40.52 | 1477 | - | - | 0.66 |
| -173.09 | 45.52 | - | -463.9 | 1144-1255 | 0.78 |
| -204.45 | 57.16 | - | -660.0 | 1144-1366 | 0.68 |
| -130.46 | 38.92 | - | -597.9 | 1144-1477 | 0.58 |

* FOLLOWING DATA DELETED FROM OR ADDED TO ANALYSIS

| TEMPERATURE, K | STRESS, MEGAPASCALS | STEADY STATE CREEP RATE, S**-1 |
|-------------------|------------------------|--------------------------------------|
|-------------------|------------------------|--------------------------------------|

DELETED DATA

| | | |
|------|------|----------|
| 1144 | 75.8 | 3.02E-10 |
| 1366 | 74.1 | 1.00E-11 |
| 1477 | 62.1 | 1.10E-06 |
| 1477 | 63.8 | 4.53E-10 |
| 1477 | 65.5 | 8.33E-09 |
| 1477 | 65.5 | 2.02E-08 |

ADDED DATA

| | | |
|------|------|----------|
| 1366 | 77.1 | 3.33E-06 |
| 1366 | 76.9 | 3.33E-06 |
| 1366 | 77.8 | 8.33E-07 |
| 1366 | 73.3 | 8.33E-08 |
| 1366 | 70.7 | 8.33E-08 |

TABLE XVII. - REGRESSION ANALYSIS OF STEADY STATE CREEP RATE OF STCA ALLOYS
 TESTED IN THE LONGITUDINAL DIRECTION AT 1366 K

| HEAT | CONSTANT | STRESS EXPONENT | REGRESSION COEFFICIENT, R**2 |
|--------|----------|-----------------|------------------------------------|
| 262/4S | -160.62 | 33.16 | 0.96 |
| 265S | -150.87 | 30.93 | 0.78 |
| 265SC | -130.76 | 26.36 | 0.87 |
| 266S | -100.42 | 19.73 | 0.75 |
| 265S | | | |
| 265SC | -135.65 | 27.45 | 0.81 |
| 262/4S | | | |
| 265S | -155.18 | 31.91 | 0.86 |

TABLE XVIII. - REGRESSION ANALYSIS OF STEADY STATE CREEP RATE OF STCA ALLOYS
TESTED IN THE LONG TRANSVERSE DIRECTION AT 1366 K

| HEAT | CONSTANT | STRESS EXPONENT | REGRESSION COEFFICIENT, R**2 |
|---------------|----------|-----------------|------------------------------------|
| UNEDITED DATA | | | |
| 262/4S | -45.58 | 7.87 | 0.90 |
| 265S | -31.85 | 4.34 | 0.60 |
| 265SC | -32.66 | 4.27 | 0.75 |
| 266S | -37.93 | 5.68 | 0.89 |
| 266SC | -37.05 | 5.84 | 0.80 |
| EDITED DATA * | | | |
| 262/4S | -45.58 | 7.87 | 0.90 |
| 265S | -30.77 | 3.96 | 0.95 |
| 265SC | -33.82 | 4.75 | 0.93 |
| 266S | -37.93 | 5.68 | 0.89 |
| 266SC | -33.12 | 4.79 | 0.79 |
| 265S | | | |
| 265SC | -32.72 | 4.47 | 0.90 |
| 262/4S | | | |
| 266S | -40.79 | 6.50 | 0.86 |
| 265S | | | |
| 266SC | -31.98 | 4.39 | 0.96 |

* FOLLOWING DATA DELETED FROM ANALYSIS

| HEAT | STRESS, MEGAPASCALS | STEADY STATE CREEP RATE, S**-1 |
|-------|------------------------|--------------------------------------|
| 265S | 27.6 | 6.28E-09 |
| 265S | 29.3 | 3.20E-07 |
| 265SC | 22.4 | 1.54E-09 |
| 265SC | 27.6 | 2.90E-09 |
| 265SC | 31.0 | 8.45E-09 |
| 266SC | 17.2 | 4.83E-10 |
| 266SC | 20.7 | 1.14E-09 |
| 266SC | 24.1 | 3.20E-09 |

TABLE XIX. - REGRESSION ANALYSIS OF STEADY STATE CREEP RATE OF YD-NiCrAl
 TESTED IN THE LONGITUDINAL DIRECTION AT 1366 K

| HEAT | CONSTANT | STRESS EXPONENT | REGRESSION COEFFICIENT, R^{**2} |
|------|----------|-----------------|---|
| - | -54.76 | 9.12 | 0.75 |

| | | | |
|---|---|--|---|
| 1. Report No. NASA TP-1781 | 2. Government Accession No. | 3. Recipient's Catalog No. | |
| 4. Title and Subtitle CREEP AND RESIDUAL MECHANICAL PROPERTIES OF CAST SUPERALLOYS AND OXIDE DISPERSION STRENGTHENED ALLOYS | | 5. Report Date February 1981 | 6. Performing Organization Code 506-56-12 |
| | | 7. Author(s) J. Daniel Whittenberger | 8. Performing Organization Report No. E-472 |
| 9. Performing Organization Name and Address National Aeronautics and Space Administration Lewis Research Center Cleveland, Ohio 44135 | | 10. Work Unit No. | |
| | | 11. Contract or Grant No. | |
| 12. Sponsoring Agency Name and Address National Aeronautics and Space Administration Washington, D. C. 20546 | | 13. Type of Report and Period Covered Technical Paper | |
| | | 14. Sponsoring Agency Code | |
| 15. Supplementary Notes | | | |
| 16. Abstract <p>Tensile, stress-rupture, creep, and residual tensile properties after creep testing were determined for two typical cast superalloys and four advanced oxide dispersion strengthened (ODS) alloys. The superalloys examined included the nickel-base alloy B-1900 and the cobalt-base alloy MAR-M509. The nickel-base ODS alloy MA-757 (Ni-16Cr-4Al-0.6Y₂O₃) and the iron-base ODS alloy MA-956 (Fe-20Cr-5Al-0.8Y₂O₃) were extensively studied, while limited testing was conducted on the ODS nickel-base alloys STCA (Ni-16Cr-4.5Al-2Y₂O₃) with and without Ta and YD-NiCrAl (Ni-16Cr-5Al-2Y₂O₃). Elevated temperature testing was conducted from 1144 to 1477 K except for STCA and YD-NiCrAl alloys, which were only tested at 1366 K. The residual tensile properties of B-1900 and MAR-M509 are not reduced by prior creep testing (strains at least up to 1 percent), while the room temperature tensile properties of ODS nickel-base alloys can be reduced by small amounts of prior creep strain (less than 0.5 percent). The iron-base ODS alloy MA-956 does not appear to be susceptible to creep degradation at least up to strains of about 0.25 percent. However, MA-956 exhibits unusual creep behavior which apparently involves crack nucleation and growth.</p> | | | |
| 17. Key Words (Suggested by Author(s)) High temperature mechanical properties; Oxide dispersion strength (ODS) alloys; ODS alloys; Nickel-base alloy; Iron-base alloy | | 18. Distribution Statement Unclassified - unlimited STAR Category 26 | |
| 19. Security Classif. (of this report) Unclassified | 20. Security Classif. (of this page) Unclassified | 21. No. of Pages 67 | 22. Price* A04 |

* For sale by the National Technical Information Service, Springfield, Virginia 22161

National Aeronautics and
Space Administration

Washington, D.C.
20546

Official Business

Penalty for Private Use, \$300

THIRD-CLASS BULK RATE

Postage and Fees Paid
National Aeronautics and
Space Administration
NASA-451



15 1 1U,C, 022381 S00903DS
DEPT OF THE AIR FORCE
AF WEAPONS LABORATORY
ATTN: TECHNICAL LIBRARY (SUL)
KIRTLAND AFB NM 87117



NASA

POSTMASTER:

If Undeliverable (Section 158
Postal Manual) Do Not Return