

## General Disclaimer

### One or more of the Following Statements may affect this Document

- This document has been reproduced from the best copy furnished by the organizational source. It is being released in the interest of making available as much information as possible.
- This document may contain data, which exceeds the sheet parameters. It was furnished in this condition by the organizational source and is the best copy available.
- This document may contain tone-on-tone or color graphs, charts and/or pictures, which have been reproduced in black and white.
- This document is paginated as submitted by the original source.
- Portions of this document are not fully legible due to the historical nature of some of the material. However, it is the best reproduction available from the original submission.

**NASA TECHNICAL  
MEMORANDUM**

**NASA TM X- 73,126**

**NASA TM X- 73,126**

**A COMPOSITE SYSTEM APPROACH TO AIRCRAFT CABIN FIRE SAFETY**

**Demetrius A. Kourtides, John A. Parker,  
William J. Gilwee, Jr., and Narcinda R. Lerner  
Ames Research Center  
Moffett Field, CA 94035**

**Carlos J. Hilado and Lisa A. LaBossiere  
Fire Safety Center, Institute of Chemical Biology  
University of San Francisco  
San Francisco, CA 94117**

**Ming-ta Hsu  
Department of Chemistry  
San Jose State University  
San Jose, CA 95192**

(NASA-TM-X-73126) A COMPOSITE SYSTEM  
APPROACH TO AIRCRAFT CABIN FIRE SAFETY  
(NASA) 46 P HC 54.00 CSCL 11D

NT6-25354

UNCLAS

G3/24 42223

**April 1976**



1. Report No. NASA TM X-73,126	2. Government Accession No.	3. Recipient's Catalog No.	
4. Title and Subtitle A COMPOSITE SYSTEM APPROACH TO AIRCRAFT CABIN FIRE SAFETY		5. Report Date	
		6. Performing Organization Code	
7. Author(s) Demetrius A. Kourtides,* John A. Parker,* William J. Gilwee, Jr.,* Narcinda R. Lerner,* Carlos J. Hilado,+ Lisa A. LaBossiere,+ and Ming-ta S. Hsu ++		8. Performing Organization Report No. A-6555	
		10. Work Unit No. 510-56-01	
9. Performing Organization Name and Address *Ames Research Center, Moffett Field, CA 94035 +Fire Safety Center, Institute of Chemical Biology, University of San Francisco, San Francisco, CA 94117 ++Dept. of Chemistry, San Jose State University, San Jose, CA 95192		11. Contract or Grant No.	
		13. Type of Report and Period Covered Technical Memorandum	
12. Sponsoring Agency Name and Address National Aeronautics and Space Administration Washington, D. C. 20546		14. Sponsoring Agency Code	
		15. Supplementary Notes	
16. Abstract  The thermochemical and flammability characteristics of two polymeric composites currently in use and seven others being considered for use as aircraft interior panels are described. The properties studied included: (1) limiting oxygen index of the composite constituents; (2) fire containment capability of the composite; (3) smoke evolution from the composite; (4) thermo-gravimetric analysis; (5) composition of the volatile products of thermal degradation; and (6) relative toxicity of the volatile products of pyrolysis. The performance of high-temperature laminating resins such as bismaleimides is compared with the performance of phenolics and epoxies. The relationship of increased fire safety with the use of polymers with high anaerobic char yield is shown. Processing parameters of one of the bismaleimide composites is detailed.			
17. Key Words (Suggested by Author(s)) Fire protection Aircraft interior materials Flammability Composites		18. Distribution Statement  Unlimited  STAR Category - 24	
19. Security Classif. (of this report) Unclassified	20. Security Classif. (of this page) Unclassified	21. No. of Pages 43	22. Price* \$3.75

## A COMPOSITE SYSTEM APPROACH TO AIRCRAFT CABIN FIRE SAFETY

**ABSTRACT:** The thermochemical and flammability characteristics of two polymeric composites currently in use and seven others being considered for use as aircraft interior panels are described. The properties studied included: (1) limiting oxygen index of the composite constituents; (2) fire containment capability of the composite; (3) smoke evolution from the composite; (4) thermogravimetric analysis; (5) composition of the volatile products of thermal degradation; and (6) relative toxicity of the volatile products of pyrolysis. The performance of high-temperature laminating resins such as bismaleimides is compared with the performance of phenolics and epoxies. The relationship of increased fire safety with the use of polymers with high anaerobic char yield is shown. Processing parameters of one of the bismaleimide composites is detailed.

### INTRODUCTION

The purpose of this program was to assess the relative flammability and thermochemical properties of some typical state-of-the-art and candidate experimental aircraft interior composite panels, and to develop an understanding of the relationship of flammability and thermochemical properties of these systems.

Composite sandwich panels constitute most of the surface of aircraft interiors as sidewalls, partitions, ceiling panels, and overhead stowage bins. Currently used composites meet or exceed regulatory requirements [1] and offer excellent aesthetic, serviceability, maintenance, and other properties. However, additional improvements are being sought to reduce ignition susceptibility, fuel contribution, smoke and toxic fume emission, and to increase fire containment capability [2-8]. Experimental composite panels that could offer improved fire resistance and smoke reduction in aircraft fires are now being



developed and tested. In this program, nine different types of experimental composite panels were evaluated in terms of their flammability properties. Two of these were typical state-of-the-art interior panels and seven were experimental. The composite panels used by most airframe manufacturers as interior paneling are sandwich panels that vary slightly in configuration, component composition, thickness, and density depending on the type of aircraft in which they are used and the specific application. In general, the panel consists of polyvinyl fluoride decorative finish bonded to a fiberglass-resin laminate which is bonded to an aromatic polyamide honeycomb core as shown in Figure 1.

## DISCUSSION

### Description of Composites

Nine types of composite panels were evaluated. Three types of resin systems were used for the fabrication of the laminates used in these composites: epoxy, bismaleimide, and various modifications of phenolic resins. The general chemical structure of these resins is shown in Figure 2; the composition of the composites is shown in Tables 1-3. All composites fabricated were 2.54 cm thick. Composite No. 1-6 had a decorative surface of a polyvinyl fluoride film printed with an acrylic ink and bonded to a laminate. The laminates consisted of various types of fiberglass preimpregnated with various types of phenolic resins. The laminates were adhered to the hexagonal-cell aromatic polyamide honeycomb structure using various types of phenolic resin-fiberglass adhesive ply. Composite No. 1 was considered a typical state-of-the-art phenolic resin panel. Resins used in the preparation of the laminates for composites No. 1-6 were obtained commercially and are designated as phenolic types A through G. The exact formulation for these resins was not available

from the suppliers. The decorative laminates of composites No. 1-6 were press-bonded to the honeycomb using an adhesive bond ply at 160° C for 12 min at 689.6 kN/m<sup>2</sup> pressure. The sandwich panel was then cured at 123° C for 1 h with 50 mm Hg minimum vacuum bag pressure. Composite No. 7 was composed of a laminate of bismaleimide-fiberglass adhered to the aromatic polyamide honeycomb. The processing and composition of this type of composite was similar to those of the advanced composite panel described previously [9] except that a foam produced by heating quinone dioxime was used as the core filler material [10]. Composite No. 8 is a typical state-of-the-art composite panel consisting of polyvinyl fluoride film bonded to a laminate of epoxy-fiberglass. The laminate is adhered to the aromatic polyamide honeycomb using an epoxy-fiberglass ply. Process description and composition of this composite has been described in detail previously [9,11,12]. Composite No. 9 was similar to composite No. 7 except that a bismaleimide-fiberglass honeycomb is used that is partially filled with a mixture of carbon microballoon and bismaleimide resin.

#### Processing and Fabrication, Composite No. 9

The fabrication process for composite No. 9 is shown schematically in Figure 3. Processing a typical 30 cm × 30 cm × 2.5 cm composite panel of this type is done as follows.

**FACE SHEET FABRICATION PROCESS.**— The face sheet fabrication essentially consists of resin preimpregnation of the fiberglass (MIL-C-9084C Type IIX) cloth, and the forming and cure of the prepreg into the required face sheets.

A 50% solution is prepared by sifting bismaleimide resin powder into N-methyl-2-pyrrolidone solvent under vigorous agitation, avoiding resin caking on the container walls or lump formation; a high-speed agitator is used. The initial viscosity of a 50% by weight solution is less than 10 P at room

temperature, but the viscosity rapidly increases with aging. Solutions are prepared immediately prior to use. Under controlled storage conditions, a maximum use-life of 20 days is projected for the prepared resin solution.

The process used to impregnate the resin into the fiberglass consists of passing the dried cloth through the 50% solution of bismaleimide resin. Further resin impregnation and removal of excess resin is accomplished by passing the resin wet cloth between a steel roller and a wiper blade.

To achieve uniform impregnation, the glass fabric is pulled through the impregnator at a constant speed of 0.6 m/min with a constant wiper blade pressure exerted on the impregnated cloth. The prepregged cloth is then B-staged in an air-circulation oven for 15 min at 82° C and for 30 min at 93° C. The prepreg thus processed has average resin content and volatile content of 41.3% and 5.2%, respectively.

The prepreg face sheets are cured using either the autoclave vacuum bag technique or platen pressure method. In the autoclave vacuum bag technique, a 33 cm × 33 cm prepreg single layer cloth sandwiched between porous teflon-coated glass fabric is placed on a 0.6-cm-thick aluminum plate. On top of this, a glass bleeder cloth is placed against the sandwiched prepreg. This assembly is vacuum bagged and cured at an external pressure of 345 kN/m<sup>2</sup> and a temperature of 177° C for 1 h. In the press cure method, the 35 cm × 35 cm prepreg material is sandwiched between porous teflon-coated fabric and cured between 0.6-cm-thick aluminum plates treated with a mold release. The prepreg is cured at 345 kN/m<sup>2</sup> for 1 h at 177° C. After cure, the face sheets are visually checked for flaws, voids, thickness uniformity, and resin content. Thickness of the face sheets fabricated averaged 0.025 cm and the sheets contained 30% to 34% resin.

**CORE FABRICATION PROCESS.**— The core consists of a bismaleimide-fiberglass honeycomb filled with carbon microballoons bound with bismaleimide resin. The carbon microballoons are prepared by pyrolyzing phenolic microballoons in a nitrogen atmosphere. A stainless steel container is filled with phenolic microballoons and enclosed in a larger stainless steel container with a nitrogen inlet to provide an oxygen-free atmosphere. The assembly is placed in a larger furnace. The pyrolysis cycle is as follows: room temperature to 816° C in 4 h; hold at 816° C for 4 h; and cool to room temperature in 2 days. Pyrolyzed carbon microballoons must be cooled to 38° C, before removal of the nitrogen blanket, to prevent spontaneous ignition of the carbon microballoons. After pyrolysis the carbon microballoons are no longer free-flowing and are agglomerated as large cakes. To break them into smaller agglomerates, the caked microballoons are placed in a container with isopropanol (ratio of 1 kg balloons/7 liters solvent) and mixed in a paint shaker for 15 min. The slurry is then screened through a 20-mesh screen to remove the larger non-separated agglomerates. The screened isopropanol/carbon microballoon slurry is now ready for core impregnation.

The equipment illustrated in Figure 4 is used to fill the cores of the fiberglass-bismaleimide honeycomb with the prepared carbon microballoons. A high density 0.3-cm cell aluminum honeycomb is fitted and restrained on the bottom inside of the vacuum filling box. A nylon screen (120 mesh) is placed between the aluminum support honeycomb and the fiberglass reinforced polyimide honeycomb to retain the microballoons. High vacuum is not required to effectively impregnate the honeycomb, but a high volume of air displacement is required. A vacuum reservoir chamber is pumped to a vacuum of approximately 10 mm Hg.

To make honeycomb that is completely filled with the microballoons, the carbon microballoon/isopropanol slurry is poured over the honeycomb. To control the fill rate, the vacuum applied is regulated by the valve between the box and solvent recovery trap. The negative pressure causes the microballoons to be pulled into the cells. This process is repeated several times to fill all cells. Excess slurry is then removed with a teflon blade.

To make honeycomb that is partially filled with a particular quantity of microballoons, the following method is used: Prior to placing the fine mesh screen and the fiberglass-bismaleimide honeycomb into the vacuum filling box, the vacuum control valve to the box is closed. The vacuum filling box is filled with isopropanol to the top edge of the aluminum support honeycomb. After placement of the fine mesh screen and the fiberglass bismaleimide honeycomb, the isopropanol-microballoon slurry with the desired microballoon weight content is poured over the honeycomb. Sufficient isopropanol is used to achieve good flow and complete coverage of the honeycomb. The vacuum control valve is then opened to draw the microballoons into the cells, and the solvent is removed and contained in the solvent recovery trap. The filled honeycomb cores, sandwiched between two nylon, fine-mesh screens and between two aluminum support honeycombs, are dried for 16 h in an air-circulating oven at 93° C. After drying, the microballoon fill is saturated with a 2% solution of bismaleimide resin in N-methyl-2-pyrrolidone solvent. On cores that are partially filled with the microballoons, the 2% solution is sprayed into the cores at low air and material pressure. On cores that are completely filled with microballoons, the spray process will tend to blow out the microballoons; therefore, the 2% solution is applied by brush. Care must be exercised to uniformly maintain the filled microballoons within the cells. After saturation

of the microballoons with the 2% bismaleimide resin solution, the honeycomb is heated for 2 h at 93° C and for 1 h at 204° C to completely cure the bismaleimide binder. Prior to final assembly, the combined weight of the microballoons, bismaleimide resin binder is checked. For the microballoon resin combination, the resin by weight is approximately 4-10%. For a half-filled 2.4-cm-thick core, the fill weight should be approximately 145 g/1000 cm<sup>2</sup>.

**SANDWICH STRUCTURE PANEL ASSEMBLY.**— The assembly process consists of forming the aircraft interior panel by bonding the face sheets to the microballoon filled fiberglass bismaleimide honeycomb panel with a polyimide film adhesive.

Prior to the bonding operation, the face sheets and the microballoon-filled honeycomb are cleaned. To achieve the required fileting of the film adhesive to the core, loose microspheres must be removed from the bonding faces and the faces cleaned with a methyl-ethyl-ketone-soaked cleaning cloth. The assembly is then placed in a platen press at 204° C and cured for 2 h at 700 kN/m<sup>2</sup>. Afterward, the panel is cured for 24 h at 254° C to remove volatile materials and to achieve reduced smoke characteristics.

On completion of the assembly, the panel is weighed and examined for uniformity of bonding.

## TEST RESULTS AND ANALYSIS

### Thermochemical Characterization of Composites

Samples of the nine types of composites were cut to a size of 2.5 cm × 2.5 cm × 2.5 cm and were ground uniform to approximately 250 mesh. The samples were subjected to the following thermochemical studies in order to (1) determine the relative thermal stability of the samples under anaerobic and oxidative conditions, (2) determine the major volatile products produced

from the pyrolysis of the samples in vacuum, and (3) determine the relative toxicity of the pyrolysis effluents by exposing animals to them.

#### Thermogravimetric Studies

Thermal analyses of the composites were conducted on a DuPont 950 Thermogravimetric Analyzer (TGA) using both nitrogen and air atmospheres with a sample size of 10 mg. The thermogravimetric analyses data of 10° C/min heating rate in nitrogen and in air are shown in Figures 5 and 6, respectively.

The pyrolysis of the samples in air and nitrogen atmospheres was conducted to obtain a relative understanding of the pyrolysis of the samples in the furnace used to pyrolyze samples for assessing their relative toxicity as described later in the text. Pyrolysis in an air atmosphere is intended to approximate the environment in the pyrolysis tube at the start of the toxicity test, and pyrolysis in a nitrogen atmosphere is intended to approximate the environment in the pyrolysis tube during the test after the original air has been essentially displaced by pyrolysis effluent. The degradation products are continuously removed from the sample during thermogravimetric analysis, and in the relative toxicity test apparatus described later they are conveyed only by normal thermal flow. The TGA data in the nitrogen atmosphere are considered more relevant, because in the toxicity apparatus the pyrolysis effluents that evolved at lower temperature have essentially displaced the original air by the time the temperature has reached 700° C.

Composite No. 9 is the most stable composite and gives the highest char yield in nitrogen. All the composites except No. 7 were oxidized completely in air above 600° C and gave constant weight residues.

## Analysis of Volatile Products

Samples of the composites were pyrolyzed using the apparatus shown in Figure 7. The samples were placed in quartz tubes that were 2.5 mm in diameter. Each sample tube was attached to a manifold and evacuated to  $10^{-4}$  torr. There was a stopcock between the manifold and the sample tube so that the sample tube could be isolated while gas samples were being collected. An infrared cell, attached to the manifold via a stopcock, a mercury manometer, and a trap were also attached to the manifold. At the beginning of a pyrolysis run the stopcock to the vacuum pump was closed and a furnace at  $700^{\circ}$  C was placed around the sample tube. At this point a timer was started. The pressure of the gases evolved during the pyrolysis was monitored with the pressure gauge. After 5 min the furnace was removed, the stopcock to the sample tube was closed, and the stopcock leading to the infrared cell was opened allowing the pyrolysis gases to enter the infrared cell. After a pressure reading was taken, the stopcock leading from the infrared cell to the gas manifold was closed. Dry air was admitted to the infrared cell so that the total pressure was equal to atmospheric pressure. This was done so that the pyrolysis gases were always measured at the same total pressure, the main portion of which was dry air, thus eliminating the effects of pressure broadening. Infrared spectra were taken using a Perkin Elmer Model 180 infrared spectrometer. Finally, the sample tube was removed from the manifold, broken open, and the residual char was weighed.

Part of the material that was volatile at  $700^{\circ}$  C condensed on the sample tube as it was removed from the furnace; salt plates were made from methanol solutions of this material. Infrared spectra, obtained from the salt plates, appeared to be those of a mixture. All infrared spectra displayed a sharp



intense line at  $2240\text{ cm}^{-1}$ . This type of an absorption is characteristic of organic compounds containing a -CN group.

The results of the analysis of the volatile species are presented in Tables 4 and 5. These results were obtained from samples that were pyrolyzed in vacuum. A considerably different distribution of products might have been obtained had the samples been pyrolyzed in air, in which case the products would be a function of the partial pressure of oxygen at the sample, the temperature of pyrolysis, and the time that it took the sample to reach the pyrolysis temperature.

#### Flammability Properties

**THERMAL EFFICIENCY.**— The NASA Ames T-3 thermal test (Fig. 6) [13] was used to determine the fire endurance or fire containment capability of the composite panels. In this test, specimens measuring  $25\text{ cm} \times 25\text{ cm} \times 2.54\text{ cm}$  thick are mounted in the chamber and thermocoupled on the backface of the specimen. The flames from an oil burner supplied with approximately 5 lit/h of JP-4 jet aviation fuel provide heat flux to the front face of the sample in the range of  $10.4\text{--}11.9\text{ W/cm}^2$ .

The fire endurance capability of the nine composite panels is compared in Figures 7-9. In these figures, the backface temperature rise of the panel is plotted as a function of the time in minutes when the sample is subjected to this type of fire. It can be seen (Fig. 8) that the backface temperature of the conventional composite, No. 8, reached  $200^\circ\text{C}$  in 2.5 min whereas it took as long as 8 min for the bismaleimide composites, No. 7 and No. 9, to reach a comparable backface temperature.

**LIMITING OXYGEN INDEX.**— The limiting oxygen index (LOI) of the components comprising the composites was determined per ASTM D-2863 and are indicated in

Table 6. The values indicated are for the laminated or composite components as they are used in the sandwich composite and not for the individual polymers. The average LOI value shown for each composite structure is based on the values obtained from the components.

SMOKE EVOLUTION.— Smoke evolution from the composites was determined using NBS-Aminco Smoke density chambers at two laboratories: laboratory A and laboratory B. The procedure and test method used were essentially those described by NFPA 258-T [14]. A detailed description of the NBS smoke chamber can be found in Reference 15.

The test results obtained with the NBS smoke chamber, modified by the incorporation of an animal module accessory [16], are presented in Table 7. Values of specific optical density (Ds) at 1.5 min, 4.0 min, and maximum (Dm) are presented; standard deviations are also given.

Composites No. 1 and 8 represented the state-of-the-art baseline materials. All the other composites exhibited significantly lower smoke density values, indicating that the phenolic and bismaleimide offer the advantage of smoke reduction.

A comparison of the Ds values obtained by the two laboratories is presented in Table 8. In addition to possible differences in apparatuses at the two laboratories, the calculation procedures were slightly different. In laboratory A, the Ds values are obtained from individual test data and then averaged. In laboratory B, an average curve is generated by computer from the data of the individual tests, and the Ds values are obtained from the computer-averaged curve. The smoke density of composite panels similar to composite No. 8 has also been evaluated by other laboratories [17]. Composition of the

panel was essentially the same as composite No. 8 except the panel was 0.70 cm thick. The maximum smoke level,  $D_m(\text{corr})$  was 54 whereas the average in the present studies was  $D_m$  58.7.

RELATIVE TOXICITY.— Efforts to obtain relative toxicity information by using the NBS smoke chamber with the animal module accessory were unsuccessful. The mice and rats exposed during the standard smoke tests showed no evidence of death or even incapacitation [15]. The heat flux of  $2.5 \text{ W/cm}^2$  used in the standard test procedure appears to be incapable of producing sufficient effluents from these high-performance materials.

To provide an indication of relative toxicity, 1.0 g of each of the powdered specimens of the composites was pyrolyzed as a heating rate of  $40^\circ \text{ C/min}$  in a quartz tube to an upper temperature limit of  $700^\circ \text{ C}$ , and the effluents conveyed by natural thermal flow into a 4.2 liter hemispherical chamber containing four Swiss albino male mice. The apparatus (Fig. 12) and procedure have been described previously in detail [18,19]. The test was continued for 30 min, unless terminated earlier upon the death of all four animals. The highest chamber temperature recorded was  $29.5^\circ \text{ C}$ , indicating that the pyrolysis gases were adequately cooled before entering the animal exposure chamber. Some condensation of higher-boiling vapors in the connecting tube was observed, and some of the effluent gases entered the animal exposure chamber as visible heavy vapors, indicating that some higher-boiling compounds did reach the animals and were not lost entirely by cooling. The lowest oxygen concentration recorded was 12%, indicating that hypoxia was not a significant factor in animal response. Table 9 shows the relative toxicity to mice of the degradation products from the powdered composites when heated in this manner.

During the 30-min exposure period, composite No. 9 caused no deaths in the test animals. The other composites, that is, No. 1-8 caused death to the animals at times ranging from 19.65 min to 28.31 min.

The test time-to-death was judged as the time elapsed at cessation of movement and respiration, as judged by the observer. Time to incapacitation was judged as the time to the first observation of loss of equilibrium, collapse, or convulsions, whichever came first. As a comparison, 1.0 g of wool fabric causes death to four mice in approximately 9.5 min when tested in a similar manner.

EFFECT OF CHAR YIELD ON SMOKE EVOLUTION AND OXYGEN INDEX.— Previous studies [20] have shown a correlation between the flammability properties of polymers and their char yield. A decrease in ease of ignition and smoke evolution is observed with high char yield polymers. The same relationship seems to exist with composites consisting of polymers and inorganic reinforcements.

Figure 13 compares the smoke density and relative anaerobic char yield of those composites when they are tested in the NBS smoke chamber. It can be seen that in general composites with high char yield have fairly low smoke evolution.

Figure 14 compares the limiting oxygen index of these composites with their relative anaerobic char yield. It can be seen that in general composites with very high char yield exhibited a high limiting oxygen index.

#### Thermophysical Characterization of Composites

The thermal conductivity of panels No. 8 and No. 9 were determined in accordance with ASTM C-177-45. The thermal conductivity of composite No. 8 was significantly higher than that of composite No. 9, probably due to the absence of any insulative material in the honeycomb; the data are presented in Table 12. The flatwise tensile strength of the laminates to the honeycomb was

determined per ASTM C-307; as shown in Table 10, composite No. 9 has a slightly lower tensile strength than the state-of-the-art composite No. 8. In addition to these properties, the flammability properties of these composites are compared in Table 10.

#### CONCLUSIONS

Composite No. 9, consisting of bismaleimide-fiberglass/bismaleimide honeycomb with carbon microballoons, exhibited the highest fire containment capability. Similarly, composite No. 7 exhibited high fire containment capability.

Advanced composite panels consisting of PVF/phenolic-fiberglass/aromatic polyamide honeycomb/phenolic-fiberglass (composites No. 2-6) and composites No. 7 and 9 exhibited lower smoke evolution than the state-of-the-art composite No. 8.

The relative toxicity of the pyrolysis products of composite No. 9 was the lowest, as measured using the methodology indicated, of all the composites tested. It had also the highest anaerobic char yield of all the composites tested.

A correlation was established between the anaerobic char yield of the composites and their relative limiting oxygen index and smoke evolution. Generally, composites consisting of polymers with high anaerobic char yield, had a high limiting oxygen index and low smoke evolution.

No definite correlation was found between the concentration of the toxic pyrolysis products of the composites and their relative toxicity to animals indicating possibly that additional toxic species may be present both in the volatile gases, which accounted for only 18% of the degradation products, and in the solid particulates. Additional studies should be conducted using gas

chromatography-mass spectrometry to identify these compounds and their relative concentrations.

#### ACKNOWLEDGMENTS

The authors are indebted to Mr. Daniel B. Arnold, Boeing Commercial Airplane Company, for providing some of the smoke density data, Mr. Harry Nakano, Lockheed Missiles and Space Company, for fabrication of some of the composite panels, and to Mr Steve Calvert, NASA, for making measurements of the limiting oxygen indexes.

#### REFERENCES

1. Department of Transportation, Federal Aviation Administration, Airworthiness Standards: Transport Category Airplanes, Federal Aviation Regulations, Vol. III, Part 25, Transmittal 10, effective May 1, 1972.
2. Department of Transportation, Federal Aviation Administration; Notice 75-31: Aircraft, Engine, and Propeller, Airworthiness, and Procedural Proposals; Federal Register, Volume 40, June 11, 1975.
3. Department of Transportation, Federal Aviation Administration, Flight Standard, Service, Transport Category Airplanes, Notice 75-3, Smoke Emission from Compartment Interior Materials; Federal Register, Volume 40, p. 6505, February 12, 1975.
4. Department of Transportation, Federal Aviation Administration, Flight Standards Service, Notice 74-38, Compartment Interior Materials: Toxic Gas Emission; Federal Register, Volume 39, p. 45044, December 30, 1974.
5. "Flaming and Self Extinguishing Characteristics of Aircraft Cabin Interior Materials," FAA Final Report No. NA-68-30 (DS-68-13), July 1968.

6. D. Gross, J. J. Loftus, T. G. Lee, and V. E. Gray, "Smoke and Gases Produced by Burning Aircraft Interior Materials," Federal Aviation Administration Report No. NA-68-36 (DS-68-16), June, 1968.
7. D. R. Mott, W. W. Spruance, D. Danaher, R. McGuire, D. A. Kourtides, A. Bigelow, and R. Ault, "Cabin Interiors - Smoke and Fire," Proceedings of the 12th Annual Conference and Trade Exhibit of the Survival and Flight Equipment Association, September 1974, pp. 114-120.
8. D. Gross, "Smoke and Gases Produced by Burning Interior Materials," NBS Building Science Series 18, February 1968.
9. D. A. Kourtides, J. A. Parker, and W. J. Gilwee, Jr., "Thermochemical Characterization of Aircraft Interior Panel Materials," J. Fire and Flammability, Vol. 6, July 1975, pp. 373-391.
10. W. J. Gilwee, J. A. Parker, D. A. Kourtides, and C. J. Hilado, "Fire Resistant Low Density Composites," to be presented at the ANTEC Meeting, Society of Plastics Engineers, Cleveland, Ohio, Oct. 4-7, 1976.
11. D. A. Kourtides, J. A. Parker, C. J. Hilado, R. A. Anderson, E. Tustin, D. B. Arnold, J. G. Grume, A. J. Binding, and J. L. Mikeska, "Fire Safety Evaluation of Aircraft Lavatory and Cargo Compartments," J. Fire and Flammability, Vol. 7, January 1976, pp. 125-159.
12. D. A. Kourtides, J. A. Parker, H. A. Leon, R. B. Williamson, H. Hasegawa, F. Fisher, R. Draemel, W. H. Marcussen, and C. J. Hilado, "Fire Containment Tests of Aircraft Interior Panels," J. Fire and Flammability, Vol. 7, April 1976, pp. 257-278.

13. S. R. Riccitiello, R. H. Fish, J. A. Parker, and E. J. Gustafson, "Development and Evaluation of Modified Polyisocyanurate Foams for Low-Heating-Rate Thermal Protection," *Journal of Cellular Plastics*, Vol. 7, No. 2, 91-96, March/April 1971.
14. National Fire Protection Association, NFPA 258-T (1974).
15. T. G. Lee, Interlaboratory Evaluation of Smoke Density Chamber, National Bureau of Standards Technical Note 708, December 1971.
16. C. J. Hilado, and L. A. LaBossiere, "Evaluation of the Smoke Density Chamber as an Apparatus for Fire Toxicity Screening Tests," *J. of Combustion Toxicology*, Vol. 3, No. 2, May 1976.
17. E. P. Sarkos, "Measurement of Toxic Gases and Smoke from Aircraft Cabin Interior Materials Using the NBS Smoke Chamber and Colorimetric Tubes," Department of Transportation, Federal Aviation Administration, Report No. FAA-RD-76-7, March 1976, pp. 15-19.
18. C. J. Hilado, "Evaluation of the NASA Animal Exposure Chamber as a Potential Chamber for Fire Toxicity Screening Tests," *J. Combustion Toxicology*, Vol. 2, November 1975, pp. 298-314.
19. C. J. Hilado, "Relative Toxicity of Pyrolysis Products of Some Foams and Fabrics," *J. of Combustion Toxicology*, Vol. 3, No. 1, 32-60, February 1976.
20. J. A. Parker, D. A. Kourtides, R. H. Fish, and W. J. Gilwee, Jr., "Fire Dynamics of Modern Aircraft from a Materials Point of View," *J. Fire and Flammability*, Vol. 6, October 1975, pp. 534-553.



#### D. A. Kourtides

D. A. Kourtides received a B.S. degree in metallurgical engineering from Brigham Young University, Provo, Utah, and has attended graduate classes at San Jose State College. Since 1967 he has been working on the development of fire-resistant polymeric foams, such as polybenzimidazole. Before joining Ames Research Center, NASA, in 1964, he worked for Varian Associates, Palo Alto, California in the development of electroplating processes. He is a member of the Society of Plastics Engineers.

#### J. A. Parker

J. A. Parker is Chief, Chemical Research Projects Office, at NASA's Ames Research Center, California. In 1968 he was awarded the NASA Exceptional Service Medal for his pioneering research in reentry technology and on the ablation of heat shield materials. The results of this work have been used to provide protection from fire, with a wide range of commercial applications. Prior to joining Ames as a research scientist in 1962, Dr. Parker was manager of the Chemistry Department of Armstrong Cork Company in Lancaster, Pennsylvania. Dr. Parker received his bachelor's degree in chemistry from the University of Pennsylvania in 1948, and his master's and Ph.D. from the same university, also in chemistry, in 1949 and 1951. He is a member of Sigma Xi, a Fellow of the American Institute of Chemists, and a member of the American Chemical Society.

#### W. J. Gilwee

W. J. Gilwee received his undergraduate degree from Rockhurst College, Kansas City, Missouri, and took graduate courses at George Washington University, Washington, D.C. Before joining Ames Research Center, NASA, he worked

for TRW, Cleveland, Ohio and General Electric Company, Coshocton, Ohio. Since 1966 Mr. Gilwee has been working on the development and processing of high temperature polymers and fire retardant materials. He is a member of the American Chemical Society and the Society of Plastics Engineers.

N. R. Lerner

N. R. Lerner is a research scientist in the Chemical Research Projects Office of NASA at the Ames Research Center at Moffett Field, California. She received her B.A. degree in chemistry, cum laude, from Hofstra University in 1956; her M.S. degree (1959) and Ph.D. degree (1962) were received from the University of Chicago. Since joining NASA in 1970 she has worked on flame inhibition and on mechanisms of thermal degradation of polymers.

Carlos J. Hilado

Carlos J. Hilado is a research professor in the Institute of Chemical Biology of the University of San Francisco, and conducts research programs at San Francisco and at the NASA Ames Research Center at Moffett Field, California. He received his B.S. degree in chemical engineering from De La Salle College in Manila, Philippines in 1954; his M.S. degree in chemical engineering practice from Massachusetts Institute of Technology in 1956; and his Sc.D. degree in applied science, honoris causa, from De La Salle University in 1974. His teaching experience includes De La Salle College and the West Virginia College of Graduate Studies. From 1956 to 1975 he was a member of the Chemicals and Plastics Research and Development Department of Union Carbide Corporation at South Charleston, West Virginia. He has had experience in sugar milling and refining, food technology and microbiology, pulp and paper,

vinyl and urethane foams, vinyl polymerization, materials evaluation, industrial insulation, and fire safety research.

Lisa A. LaBossiere

Lisa A. LaBossiere is a technical assistant in the Institute of Chemical Biology of the University of San Francisco. She received her B.A. degree in psychology from Boston College in 1976. Before starting work on toxic materials characterization, she worked in the Department of Pathology at Harvard Medical School, Department of Neuroscience at Children's Hospital in Boston, and Department of Psychology at Boston College. She has had experience in animal care and breeding, tissue culture, animal immunization, and activity studies in stressful environments.

M.t. Hsu

Ming-ta S. Hsu is a lecturer in the Department of Chemistry, San Jose State University at San Jose, California. She received her B.S. degree in chemistry from National Taiwan University in 1960, her M.S. degree in chemistry from New Mexico Highlands University in 1963, and her Ph.D. degree in chemistry from Iowa State University in 1967. Before joining the San Jose State University in 1972, she was a NRC postdoctoral associate with NASA-Ames Research Center. She has worked on characterization and thermal degradation of polymers.

TABLE 1.- COMPOSITION OF COMPOSITES: NO. 1-3.

COMPOSITE NO.	1	2	3
A	DECORATIVE SURFACE, cm THICK, % WT 0.002 PVF CLEAR ACRYLIC INK, 0.005 PVF	SAME AS 1-A	SAME AS 1-A
B	FACE SHEET, RESIN/ FABRIC: % WT PHENOLIC TYPE A/7581 GLASS	PHENOLIC TYPE C/7581 GLASS	SAME AS 2-B
C	BOND SHEET, RESIN/ FABRIC: % WT PHENOLIC TYPE B/120 GLASS	PHENOLIC TYPE D/120 GLASS	PHENOLIC TYPE C/120 GLASS
D	CORE TYPE: THICKNESS, cm; CELL SIZE, cm; 3 DENSITY, kg/m <sup>3</sup> AROMATIC POLYAMIDE- PAPER HONEYCOMB; 2.413; 0.31; 48.06	SAME AS 1-D	SAME AS 1-D
E	CORE FILLER: DENSITY, kg/m <sup>3</sup> NONE	NONE	NONE
F	SAME AS C	SAME AS 2-C	SAME AS 3-C
G	SAME AS B	SAME AS 2-C	SAME AS 3-C
H	SAME AS A	NONE	NONE
	COMPOSITE DENSITY, kg/m <sup>3</sup> 72.410	79.138	70.488

TABLE 2.- COMPOSITION OF COMPOSITES: NO. 4-6.

	COMPOSITE NO.	4	5	6
A	DECORATIVE SURFACE, cm THICK; % WT	0.002 PVF CLEAR ACRYLIC INK 0.005 PVF	SAME AS 4-A	SAME AS 4-A
B	FACE SHEET, RESIN/ FABRIC; % WT	PHENOLIC TYPE E/ 7581 GLASS	PHENOLIC TYPE F/7581 GLASS	PHENOLIC TYPE G/7581 GLASS
C	BOND SHEET, RESIN/ FABRIC; % WT	SAME AS 4-B	PHENOLIC TYPE F/120 GLASS	PHENOLIC TYPE G/120 GLASS
D	CORE TYPE: THICKNESS, cm; CELL SIZE, cm; DENSITY, kg/m <sup>3</sup>	AROMATIC POLYAMIDE: PAPER HONEYCOMB; 2.413; 0.31; 48.06	SAME AS 4-D	SAME AS 4-D
E	CORE FILLER: DENSITY, kg/m <sup>3</sup>	NONE	NONE	NONE
F	SAME AS C	PHENOLIC TYPE E	SAME AS 5-C	SAME AS 6-C
G	SAME AS B	SAME A: 4-F	SAME AS 5-C	SAME AS 6-C
H	SAME AS A	NONE	NONE	NONE
	COMPOSITE DENSITY kg/m <sup>3</sup>	76.575	76.095	70.968

TABLE 3.- COMPOSITION OF COMPOSITES: NO. 7-9.

	COMPOSITE NO.	7	8	9
A	DECORATIVE SURFACE cm THICK; % WT	NONE	0.002 PVF ACRYLIC INK 0.005 PVF	NONE
B	FACE SHEET, RESIN/ FABRIC; % WT	BISMALEIMIDE/120 GLASS	EPOXY TYPE H/181 E GLASS B + C = 35.9%	BISMALEIMIDE/181 E GLASS B + G = 14.1%
C	BOND SHEET, RESIN/ FABRIC; % WT	POLYIMIDE ADHESIVE	EPOXY TYPE H/120 GLASS	SAME AS 7-C C + F = 5.1%
D	CORE TYPE; THICKNESS, cm; CELL SIZE, cm; 3, % WT DENSITY, kg/m <sup>3</sup> , % WT	AROMATIC POLYAMIDE- PAPER HONEYCOMB; 2.413; 0.31; 48.06	SAME AS 7-D 2.413; 0.31; 48.06; 20.5%	BISMALEIMIDE- GLASS HONEYCOMB; 2.413; 0.47; 80.1; 30.3%
E	CORE FILLER; DENSITY, kg/m <sup>3</sup> , % WT	QUINONE DIOXIME FOAM	NONE	CARBON MICRO- BALLOONS WITH 5% BISMALEIMIDE; 112; 50.5%
F	SAME AS C	SAME AS 7-C	SAME AS 7-C F + G = 35.9%	SAME AS 7-C
G	SAME AS B	SAME AS 7-B	SAME AS 7-B	SAME AS 9-B
H	SAME AS A	NONE	SAME AS 7-A A + H = 7.7%	NONE
	COMPOSITE DENSITY, kg/m <sup>3</sup>	110	95	130

TABLE 4.- MAJOR VOLATILE PRODUCTS AT 23° C FROM THE PYROLYSIS OF COMPOSITES IN VACUUM AT 700° C FOR 5 MIN. (me volatile/gm in wt)

COMPOSITE NO.	(a) WT LOSS, %	(b) VOLATILE WT LOSS, %	VOLATILES me/g										(d) TOTAL me/g
			CO <sub>2</sub>	CO	CH <sub>4</sub>	HCN	C <sub>6</sub> H <sub>6</sub>	NH <sub>3</sub>	H <sub>2</sub> (c)				
1	48.8 ± 2.1	5.8 ± 0.1	2.02 ± 0.53	0.36 ± 0.08	0.74 ± 0.04	0.24 ± 0.03	0.05 ± 0.01	-	1.63 ± 0.10	5.03 ± 0.18			
2	48.8 ± 2.1	12.0 ± 0.8	1.54 ± 0.07	0.54 ± 0.09	1.26 ± 0.20	0.32 ± 0.03	0.06	-	1.76 ± 0.32	5.64 ± 0.38			
3	39.9 ± 2.2	12.9 ± 0.2	1.93 ± 0.14	0.50 ± 0.03	0.92 ± 0.24	0.28 ± 0.02	0.04 ± 0.01	-	2.16 ± 0.54	5.90 ± 0.40			
4	41.9 ± 2.8	14.4 ± 0.6	2.22 ± 0.17	0.51	1.06 ± 0.02	0.26 ± 0.01	0.06 ± 0.01	-	1.60 ± 0.23	5.68 ± 0.05			
5	42.0 ± 1.3	12.6 ± 0.1	1.89 ± 0.14	0.52 ± 0.05	0.90 ± 0.30	0.26 ± 0.01	0.042 ± 0.001	-	1.94 ± 0.40	5.61 ± 0.51			
6	42.6 ± 1.1	12.4 ± 1.3	1.92 ± 0.20	0.42 ± 0.09	0.80 ± 0.03	0.22	0.062 ± 0.005	-	1.72 ± 0.23	5.02 ± 0.52			
7	35.8 ± 7.0	10.8 ± 1.8	1.81 ± 0.34	0.32 ± 0.09	0.26 ± 0.02	0.18 ± 0.03	0.04 ± 0.03	0.28 ± 0.28	0.16 ± 0.02	3.45 ± 0.31			
8	43.6	11.6	1.95	0.22	0.59	0.12	0.053	-	0.62	3.56			
9	20.4 ± 0.3	18.0 ± 0.1	3.53 ± 0.10	0.51 ± 0.06	0.08 ± 0.04	0.22 ± 0.02	-	0.21 ± 0.12	-	4.22 ± 0.01			

$$(a) \text{ WT LOSS, \%} = \left[ \frac{(\text{INITIAL WT SAMPLE}) - (\text{FINAL WT SAMPLE})}{(\text{INITIAL WT SAMPLE})} \right] (100)$$

$$(b) \text{ VOLATILE WT LOSS, \%} = \left[ \frac{\sum (\text{MILLIEQUIVALENTS})_i (\text{MOLECULAR WT})_i}{(\text{INITIAL WT SAMPLE}) (100)} \right]$$

(c) H<sub>2</sub> DETERMINED BY DIFFERENCE

$$(d) \text{ TOTAL me/g VOLATILES DETERMINED FROM: me/g} = \left[ \frac{(P) (V)}{(R) (T)} \right] \left[ \frac{1}{(\text{INITIAL WT SAMPLE})} \right]$$

TABLE 5.- MAJOR VOLATILE PRODUCTS AT 23° C FROM THE PYROLYSIS OF COMPOSITES IN  
 VACUUM AT 700° C FOR 5 MIN. (mg volatile/gm in wt)

COMPOSITE NO.	QUANTITY(a)							
	CO <sub>2</sub>	CO	CH <sub>4</sub>	HCN	C <sub>6</sub> H <sub>6</sub>	NH <sub>3</sub>	H <sub>2</sub>	
1	88.9	10.1	11.8	6.5	3.9		3.3	
2	67.8	15.1	20.2	8.6	4.7		3.5	
3	84.9	14.0	14.7	7.6	3.1		4.3	
4	97.7	14.3	17.0	7.0	4.7		3.2	
5	83.2	14.6	14.4	7.0	3.3		3.9	
6	84.5	11.8	12.8	5.9	4.8		3.4	
7	79.6	9.0	4.2	4.9	3.1	4.8	3	
8	85.5	6.2	9.4	3.2	4.1		1.2	
9	155.3	14.3	1.3	5.9		3.6		

(a) MILLIGRAMS OF VOLATILE COMPOUND AT 23 C PER GRAM OF  
 INITIAL SAMPLE



TABLE 6.- LIMITING OXYGEN INDEX FOR COMPOSITE COMPONENTS.

COMPOSITE NO.	COMPOSITE COMPONENT	LOI @ 23 C O <sub>2</sub> /(N <sub>2</sub> + O <sub>2</sub> )
1	PVF, PHENOLIC A/7581 GLASS, PHENOLIC B/120 GLASS	27
	AROMATIC POLYAMIDE-PAPER	32
	PHENOLIC A/7581 GLASS, PHENOLIC B/120 GLASS	26
	AVERAGE	28.3
2	PVF, PHENOLIC C/7581 GLASS, PHENOLIC D/120 GLASS	45
	AROMATIC POLYAMIDE-PAPER	32
	PHENOLIC C/7581 GLASS, PHENOLIC D/120 GLASS	32
	AVERAGE	36.3
3	PVF, PHENOLIC C/7581 GLASS, PHENOLIC C/120 GLASS	38
	AROMATIC POLYAMIDE-PAPER	32
	PHENOLIC E/120 GLASS (2 PLIES)	33
	AVERAGE	34.3
4	PVF, PHENOLIC E/7581 GLASS, PHENOLIC F/120 GLASS	47
	AROMATIC POLYAMIDE-PAPER	32
	PHENOLIC E/120 GLASS (2 PLIES)	30
	AVERAGE	35.3
5	PVF, PHENOLIC F/7581 GLASS, PHENOLIC F/120 GLASS	44
	AROMATIC POLYAMIDE-PAPER	32
	PHENOLIC F/120 GLASS (2 PLIES)	32
	AVERAGE	36
6	PVF, PHENOLIC G/7581 GLASS, PHENOLIC G/120 GLASS	74
	AROMATIC POLYAMIDE-PAPER	32
	PHENOLIC G/120 GLASS (2 PLIES)	36
	AVERAGE	47.3
7	BISMALEIMIDE/120 GLASS/POLYIMIDE	99
	AROMATIC POLYAMIDE-PAPER	32
	QUINONE DIOXIME FOAM	100
	AVERAGE	82.5
8	PVF, EPOXY H/181E GLASS, EPOXY H/120 GLASS	29
	AROMATIC POLYAMIDE-PAPER	32
	EPOXY H/181 GLASS, EPOXY H/120 GLASS	28
	AVERAGE	29.6
9	BISMALEIMIDE/181E GLASS/POLYIMIDE	62
	BISMALEIMIDE/GLASS	58
	CARBON MICROBALLOONS/BISMALEIMIDE	85
	AVERAGE	66.7

TABLE 7.- SMOKE EVOLUTION FROM COMPOSITE PANELS (NBS SMOKE CHAMBER, 2.5 W/cm<sup>2</sup>).

COMPOSITE NO.	SPECIFIC OPTICAL DENSITY (FLAMING CONDITION)			NO. OF TESTS
	D <sub>s</sub> , 1.5 min	D <sub>s</sub> , 4.0 min	D <sub>m</sub> , maximum	
1	44.7 ± 13.3	51.7 ± 6.9	53.3 ± 8.9	3
2	3.9 ± 3.9	5.7 ± 4.1	8.6 ± 3.0	3
3	11.6 ± 0.9	13.6 ± 3.2	17.1 ± 6.4	3
4	7.1 ± 5.5	7.2 ± 5.3	8.4 ± 5.8	3
5	9.2 ± 8.2	12.2 ± 8.5	15.3 ± 8.5	3
6	8.8 ± 8.2	10.3 ± 7.3	16.0 ± 6.7	3
7	1.3 ± 1.0	4.5 ± 3.5	20.4 ± 4.7	2
8	48.3 ± 7.4	58.7 ± 6.2	59.1 ± 6.4	3
9	1.0 ± 0.7	4.9 ± 4.0	18.2 ± 7.9	4
(NONFLAMING CONDITION)				
1	11.7 ± 4.5	19.2 ± 3.1	20.2 ± 3.3	3
2	0.4 ± 0.2	0.7 ± 0.2	1.6 ± 0.2	3
3	1.0 ± 0.7	1.2 ± 0.7	2.0 ± 1.3	3
4	0.7 ± 0.1	0.7 ± 0.2	1.5 ± 0.2	3
5	1.2 ± 0.2	2.6 ± 0.3	5.2 ± 0.7	3
6	2.1 ± 0.8	2.2 ± 0.6	2.7 ± 0.7	3
8	2.6 ± 0.3	11.2 ± 1.1	19.0 ± 1.9	3

TABLE 8.- SMOKE EVOLUTION FROM COMPOSITE PANELS FROM TWO CHAMBERS (NBS SMOKE CHAMBER, 2.5 N/cm<sup>2</sup>, FLAMING).

COMPOSITE NO.	SPECIFIC OPTICAL DENSITY									
	D <sub>s</sub> , 1.5 min			D <sub>s</sub> , 4.0 min			D <sub>m</sub> , maximum			
	CHAMBER A	CHAMBER B	AVERAGE	CHAMBER A	CHAMBER B	AVERAGE	CHAMBER A	CHAMBER B	CHAMBER AVERAGE	CHAMBER B AVERAGE
1	44.7	-	44.7	51.7	-	51.7	53.3	-	53.3	53.3
2	3.9	10.5	7.2	5.7	15.5	10.6	8.6	19.4	14.0	14.0
3	11.6	12.7	12.2	13.6	15.0	14.8	17.9	17.4	17.6	17.6
4	7.1	11.7	9.4	7.2	13.9	10.6	8.4	16.1	12.2	12.2
5	9.2	16.7	13.0	12.2	20.7	16.4	15.3	22.8	19.0	19.0
6	8.8	13.3	11.0	10.3	16.6	13.4	16.0	17.3	16.6	16.6
7	1.3	-	1.3	4.5	-	4.5	20.4	-	20.4	20.4
8	48.3	57.6	53.0	58.7	57.5	58.1	59.1	58.3	58.7	58.7
9	1.0	-	1.0	4.9	-	4.9	18.2	-	18.2	18.2

TABLE 9.- RELATIVE TOXICITY OF PYROLYSIS PRODUCTS FROM COMPOSITE PANELS.

(1.0 g POWDERED SPECIMENS PYROLYZED AT 40 C/min TO 700 C;  
4 SWISS ALBINO MICE IN 4.2 LITER EXPOSURE CHAMBER, 30 min EXPOSURE)

PANEL NO.	TEST NO.	TIME TO INCAPACITATION, min	TIME TO DEATH, min
1	1	18.1	28.31 ± 1.67
	2	21.9	25.21 ± 3.51
	3	16.3	25.83 ± 1.02
	4	18.9	22.90 ± 1.42
	MEAN	18.8	25.56 ± 2.76
2	1	20.9	26.74 ± 0.89
	2	21.0	24.90 ± 0.11
	MEAN	21.0	25.82 ± 1.13
3	1	19.0	24.52 ± 0.69
	2	22.1	25.35 ± 0.97
	MEAN	20.6	24.94 ± 0.90
4	1	20.5	24.17 ± 3.01
	2	19.3	23.48 ± 0.31
	MEAN	19.9	23.82 ± 2.01
5	1	20.3	26.18 ± 1.83
	2	19.7	22.48 ± 0.52
	MEAN	20.0	24.33 ± 1.17
6	1	17.1	19.65 ± 0.31
	2	20.9	22.90 ± 0.96
	MEAN	19.0	21.28 ± 0.63
7	1	22.8	27.40 ± 1.46
	2	24.8	28.28 ± 0.70
	MEAN	23.8	27.84 ± 1.16
8	1	18.5	27.50 ± 1.86
9	1	8.7	N.D.
	2	N.I.	N.D.

N.I. - NO INCAPACITATION OBSERVED

N.D. - NO DEATHS

TABLE 10.- SUMMARY OF COMPOSITE PROPERTIES (NO. 8, 9).

PROPERTY	COMPOSITE NO. 8	COMPOSITE NO. 9
BULK DENSITY RANGE $\text{kg/m}^3$ (ASTM D 1622)	90-96	109-113
FLATWISE TENSILE STRENGTH, AT 23°C $\text{KN/m}^2$ (ASTM C-307)	690	500-610
VERTICAL BURN TEST, FAA FAR 25.853	PASSES	PASSES
THERMAL CONDUCTIVITY AT 23°C $\text{W-cm/cm}^2\cdot\text{C}$ (ASTM C-177-45)	$1.296 - 1.44 \times 10^{-3}$	$4.932 \times 10^{-4}$
SMOKE DENSITY (NBS), (SPECIFIC OPTICAL DENSITY, FLAMING CONDITION, 2.5 W/cm <sup>2</sup> )	$D_s$ 1.5 min.:53.0 $D_s$ 4.0 min.:58.1 $D_m$ :58.7	1.0 4.9 18.2
LIMITING OXYGEN INDEX, $\text{O}_2 / (\text{N}_2 + \text{O}_2)$ , (ASTM D-2863)	EPOXY-FIBERGLASS:29 AROMATIC POLYAMIDE:32 COMPOSITE: 29.6	BISMALEIMIDE-FIBERGLASS/ POLYIMIDE:62 CARBON MICROBALLOONS, BISMALEIMIDE:85 BISMALEIMIDE-FIBERGLASS:58 COMPOSITE:66.7

Table 10 - Concluded.

PROPERTY	COMPOSITE NO. 8	COMPOSITE NO. 9
<p>RELATIVE TOXICITY OF PYROLYSIS PRODUCTS (1.0 g. 40° C/min to 700° C, 4 MICE IN 4.2 liter EXPOSURE CHAMBER, 30 min EXPOSURE) TIME TO INCAPACITATION; TIME TO DEATH (min)</p>	<p>18.5; 27.5 ± 1.86</p>	<p>&gt;30; &gt;30</p>
<p>FIRE ENDURANCE, NASA AMEST-3 TEST, TIME TO REACH BACK-FACE TEMP. OF 204° C AT FRONT FACE HEAT FLUX OF 10.4-11.9 W/cm<sup>2</sup></p>	<p>2 min. 20 sec</p>	<p>7 min. 45 sec</p>
<p>VOLATILES AT 23° C FROM PYROLYSIS IN VACUUM AT 700° C FOR 5 min Mg OF VOLATILE PER g OF INITIAL SAMPLE.</p>	<p>CO<sub>2</sub>: 85.5            CO : 6.2            CH<sub>4</sub>: 9.4            HCN: 3.2            C<sub>6</sub>H<sub>6</sub>: 4.1            NH<sub>3</sub>: -            H<sub>2</sub> : 1.2</p>	<p>155.3            14.3            1.3            5.9            -            3.6            -</p>
<p>TGA, % WEIGHT REMAINING AT 700° C (N<sub>2</sub>, 10° C/min).</p>	<p>51.0</p>	<p>73.5</p>



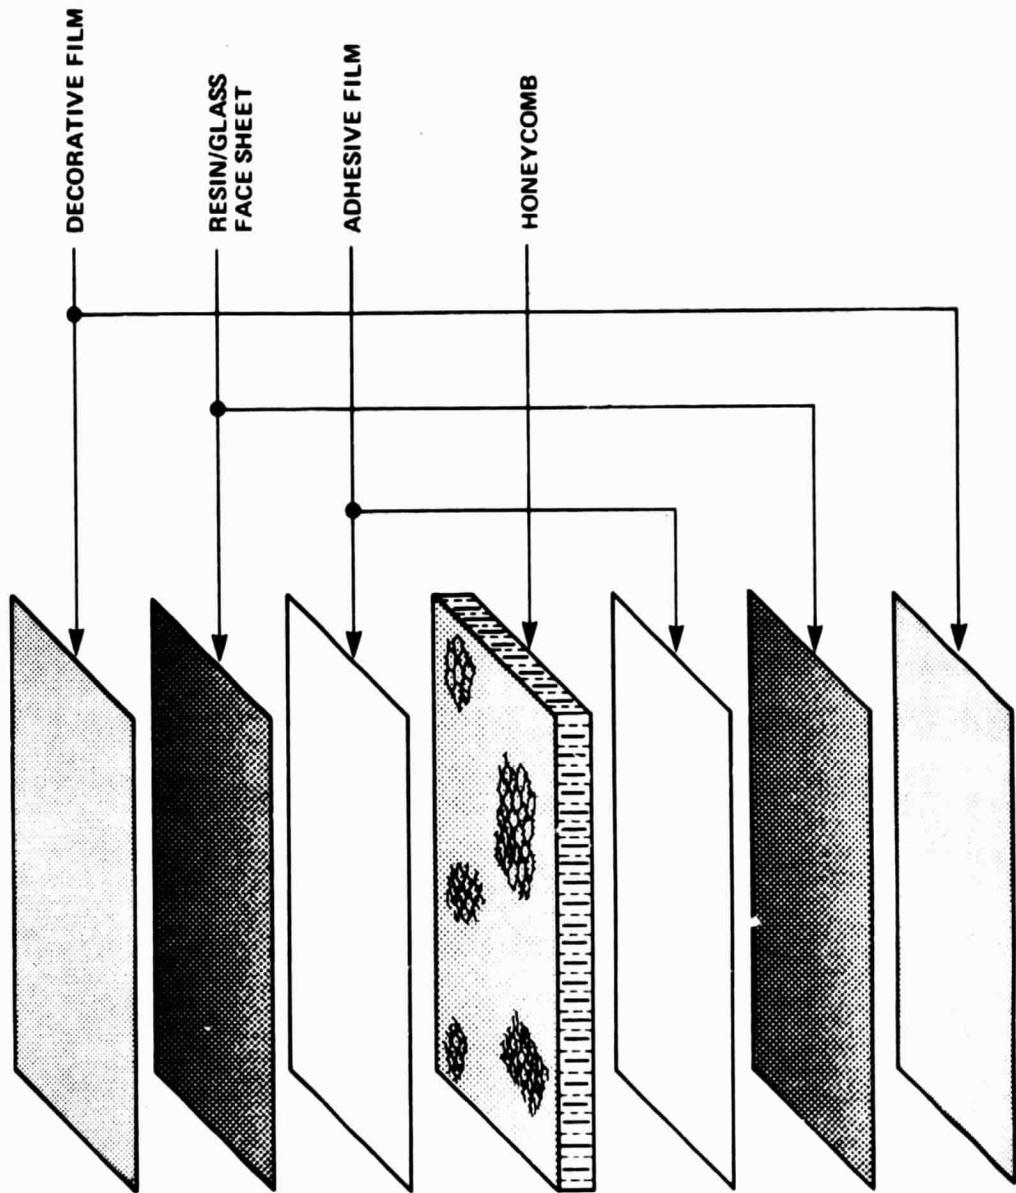


Figure 1.- Typical Composite Configuration of Aircraft Interior Panels.

**COMPOSITES NO. 1-6**

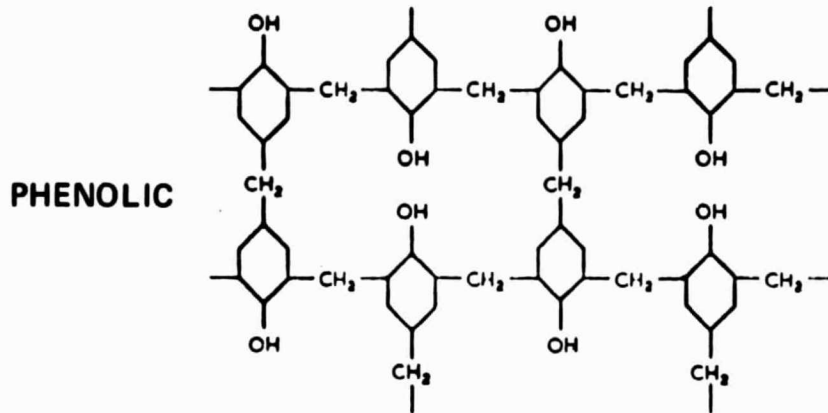

**COMPOSITE NO. 8**

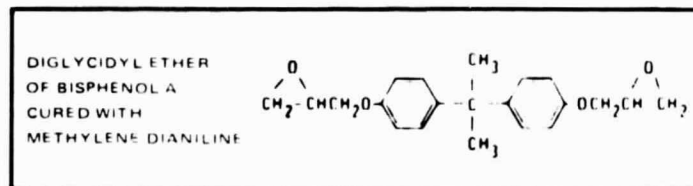

**COMPOSITES NO. 7, 9**

**BISMALEIMIDE**

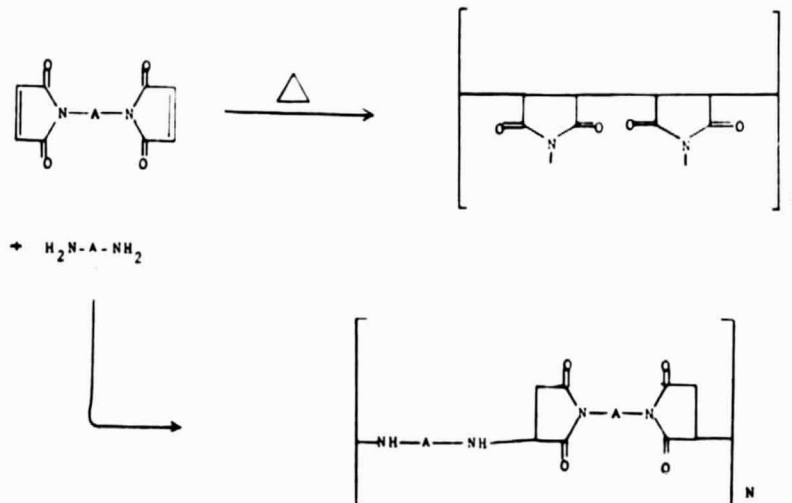


Figure 2.- Chemical Structure of Laminating Resins.



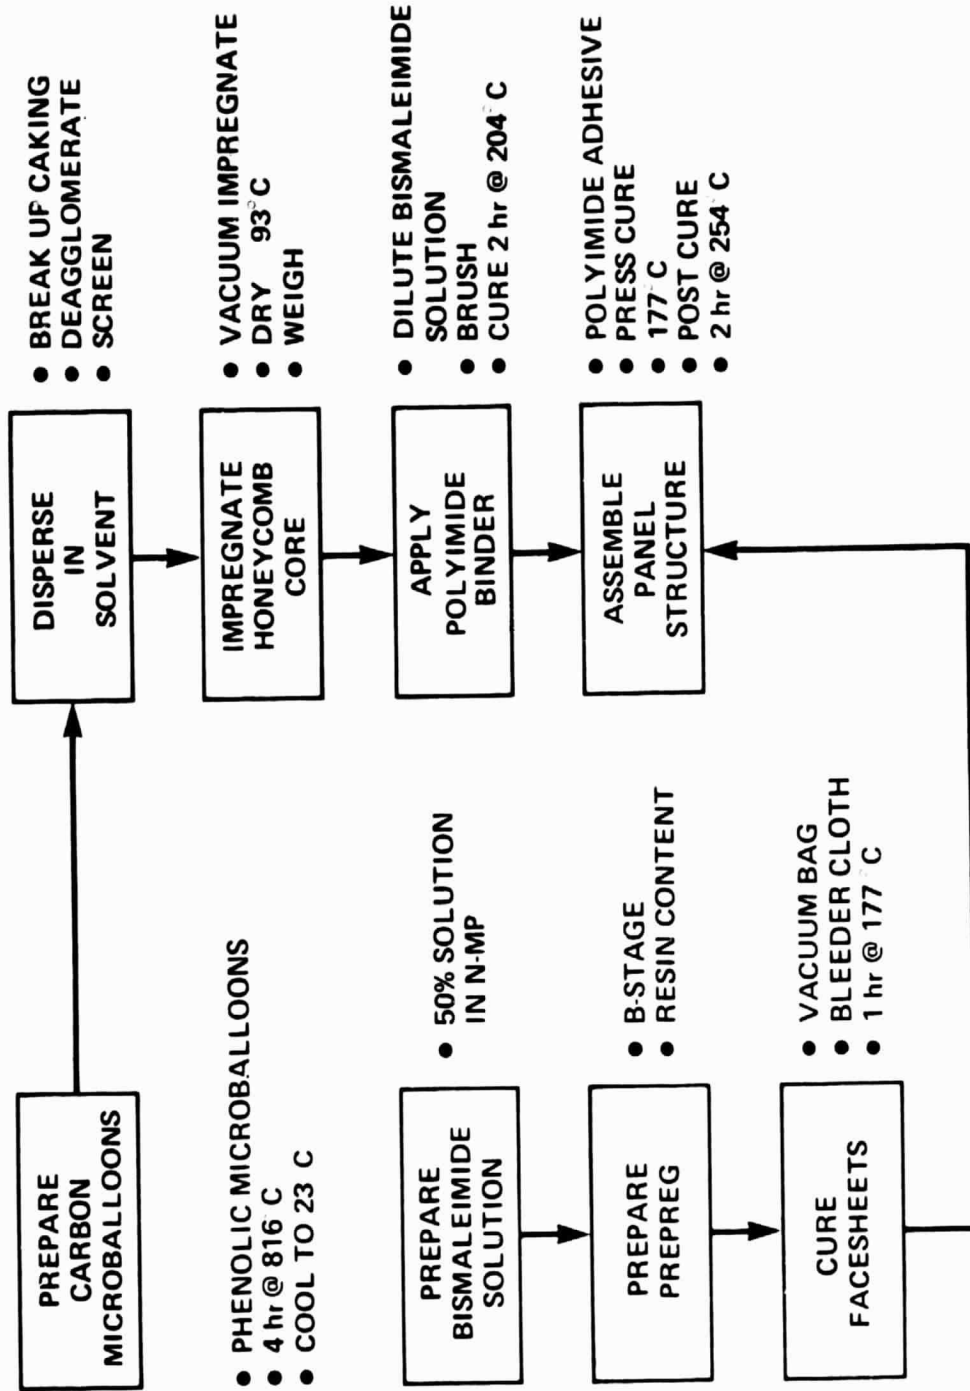


Figure 3.- Fabrication Process for Composite No. 9.

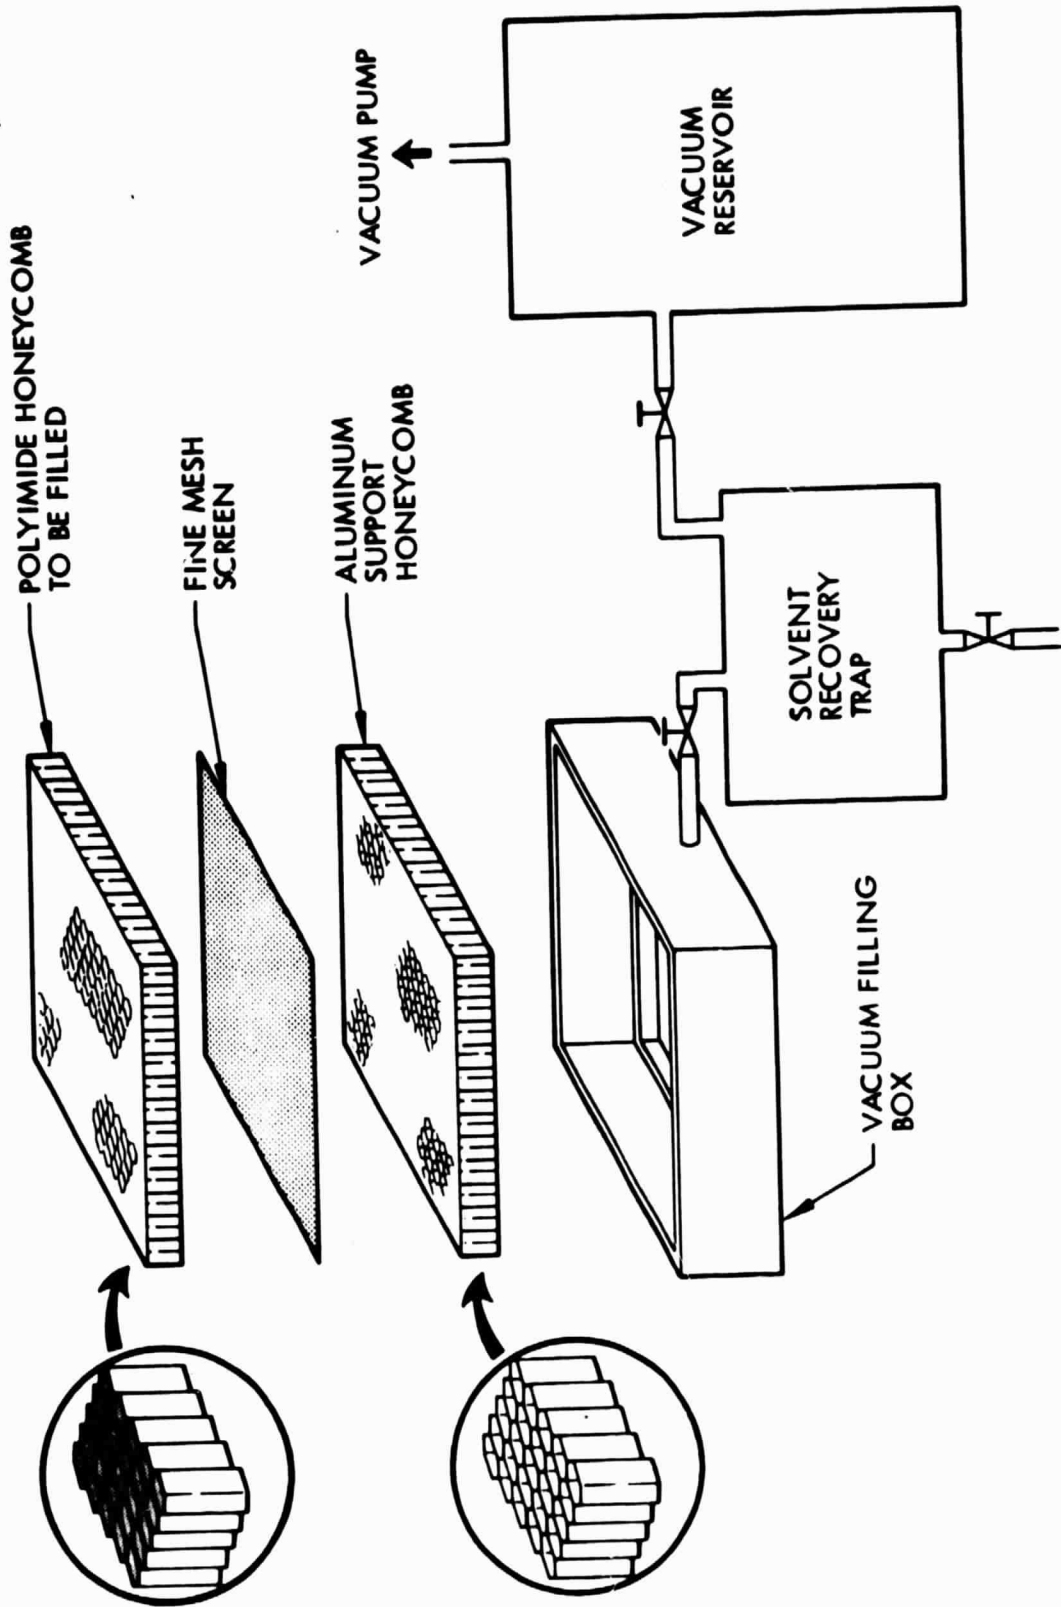


Figure 4.- Honeycomb Core Impregnation Equipment.

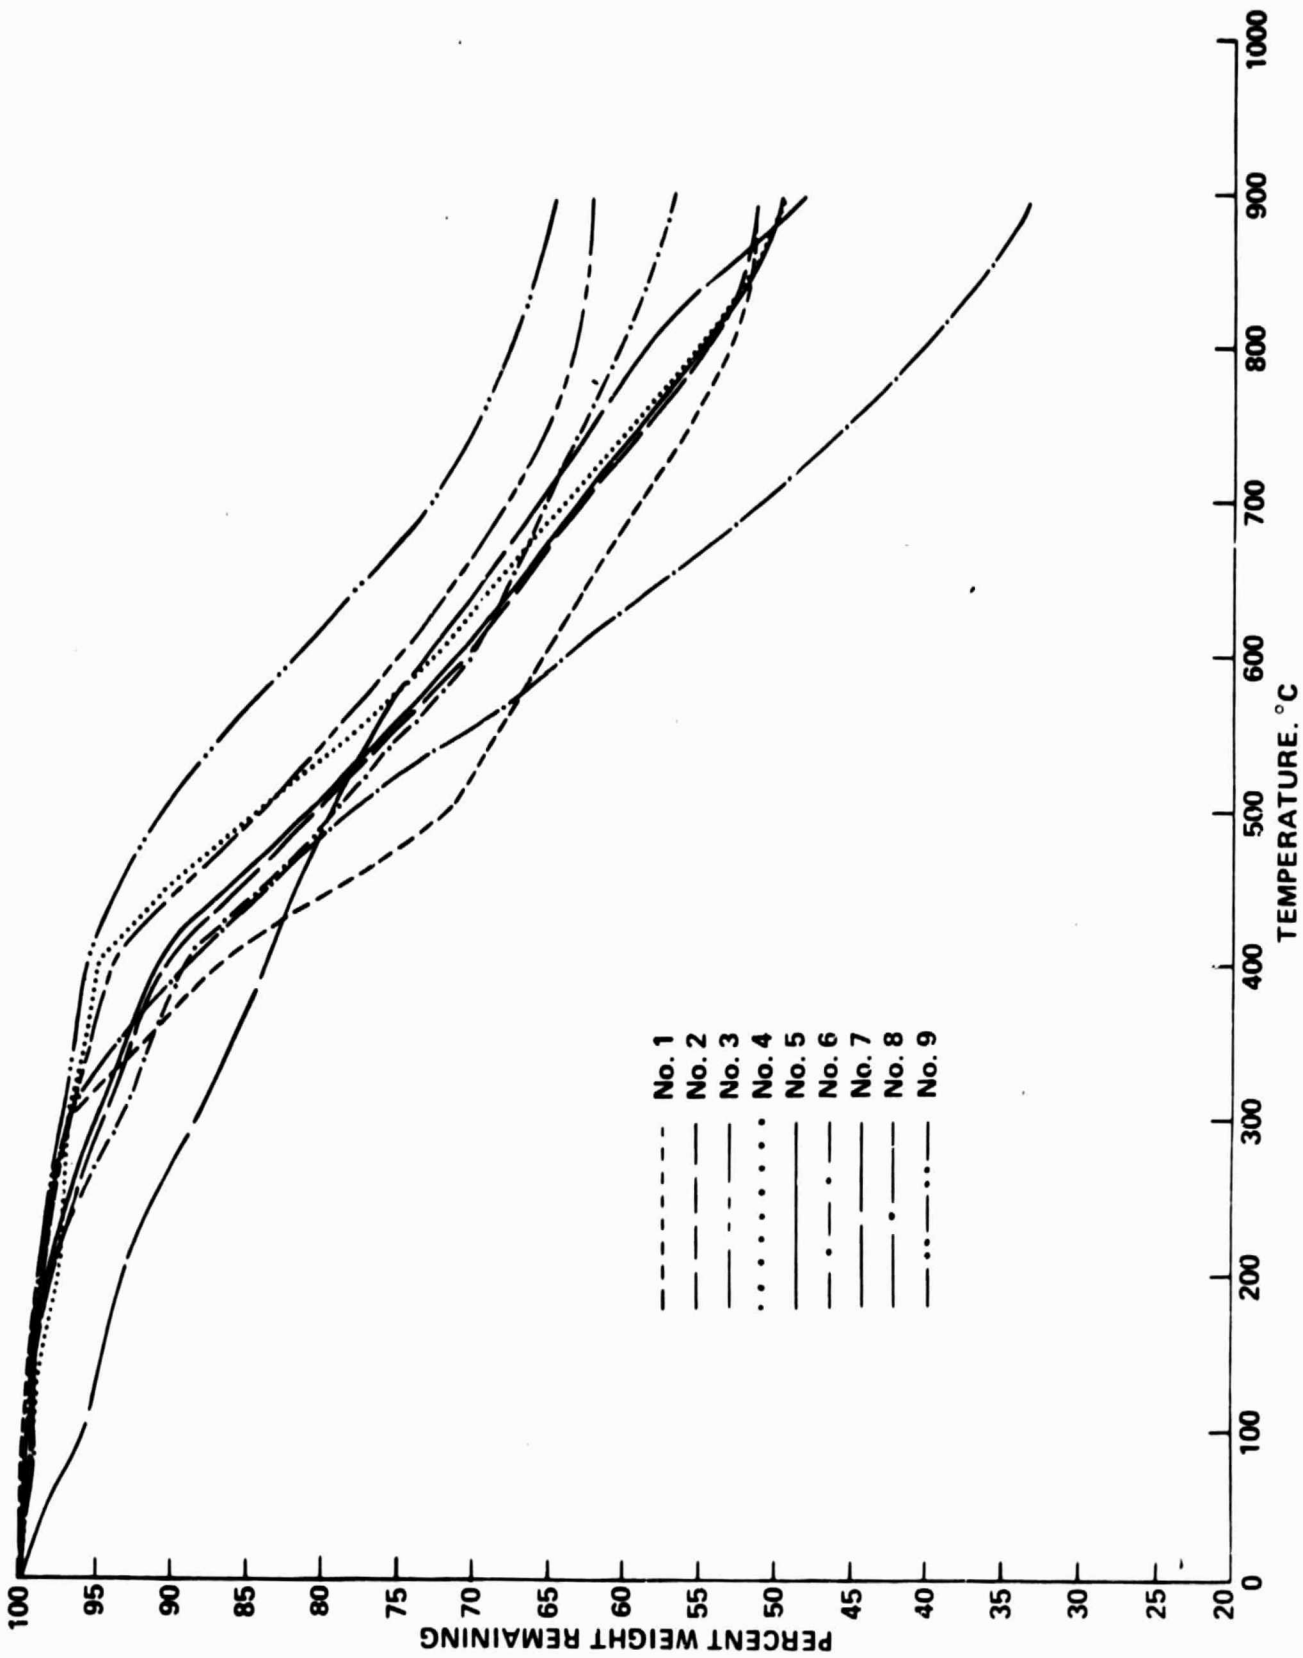


Figure 5.- Dynamic Thermograph of Composites 1-9 (heating rate 10° C/min, N<sub>2</sub>).

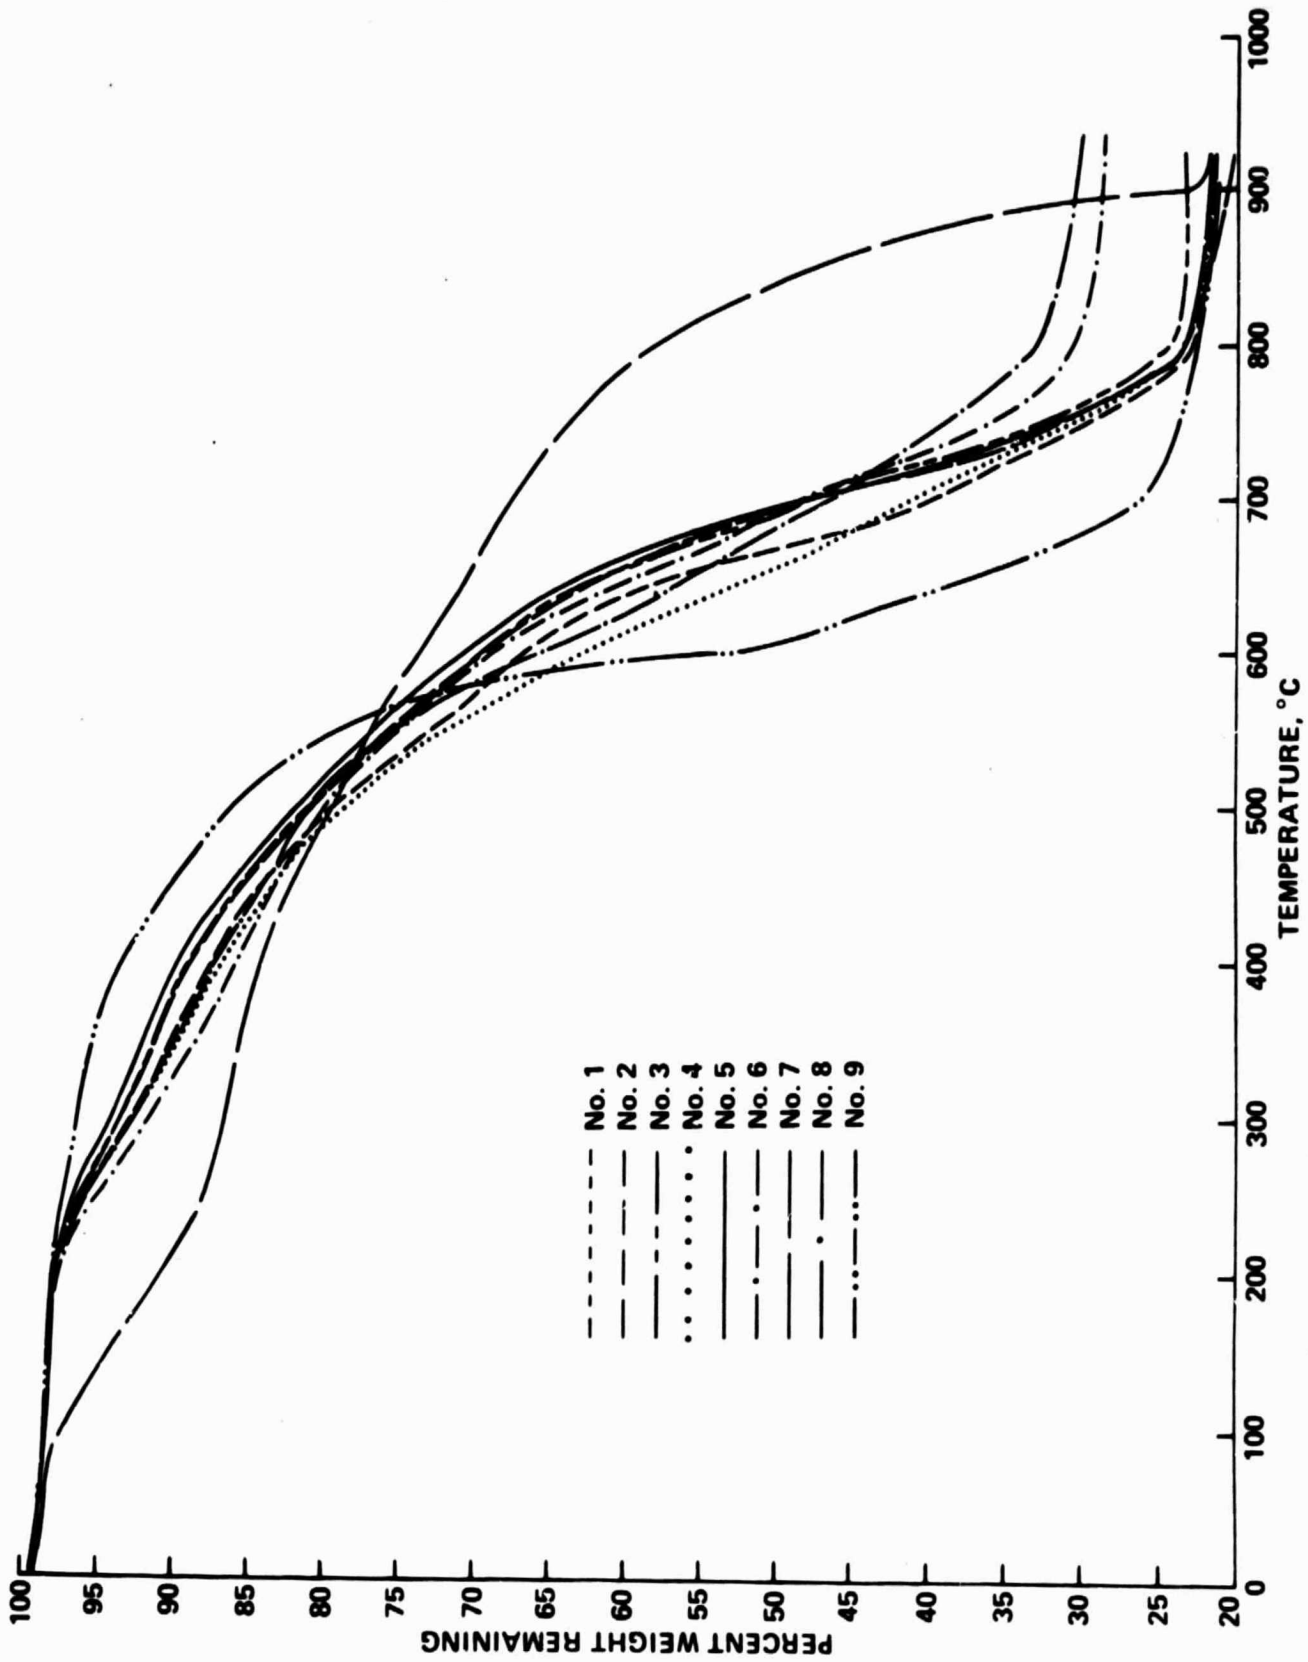


Figure 6.- Dynamic Thermograph of Composites 1-9 (heating rate 10° C/min, air).

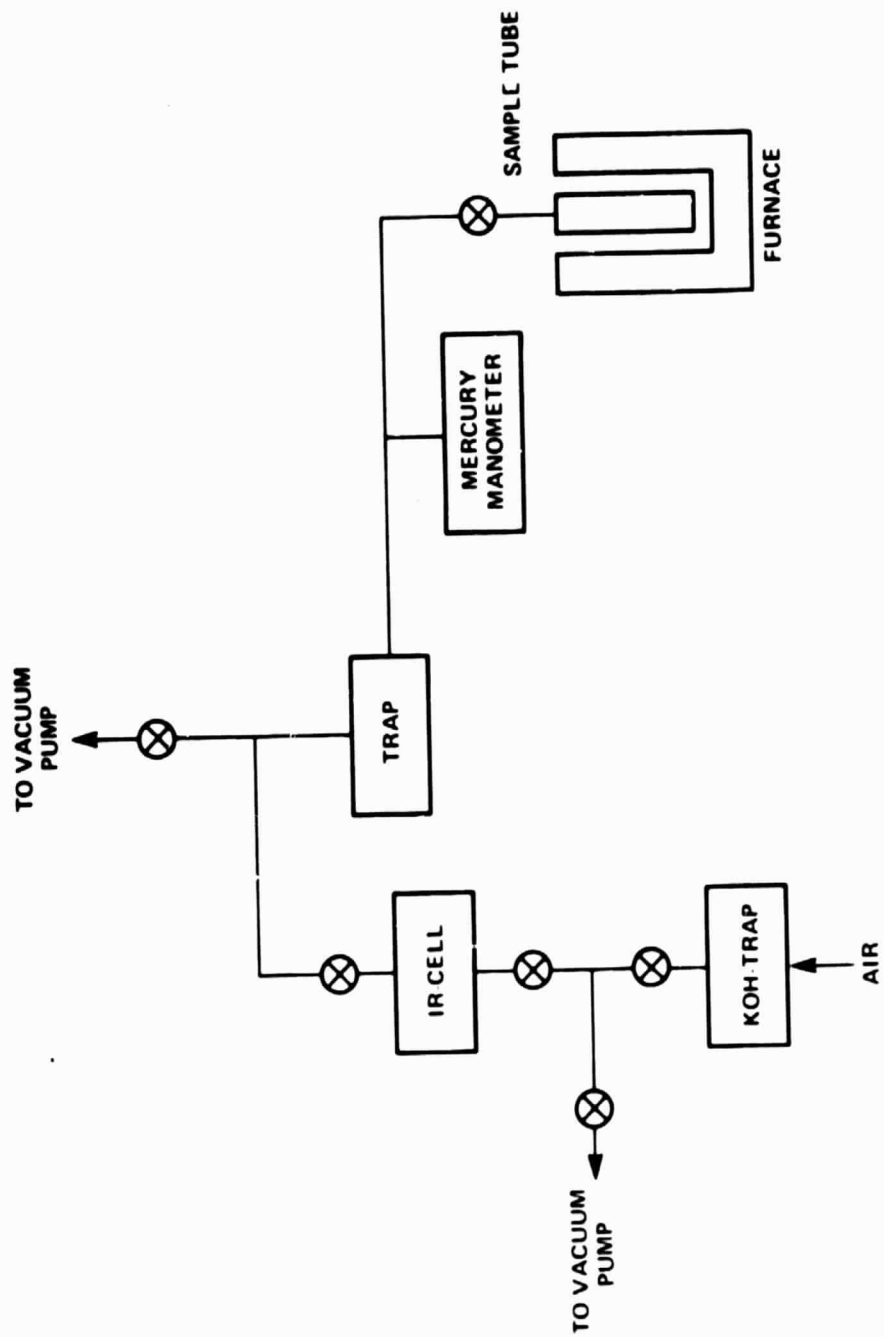


Figure 7.- Apparatus for pyrolysis of materials.

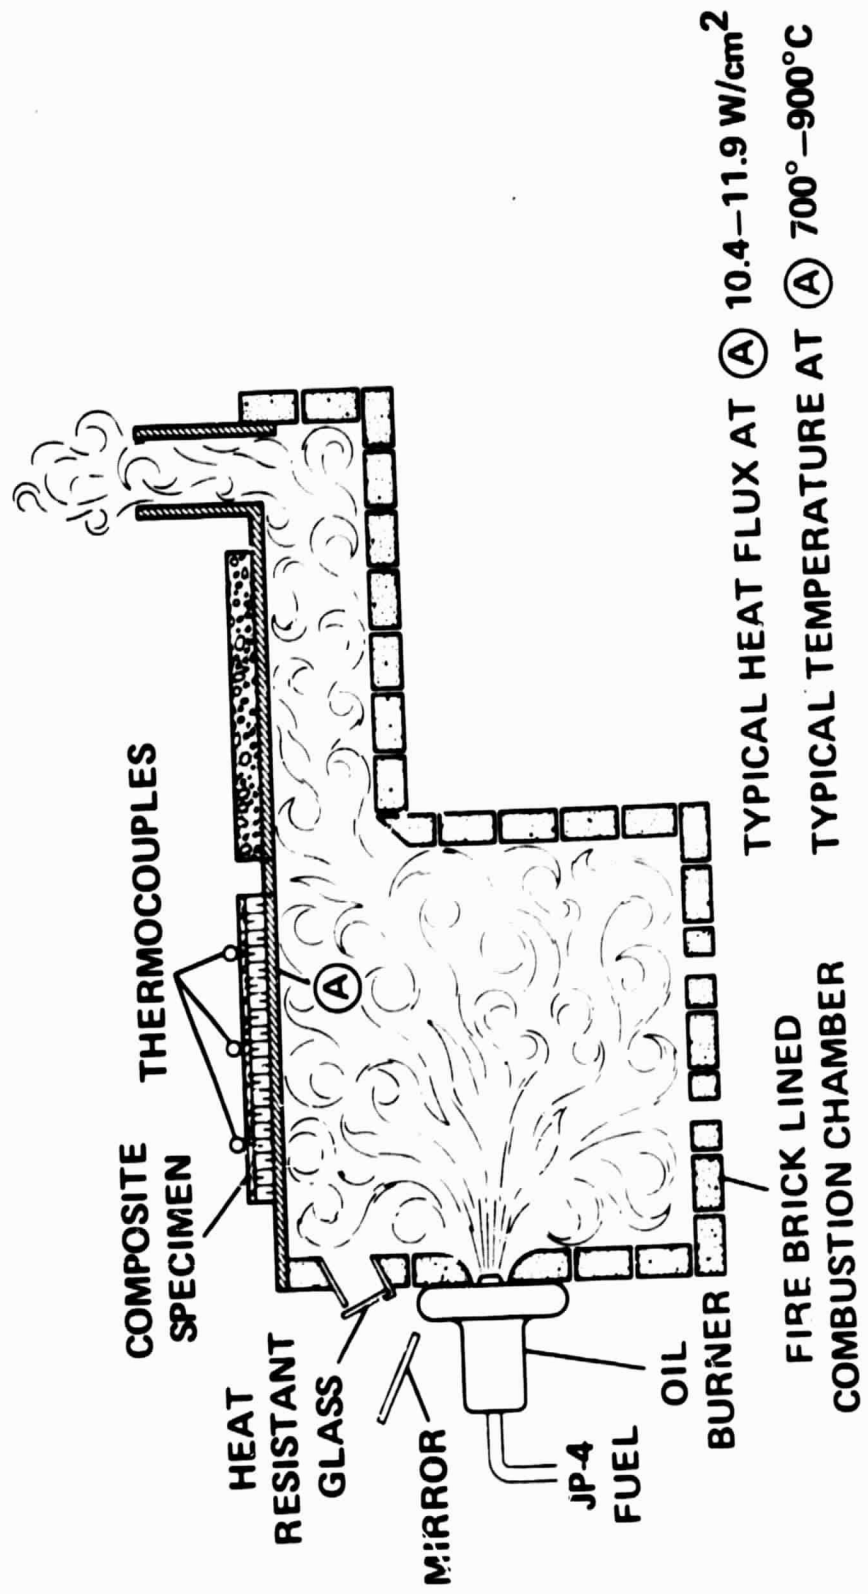


Figure 8.- NASA-Ames T-3 Thermal Efficiency Apparatus.

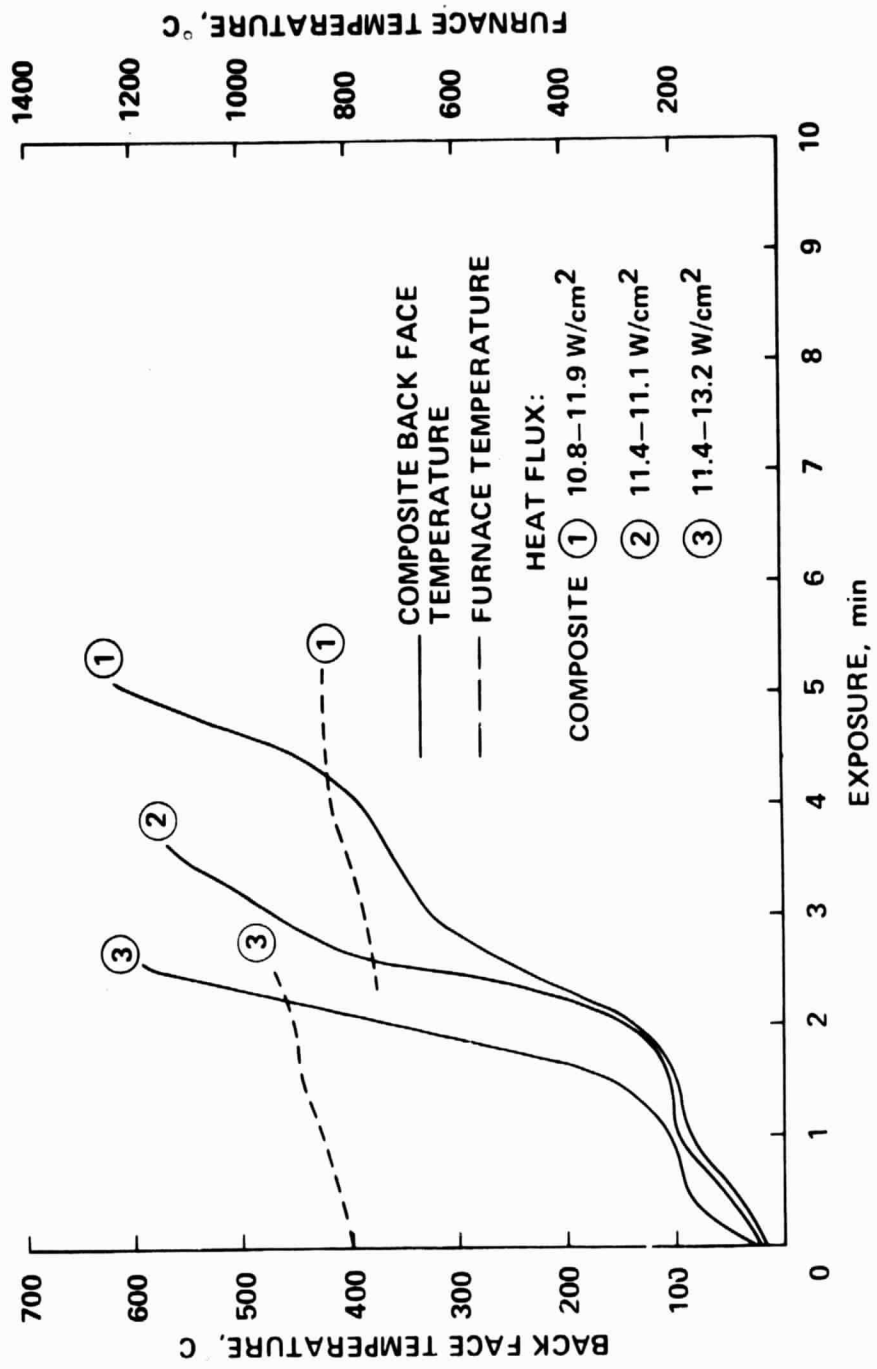


Figure 9.- Thermal Efficiency of Composites: No. 1-3.

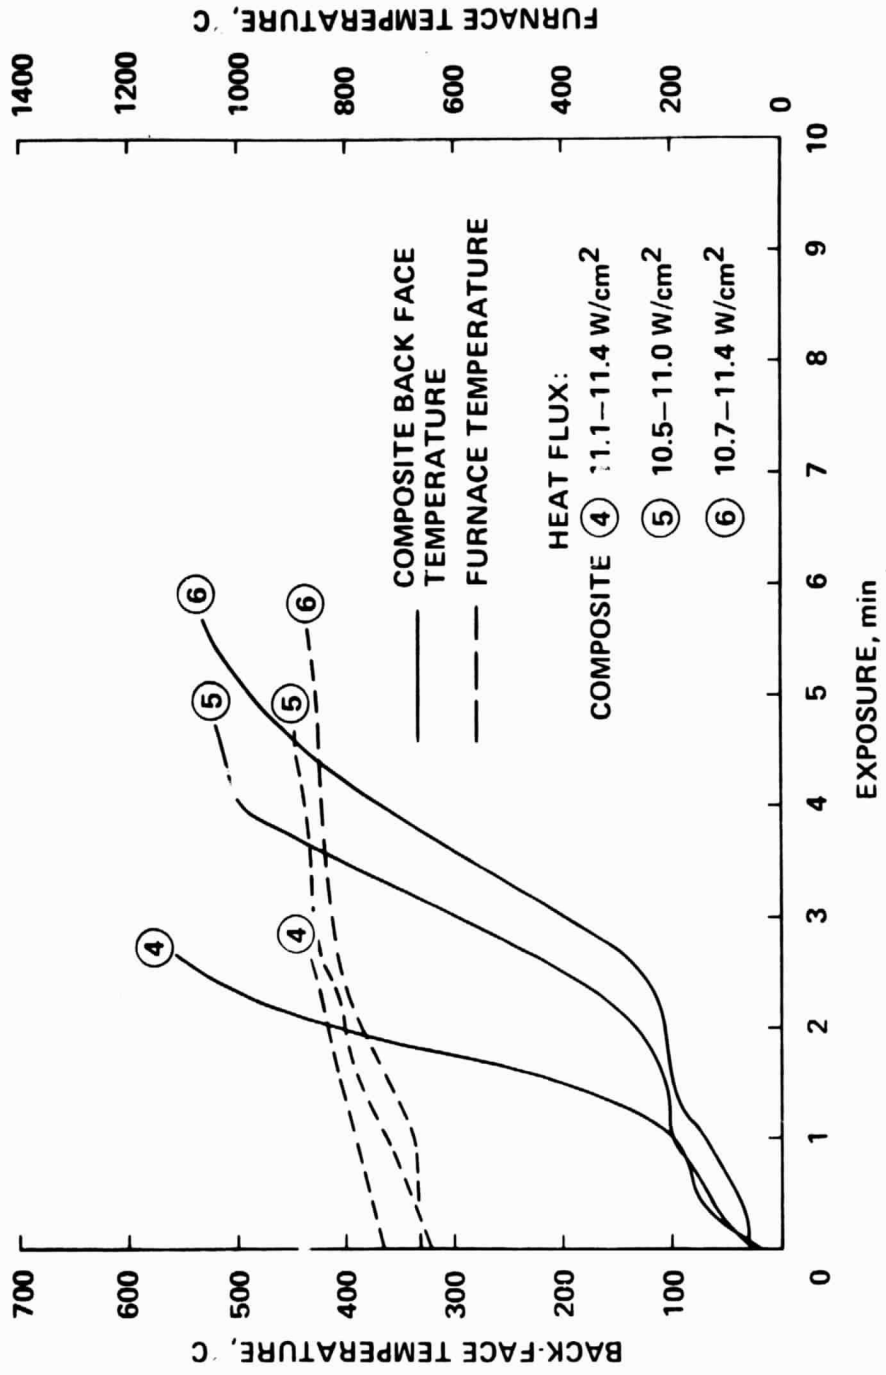


Figure 10. Thermal Efficiency of Composites: No. 4-6.



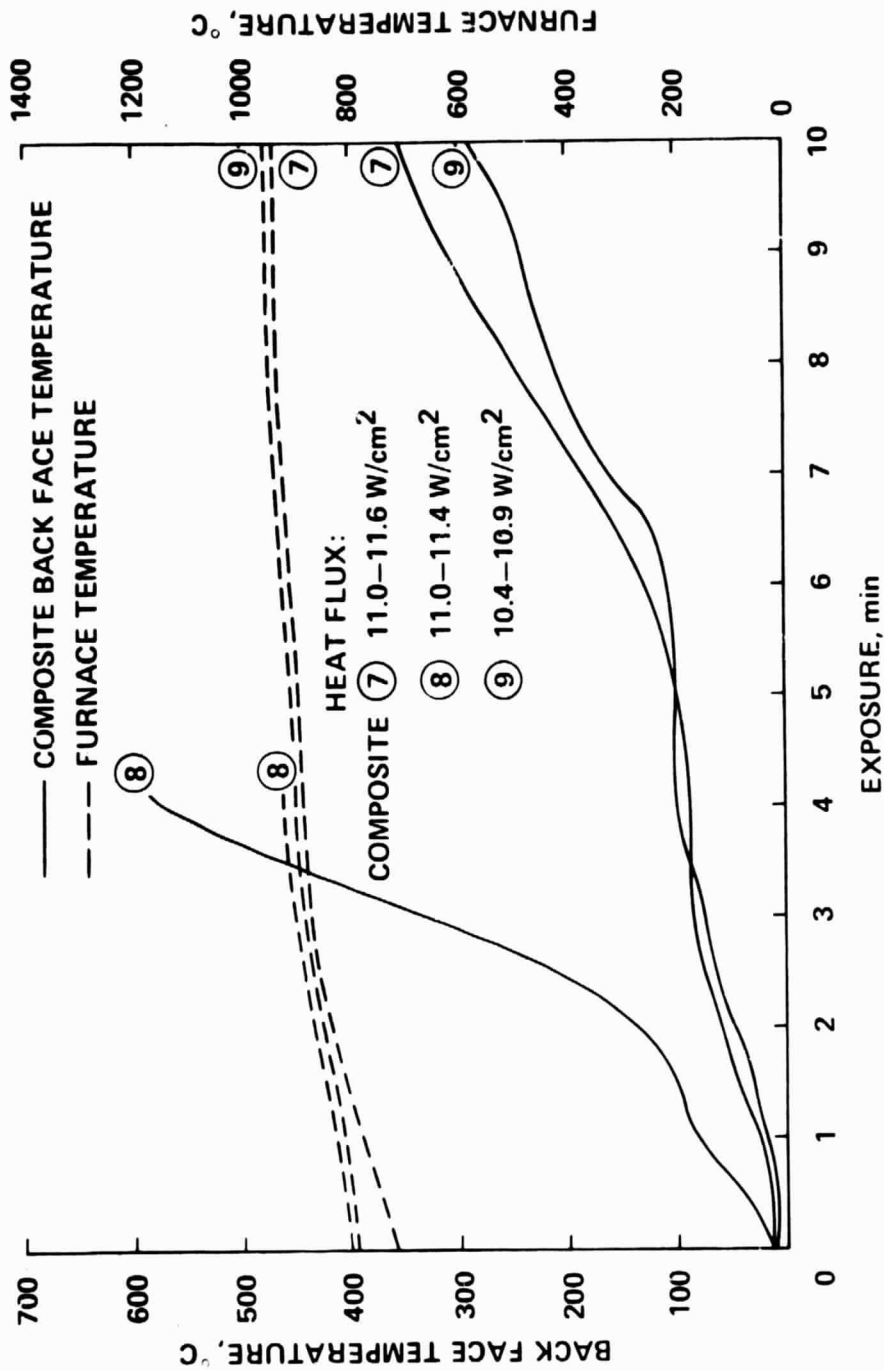


Figure 11. Thermal Efficiency of Composites: No. 7-9.

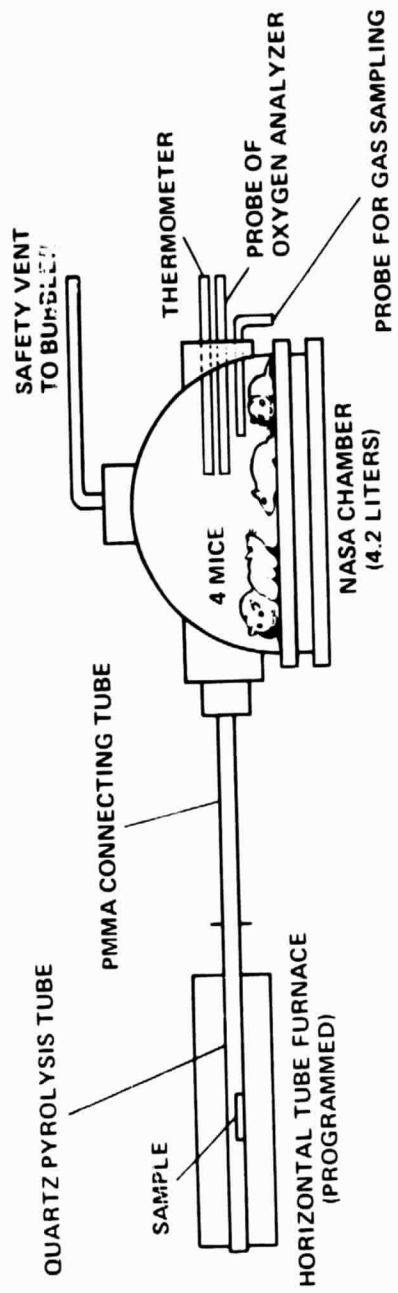


Figure 12. Pyrolysis Toxicity Apparatus.

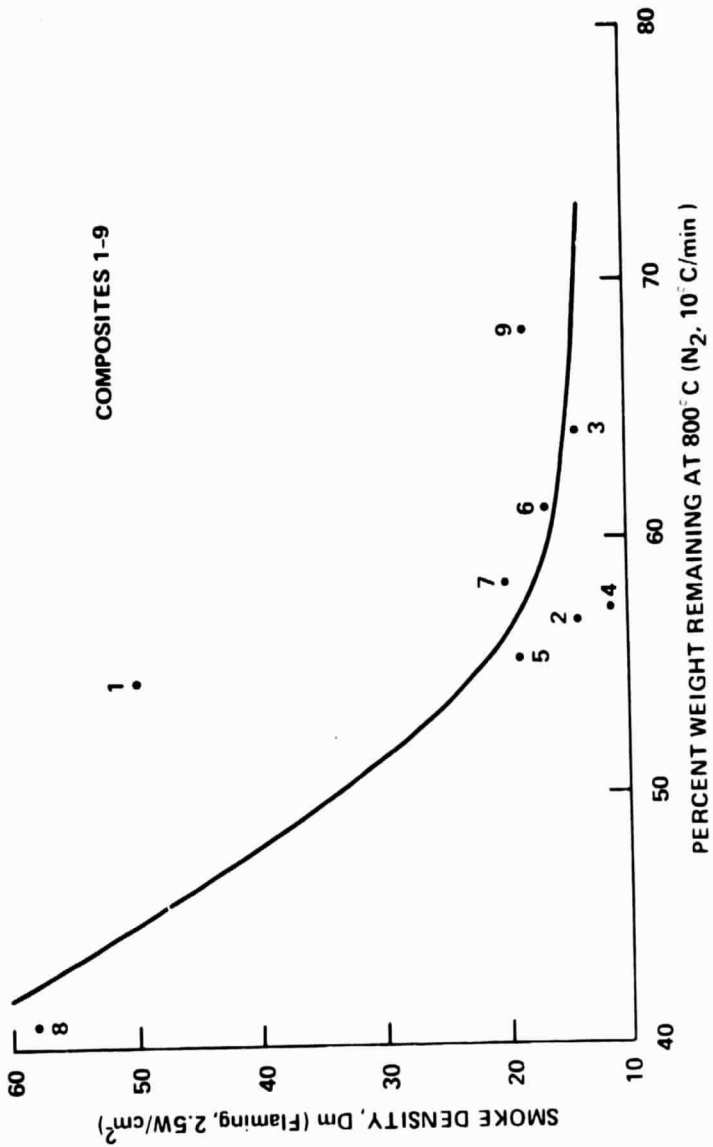


Figure 13. Effect of Char Yield of Composites on Smoke Evolution.

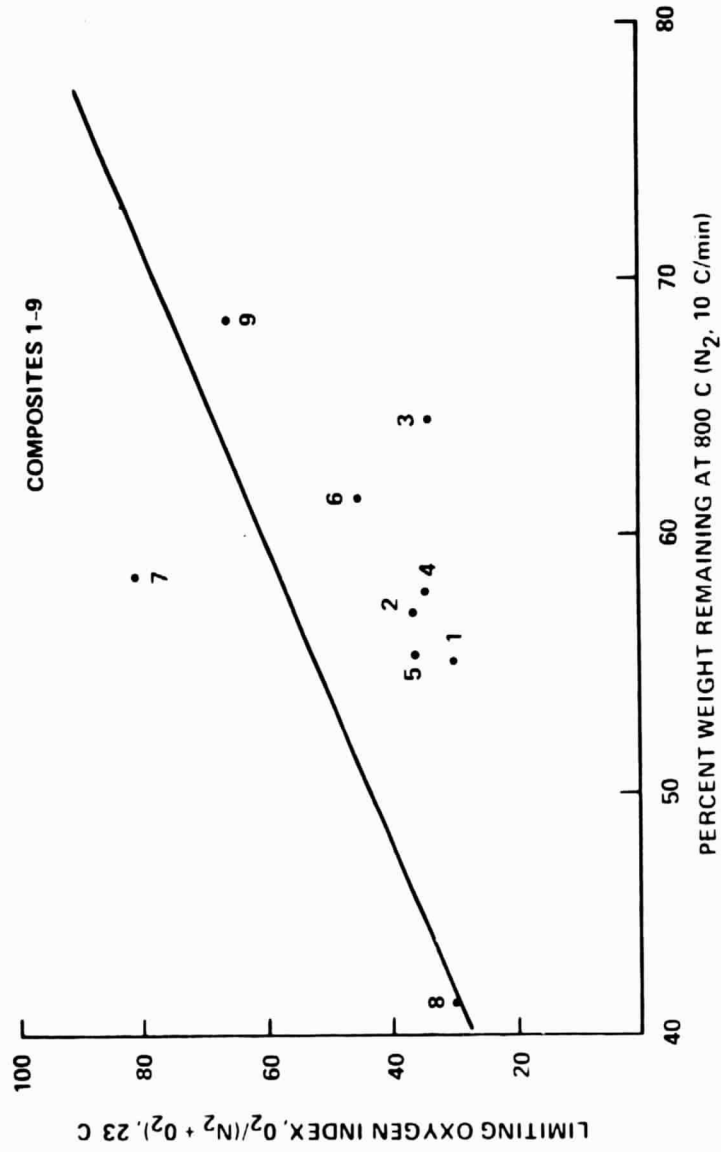


Figure 14. Effect of Char Yield of Composites on Limiting Oxygen Index.