



# Ensemble averaging stress-strain fields in polycrystalline aggregates with a constrained surface microstructure-Part 1: Computational tools and application to anisotropic elastic behaviour

Samuel Forest, Asmahana Zeghadi, Franck Nguyen, Anne-Francoise Gourgues,  
Olivier Bouaziz

## ► To cite this version:

Samuel Forest, Asmahana Zeghadi, Franck Nguyen, Anne-Francoise Gourgues, Olivier Bouaziz. Ensemble averaging stress-strain fields in polycrystalline aggregates with a constrained surface microstructure-Part 1: Computational tools and application to anisotropic elastic behaviour. Philosophical Magazine, Taylor & Francis, 2007, 87, pp.1401-1424. <10.1080/14786430601009509>. <hal-00513781>

**HAL Id: hal-00513781**

**<https://hal.archives-ouvertes.fr/hal-00513781>**

Submitted on 1 Sep 2010

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.





**Ensemble averaging stress-strain fields in polycrystalline aggregates with a constrained surface microstructure-Part 1:  
Computational tools and application to anisotropic elastic behaviour**

Journal:	<i>Philosophical Magazine &amp; Philosophical Magazine Letters</i>
Manuscript ID:	TPHM-06-Apr-0094.R1
Journal Selection:	Philosophical Magazine
Date Submitted by the Author:	21-Jun-2006
Complete List of Authors:	Forest, Samuel; Ecole Nationale Supérieure des Mines de Paris/CNRS, Centre des Matériaux UMR 7633 Zeghadi, Asmahana; EDF Nguyen, Franck; Ecole des Mines de Paris Gourgues, Anne-Francoise; Ecole des Mines de Paris Bouaziz, Olivier; Arcelor Research
Keywords:	anisotropic elasticity, polycrystalline metals
Keywords (user supplied):	ensemble average, finite element
<p>Note: The following files were submitted by the author for peer review, but cannot be converted to PDF. You must view these files (e.g. movies) online.</p>	
<p>zeghadi-part1-final.tex zeghadi-part1-final.bbl</p>	

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60



For Peer Review Only

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30

# Ensemble averaging stress–strain fields in polycrystalline aggregates with a constrained surface microstructure—Part 1: Anisotropic elastic behaviour

18 A. Zeghadi <sup>a</sup>, F. N’Guyen <sup>a</sup>, S. Forest <sup>a,\*</sup>, A.–F. Gourgues <sup>a</sup>,  
19 O. Bouaziz <sup>b</sup>,

22 <sup>a</sup>*Centre des Matériaux / Mines Paris, Paristech, CNRS UMR 7633, B.P. 87,*  
23 *91003 Evry Cedex, France*

26 <sup>b</sup>*ARCELOR Research, Voie Romaine, B.P. 30320,*  
27 *57283 Maizières-lès-Metz, France*

---

## 31 Abstract

33 The effect of three–dimensional grain morphology on the deformation at a free  
34 surface in polycrystalline aggregates is investigated by means of a large scale finite  
35 element and statistical approach. For a given 2D surface at  $z = 0$  containing 39  
36 grains with given crystal orientations, 17 random 3D polycrystalline aggregates are  
37 constructed having different 3D grain shapes and orientations except at  $z = 0$ ,  
38 based on an original 3D image analysis procedure. They are subjected to overall  
39 tensile loading conditions. The resulting stress–strain fields at the free surface  
40  $z = 0$  are analysed. Ensemble average and variance maps of the stress field at the  
41 observed surface are computed. In the case of an anisotropic elastic behaviour of  
42 the grains, fluctuations ranging between 5% and 60% are found in the equivalent  
43 stress level at a given material point of the observed surface from one realization  
44 of the microstructure to another. These results have important implications in the  
45 way of comparing finite element simulations and surface strain field measurements  
46 in metal polycrystals.

56 *Key words:* Polycrystal, Anisotropic elasticity, Ensemble average, Finite element,  
57 Copper  
58  
59  
60

## 1 Introduction

The development of field measurement methods in the past 15 years provides us with a precise knowledge of the heterogeneity of strains, stresses (via the determination of elastic strains) and lattice rotations in metallic polycrystals (Becker, 1991; Allais et al., 1994; Ziegenbein et al., 1998). The deformation of grids deposited on the surface specimen, interpreted by means of image correlation analysis, X-ray microdiffraction, and Electron Back-Scatter Diffraction (EBSD) are respectively used to evaluate the fields of total strain, elastic strain and lattice orientation at various stages of the deformation of polycrystals, with a pixel resolution below the micron scale (Mohamed et al., 1997; Delaire et al., 2000; Eberl et al., 2002; Parisot et al., 2001; Mary et al., 2005). The observation of detailed strain fields inside the individual grains for a large number of grains reveals the extreme heterogeneity of deformation due to crystal slip processes. The development of bands of intense plastic deformation crossing several grains is often reported, in addition to the strong intragranular heterogeneities induced by strain incompatibilities at grain boundaries. These now standard experimental techniques can be applied at the free surface of a polycrystal subjected to various loading conditions such as tension and shear. The analysis of grid deformation usually provides the in-plane components of the displacement field, from which in-plane components of the strain tensor can be evaluated. EBSD analysis gives the full 3D orientation map of all surface grains. Micro-diffraction analyses using for instance synchrotron radiation provide 2D maps of the 3D elastic strain tensor field for material points at the surface of polycrystals (Eberl et al., 2002).

Such field measurements can be used to validate the theoretical framework of continuum crystal plasticity settled in (Mandel, 1971; Asaro, 1983a). The results of finite element simulations based on the numerical integration of the constitutive equations for single crystals, can be compared to the corresponding experimental information (Teodosiu et al., 1993; Delaire et al., 2000; Eberl et al., 2002; Eriean and Rey, 2004; Cheong and Busso, 2005). Continuum crystal plasticity takes the crystallographic nature of plastic slip into account via a set of slip variables  $\gamma^s$  associated with each slip system  $s$ . The first finite element simulations of the elastic-viscoplastic behavior of polycrystals go back to (Miyamoto, 1972; Asaro, 1983b; Harren and Asaro, 1989; Havlicek et al., 1990; Teodosiu et al., 1993) in which

\* Corresponding author. Tel.: +33-1-60-76-30-51; Fax: +33-1-60-76-31-50  
*Email address:* samuel.forest@ensmp.fr (S. Forest).

1  
2  
3 two-dimensional analyses of the problem are proposed. With a view to more realistic simulations and  
4 more accurate comparisons with the experimental results, a trend towards 3D finite element modeling  
5 of polycrystals is observed since the early 1990s (Becker and Panchanadeeswaran, 1995; Beaudoin et al.,  
6 1995; Sarma et al., 1998; Delaire et al., 2000; Barbe et al., 2001a; Barbe et al., 2001b; Bhattacharyya  
7 et al., 2001; Eriean and Rey, 2004). The usual strategy for a direct comparison between strain field  
8 measurements and finite element results consists in producing a finite element mesh of the surface  
9 morphology of the observed grains and subjecting it to boundary conditions as close as possible to the  
10 experimental ones. A 2D finite element mesh of the grains is generally obtained starting from the EBSD  
11 map of the considered surface which simultaneously provides the orientation map of the grains and the  
12 location of grain boundaries. In most cases, the actual 3D morphology of the considered surface grains  
13 remains unknown and specific assumptions have to be made for the finite element simulations. A 3D  
14 mesh of the polycrystalline sample can be obtained by simple extension of the 2D mesh with respect to  
15 the normal direction, in the case of quasi-columnar grains (Parisot et al., 2001; Bhattacharyya et al.,  
16 2001), or by interpolating the grain shape from the intersection of the grains with the other free surfaces  
17 of the sample in the case of large recrystallized grains (Teodosiu et al., 1993; Eberl et al., 2002). **In  
18 these simulations, grain boundaries are perfect interfaces with continuity of displacement and traction  
19 vectors. No grain boundary migration is accounted for. Grain boundaries are regarded as pure sources  
20 of strain incompatibilities between grains which induce strong strain heterogeneities.**

21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34 The main problem in assessing the quality of the simulation results compared to the available experi-  
35 mental data such as strain and lattice rotation fields lies in the fact that the usually unknown actual  
36 3D morphology of the grains can significantly affect the strain and lattice rotation fields at the surface.  
37 As a result, only uncertain and incomplete validation of the continuum models can be gained from  
38 direct comparison of the experimental and simulated fields. The discrepancy between computation and  
39 observation in some grains is usually attributed to at least three reasons:

- 44 (1) Insufficient refinement of the finite element mesh; effects of mesh sensitivity have already been  
45 analysed in the references (Barbe et al., 2001a; Diard et al., 2005). Coarse meshes are sufficient to  
46 obtain a correct estimation of the overall response. In contrast, very fine meshes are required to  
47 get a detailed and converged description of the intragranular fields.
- 48 (2) Physical relevance of the constitutive equations; **the objective of the present paper is not to show  
49 the relevance of the continuum crystal plasticity model which has already been demonstrated at  
50 least in the case of large grains in multicrystals; indeed, the fact that good correlations are reported  
51 in the literature between model and field measurements when the grain morphology is exactly  
52 known (Teodosiu et al., 1993; Delaire et al., 2000; Eriean and Rey, 2004), indicates that available**

1  
2  
3 constitutive equations can be trusted, at least in the case of large grains for which size effects can  
4 be excluded.

- 5  
6 (3) Uncertainty in the actual 3D morphology of the observed grains (Becker and Panchanadeeswaran,  
7 1995; Crépin et al., 2000); it seems that no systematic study has been performed to quantify the  
8 impact of the 3D grain morphology on the fluctuations of stress and strain at a given surface of  
9 a polycrystal. At least, in (Musienko, 2005), the responses of a columnar microstructure and of a  
10 random polycrystal are compared for a given 2D grain repartition and lattice orientation map at  
11 one free surface. Huge differences in local plastic strain values at the free surface are reported at  
12 the same overall loading stage.  
13  
14  
15  
16  
17

18  
19 In the present work, a large scale computational and statistical approach is developed to give a quan-  
20 titative assessment of the bias introduced in the estimation of surface stress–strain and lattice rotation  
21 fields, by the incomplete knowledge of the 3D grain morphology below a given surface with fixed 2D  
22 grain morphology. It aims at estimating the fluctuations of plastic strain on a free surface with fixed  
23 2D grain morphology and orientations when the 3D shape of the grains below the surface are changed.  
24 This is a question often raised in the interpretation of strain field measurements at the surface of de-  
25 formed polycrystals. There is currently no precise answer in the literature to this question. For explicit  
26 comparison with experimental results, the assumption of columnar morphology is usually made in the  
27 computations. We show in the present work that this introduces a strong bias in the estimation of  
28 strain fields. To give a quantitative answer to the previous question, the following tools are needed:  
29  
30  
31  
32  
33  
34  
35

- 36  
37 (1) an image analysis algorithm to produce 3D polycrystalline aggregates with a constrained 2D mor-  
38 phology; such an algorithm has no equivalent in the literature to the knowledge of the authors;  
39  
40 (2) a statistical approach; the fluctuations can be estimated only by a sufficiently high number of  
41 simulations with different 3D grain morphologies below the constrained surface; such a strategy  
42 was not developed in the previous contributions.  
43  
44  
45

46  
47 The first part of this work is devoted to the presentation of the 3D polycrystalline microstructures  
48 obtained from a given set of surface grains and to the analysis of the stress–strain heterogeneity in the  
49 case of anisotropic linear elasticity. The case of elastoplastic crystal behaviour is analysed in part 2 of  
50 this work (Zeghadi et al., 2006). Random three–dimensional polycrystalline aggregates having different  
51 grain morphology and crystal orientations except at a given free surface are constructed and analysed  
52 in section 2. The computational tools required to perform large–scale 3D finite element analyses of the  
53 deformation of polycrystalline aggregates are presented in section 3. Precise notations regarding the  
54 statistical treatment of simulation results including volume and ensemble average and variance operators  
55  
56  
57  
58  
59  
60



1  
2  
3 are introduced in subsection 3.2. The question of the choice of the sample thickness, i.e. the number of  
4 grains within the thickness of the polycrystalline aggregates to be subjected to mechanical loading, is  
5 addressed in section 4. In section 5 the stress fields in 18 linear elastic copper polycrystalline aggregates  
6 sharing a common free surface and deformed in tension are analysed following the systematic statistical  
7 approach defined in section 3.  
8  
9  
10

## 11 12 13 14 **2 Representation of the microstructure** 15 16

17  
18 The basic model retained in this work for the morphology of polycrystals is that of Voronoi polyhedra  
19 (Barbe et al., 2001a). This is a simple and widely used model to represent equiaxed grains without  
20 special morphological texture (Barbe et al., 2001a; Diard et al., 2005). The Voronoi cells correspond  
21 to the uniform growth of grains nucleated at seeds dispersed in the 3D space according to a Poisson  
22 process. A repulsion distance is used to avoid too small grains. The objective of this section is to show  
23 how such a 3D Voronoi tessellation can be connected to a constrained surface microstructure.  
24  
25  
26  
27  
28  
29

### 30 *2.1 Original algorithm for obtaining a 3D grain distribution with a constrained surface geometry* 31 32

33  
34 In this work, the reference (free) surface of polycrystalline aggregates is composed of 39 grains labelled  
35 in figure 1. This image was generated by a section of a given set of 3D Voronoi polyhedra, but  
36 could also have been obtained from EBSD analysis (Schwartz et al., 2000; Parisot et al., 2004). The  
37 color of each surface grain corresponds to a given specific crystal orientation. The objective of the  
38 algorithm presented in this section is to produce random 3D polycrystalline microstructures that share  
39 this common reference surface at  $z = 0$ . For each realization the constructed volume is therefore located  
40 at  $0 \leq z \leq H$  where  $H$  is the thickness of the polycrystalline volume. The size of images that will  
41 be produced is  $200 \times 200 \times 200$  voxels (so  $H = 200$ ). The number of grains contained in the images is  
42 in average  $6 \times 6 \times 6 = 216$  grains. The mean grain volume is  $V_0 = 37037$  voxels. The mean grain size is  
43 conventionally taken as  $d_0 = V_0^{1/3} \simeq 33$  voxels. The construction of the aggregates is decomposed into  
44 two main stages:  
45  
46  
47  
48  
49  
50  
51

- 52  
53 (1) *Generation of the first layer of 3D grains starting from the reference free surface.* The first layer  
54 of voxels is made of the image of the constrained surface  $z = 0$  (see figure 1). It is the same for  
55 all realizations of the microstructure. The second layer of voxels is obtained from the first one by  
56 expanding or eroding each grain based on a random process. The procedure is carried out one grain  
57  
58  
59  
60

1  
2  
3 after another. The erosion of one grain and the subsequent growth of the neighboring grains are  
4 illustrated in figure 2. The initial eroded grain A is shown in figure 2(a) whereas the final state of  
5 this grain and its environment is shown in figure 2(b). Five steps were needed to reach this final  
6 shape. They are illustrated in figure 2(c). Each step corresponds to the motion of one boundary  
7 of the labeled neighbouring grains. A new grain, labeled 7 in the picture, had to be created to  
8 close this process. When a growth or reduction rate distribution has been chosen and enforced for  
9 all grains of the section, a 2D convexifying procedure is performed by replacing the obtained 2D  
10 grains by their convex envelopes. This algorithm is run again for the next layer of voxels. In the  
11 case of expanding grains, the growth rate chosen initially is kept constant for the subsequent layers  
12 until the depth  $z = d_0/2$  is reached in average. Afterwards, the sign of the growth rate is changed  
13 in order to finally close the grain. This part of the algorithm stops when all the 39 initial grains  
14 have been expanded or reduced and closed. An example of resulting microstructure is provided in  
15 figure 3(a) which shows a section perpendicular to the constrained surface. The section of 8 grains  
16 grown from the surface  $z = 0$  can be seen.

17  
18  
19  
20  
21  
22  
23  
24  
25  
26 (2) *Union of the first layer of grains with of the Voronoi tessellation.* The next step consists in gener-  
27 ating random seeds in the remaining volume of the image and in producing a Voronoi tessellation.  
28 This is done in 3D but a 2D illustration is shown in figure 3(b). The voxels of the first layer  
29 of grains constructed previously is superimposed on the Voronoi tessellation made of 216 grains  
30 by substituting the corresponding voxels. This procedure generally leads to unacceptable grain  
31 shapes just below the first layer of grains. That is why a final 3D convexifying process is carried  
32 out for all the grains except those of the first layer since they are already convex. The grains are  
33 replaced by their convex envelop; this convexifying procedure is run until all the grains in the vol-  
34 ume are convex; this may require several iterations; if the procedure does not converge, the volume  
35 is excluded. The constraint of grain convexity is introduced to avoid unrealistic grain shapes and  
36 because grains are convex in the reference Voronoi model. Figure 3(c) shows the result of the union  
37 and convexifying process in one section perpendicular to the constrained surface.  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50

51 The proposed algorithm remains heuristic and the existence of a solution for each realization of the  
52 random parameters is not ensured. In particular, the produced aggregates do not correspond strictly  
53 to a Voronoi tessellation. The surface constraint and the construction method introduce a bias in the  
54 cell distributions. Algorithms keeping the Voronoi character of the model do exist, as demonstrated in  
55 (Lantuéjoul, 2002), but turn out to be too time-consuming in the 3D case.  
56  
57  
58  
59  
60

## 2.2 Description of the obtained 3D polycrystalline aggregates

17 polycrystalline microstructures with the constrained surface of figure 1 have been produced. Six of them are shown in figure 4. The 3D images of two of them have been cut perpendicularly to the free surface along line *hline* in figure 4(a). The morphology of the grains directly below the free surface can be clearly seen. Slices perpendicular to the free surface and going through the line *hline* of figure 1 are shown for four realizations in figure 4(b). The proposed algorithm leads to strongly different grain shapes below the constrained surface from one realization to another. In particular the angle between grain boundaries and the surface  $z = 0$  can be significantly changed from one realization to another. As a result, orange grain 18 is significantly larger in the first realization of figure 4(a) than in the second one. This can be seen also on the first and fourth slices of figure 4(b). Red grain 15 is very small in the first slice of 4(b) and much larger in the fourth slice. The reverse holds for brown grain 19. These strong differences are expected to play an important role on the development of stresses at the free surface.

The characteristics of the produced microstructures can be analysed quantitatively. An histogram of grain sizes in a polycrystalline volume with constrained surface was compared to the corresponding histogram for the a realization of pure Voronoi polyhedra. The differences remain small ( $< 3\%$ ) so that the constrained microstructures do not differ essentially from Voronoi polyhedra. This statement is confirmed by the analysis of average grain size and variance in sections parallel to the constrained free surface  $z = 0$  as a function of the coordinate  $z$ . The grain size close to the free surface does not differ significantly from the size of grains far from the surface, as shown in (Zeghadi, 2005).

Finally, the constructed microstructures are available for subsequent mechanical computations carried out in the case of elasticity in this part and in the nonlinear case in part 2 of this work (Zeghadi et al., 2006). Another grain morphology will be useful to assess the results based on the previous random microstructures, namely, the columnar microstructure deduced from the surface image of figure 1 by translation along  $z$ , and shown in figure 5.

### 3 Computational methods

#### 3.1 Finite element meshing and parallel computing

All the aggregates are constrained to share the common surface at  $z = 0$ . Fixed crystal orientations are attributed to the 39 grains of the constrained surface according to table 1. They are unchanged from one realization to another. The orientations of the remaining grains in the 3D aggregates are chosen randomly and differ from one realization to another. The target crystallographic texture is isotropic.

The multiphase element technique is used to obtain a finite element mesh from the images of microstructures produced in the previous sections. This technique was initially proposed in (Lippmann et al., 1997) and extensively used for the computation of elastoplastic polycrystalline aggregates (Barbe et al., 2001a). It consists in superimposing a regular finite element grid on the image of the microstructure. The constitutive behavior at each integration point corresponds to the color of the voxel it belongs to. In the images of the polycrystalline microstructures each color indicate the crystal orientation of a grain. The constitutive equations are the same for all integration points of the mesh but the initial lattice orientation differs from grain to grain.

The finite elements used in this work are quadratic bricks with 20 nodes and 27 integration points. As a consequence of the multiphase element technique, integration points belonging to the same element may possess different crystal orientations. This is known to provide a poor description of grain boundaries. However, the quality of the description of the variables close to grain boundaries can be restored if the number of elements per grain is sufficiently high (Barbe et al., 2001b; Diard et al., 2005). An example of a regular mesh made of  $60 \times 60 \times 21$  quadratic elements superimposed on the image of a polycrystalline aggregate is shown in figure 6(a).

The numerical cost of the computations with such huge meshes is very high. The number of degrees of freedom of the typical mesh of figure 6(a) is close to 1,000,000. The resolution of such problems in reasonable time requires parallel computing. The parallel version of the finite element code Zset is presented in (Feyel et al., 1997; Z-set package, 2001). The problem is solved with the FETI (Finite Element Tearing and Interconnecting) method. The parallelisation scheme is based on a domain decomposition algorithm. The finite element mesh is thus decomposed into several domains (see for instance the decomposition into thirty sub-domains in figure 6(b)). Data exchange between the different tasks uses a PVM communication protocol. A cluster of 34 Linux PC 1.2GHz has been used in this work for the largest computation. It corresponds to 29 Go memory needed to solve the largest problem.

### 3.2 Ensemble averaging and dispersion operators

In this subsection, average and variance operators are defined, that will be applied to the mechanical field variables computed in this work. A limited domain  $V$  in the physical space is considered. The volume (spatial) average  $\langle f \rangle$  of the field quantity  $f$  over volume  $V$  is defined as

$$\langle f \rangle := \frac{1}{V} \int_V f dV \quad (1)$$

When applied to the stress field component  $\sigma_{22}$  or strain field component  $\varepsilon_{22}$ , the application of the average volume operator gives, for a given volume  $V$  :

$$\Sigma_{22} := \langle \sigma_{22} \rangle = \frac{1}{V} \int_V \sigma_{22} dV, \quad E_{22} := \langle \varepsilon_{22} \rangle = \frac{1}{V} \int_V \varepsilon_{22} dV \quad (2)$$

The ensemble averaging operator  $\bar{f}$  for  $N$  realizations of the field  $f$  is defined as

$$\bar{f} := \frac{1}{N} \sum_{i=1}^N f^i \quad (3)$$

where  $f^i$  is the  $i^{\text{th}}$  realization of  $f$ . This operator will be applied to the von Mises equivalent stress, at a material point  $\underline{x}$  for  $N$  realizations:

$$\bar{\sigma}_{eq}(\underline{x}) := \frac{1}{N} \sum_{i=1}^N \sigma_{eq}^i(\underline{x}), \quad \text{with} \quad \sigma_{eq} := \sqrt{\frac{3}{2} \boldsymbol{\sigma}^{dev} : \boldsymbol{\sigma}^{dev}} \quad (4)$$

where  $\boldsymbol{\sigma}^{dev}$  is the deviatoric part of the stress tensor  $\boldsymbol{\sigma}$ . Ensemble averaging can also be applied to volume averaged quantities such as the global stress component  $\Sigma_{22}$  :

$$\bar{\Sigma}_{22} := \frac{1}{N} \sum_{i=1}^N \Sigma_{22}^i = \frac{1}{N} \sum_{i=1}^N \langle \sigma_{22} \rangle_i = \frac{1}{N} \sum_{i=1}^N \frac{1}{V_i} \int_{V_i} \sigma_{22}^i dV \quad (5)$$

where  $\sigma_{22}^i$  is the  $i^{\text{th}}$  realization of the field  $\sigma_{22}(\underline{x})$ . The variance of a random variable  $f$  is denoted by  $D(f)$ . The relative variance is obtained by dividing the variance by the ensemble average value:

$$D(f) := \sqrt{\frac{1}{N} \sum_{i=1}^N (f^i - \bar{f})^2}, \quad \epsilon(f) = \frac{D(f)}{\bar{f}} \quad (6)$$

The square of the variance of the von Mises equivalent stress and its relative variance at point  $\underline{\mathbf{x}}$  are therefore

$$D^2(\sigma_{eq}(\underline{\mathbf{x}})) = \frac{1}{N} \sum_{i=1}^N (\sigma_{eq}^i(\underline{\mathbf{x}}) - \overline{\sigma_{eq}}(\underline{\mathbf{x}}))^2, \quad \epsilon(\sigma_{eq}(\underline{\mathbf{x}})) = \frac{D(\sigma_{eq}(\underline{\mathbf{x}}))}{\overline{\sigma_{eq}}(\underline{\mathbf{x}})} \quad (7)$$

#### 4 Estimating the range of elastic stresses

In this section, several characteristics of the finite element computations to be performed in section 5.1 are settled, namely, boundary conditions, mesh density and sample thickness. The latter issue is of strong mechanical importance: How many grains within the thickness of the sample do affect the stress field at the constrained surface?

##### 4.1 Position of the boundary value problem

All considered polycrystalline aggregates are subjected to pure tension using mixed homogeneous boundary conditions. Tension is prescribed along direction  $y$ . The displacement component  $u_2$  is zero at the bottom surface  $y = 0$  and prescribed at all nodes of the top surface  $y = L$ ,  $L$  being the length of the sample. All lateral surfaces, including the constrained surface, are free of forces. As a result of these boundary conditions, for all realizations of the microstructure, all components of the mean stress tensor  $\underline{\Sigma}$  vanish, except  $\Sigma_{22}$ . The boundary conditions are summarized in figure 7. The grains of the polycrystalline aggregates are taken to be copper single crystals. Their mechanical behavior is assumed here to be purely elastic. The cubic elasticity of copper single crystals is characterized by the three moduli

$$C_{11} = 168400 \text{ MPa}, \quad C_{12} = 121400 \text{ MPa}, \quad C_{44} = 75390 \text{ MPa} \quad (8)$$

according to (Gairola and Kröner, 1981). The corresponding value of the anisotropy coefficient  $a = 2C_{44}/(C_{11} - C_{12})$  is 3.2. This rather strong anisotropy is responsible for the non homogeneous deformation of polycrystalline copper aggregates in the elastic regime.

#### 4.2 Influence of mesh size

The finite element mesh size must be sufficiently small to ensure the convergence of the results and large enough to make the computations tractable. Convergence must be tested at both global and local levels. For this purpose, the effect of mesh refinement was studied for one particular 3D polycrystalline aggregate containing 52 grains. Ten different mesh densities were tested for this specific aggregate. The number of degrees of freedom is equal to the number of nodes multiplied by three, i.e. the number of displacement components. It was varied from 53,847 for the coarsest mesh up to 1,741,833 for the finest one. For each computation an apparent Young's modulus can be defined as

$$E^{app} = \frac{\Sigma_{22}}{E_{22}} = \frac{\langle \sigma_{22} \rangle}{\langle \varepsilon_{22} \rangle} \quad (9)$$

The apparent Young's modulus was studied as a function of mesh size in (Zeghadi, 2005). The analysis shows the convergence of the apparent Young's modulus for increasing number of degrees of freedom. For more than 100,000 degrees of freedom, the apparent Young's modulus does not vary by more than 0.3%.

Since we are interested in an accurate description of the intragranular mechanical fields, the convergence of the results with respect to mesh density must also be tested at the local level. For that purpose, the normalized stress profiles along a line on a free surface were plotted for the same aggregate and three mesh refinements in figure 8. The differences mainly arise close to grain boundaries. To ensure a proper description of these critical regions, a mesh density of 11,300 d.o.f. (degree of freedom) per grain in average was finally chosen, which is an intermediate value between the two finest meshes used in this section. As a result, the number of degrees of freedom in the computations presented in the sequel is proportional to the number of grains considered.

#### 4.3 Number of grains within the thickness

The sample thickness is also the result of a compromise. The number of grains within the thickness must be large enough for the stress-strain field at the constrained free surface to be practically unaffected by a further increase of the thickness. It must however be kept as small as possible for the computation to remain tractable. This section therefore addresses a longstanding question of the mechanics of polycrystals: What is the range of stress-strain fields in polycrystals? This question is treated here in the case of anisotropic elasticity. The question can be rephrased as follows. For a polycrystalline

1  
2  
3 lamella in tension with a given free surface of observation, it is intuitive that the stress–strain field at  
4 this surface will become stationary as the sample thickness is gradually increased. What is the critical  
5 thickness and the corresponding number of grains required to reach this stationary field? For that  
6 purpose, three polycrystalline aggregates sharing the same surface  $z = 0$  but with distinct thicknesses  
7 were taken out of the same 3D microstructure image:  
8  
9  
10

- 11 • one grain in the thickness in average (in fact 0.7 grain in average), leading to a mesh containing  
12  $60 \times 60 \times 7$  quadratic elements, i.e. 343,125 d.o.f.
- 13 • 1.5 grains in the thickness in average (in fact 1.4 grains in average), leading to a mesh containing  
14  $60 \times 60 \times 14$  quadratic elements, i.e. 653,127 d.o.f.
- 15 • two grains in the thickness in average (in fact 2.1 grains in average), leading to a mesh containing  
16  $60 \times 60 \times 21$  quadratic elements, i.e. 963,129 d.o.f.

17  
18  
19 The three samples were subjected to simple tension and the resulting stress fields at the free surface were  
20 observed. Figure 9 shows the corresponding equivalent von Mises stress profiles along a line belonging  
21 to the constrained free surface. The local stress values turn out to only slightly depend on the sample  
22 thickness. The differences obtained for 1.5 and 2 grains within the thickness are less than 3%. In the  
23 computations presented in this work, the sample thickness will therefore be kept to two grains within  
24 the thickness in average. This result indicates that the spatial range of elastic stresses is rather low. Its  
25 order of magnitude is of about two grains.  
26  
27

28  
29 Finally, the 17 realizations of polycrystalline microstructures with the constrained surface geometry of  
30 figure 1 are meshed according to the mesh density determined in section 4.2. This corresponds to a  
31 mesh containing  $60 \times 60 \times 21$  quadratic elements, i.e. 963129 d.o.f. These meshed microstructures are  
32 2–grain thick in average and contain 85 grains in average with a variance of 9 grains.  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48

## 49 **5 Ensemble averaging stress fields at a given surface of elastic copper polycrystals**

50  
51  
52 The results of the 17 tensile tests performed numerically on the polycrystalline aggregates with a  
53 constrained free surface are presented and commented. The ensemble average and variance operators  
54 are then applied to the stress field at the constrained free surface. This gathered information fully  
55 characterizes the sensitivity of surface grains to their 3D environment.  
56  
57  
58  
59  
60



### 5.1 *Stress–strain heterogeneities at the common free surface*

The applied mean strain  $E_{22}$  was 0.01. However, within the framework of linear elasticity, normalized stress distributions contain the whole information that can be extracted from the computations. The normalized von Mises equivalent stress maps at the constrained free surface are shown for four random polycrystalline aggregates in figures 10(a) to (d).

The first striking feature of all the simulations is that stress concentrations systematically occur close to grain boundaries which represent the main sources of strain incompatibilities in anisotropic elastic polycrystals. Stress concentration factors greater than 2.3 are observed at the free surface near grain boundaries. As a result, the stress distribution patterns are intimately related to the grain morphology. This feature of polycrystalline anisotropic elasticity has been documented in literature especially in the case of cubic and hexagonal symmetry: cubic elasticity in (Quilici and Cailletaud, 1999; Nygård, 2003), zinc polycrystals in (Barbe et al., 2001c; Parisot et al., 2004) and zirconium alloy polycrystals in (Diard et al., 2005). This effect is not an artifact due to the multiphase element meshing technique, as checked e.g. in (Barbe et al., 2001b; Diard et al., 2002; Nygård, 2003; Diard et al., 2005). Note also that the zones with enhanced stress levels generally extend far beyond the first row of elements close to the grain boundaries and affected by the multiphase element technique.

The second striking result of these simulations is the strong differences observed in the stress fields at the constrained free surface from one realization to another. In the realization of figure 10(d), the local stress concentration factors in grain 27 are mostly lower than 1.5. In contrast, a large zone of stress concentration larger than 2 is observed in the same grain in realization 10(c). Almost one half of grain 23 displays stress concentration factors higher than 1.5 in the realizations 10(a) to (c). They are always smaller than 1.4 in the same grain for the realization 10(d). The stress fields have common features, in particular a strong strain incompatibility at the junction between the grains 22–27–28–23–18 situated in the middle of the surface. It must be recalled that the initial crystal orientation of all the surface grains 1 to 39 of figure 1 is the same in all the finite element computations. As a result, the differences in stress observed at the free surface from one realization to another are solely due to the variation of grain shape below the surface.

Figure 10(e) shows the stress concentration map obtained with the columnar grains of figure 5. The stress field is found to be smoother than for the random polycrystals. In particular, it is more homogeneous inside the grains. Stress concentration takes place at several grain boundaries but the extent of strain incompatibility is significantly smaller than for the random polycrystals. Minimal and max-

1  
2  
3 imal values are found to be closer from each other in this columnar polycrystal. Note that the same  
4 finite element meshes have been used for the columnar and random microstructures so that no bias is  
5 introduced by the mesh.  
6  
7

8  
9 The fluctuations from one realization to another can be analysed more quantitatively by plotting the  
10 stress concentration values along the horizontal line *hline* and the vertical line *vline* of figure 1. These  
11 profiles are shown in figures 11(a) and (b) for eight realizations. The positions of the grain boundaries  
12 crossed by the two lines are marked by vertical lines in the plots. The stress peaks close to grain  
13 boundaries are clearly visible. The stress level is almost constant along *hline* in the large grains  
14 and 18 for realizations 1, 3 and 4. In contrast, a steep stress gradient is observed in the same grains  
15 for realization 2. The reason for such differences is the difference in grain geometry. This fact will be  
16 illustrated in detail by comparing the different environments of a specific grain in the section 4 of the  
17 part 2 of this work in the case of linear and nonlinear behavior (Zeghadi et al., 2006). Pronounced  
18 stress gradients are generally characteristic of smaller grain segments, especially along *vline*. In a given  
19 grain, the average stress level can vary by a factor of 2 from one realization to another. A systematic  
20 statistical analysis of these results is presented in the next subsection.  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30

## 31 5.2 Ensemble averages and dispersion 32

33  
34 Each material point  $P(\underline{x})$  of the constrained free surface of figure 1 experiences various stress states  
35 depending on the specific realization. In statistical physics, one usually considers the ensemble average  
36 of the phase state at a material point and the corresponding variance (Beran, 1968; Kröner, 1972;  
37 Jeulin and Ostoja-Starzewski, 2001). In this work, we present the ensemble averaged field of von Mises  
38 equivalent stresses  $\overline{\sigma_{eq}}(\underline{x})$  computed according to formula (4) where  $N = 17$  has to be substituted. A  
39 schematic view of this ensemble averaging procedure is shown in figure 12.  
40  
41  
42  
43  
44  
45

46 The map of the ensemble averaged field of von Mises equivalent stresses at the free surface is shown in  
47 figure 13(a). As a result of the averaging process, the ensemble averaged stress field is smoother than  
48 for the individual realizations. However, stress concentrations still remain with values ranging from  
49 0.3 to 4. The averaged stress field is not quasi-uniform, because the grain morphology and the crystal  
50 orientations at the free surface do not vary from one realization to another. The obtained averaged  
51 stress field therefore reveals the main effect of grain boundaries of the free surface. This corresponds to  
52 a kind of effective behavior of the observed surface. For comparison, the same averaging procedure has  
53 been applied to the rear free surface  $z = H$  where both grain shape and grain orientation vary from one  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 realization to another. In this case, the averaged stress field is uniform and equal to  $\overline{\Sigma_{22}}$  with fluctuations  
4 smaller than 5% which correspond to a relative variance of  $\epsilon = 0.05/\sqrt{17} = 1.2\%$  in the estimation of  
5 the mean. The found mean apparent stiffness is in fact an estimation of the effective behavior of copper  
6 polycrystals (Nygårds, 2003). The ensemble averaged stress map of figure 13(a) shows a central zone of  
7 the free surface, made of the grains 27–28–23–18, where the stress concentration factors are the highest,  
8 reaching values as high as 2 to 2.5. It can be noted also that the mixed homogeneous conditions applied  
9 at the top and bottom do not introduce artificially high stress concentrations in average. The same  
10 holds for the lateral free surfaces.  
11  
12  
13  
14  
15  
16

17 Figure 14 shows the ensemble averaged equivalent stress along line *hline*. The stress turns out to be  
18 rather homogeneous in the 5 grains crossed by the line. The stress concentration factors take the values  
19 0.8, 1.3 and 1. Grain 18 is the most deformed one in average. The high stress levels in some grains  
20 indicate that stress concentration does not occur close to grain boundaries only.  
21  
22  
23  
24

25 The ensemble averaged stress field is to indicate in which grains of the given surface the probability  
26 of strong stress concentration is the highest. In the context of experimental strain field measurements,  
27 this map gives the most relevant zone for the deposition of a micro-grid (Allais et al., 1994; Doumalin  
28 et al., 2003).  
29  
30  
31

32 The most interesting result of these computations is the map of the relative variance of local stresses  
33  $D(\overline{\sigma_{eq}}(\underline{x}))/\overline{\sigma_{eq}}(\underline{x})$ , shown in figure 13(b). This map shows that, locally, the stress level can fluctuate  
34 around the mean value from 5% up to 60%, from one realization to another. These are the minimal and  
35 maximal values of the local relative variance. Two main sources of dispersion can be recognized. Firstly,  
36 the grain boundaries, as already noticed, are sources of stress variations from one realization to another.  
37 Most regions close to grain boundaries are red in the map of figure 13(b). This can be explained by  
38 the fact that the change in position of grain boundary plane below the surface from one realization to  
39 another leads to the strongest variations of local stress levels. Secondly, the top and bottom lines where  
40 the displacement boundary conditions are prescribed also display high levels of stress variance. The  
41 constrained displacement associated with the changes of the underlying microstructure leads to marked  
42 strain incompatibilities and strongly different local stress levels from one realization to another.  
43  
44  
45  
46  
47  
48  
49  
50

51 The intervals of confidence plotted on the curve giving the ensemble averaged stresses along *hline* in  
52 figure 14 show however that large scatter is observed at, but is not limited to grain boundaries. In the  
53 core of grains 18 and 15, the local stress concentration factor can vary by  $\pm 20\%$  from one realization  
54 to another. The relative variance also gives information about the precision of the estimated ensemble  
55 average field. By dividing the local relative variance of the stress by  $\sqrt{17}$ , the square-root of the number  
56  
57  
58  
59  
60

of considered realizations, according to standard theory of samples, an estimation of the precision in the evaluation of the local mean is obtained. In the blue regions of the figure 13(b), the precision in the evaluation of the local stress level given in figure 13(a) is better than 2.5%. In contrast, in the red regions where large fluctuations were observed, the precision may not be better than 7%. If an improved precision is wanted, a larger number of realizations must be considered.

The stress field obtained for columnar grains shown in figure 10(e) is rather similar to the smooth ensemble average field of figure 13(a) for random microstructures. However, this cannot be seen as a general result since similar computations with different lattice orientations should be performed. In particular, this statement does not hold in the case of elastoplasticity. This will be shown in part 2 (Zeghadi et al., 2006).

## 6 Conclusions

The main conclusions of the first part of this work are the following:

- (1) Polycrystalline aggregates containing 85 grains in average with different grain shapes and crystal orientations, except at one free surface where the 2D grain shape and initial lattice orientation were fixed *a priori*, have been constructed based on 3D image analysis. The obtained morphology does not significantly depart from standard Voronoi tessellation. The algorithm can be applied to real images of equiaxed grains obtained by EBSD.
- (2) 17 samples having one free surface with 39 grains in common have been subjected to overall tensile deformation assuming an anisotropic elastic response of the grains and taking the cubic elastic moduli of pure single crystal copper into account. The equivalent von Mises stress fields at the free surface with fixed microstructure were ensemble averaged in order to determine the regions where the presence of high stresses is most probable. High stress levels are observed in a central region of the surface close to 5 grain boundaries. In anisotropic elasticity, strain incompatibilities between grains systematically result in higher equivalent stresses close to grain boundaries, whatever the shape of the 3D grains.
- (3) The variance of the surface stress field from one realization to another gives a field information about fluctuations. An interval of confidence of  $\pm 20\%$  around the local average can be attached to most material points at the free surface, even far from grain boundaries. Higher fluctuations of more than 40% and reaching 60% are generally observed close to grain boundaries.
- (4) A columnar grain morphology was considered in the analysis as a reference frequently used in liter-

1  
2  
3 ature in the absence of information on 3D grain morphology. In the special case of the constrained  
4 2D microstructure, the equivalent stress field induced by the tensile deformation of the columnar  
5 grains was found to be smoother than for random 3D grain shapes. This stress field is quite similar  
6 to the ensemble averaged stress field obtained from the 17 random aggregates, especially in the  
7 central zone with high stress levels.  
8  
9  
10

11  
12 The morphology of underlying grains in the volume has a major impact on the local stress–strain fields  
13 obtained on a given polycrystalline free surface in anisotropic elasticity. This a question often raised in  
14 the interpretation of strain field measurements at the surface of deformed polycrystals. Considering only  
15 one special realization introduces a bias in the detection of the region of high stress levels. Considering  
16 only a columnar microstructure leads to an underestimation of stress gradients. Even though most  
17 authors are aware of the role that 3D grain morphology may play in the development of stress fields at  
18 a free surface, no quantitative assessment of these fluctuations was available in literature.  
19  
20  
21  
22  
23

24  
25 The stress field from a linear analysis can be used to predict the inception of plastic slip in metal  
26 polycrystals. The links between elastic strain incompatibilities from grain to grain and the onset  
27 of plasticity have been studied from the experimental point of view for instance in (Hashimoto and  
28 Margolin, 1983). The analysis of elastic strain fields can also be used to assess the quality of recent  
29 homogenization based polycrystal models providing estimations of mean fields but also of fluctuations  
30 in elastic polycrystalline aggregates (Letouzé et al., 2002). One may expect from this elasticity analysis  
31 that the activation of slip systems during subsequent plastic deformation of the material will differ  
32 significantly from one realization to another. It is the objective of the second part of this work to  
33 quantitatively assess the fluctuations in the plastic strain field observed at a given free surface by  
34 changing the 3D grain morphology of the underlying microstructure (Zeghadi et al., 2006).  
35  
36  
37  
38  
39  
40  
41  
42

## 43 44 References

- 45  
46 ALLAIS L., BORNERT M., BRETHERAU T., AND CALDEMAISON D. (1994). *Experimental characteri-*  
47 *zation of the local strain field in a heterogeneous elastoplastic material.* Acta Materialia, vol. 42,  
48 pp 3865–3880.  
49  
50 ASARO R.J. (1983a). *Crystal plasticity.* J. Appl. Mech., vol. 50, pp 921–934.  
51  
52 ASARO R.J. (1983b). *Micromechanics of crystals and polycrystals.* Advances in Appl. Mech., vol. 23,  
53 pp 1–115.  
54  
55 BARBE F., DECKER L., JEULIN D., AND CAILLETAUD G. (2001a). *Intergranular and intragranular*  
56 *behavior of polycrystalline aggregates. Part 1: FE model.* International Journal of Plasticity, vol.  
57  
58  
59  
60

- 1  
2  
3 17, pp 513–536.
- 4  
5 BARBE F., FOREST S., AND CAILLETAUD G. (2001b). *Intergranular and intragranular behavior of*  
6 *polycrystalline aggregates. Part 2 : Results.* Int. J. Plasticity, vol. 17, pp 537–563.
- 7  
8 BARBE F., PARISOT R., FOREST S., AND CAILLETAUD G. (2001c). *Calibrating a homogenized poly-*  
9 *crystal model from large scale FE computations of polycrystalline aggregates.* Journal de Physique  
10 IV, vol. 11, pp Pr5–277–284.
- 11  
12  
13 BEAUDOIN A.J., DAWSON P.R., MATHUR K.K., AND KOCKS U.F. (1995). *A hybrid finite element*  
14 *formulation for polycrystal plasticity with consideration of macrostructural and microstructural*  
15 *linking.* Int. J. Plast., vol. 11, pp 501–521.
- 16  
17  
18 BECKER R. (1991). *Analysis of texture evolution in channel die compression - I. Effects of grain*  
19 *interaction.* Acta Metall. Mater., vol. 39, pp 1211–1230.
- 20  
21 BECKER R. AND PANCHANADEESWARAN S. (1995). *Effect of grain interactions on deformation and*  
22 *local textures in polycrystals.* Acta Metall. Mater, vol. 43, pp 2701–2719.
- 23  
24 BERAN M.J. (1968). *Statistical Continuum Theories.* Intersciences Publishers, New York.
- 25  
26 BHATTACHARYYA A., EL-DANAF E., KALIDINDI S.R., AND DOHERTY R.D. (2001). *Evolution of*  
27 *grain-scale microstructure during large strain simple compression of polycrystalline aluminium with*  
28 *quasi columnar grains : OIM measurements and numerical simulations.* Acta Metall. Mater, vol.  
29 17, pp 861–883.
- 30  
31  
32 CHEONG K.S. AND BUSSO E.P. (2005). *Discrete dislocation density modelling of single phase FCC*  
33 *polycrystal aggregates.* Acta Materialia, vol. 52, pp 5665–5675.
- 34  
35 CRÉPIN J., BRETHERAU T., CALDEMAISON D., AND FERRER F. (2000). *Low cycle fatigue behaviour of*  
36 *treated zirconium: partial irreversibility of twinning and consequences for damage.* Acta Materialia,  
37 vol. 48, pp 505–516.
- 38  
39  
40 DELAIRE F., RAPHANEL J.L., AND REY C. (2000). *Plastic heterogeneities of a copper multicrystal*  
41 *deformed in uniaxial tension: experimental study and finite element simulations.* Acta Mater., vol.  
42 48, pp 1075–1087.
- 43  
44  
45 DIARD O., LECLERCQ S., ROUSSELIER G., AND CAILLETAUD G. (2002). *Distribution of normal*  
46 *stress at grain boundaries in multicrystals: application to an intergranular damage modeling.* Com-  
47 putational Materials Science, vol. 25, pp 73–84.
- 48  
49  
50 DIARD O., LECLERCQ S., ROUSSELIER G., AND CAILLETAUD G. (2005). *Evaluation of finite element*  
51 *based analysis of 3D multicrystalline aggregates plasticity. Application to crystal plasticity model*  
52 *identification and the study of stress and strain fields near grain boundaries.* International Journal  
53 of Plasticity, vol. 21, pp 691–722.
- 54  
55  
56 DOUMALIN P., BORNERT M., AND CRÉPIN J. (2003). *Caractérisation de la répartition de la*  
57  
58  
59  
60

- 1  
2  
3 *déformation dans les matériaux hétérogènes*. Mécanique et Industries, vol. 4, pp 607–617.
- 4  
5 EBERL F., FOREST S., WROBLEWSKI T., CAILLETAUD G., AND LEBRUN J.-L. (2002). *Finite ele-*  
6 *ment calculations of the lattice rotation field of a tensile loaded nickel base alloy multicrystal and*  
7 *comparison to topographical X-ray diffraction measurements*. Metallurgical and Materials Transac-  
8 *tions*, vol. 33A, pp 2825–2833.
- 9  
10  
11 ERIEAU P. AND REY C. (2004). *Modelling of deformation and rotation bands and of deformation in-*  
12 *duced grain boundaries in IF steel aggregate during large plane strain compression*. Int. J. Plasticity,  
13 *vol. 20*, pp 1763–1788.
- 14  
15  
16 FEYEL F., CALLOCH S., MARQUIS D., AND CAILLETAUD G. (1997). *F.E. computation of a triaxial*  
17 *specimen using a polycrystalline model*. Computational Materials Science, vol. 9, pp 141–157.
- 18  
19 GAIROLA B. AND KRÖNER E. (1981). *A simple formula for calculating the bounds and the self-*  
20 *consistent value of the shear modulus of polycrystalline aggregates of cubic crystals*. Int. J. Engng  
21 *Sci.*, vol. 19, pp 865–869.
- 22  
23  
24 HARREN S.V. AND ASARO R.J. (1989). *Nonuniform deformations in polycrystals and aspects of the*  
25 *validity of the taylor model*. J. Mech. Phys. Solids, vol. 37, pp 191–232.
- 26  
27 HASHIMOTO K. AND MARGOLIN H. (1983). *The role of elastic interaction stresses on the onset*  
28 *of slip in polycrystalline alpha brass-I. Experimental determination of operating slip systems and*  
29 *qualitative analysis*. Acta Met., vol. 31, pp 773–785.
- 30  
31  
32 HAVLICEK F., KRATOCHVIL J., TOKUDA M., AND LEV V. (1990). *Finite element model of plastically*  
33 *deformed multicrystal*. Int. J. of Plasticity, vol. 6, pp 281.
- 34  
35  
36 JEULIN D. AND OSTOJA-STARZEWSKI M. (2001). *Mechanics of Random and Multiscale Microstruc-*  
37 *tures*, vol. 430. CISM Lecture Notes, Springer Verlag.
- 38  
39 KRÖNER E. (1972). *Statistical Continuum Mechanics*. CISM Course, Springer Verlag, Wien.
- 40  
41 LANTUÉJOUL C. (2002). *Geostatistical simulation: Models and algorithms*. Springer, Berlin.
- 42  
43 LETOUZÉ N., BRENNER R., CASTELNAU O., BÉCHADE J.L., AND MATHON M.H. (2002). *Residual*  
44 *strain distribution in Zircaloy-4 measured by neutron diffraction and estimated by homogenization*  
45 *techniques*. Scripta Materialia, vol. 47, pp 595–599.
- 46  
47 LIPPMANN N., STEINKOPFF T., SCHMAUDER S., AND GUMBSCH P. (1997). *3D-finite-element-*  
48 *modelling of microstructures with the method of multiphase elements*. Computational Materials  
49 *Science*, vol. 9, pp 28–35.
- 50  
51  
52 MANDEL J. (1971). *Plasticité classique et viscoplasticité*, vol. 97 of *CISM Courses and lectures*. Springer  
53 *Verlag*.
- 54  
55 MARY N., VIGNAL V., OLTRA R., AND COUDREUSE L. (2005). *Finite-element and XRD methods*  
56 *for the determination of the residual surface stress field and the elastic-plastic behaviour of duplex*  
57  
58  
59  
60


- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60
- steels*. Philos. Mag., vol. 85, pp 1227–1242.
- MIYAMOTO H. (1972). *Application of Finite-Element Method to Fracture Mechanics*. In : First International Conference on Structural Mechanics in Reactor Technology, pp 535–566. Berlin.
- MOHAMED G., BACROIX B., UNGAR T., RAPHANEL J.L., AND CHAUVEAU T. (1997). *Experimental and numerical determination of the intragranular work hardening in a cold rolled multicrystal*. Mat. Sc. Engng., vol. A234-236, pp 940–943.
- MUSIENKO A. (2005). *Large deformation and damage in crystal plasticity*. PhD thesis, Ecole des Mines de Paris.
- NYGÅRDS M. (2003). *Number of grains necessary to homogenize elastic materials with cubic symmetry*. Mechanics of Materials, vol. 35, pp 1049–1057.
- PARISOT R., FOREST S., GOURGUES A.-F., PINEAU A., AND MAREUSE D. (2001). *Modeling the mechanical behavior of a multicrystalline zinc coating on a hot-dip galvanized steel sheet*. Computational Materials Science, vol. 19, pp 189–204.
- PARISOT R., FOREST S., PINEAU A., GRILLON F., DÉMONET X., AND MATAIGNE J.-M. (2004). *Deformation and Damage Mechanisms of Zinc Coatings on Galvanized Steel Sheets, Part I : Deformation Modes*. Metallurgical and Materials Transactions, vol. 35A, pp 797–811.
- QUILICI S. AND CAILLETAUD G. (1999). *F.E. simulation of macro-, meso- and micro- scales in polycrystalline plasticity*. Computational Materials Science, vol. 16, pp 383–390.
- SARMA G.B., RADHAKRISHNAN B., AND ZACHARIA T. (1998). *Finite element simulations of cold deformation at the mesoscale*. Comput. Mat. Sc., vol. 12, pp 105–123.
- SCHWARTZ A.J., KUMAR M., AND ADAMS B.L. (2000). *Electron Backscatter Diffraction in Materials Science*. Kluwer Academic, Plenum Publisher, New York.
- TEODOSIU C., RAPHANEL J., AND TABOUROT L. (1993). *Finite element simulation of the large elastoplastic deformation of multi-crystals*. In : Large Plastic Deformations MECAMAT'91, eds. Teodosiu C. and Sidoroff F., pp 153–158. Balkema, Rotterdam.
- Z-SET PACKAGE (2001). [www.nwnumerics.com](http://www.nwnumerics.com), [www.mat.ensmp.fr](http://www.mat.ensmp.fr).
- ZEGHADI A. (2005). *Effets de la morphologie tri-dimensionnelle et de taille de grain sur comportement mécanique d'agrégats polycristallins*. Phd thesis, Ecole des Mines de Paris.
- ZEGHADI A., FOREST S., GOURGUES A.-F., AND BOUAZIZ O. (2006). *Ensemble averaging stress-strain fields in polycrystalline aggregates with a constrained free surface microstructure—Part 2: Crystal plasticity*. submitted.
- ZIEGENBEIN A., NEUHÄUSER H., THESING J., RITTER R., WITTICH H., STECK E., AND LEVERMANN M. (1998). *Local plasticity of Cu–Al polycrystals - measurements and FEM simulations*. J. Phys. IV France, vol. 8, pp Pr8-407–412.




grain number	$\phi_1$	$\Phi$	$\phi_2$	grain number	$\phi_1$	$\Phi$	$\phi_2$
1	278.4	85.9	180.2	20	117.1	94.5	230.7
2	35.0	112.4	49.0	21	95.1	130.9	97.3
3	210.1	57.0	311.9	22	152.8	66.2	49.9
4	352.8	120.1	231.6	23	124.4	63.4	250.5
5	358.2	118.3	285.3	24	251.9	31.7	141.8
6	244.3	60.1	315.9	25	110.1	46.7	254.0
7	53.3	138.3	244.5	26	261.8	121.8	286.0
8	73.7	31.7	70.7	27	317.2	116.3	355.1
9	344.0	58.7	28.8	28	193.2	67.4	43.1
10	296.0	117.9	98.8	29	223.4	77.1	53.9
11	160.7	81.7	268.5	30	210.8	52.4	240.5
12	118.3	52.3	60.9	31	214.7	77.7	108.2
13	260.9	18.1	45.7	32	152.5	72.2	272.4
14	179.6	135.6	271.9	33	116.1	85.4	130.6
15	120.1	48.2	73.9	34	12.6	118.5	76.8
16	174.4	65.5	95.4	35	279.7	135.2	314.3
17	185.2	74.5	44.5	36	160.1	35.1	261.4
18	225.6	39.9	162.7	37	0.1	90.0	253.9
19	58.5	85.6	246.2	38	8.0	110.2	301.7
				39	342.7	133.0	252.8

Table 1

Crystal orientations of the 39 grains of the reference surface of figure 1. Euler–Bunge angles (in degrees) are given with respect to the reference frame of the sample ( $x, y, z$ ) defined in figure 1.

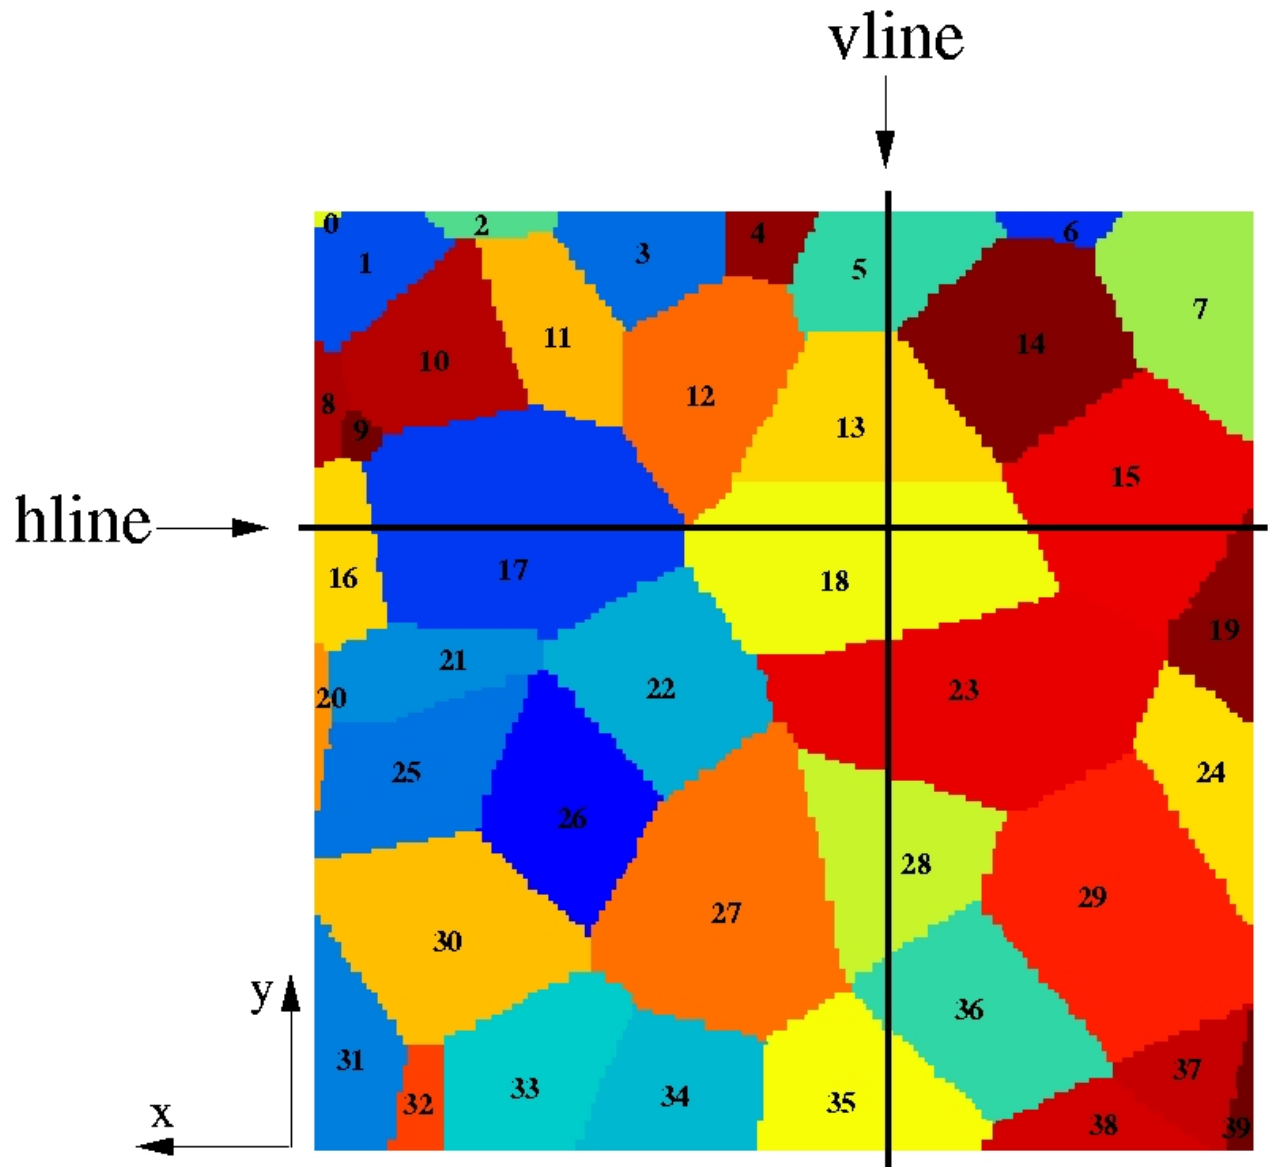

42 Fig. 1. Reference surface  $z = 0$  prescribed for the construction of polycrystalline aggregates. All surface grains  
43 are labeled from 1 to 39. Two lines *hline* and *vline* have been distinguished along which mechanical variables  
44 obtained in the finite element simulations of this work have been plotted.  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

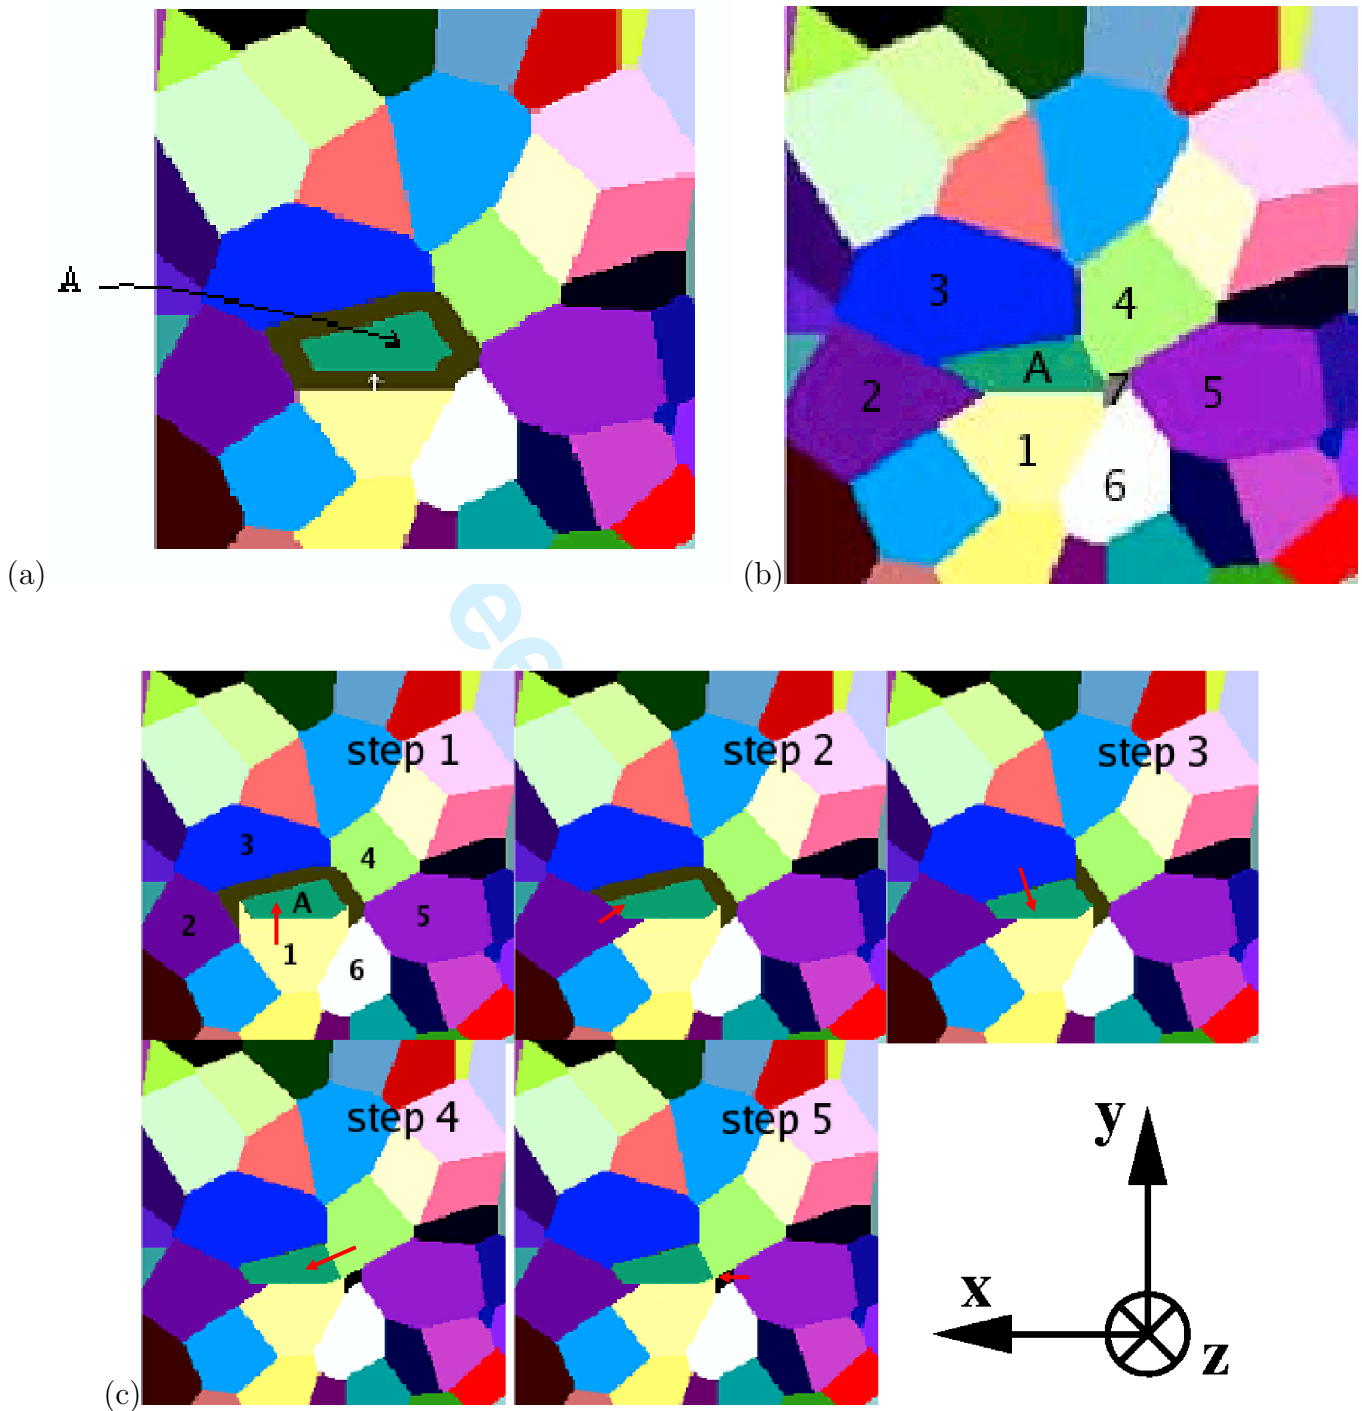

52 Fig. 2. Erosion of a grain belonging to a given surface and its modification due to the growth of neighbouring  
53 grains: (a) the considered grain A is eroded, (b) final environment of grain A, (c) the five growth steps of the  
54 grains surrounding grain A necessary to get picture (b). The  $i^{th}$  step of figure (c) corresponds to the normal  
55 growth of one grain boundary of neighbour grain  $i$ , as indicated by the red arrow.  
56  
57  
58  
59  
60

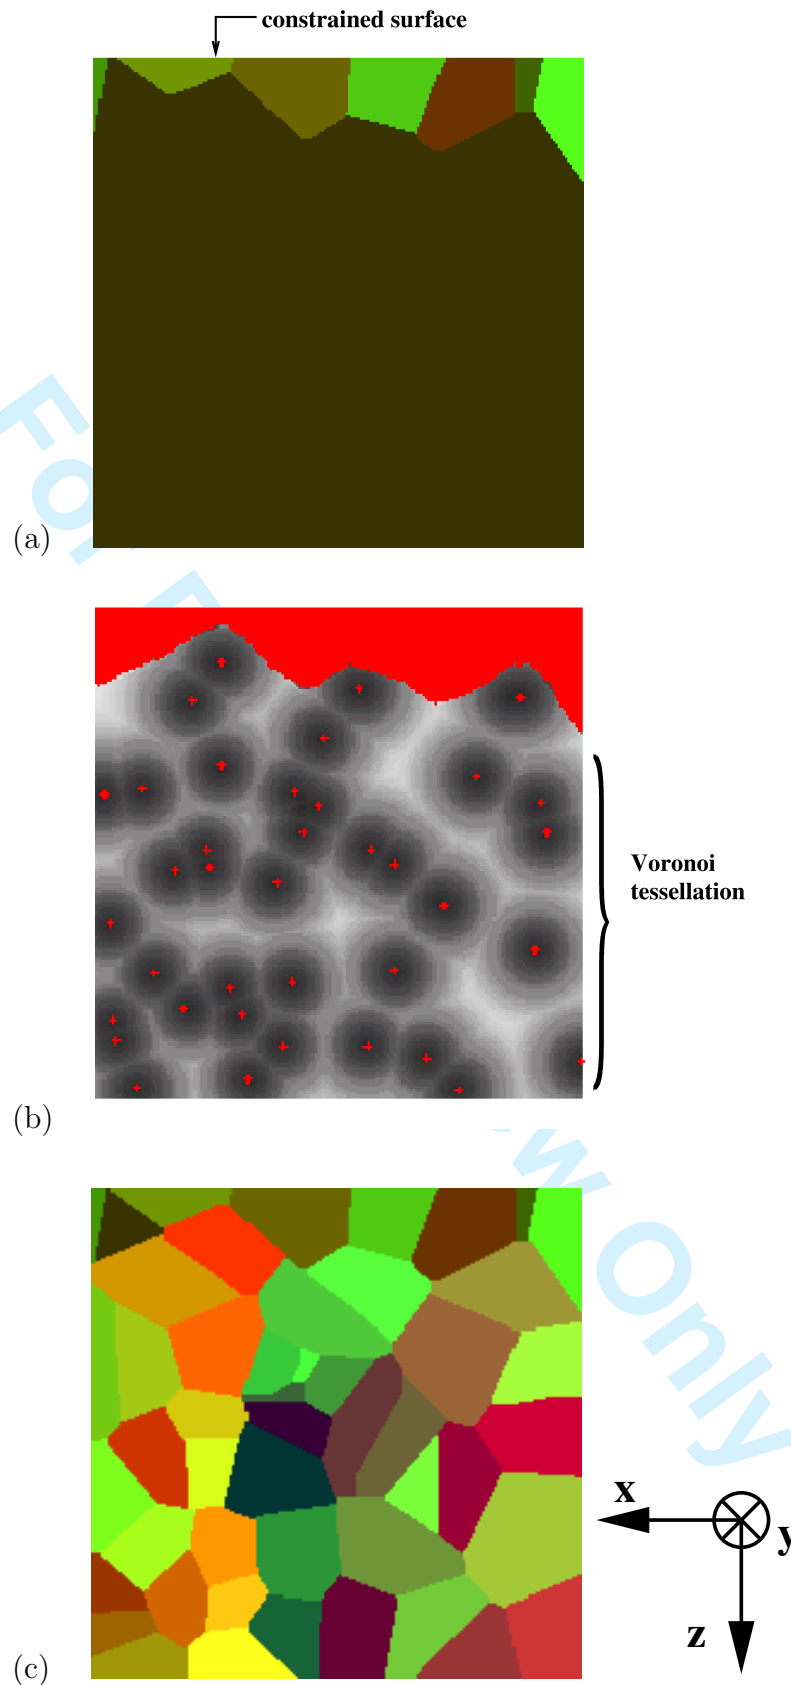


Fig. 3. (a) Section, normal to direction  $y$ , of the first layer of grains below the constrained surface; (b) Voronoi tessellation of the section below the first layer of grains; the red spots denote the random seeds of the cells; the initial first layer of grains is superimposed on the image; (c) union of the first layer of grains and of the Voronoi cells. The grains have been made convex after the union of images (a) and (b). In the three images, the top horizontal line of pixels belongs to the constrained surface  $z = 0$ .

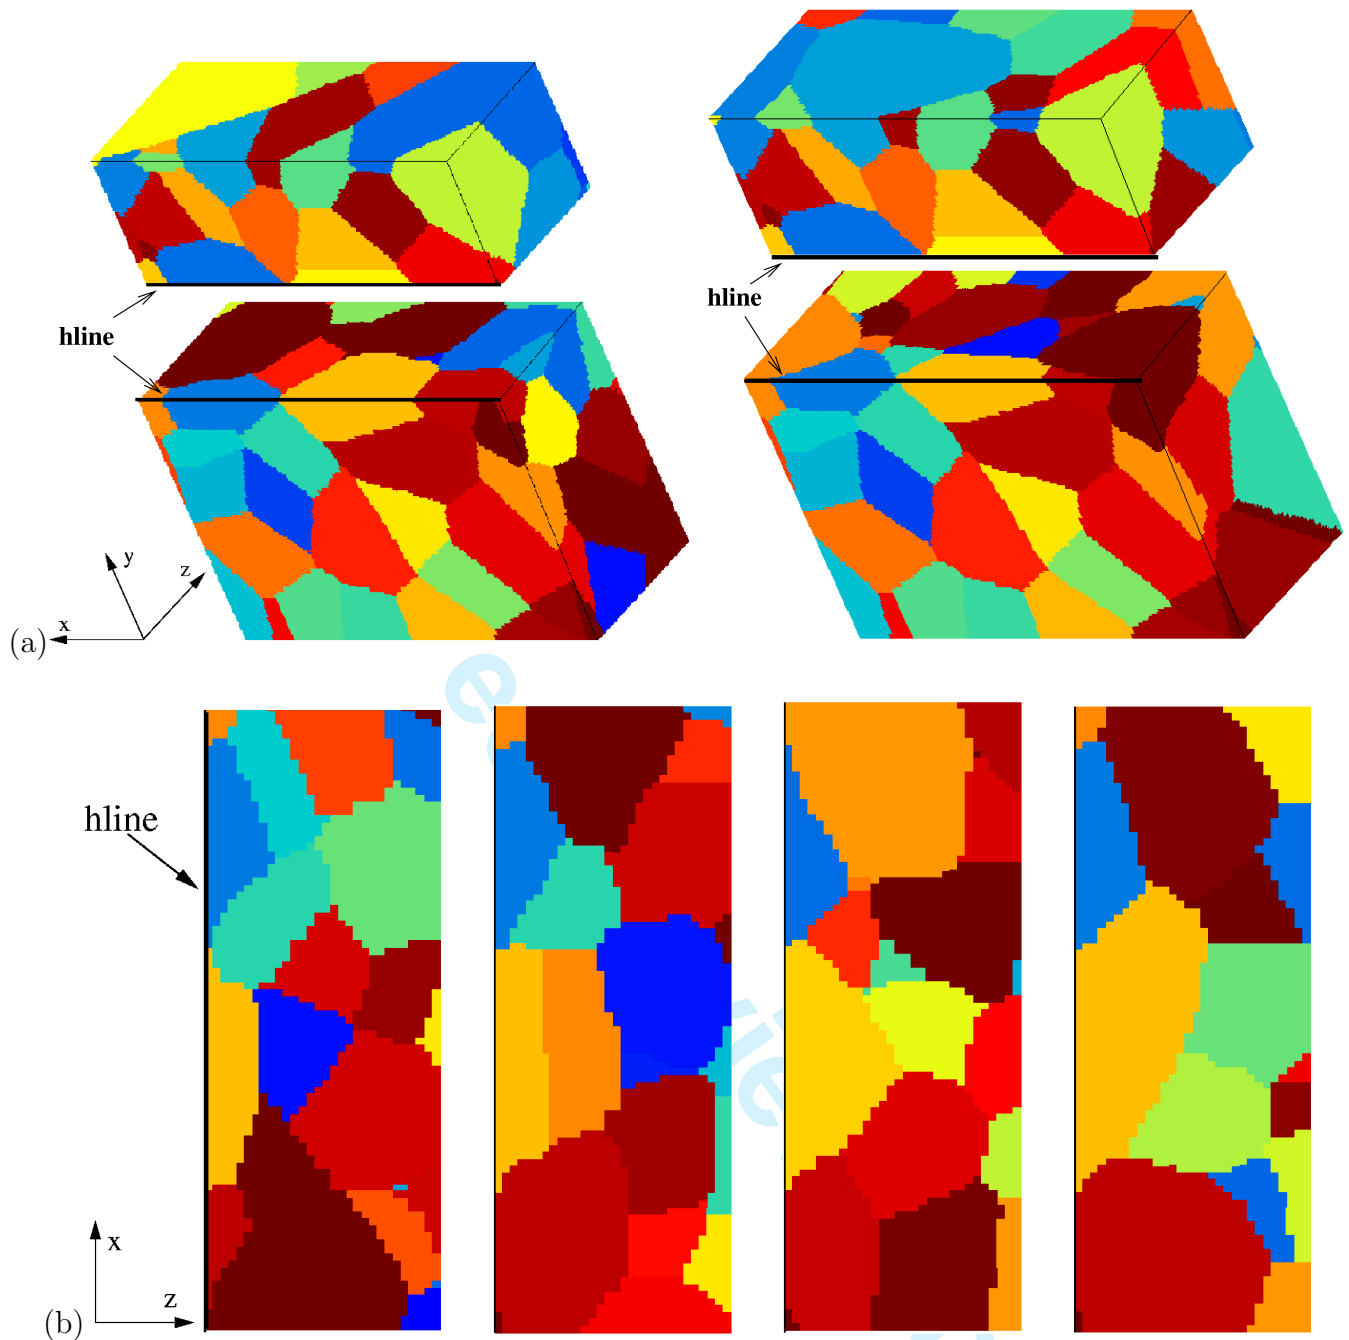


Fig. 4. (a) Two realizations of polycrystalline aggregates with constrained free surface  $z = 0$ . The reference surface  $z = 0$  is given in figure 1. The volumes have been cut into two parts along a plane perpendicular to the free surface and containing the line *hline* (in bold) of figure 1, in order to show the grain morphology below the constrained free surface. (b) Four further realizations are shown. The section plane is perpendicular to the free surface and contains *hline* (in bold).

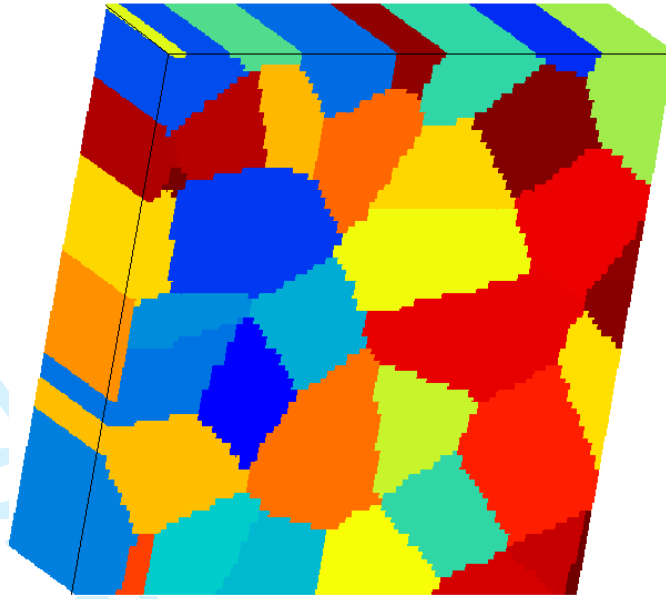


Fig. 5. Columnar grains deduced from the reference surface of figure 1. All grain boundaries are perpendicular to the constrained surface.

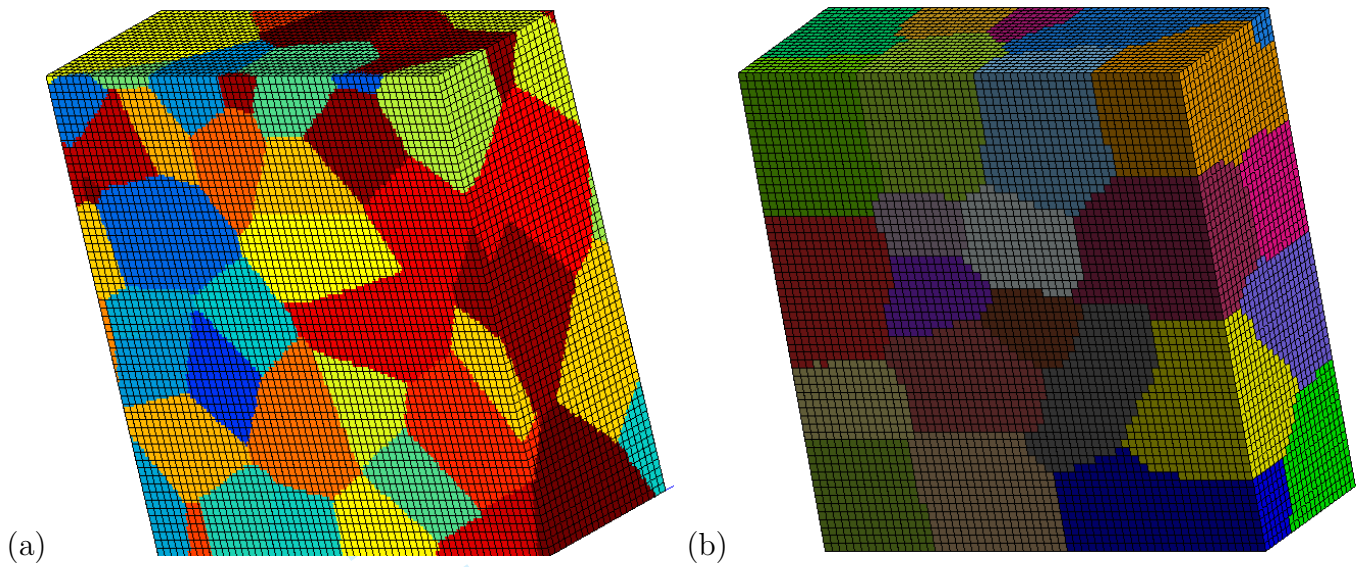


Fig. 6. (a) Multiphase finite element mesh superimposed on the image of a polycrystalline aggregate with constrained free surface; (b) Decomposition of the mesh into 30 subdomains for parallel computing.

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60



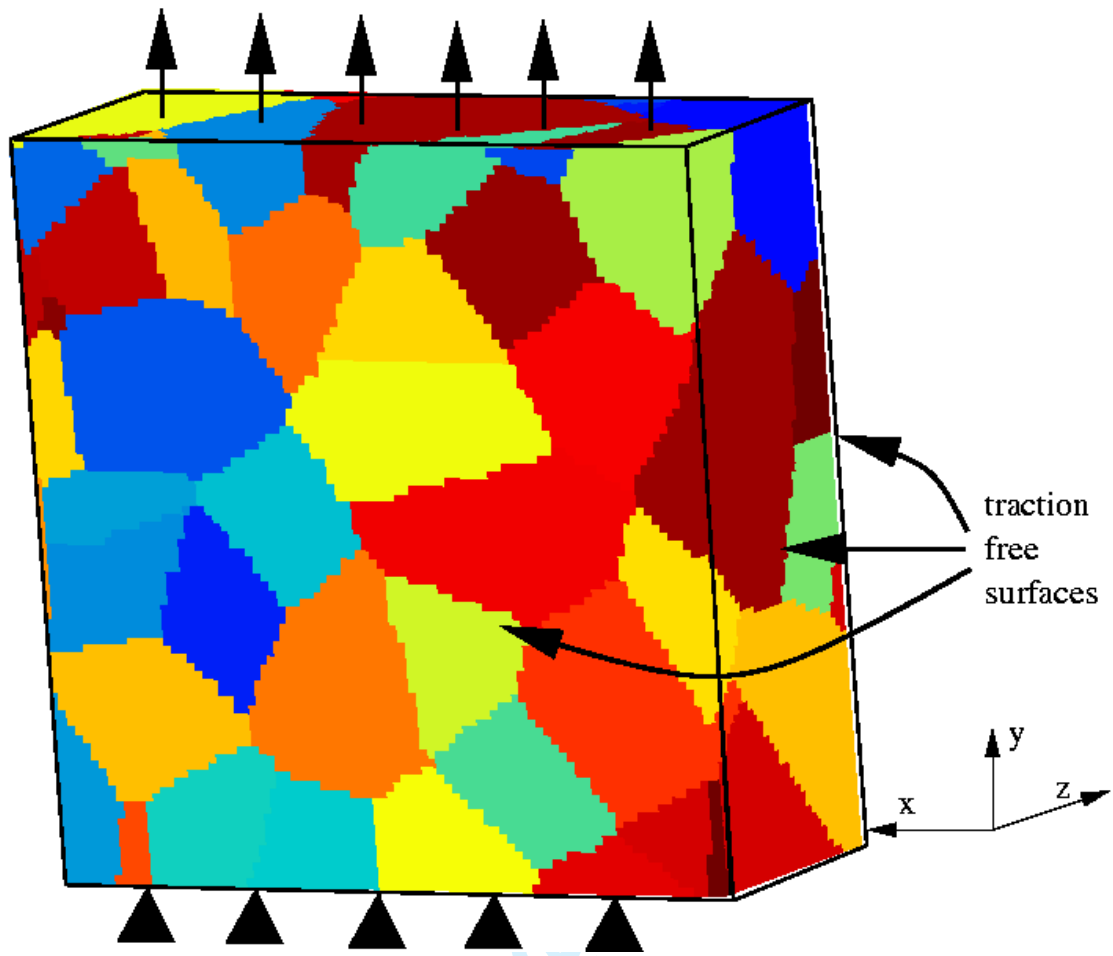


Fig. 7. Boundary value problem for the tension of a polycrystalline aggregate with a given surface morphology  $z = 0$ .

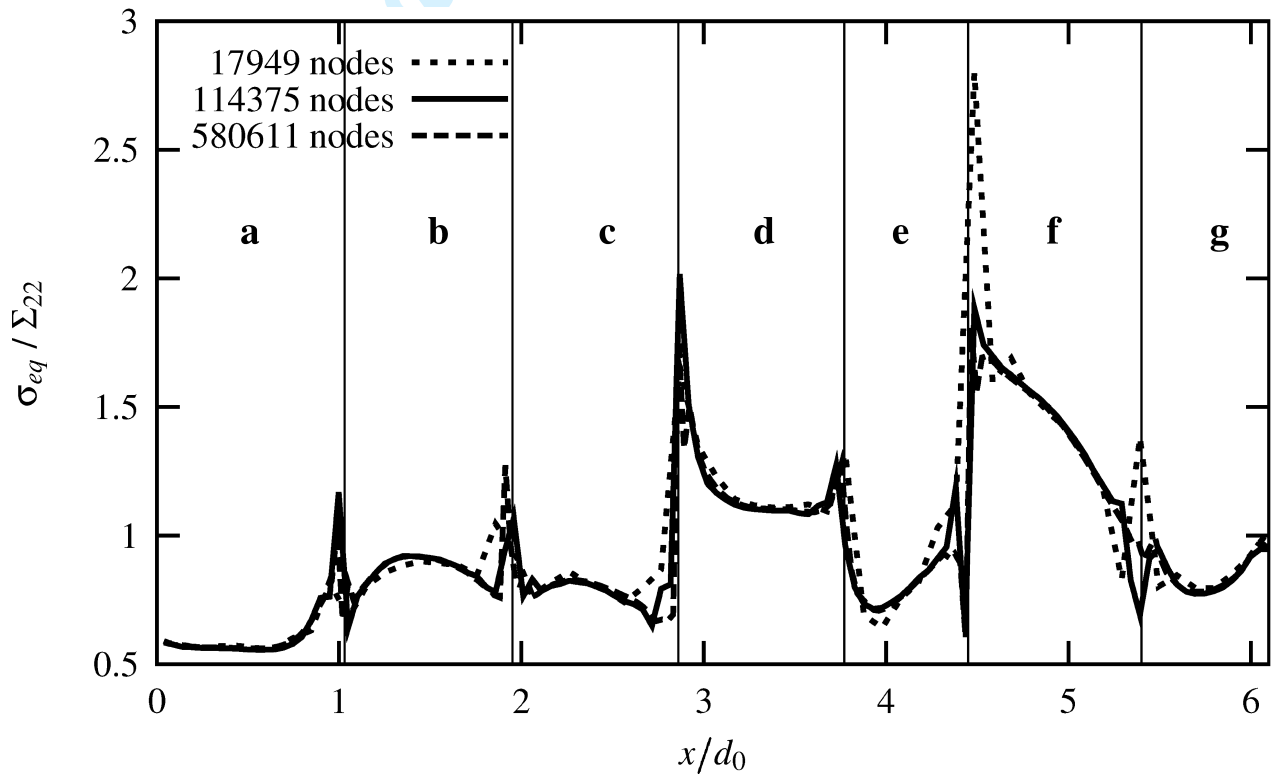

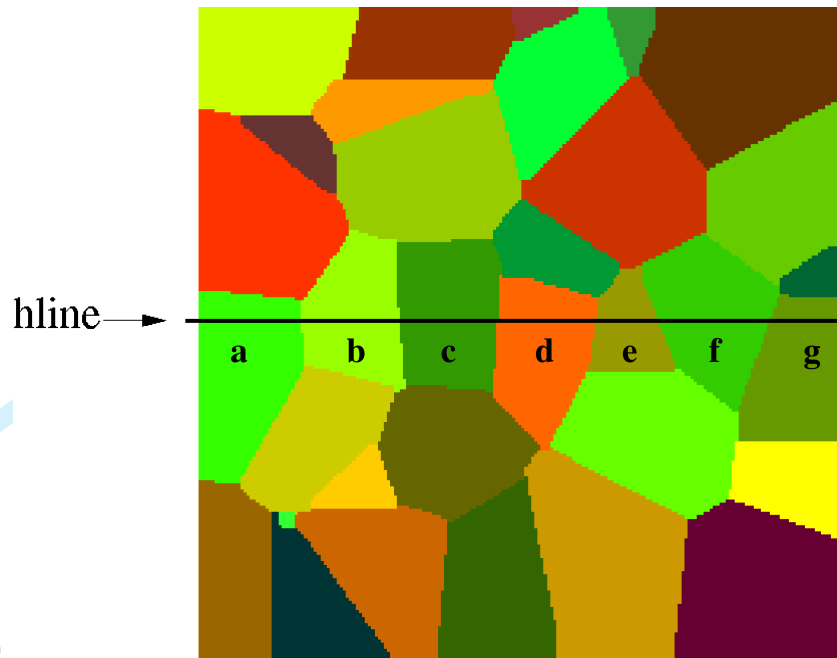

51  
52  
53  
54  
55  
56  
57  
58  
59  
60

Fig. 8. Influence of mesh size on the local stress values: (a) constrained free surface used for the determination of the optimal mesh size; (b) von Mises stress profiles along the line *hline* shown in (a) as a function of the number of nodes of the mesh. In these calculations the morphology and crystal orientations are unchanged but different meshes are used. The vertical lines indicate the  $x$ -position of the intersection between grain boundaries and line *hline*. Labels have been attributed to the grains crossed by *hline*.

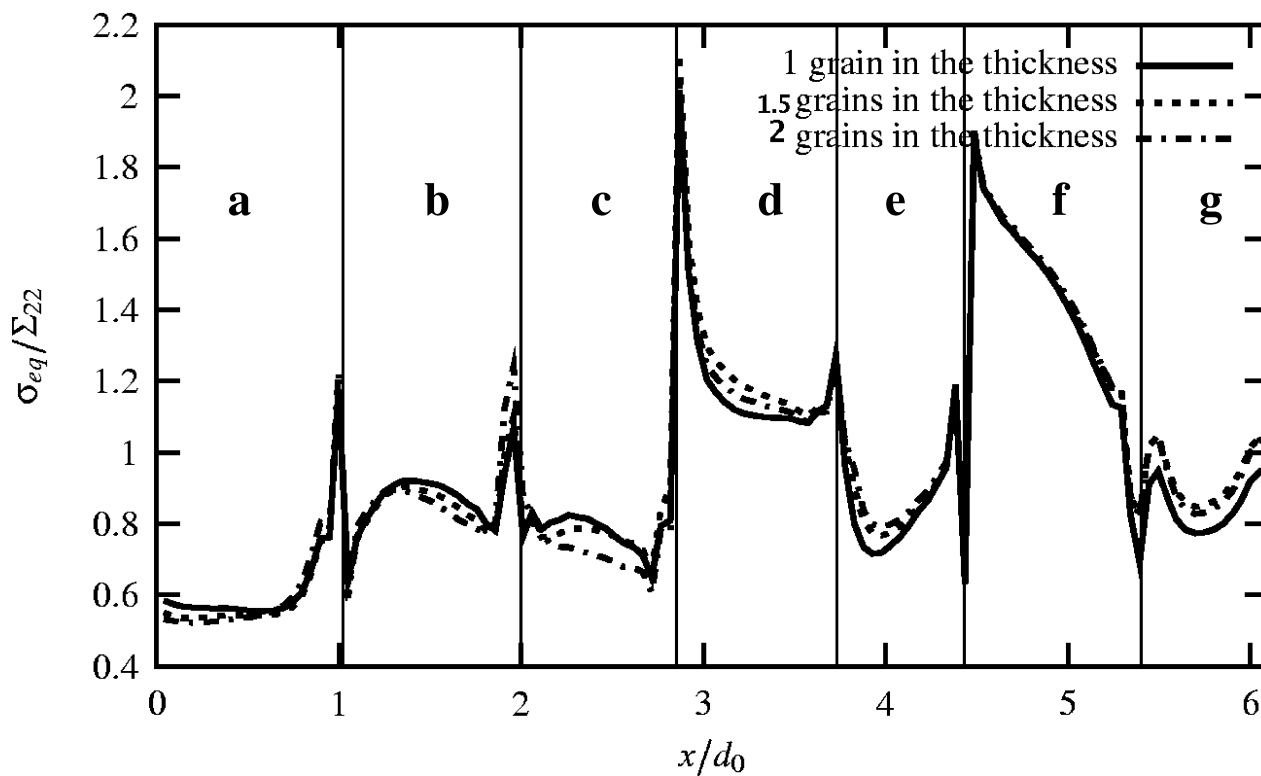


Fig. 9. Effect of the average number of grains in the thickness on the local von Mises equivalent stress level normalized by the global mean stress plotted along the line *hline* of figure 8(a). The position along the  $x$ -axis is  $x$  and  $d_0$  is the mean grain size of the considered microstructure. The vertical lines indicate the  $x$ -position of the intersection between grain boundaries and line *hline*.

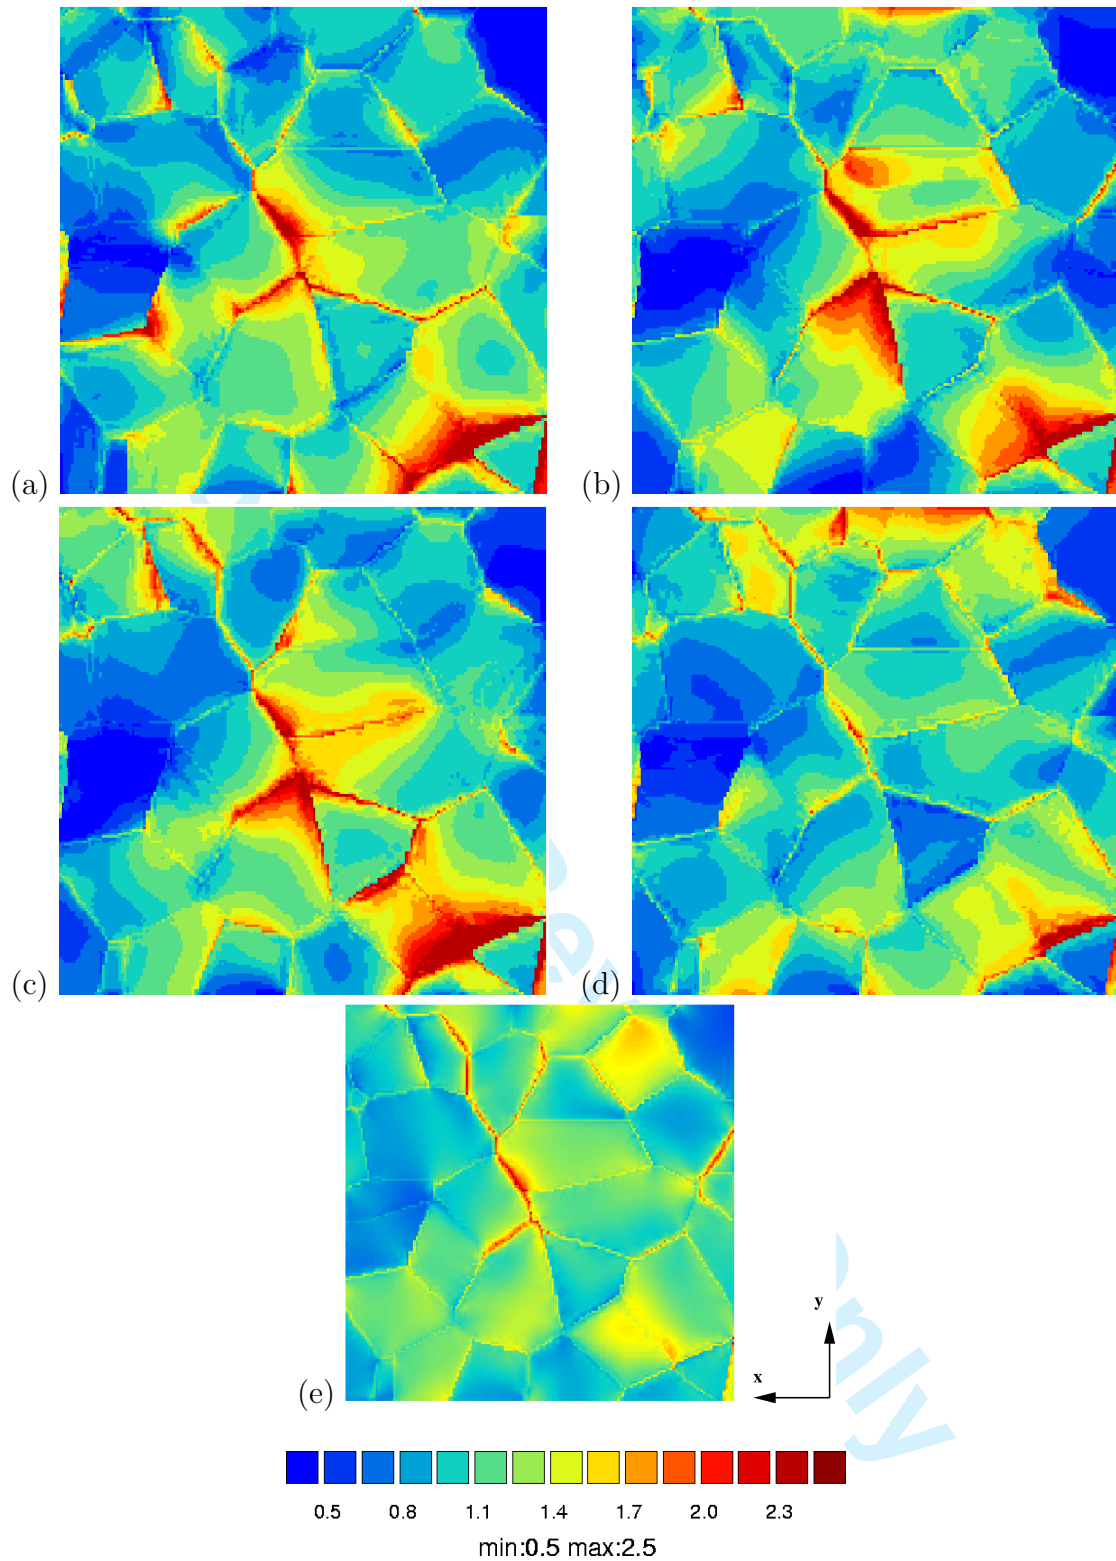


Fig. 10. Von Mises equivalent stress maps at the reference free surface for 4 different polycrystalline aggregates subjected to pure tension (a) to (d). The stress distribution is normalized by the global ensemble average stress  $\overline{\Sigma_{22}}$  over all realizations. The reference free surface is that of figure 1. Figure (e) shows the result obtained for the aggregate made of columnar grains (figure 5). Tension is applied along  $y$ -direction.

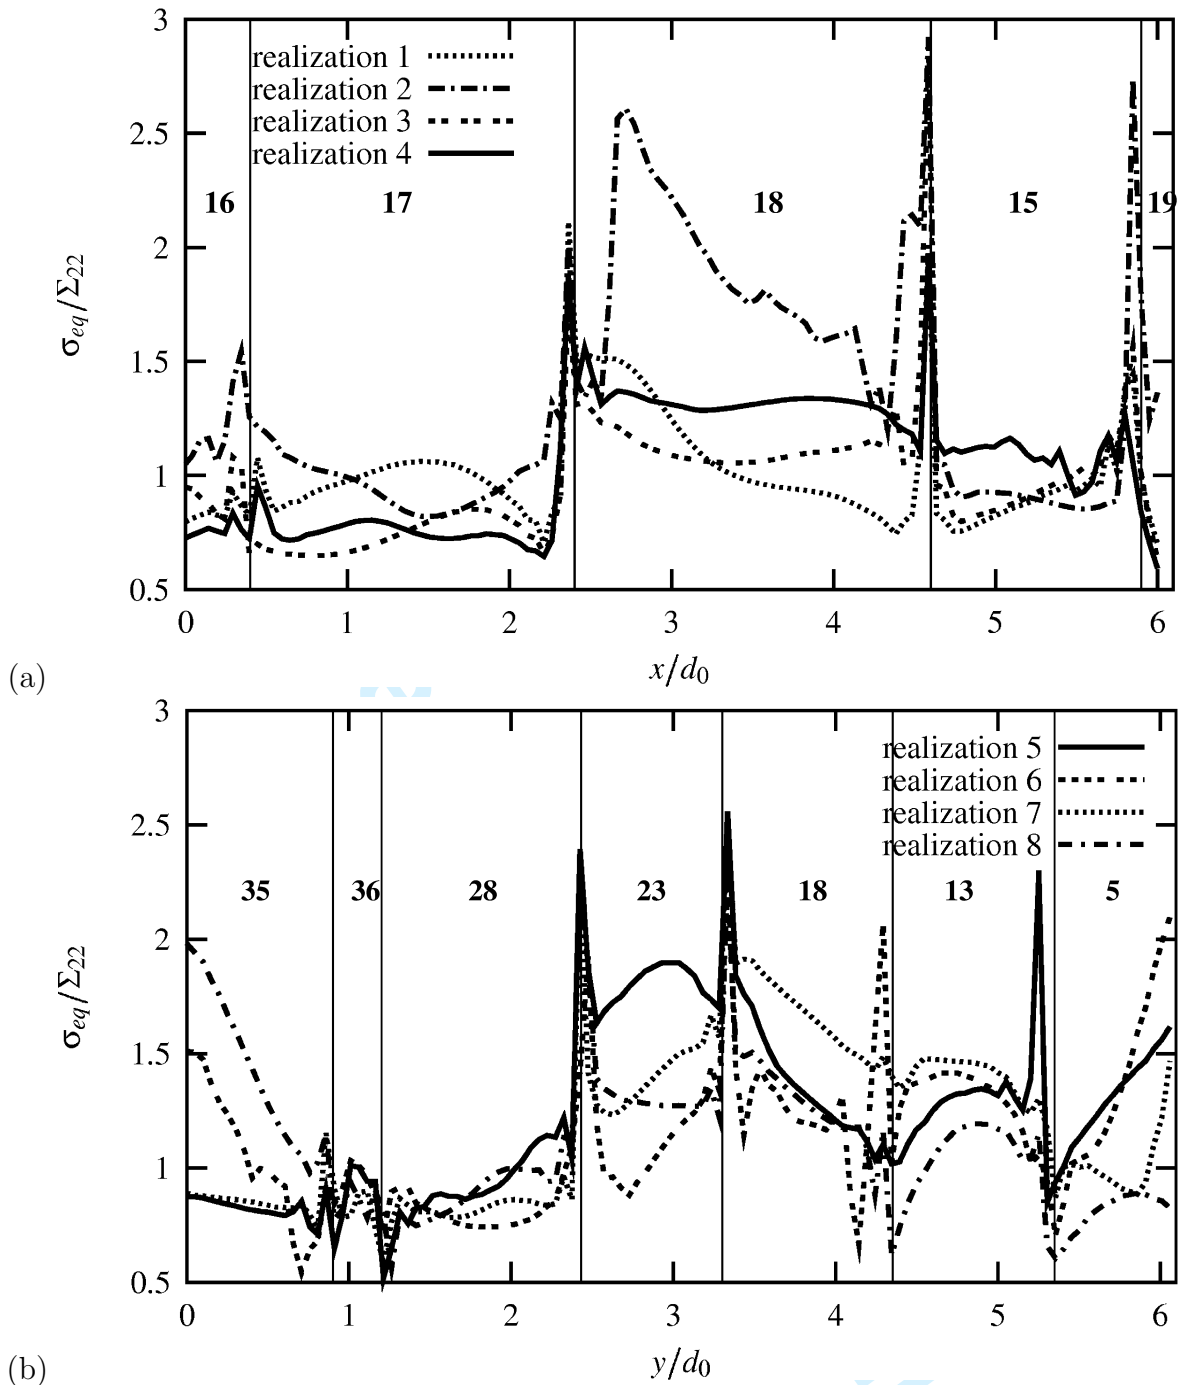


Fig. 11. Equivalent von Mises stress profiles along the lines *hline* (a) and *vline* (b) of figure 1 for eight different realizations of polycrystalline aggregates with a constrained free surface and subjected to pure tension. The stress distribution is normalized by the global ensemble average stress  $\bar{\Sigma}_{22}$  over all realizations. The reference free surface is given in figure 1. The vertical lines indicate the  $x$ -position of the intersection between grain boundaries and line *hline*. The labels of the grains crossed by *hline* and *vline* are indicated.

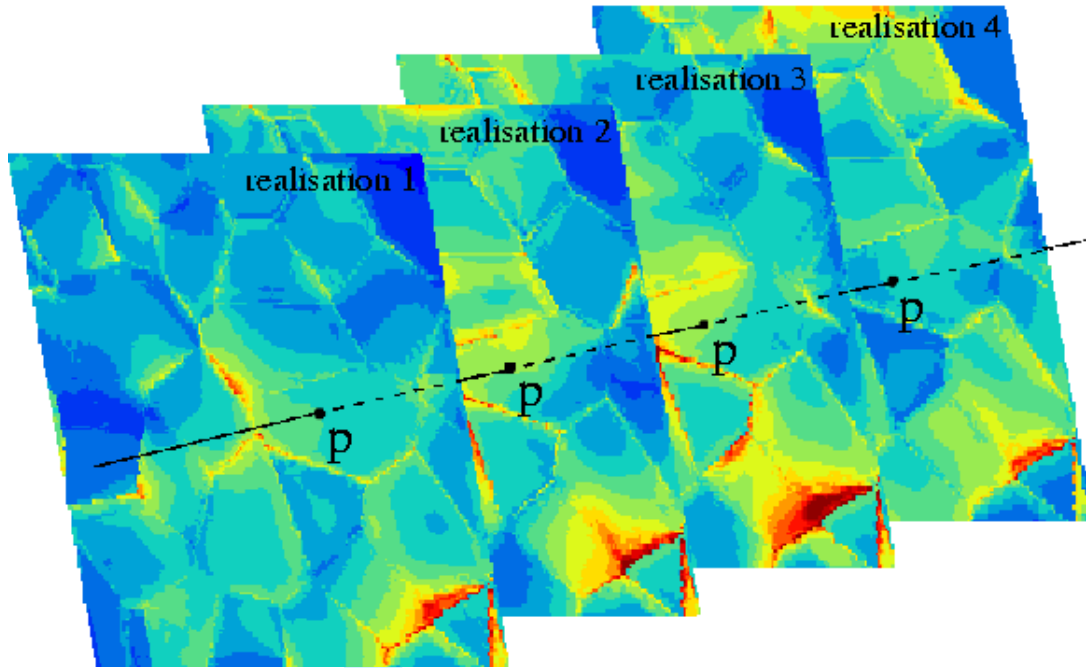


Fig. 12. Schematic view of the ensemble averaging procedure. The ensemble averaged stress field is obtained by averaging the local stress value reached at the same geometrical point  $P$  belonging to the constrained free surface for all considered realizations.

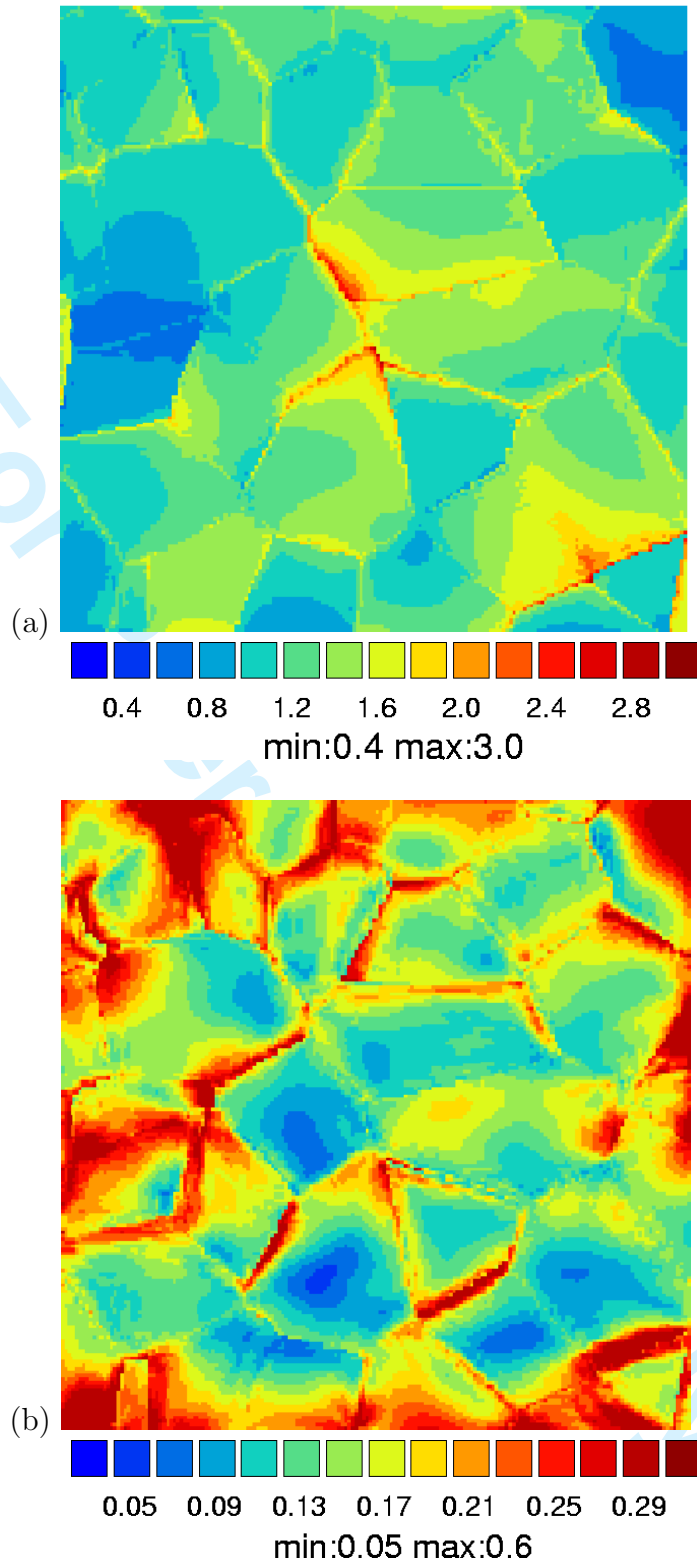


Fig. 13. (a) Ensemble average of the von Mises equivalent stress field  $\overline{\sigma_{eq}}(\underline{x})/\overline{\Sigma_{22}}$  at the imposed free surface of the polycrystalline aggregates in tension. (b) Field of the relative variance  $D(\sigma_{eq})(\underline{x})/\overline{\sigma_{eq}}(\underline{x})$  of the local von Mises equivalent stress at the imposed free surface. Tension is applied in the direction  $y$ . The  $y$ -direction is vertical in this figure.

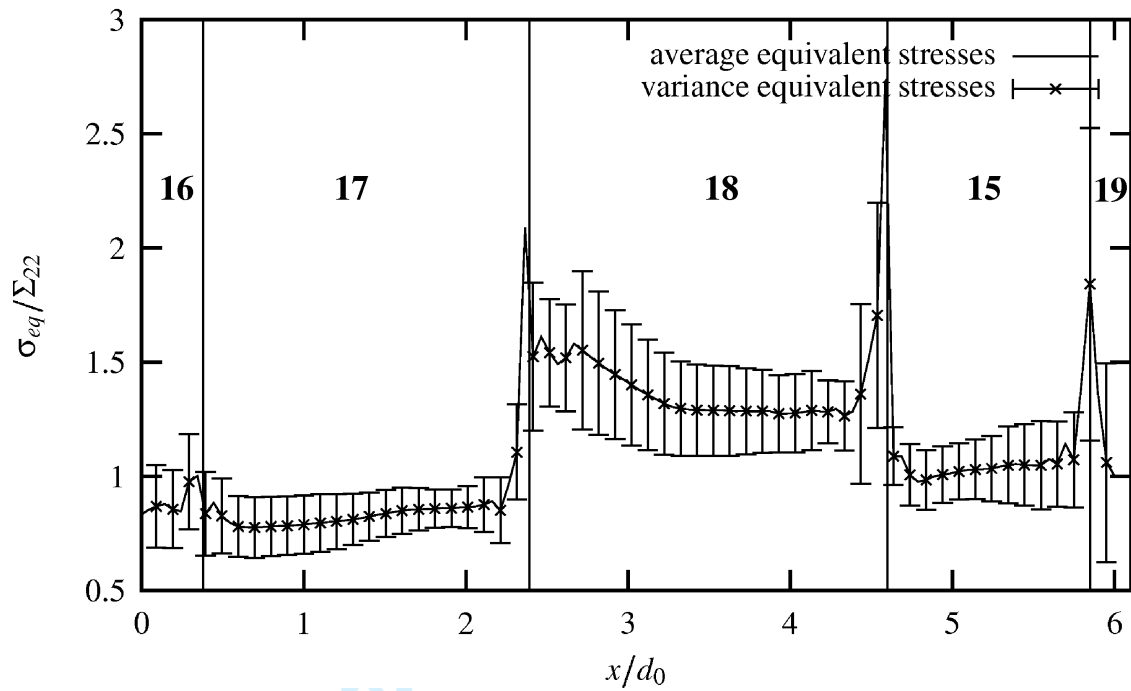


Fig. 14. Ensemble average and relative variance of the von Mises equivalent stress field along the line *hline* of figure 1. The stress values are normalized by the ensemble average  $\overline{\Sigma_{22}}$  of the mean axial stress for all samples.

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

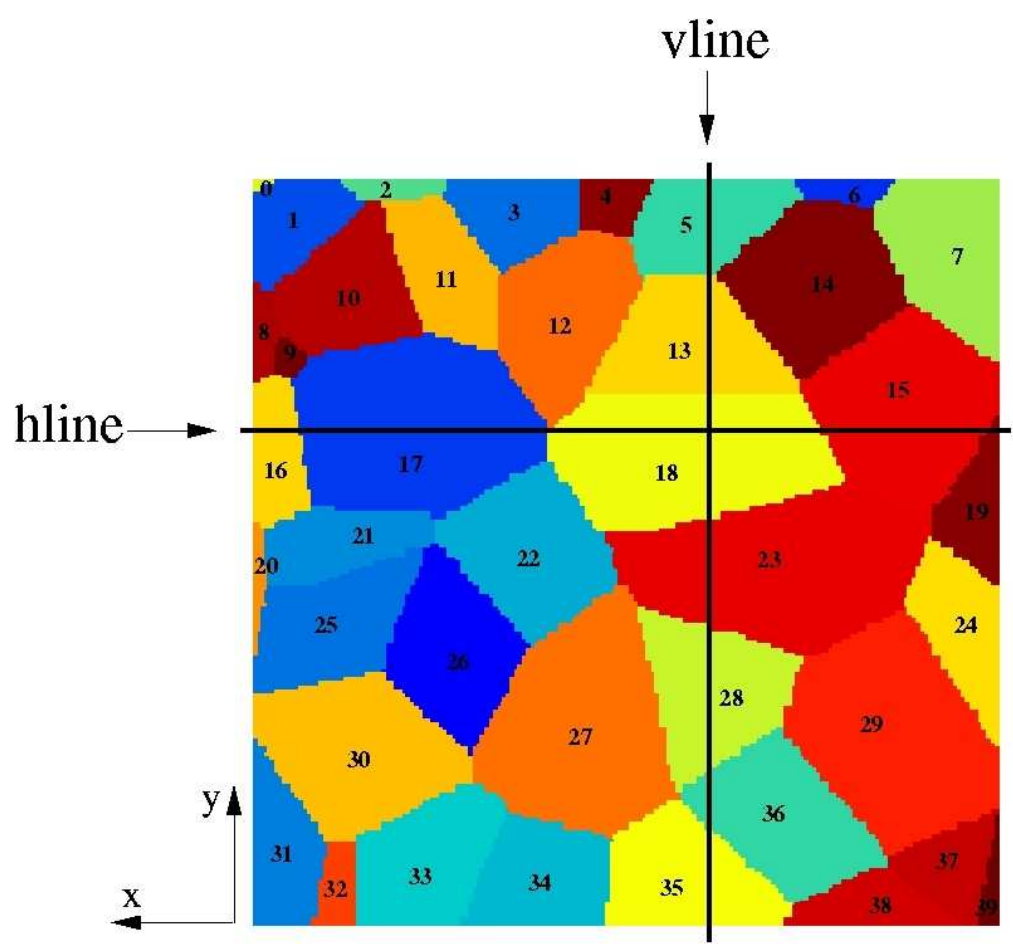


Figure 1  
202x187mm (100 x 100 DPI)

Only



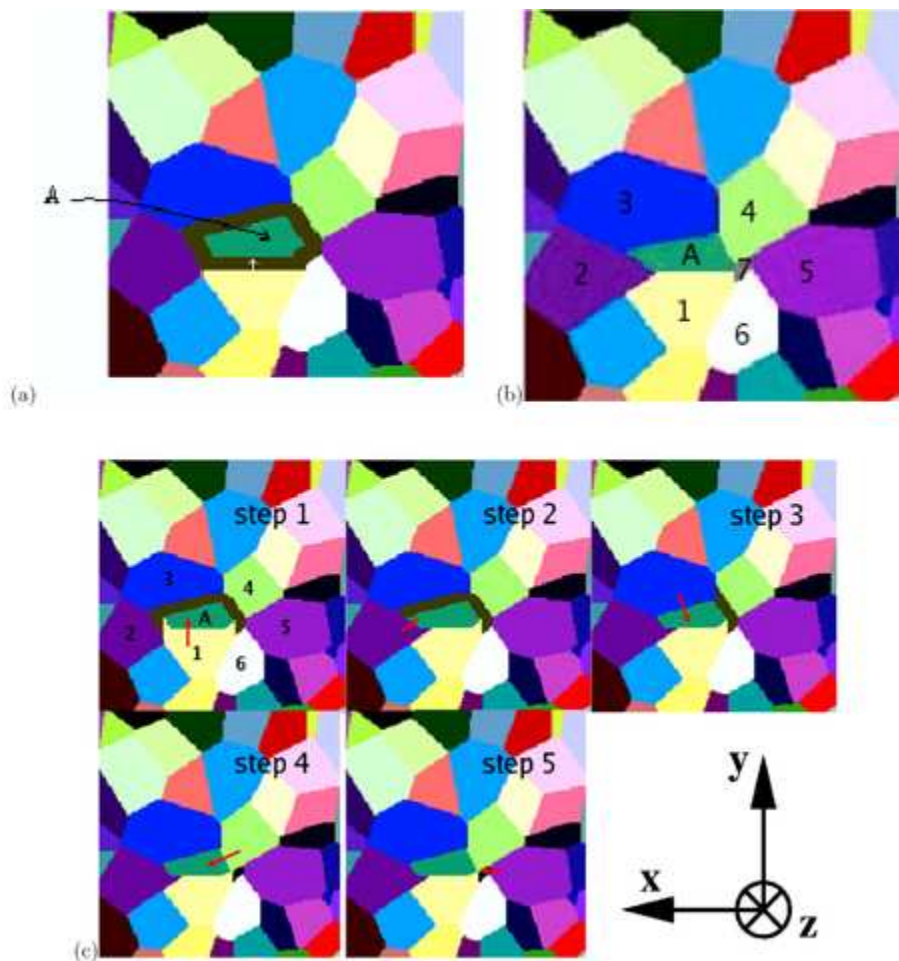


Figure 2  
19x20mm (600 x 600 DPI)

only

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

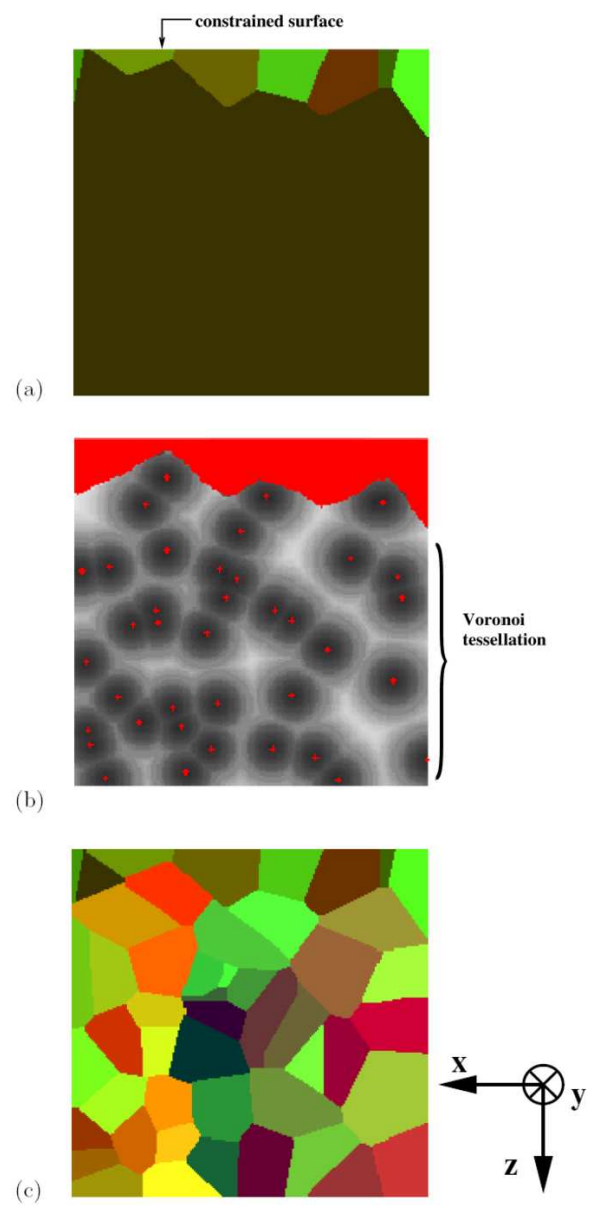


Figure 3  
28x58mm (600 x 600 DPI)

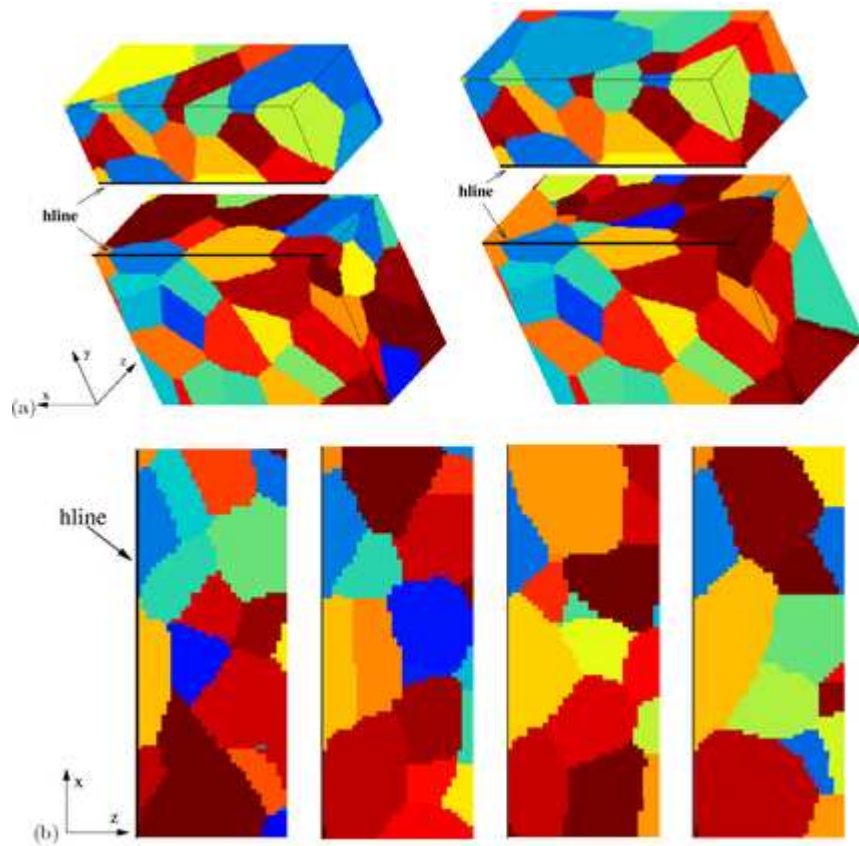


Figure 4  
18x17mm (600 x 600 DPI)

Only

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

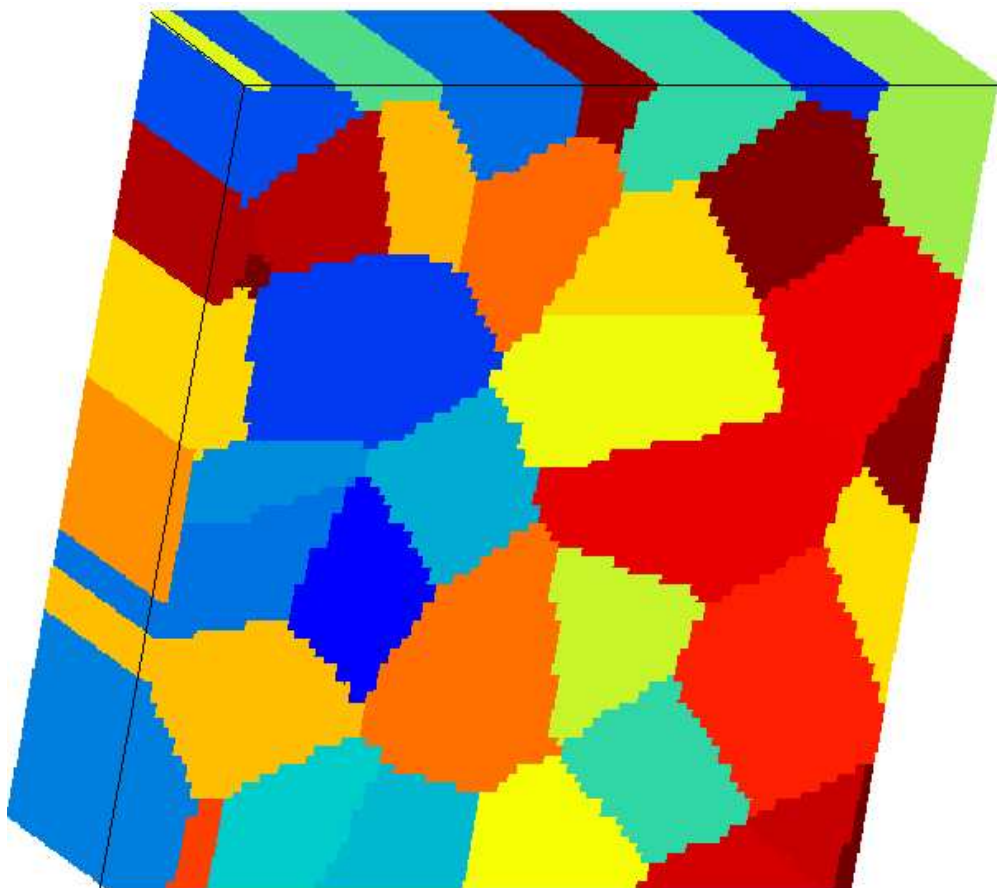


Figure 5

Only

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

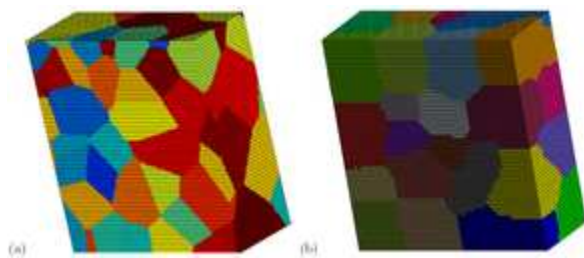


Figure 6  
12x5mm (600 x 600 DPI)

Peer Review Only

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

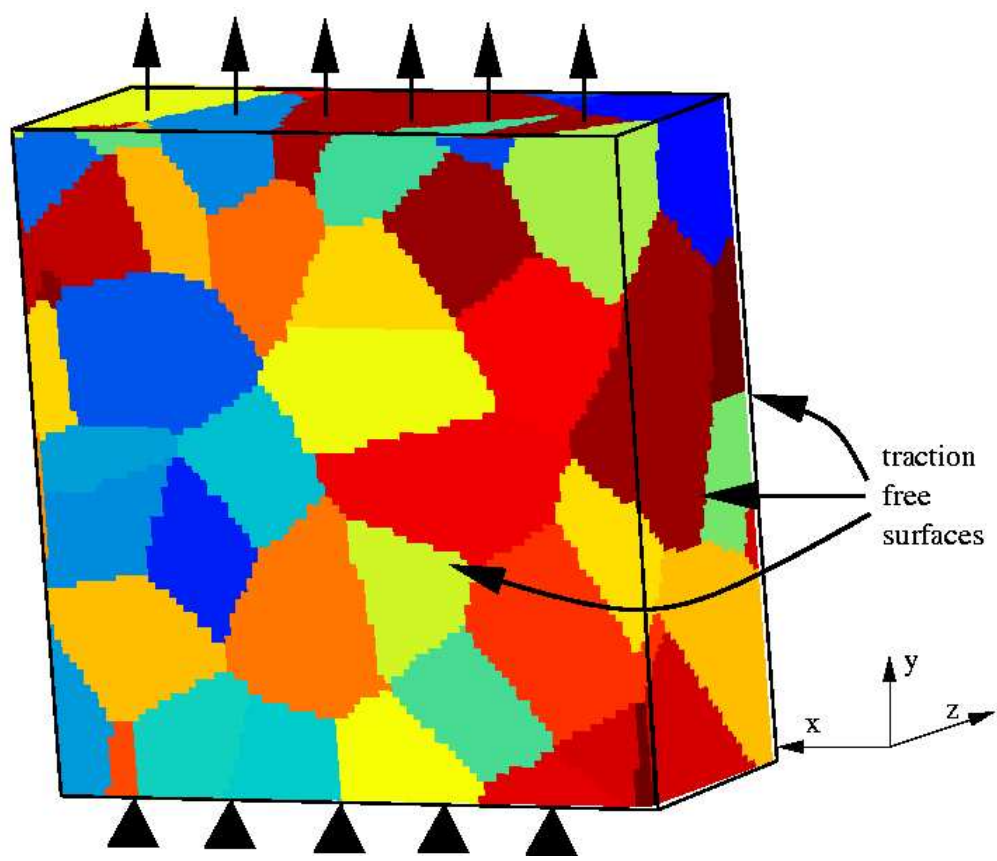


Figure 7  
226x192mm (80 x 80 DPI)

Only

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

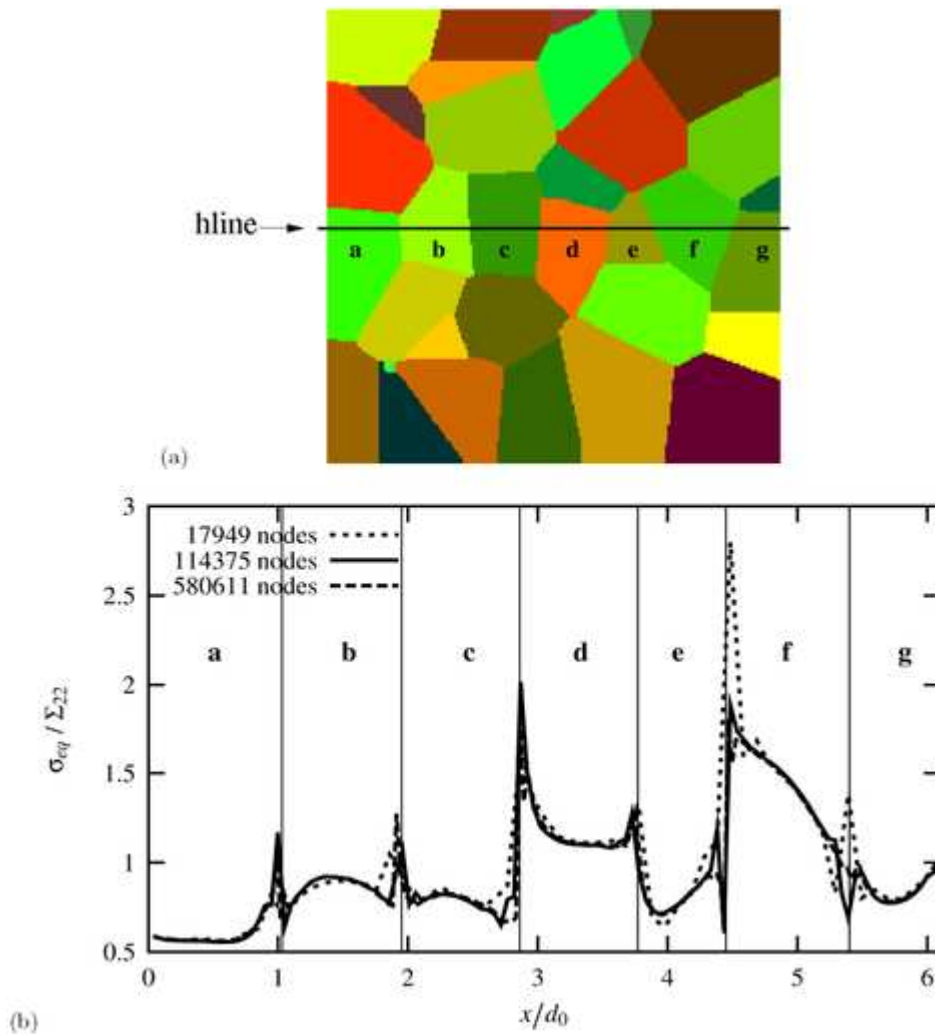


Figure 8  
19x21mm (600 x 600 DPI)



1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

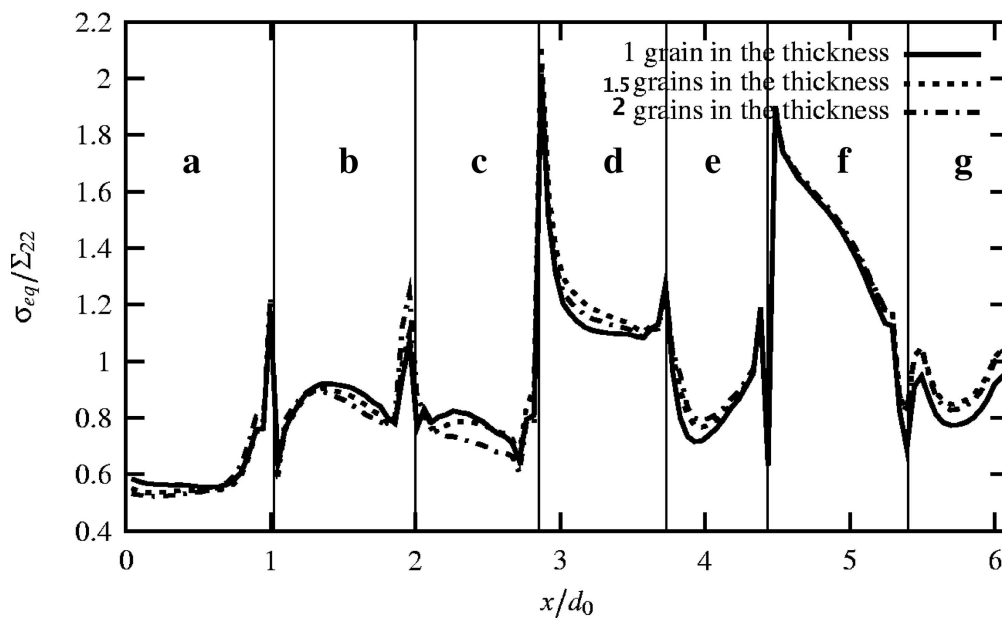


Figure 9  
123x75mm (600 x 600 DPI)

Review Only



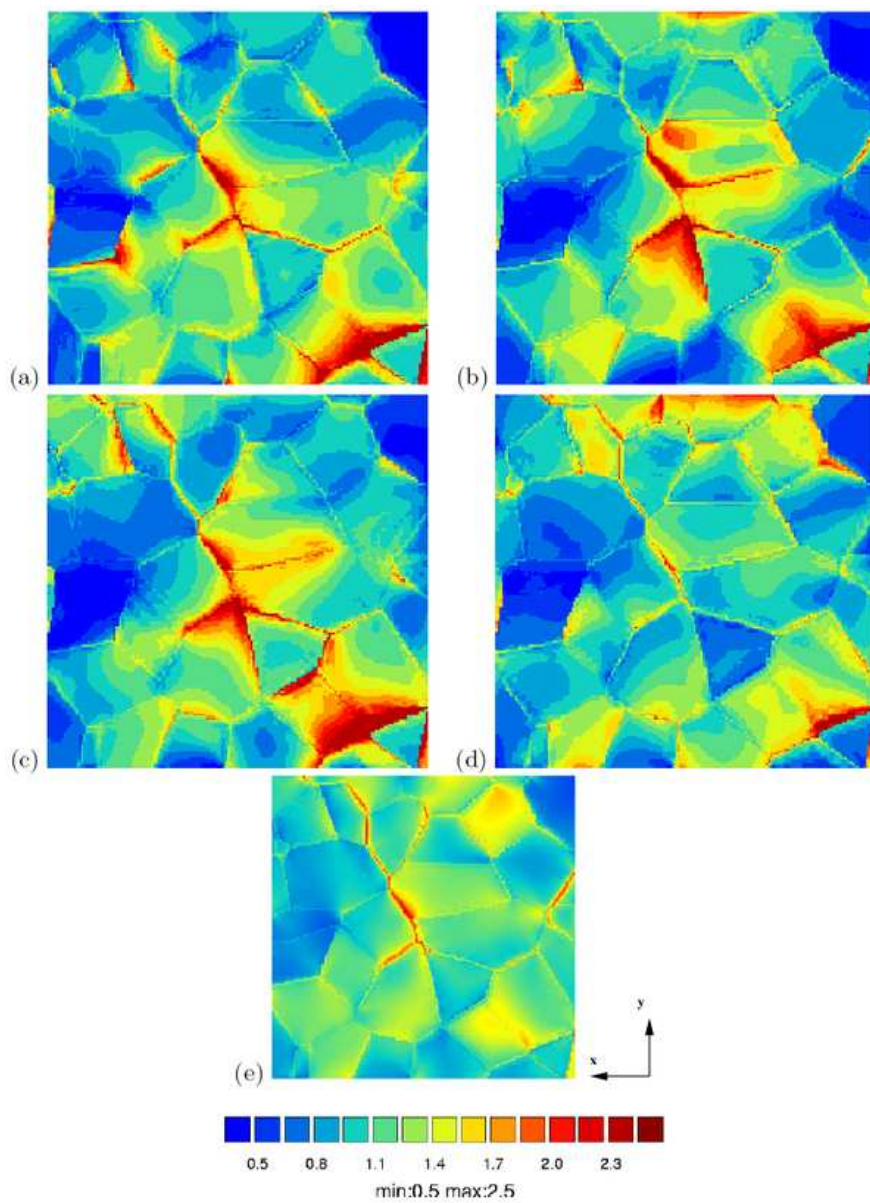


Figure 10  
25x34mm (600 x 600 DPI)

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

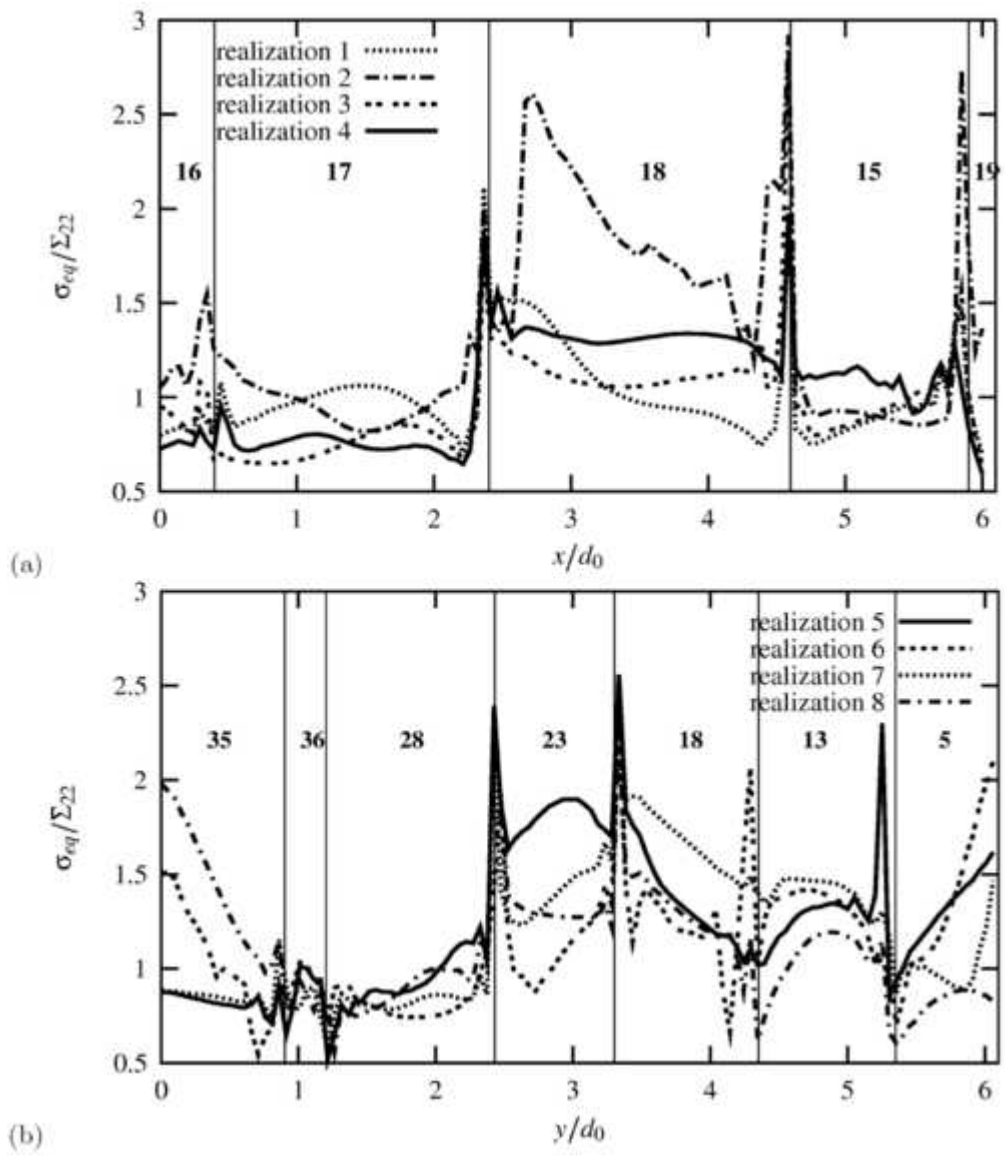


Figure 11  
21x24mm (600 x 600 DPI)

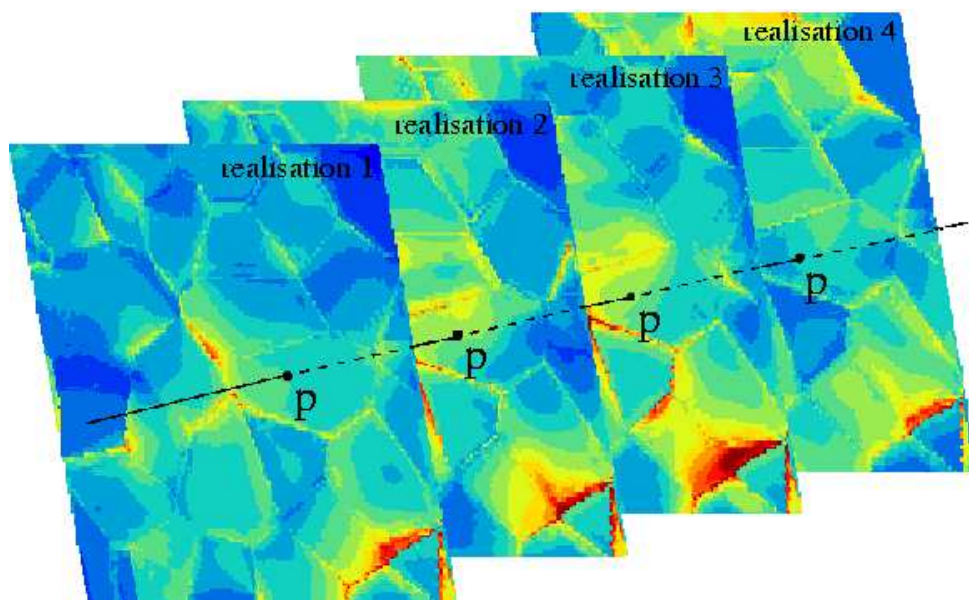


Figure 12  
152x90mm (100 x 100 DPI)

Review Only

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

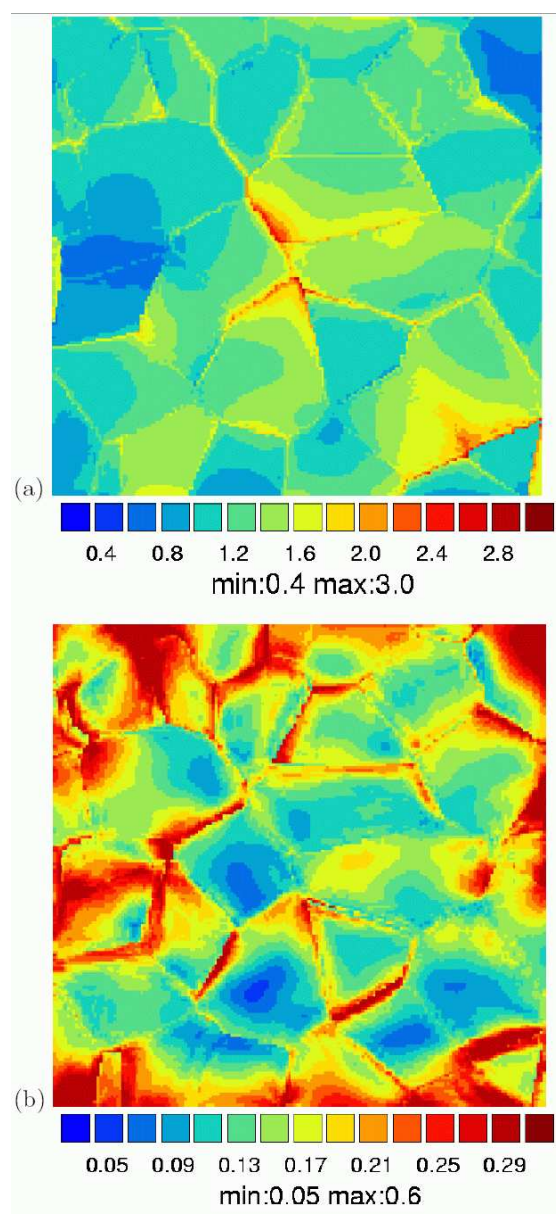


Figure 13  
218x474mm (72 x 72 DPI)

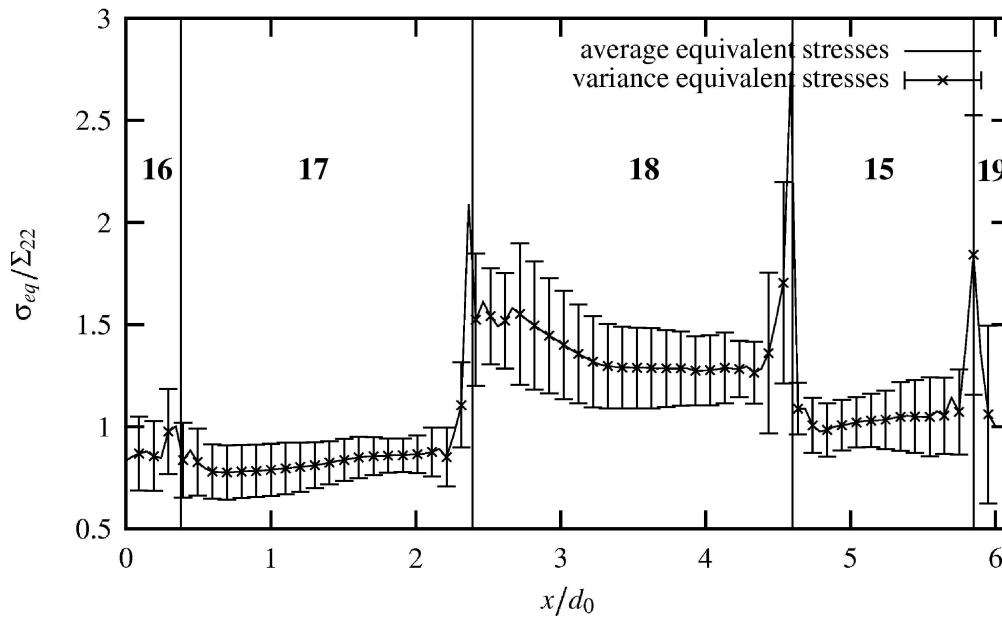


Figure 14  
182x111mm (407 x 407 DPI)

Review Only

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60