

九州工業大学学術機関リポジトリ



Title	Conformational transitions of a semiflexible polymer in nematic solvents
Author(s)	Matsuyama, Akihiko
Issue Date	2003-04
URL	http://hdl.handle.net/10228/628
Rights	Copyright © 2003 American Physical Society

Conformational transitions of a semiflexible polymer in nematic solvents

Akihiko Matsuyama*

Department of Chemistry for Materials, Faculty of Engineering, Mie University, Tsu Mie 514-8507, Japan

(Received 4 December 2002; published 11 April 2003)

Conformations of a single semiflexible polymer chain dissolved in a low-molecular-weight liquid crystalline solvent (nematogen) are examined by using a mean field theory. We take into account a stiffness and partial orientational ordering of the polymer. As a result of an anisotropic coupling between the polymer and nematogen, we predict a discontinuous (or continuous) phase transition from a condensed-rodlike conformation to a swollen one of the polymer chain, depending on the stiffness of the polymer. We also discuss the effects of the nematic interaction between polymer segments.

DOI: 10.1103/PhysRevE.67.042701

PACS number(s): 61.30.-v, 61.25.Hq, 64.70.Md

Mesomorphic mixtures consisting of polymers and low-molecular-weight liquid crystals (nematogens) are of current interest for fundamental scientific reasons and for many technological applications in electro-optical devices and high modulus fibers. The performances of these systems are related to a conformation of a polymer in a liquid crystal phase. One of the fundamental problems is how the polymer in a nematic phase interacts with a nematic field surrounding the polymer. Polymer chains have the variety of their stiffness and so when the polymer is mixed with the nematogens we can expect various conformations.

Mixtures of a flexible polymer and a nematogen show a macroscopic phase separation between an isotropic and a nematic phase below the nematic-isotropic transition (NIT) temperature of the pure nematogen [1–5]. Flexible polymers present a weak anisotropy in a nematic phase [6]. In contrast, liquid crystalline polymers, or stiffer polymers, have good miscibility with nematogens [7] due to the strong anisotropic coupling between the polymer and the nematogen. Anisotropy of the conformation for liquid crystalline polymers has been experimentally [8–11] and theoretically [12–20] studied in melt and in dilute nematic solutions. It is now important to consider the conformation of a polymer chain with various degrees of stiffness dissolved in nematogens. Recently, we presented a mean field theory to describe partial orientational ordering (induced rigidity) of semiflexible polymers dissolved in nematogens and showed various phase diagrams for the mixtures [20].

In this paper, we theoretically study the conformation of a semiflexible polymer dissolved in nematic solvents by combining the previous model [20] with an elastic free energy of the chain [21]. We show a discontinuous (or continuous) conformational transition between two different nematic states, depending on the stiffness of the polymer.

Consider a single linear polymer chain dissolved in nematogens. In order to take into account the stiffness of the polymer, we here assume that two neighboring bonds on the polymer chain have either bent (gauche state) or straightened (trans state) conformations [20,22]. Hereafter, we refer the segments in straightened bonds as “rigid” segments.

Let $V=R^3$ be the volume of the region occupied by a polymer, n be the number of segments on the polymer chain, and n_l be the axial ratio of the nematogen. The volume fraction of the polymer in the volume V is given by $\phi = a^3 n/V$, where a^3 is the volume of a unit segment. To derive an equilibrium conformation of the polymer, we consider thermodynamics of our systems. The free energy density of our system can be given by

$$f = f_{el} + f_{bent} + f_{mix} + f_{nem}. \quad (1)$$

The first term shows the elastic free energy due to the deformation of the polymer chain. Let R_z be the length of the polymer along the direction z of the nematic director and R_x be the length along the perpendicular direction ($R^3 = R_x^2 R_z$). Combining the classical elastic free energy obtained by Flory [23] with the freely jointed rod model [21], the elastic free energy is given as a function of ϕ and an orientational order parameter S_r of the rigid segments [21]:

$$\beta f_{el} = \frac{3}{2n} \left[\left(\frac{\phi}{nA} \right)^{1/3} + \frac{\phi}{3} \ln A - \phi \left(1 - \frac{2}{3} \ln \sqrt{n} \phi \right) \right], \quad (2)$$

where $A \equiv (1 + 2S_r)(1 - S_r)^2$ and $\beta \equiv k_B T$, T is the absolute temperature, k_B is the Boltzmann constant.

The second term shows the free energy change needed to straighten bent bonds on the polymer and is given by [20,22]

$$\beta f_{bent} = n_r (\beta f_0) - S_{comb} / k_B, \quad (3)$$

where f_0 is the local free energy difference between the bent and straightened conformations, and n_r shows the number of the rigid segments on the polymer. The second term in Eq. (3) is the combinatorial entropy related to the number of ways to select n_r rigid segments out of the n segments on the polymer and is given by $S_{comb}/k_B = \ln\{n!/[n_r!(n-n_r)!]\} = -n[x \ln x + (1-x) \ln(1-x)]$, where we used the Stirling's approximation and $x (\equiv n_r/n)$ shows the fraction of the rigid segments on the polymer. The volume fraction ϕ_r of the rigid segments on the polymer chain is given by $\phi_r = x \phi$. The third term in Eq. (1) is the free energy of the isotropic mixing for the polymer and nematogens. According to the Flory theory [23], the free energy is given by

*Electronic address: matuyama@chem.mie-u.ac.jp

$$\beta f_{mix} = \frac{1-\phi}{n_l} \ln(1-\phi) + \chi \phi(1-\phi), \quad (4)$$

where $\chi (\equiv U_0/k_B T)$ is the Flory-Huggins interaction parameter related to the isotropic dispersion interactions between unlike molecular species.

The last term in Eq. (1) shows the free energy for the nematic ordering. On the basis of the Maier-Saupe model [24,25] for orientational dependent-attractive interactions, the free energy of the nematic ordering is given by

$$\begin{aligned} \beta f_{nem} = & \frac{1-\phi}{n_l} \int f_l(\theta) \ln 4 \pi f_l(\theta) d\Omega \\ & + \frac{\phi_r}{n_r} \int f_r(\theta) \ln 4 \pi f_r(\theta) d\Omega - \frac{1}{2} \nu_{ll} S_l^2 (1-\phi)^2 \\ & - \nu_{lr} S_l S_r (1-\phi) \phi_r - \frac{1}{2} \nu_{rr} S_r^2 \phi_r^2, \end{aligned} \quad (5)$$

where $d\Omega \equiv 2\pi \sin\theta d\theta$, θ is the angle between the nematogen and the director of the orienting field. The ν_{ll} shows the orientational dependent (Maier-Saupe) interactions between the nematogens, ν_{lr} is that between the nematogen and the rigid segment on the polymer, and ν_{rr} is that between rigid segments. The $f_l(\theta)$ and $f_r(\theta)$ show the orientational distribution functions of the nematogens and that of the rigid segments on the polymer, respectively. The orientational order parameter S_l of the nematogens and that S_r of the rigid segments is given by

$$S_i = \int P_2(\cos\theta) f_i(\theta) d\Omega, \quad (6)$$

$i=l,r$, where $P_2(\cos\theta) \equiv 3(\cos^2\theta - 1/3)/2$.

The orientational distribution functions $f_l(\theta)$ and $f_r(\theta)$ are determined by the free energy (1) with respect to these functions: $(\partial f/\partial f_i(\theta))_{x,f_j} = 0$, under the normalization conditions $\int f_i(\theta) d\Omega = 1$. We then obtain the distribution function

$$f_i(\theta) = \frac{1}{Z_i} \exp[\eta_i P_2(\cos\theta)], \quad (7)$$

$$\eta_l \equiv n_l [\nu_{ll} S_l (1-\phi) + \nu_{lr} S_r x \phi], \quad (8)$$

$$\eta_r \equiv n [x \nu_{lr} S_l (1-\phi) + x^2 \nu_{rr} S_r \phi - E(\phi, S_r)], \quad (9)$$

where

$$E \equiv \frac{3S_r}{n\phi(1+2S_r)(1-S_r)} \left[\left(\frac{\phi}{nA} \right)^{1/3} - \phi \right]. \quad (10)$$

The constants Z_i ($i=l,r$) are determined by the normalization condition as $Z_i = 2\pi I_0[\eta_i]$, where the function $I_0[\eta_i]$ is defined as

$$I_q[\eta_i] \equiv \int_0^1 [P_2(\cos\theta)]^q \exp[\eta_i P_2(\cos\theta)] d(\cos\theta), \quad (11)$$

$q=0,1,2,\dots$. Substituting Eq. (7) into Eq. (6), we obtain two self-consistency equations for the two order parameters S_l and S_r :

$$S_i = I_1[\eta_i]/I_0[\eta_i]. \quad (12)$$

The orientational order parameter of the polymer chain is given by $S_p = x S_r$.

The fraction x of the rigid segments on the polymer is determined by minimizing the free energy (1) with respect to x : $(\partial f/\partial x)_{S_l, S_r} = 0$. This yields

$$\nu_{rr} \phi S_r^2 x + \nu_{lr} S_r S_l (1-\phi) - \ln \frac{x}{(1-x)K} = 0, \quad (13)$$

where $K \equiv \exp(-\beta f_0)$. By solving the coupled equations (12) and (13), we can obtain the values of the two order parameters S_l , S_r , and the fraction x of the rigid segments as a function of temperature and concentration.

The chemical potential $\mu_l(\phi)$ of the nematogen inside the volume V occupied by the polymer can be calculated by $\mu_l/n_l = f - \phi(df/f\phi)$ [21]:

$$\begin{aligned} \beta \mu_l(\phi)/n_l = & \frac{1}{n} \left[\left(\frac{\phi}{nA} \right)^{1/3} - \phi \right] + \frac{1}{n_l} \ln(1-\phi) + \frac{\phi}{n_l} + \chi \phi^2 \\ & + \frac{1}{2} \nu_{ll} S_l^2 (1-\phi)^2 + \nu_{lr} S_l S_r x \phi (1-\phi) \\ & + \frac{1}{2} \nu_{rr} S_r^2 x^2 \phi^2 - \frac{1}{n_l} \ln I_0[\eta_l], \end{aligned} \quad (14)$$

and the chemical potential $\mu_l^o(S_b)$ of the nematogen outside the polymer is given by substituting $\phi=0$ into $\mu_l(\phi=0)$. The orientational order parameter S_b of the bulk nematogens outside the polymer is determined by the self-consistency equation $S_b = I_1[\eta_b]/I_0[\eta_b]$, where $\eta_b \equiv n_l \nu_{ll} S_b$. The equilibrium concentration ϕ of the polymer can be determined from the balance among the nematogens existing outside and inside the polymer: $\mu_l(\phi) = \mu_l^o(S_b)$

In our numerical calculations, we further split the local free energy difference f_0 in Eq. (3) into two parts: $f_0 = \epsilon_0 - T s_0$, where $s_0 (= k_B \ln \omega)$ is the local entropy loss and $\epsilon_0 (< 0)$ is the energy change needed to straighten a bent bond. We then obtain $K = \omega \exp(-\beta \epsilon_0)$. The anisotropic interaction parameter ν_{ll} is given to be inversely proportional to temperature: [25] $\nu_{ll} = U_a/k_B T$. We define the dimensionless nematic interaction parameter $\alpha \equiv \nu_{ll}/\chi$ and the stiffness parameter $\epsilon \equiv -\beta \epsilon_0/\nu_{ll}$ of a polymer. The larger values of ϵ correspond to the stiffer chains. The most flexible polymer chain is realized when $\epsilon=0$. We also put $b = \nu_{lr}/\nu_{ll}$ and $c = \nu_{rr}/\nu_{ll}$, where b and c are constants. In the following calculations we use $\alpha=5$, $n_l=2$, $n=100$, $\omega=0.025$, and $b=1$ for a typical example. When $\alpha=5$, or for the larger values of ν_{ll}/χ , the nematogen behaves as a good solvent for the polymer because the value of the interaction parameter (χ) between the polymer and the solvent molecule is small [20]. However, the anisotropic interaction between the polymer and the nematogen exists.

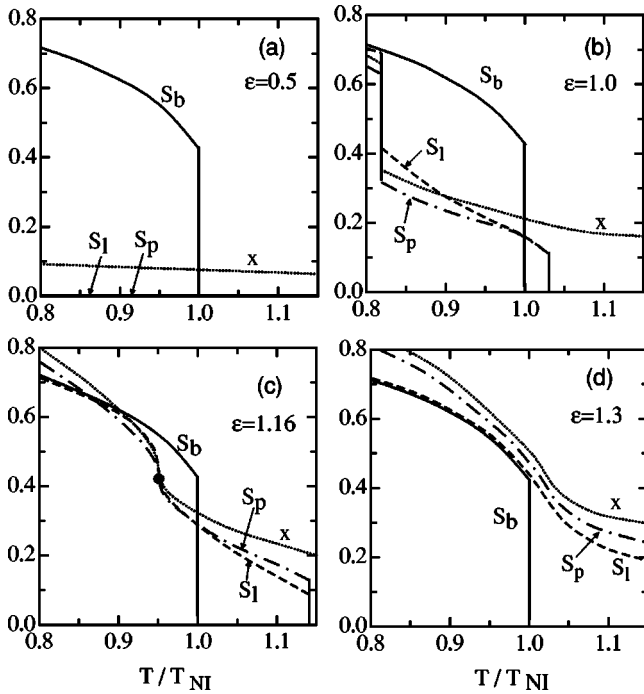


FIG. 1. Orientational order parameters and the fraction x of the rigid segments on the polymer chain plotted against the reduced temperature T/T_{NI} , where T_{NI} is the NIT temperature of the pure nematic outside the polymer. The value of stiffness parameter ϵ of the polymer is changed from (a) to (d).

Figures 1–3 show the results calculated for $c=0.1$ with a weak nematic interaction ν_{rr} . Figure 1 shows the orientational order parameters and the fraction x of the rigid segments on the polymer plotted against the reduced temperature T/T_{NI} , where T_{NI} is the NIT temperature of the pure nematic outside the polymer. The value of stiffness parameter ϵ of the polymer is changed from (a) to (d). The solid curve refers to the order parameter S_b of the nematic

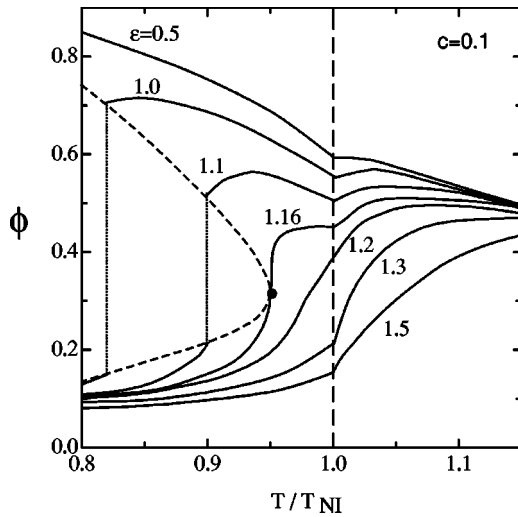


FIG. 2. Equilibrium volume fraction ϕ (swelling curve) of the polymer plotted against the reduced temperature for $c=0.1$. The stiffness (ϵ) of the polymer is changed.

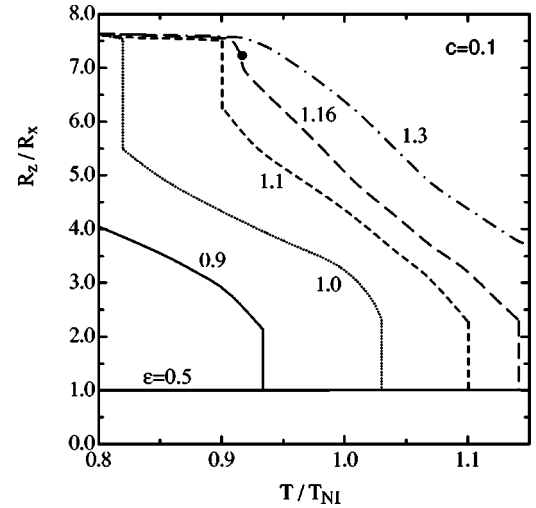


FIG. 3. Anisotropy R_z/R_x plotted against the temperature for $c=0.1$, where R_z (R_x) is the projection of the radius of gyration parallel (perpendicular) to the nematic director.

outside the polymer and the dash-dotted line shows the order parameter S_p of the polymer. The short-dashed line shows the order parameter S_l of the nematic inside the polymer and the dotted line corresponds to the fraction x of the rigid segments. For $\epsilon=0.5$, or a flexible polymer, the polymer is in an isotropic state for all temperatures and there is no anisotropic coupling between the polymer and nematic. When $\epsilon=1.0$, we find two phase transition temperatures: one is the temperature T_{NI}^p at high temperatures where the NIT of the polymer takes place and the other is the T_{NN} at low temperatures where the first-order phase transition between two different nematic states takes place. At the nematic state of the high temperature side ($T_{NN} < T < T_{NI}^p$), the fraction x of rigid segments is small. The polymer and the nematic inside the polymer are slightly ordered (weakly ordered nematic phase). In another nematic phase at $T < T_{NN}$, the value of the fraction x is large and the polymer and the nematic are strongly ordered (strongly ordered nematic phase). With increasing stiffness, T_{NI}^p and T_{NN} move to higher temperatures and a critical point (closed circle) for T_{NN} appears at $\epsilon=1.16$.

Figure 2 shows the equilibrium volume fraction ϕ (swelling curve) of the polymer plotted against the reduced temperature for various values of ϵ . When $\epsilon=0.5$, with decreasing temperature, the polymer is continuously condensed (or the volume fraction of the polymer is increased). The swelling curve has as kink at T_{NI} . For stiffer polymers, we find the first-order phase transition between a condensed conformation and a swollen one at T_{NN} . As shown in Fig. 3, the polymer is elongated along the nematic field and has a rod-like conformation. We then find two different types in the rodlike conformation of the polymer chain: one is the swollen-rodlike conformation at $T < T_{NN}$ and the other is the condensed-rodlike conformation at $T_{NN} < T < T_{NI}^p$. Above the critical stiffness, the polymer is continuously swollen with decreasing temperature.

Figure 3 shows the anisotropy R_z/R_x of the polymer chain plotted against the reduced temperature for various

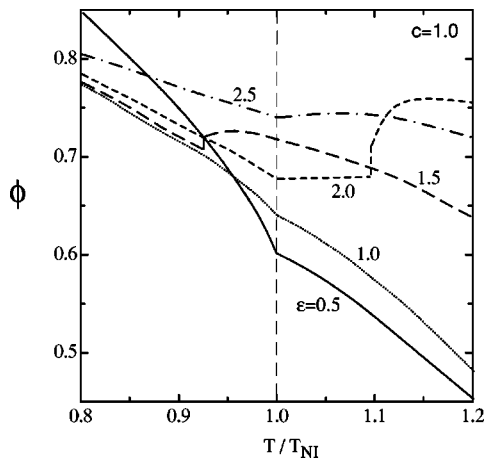


FIG. 4. Swelling curve of the polymer for $c = 1.0$. The stiffness (ϵ) of the polymer is changed.

values of ϵ . The lengths R_z and R_x are given as a function of S_r [21]. When $\epsilon = 0.5$, we have $R_z = R_x$ and the polymer has a spherical (coil) conformation. For $\epsilon = 1.0$, with decreasing temperature, the polymer is changed from a coil to a rodlike conformation at T_{NI}^p . The concentration ϕ of the polymer segments is continuously changed at T_{NI}^p (see Fig. 2). This spontaneous change in the polymer conformation at the transition T_{NI}^p has been reported [8,12,13]. Further decreasing temperatures, we find the phase transition between the two

different rodlike conformations at T_{NN} . Above the critical stiffness, the polymer continuously changed from the condensed-rodlike conformation to the swollen one with decreasing temperature.

When the anisotropic (attractive) interaction ν_{rr} between the polymer segments is strong, the swollen-rodlike conformation at lower temperatures disappears. Figure 4 shows the swelling curve of a polymer with $c = 1.0$. With decreasing temperature, the polymer is condensed with a rodlike conformation. When $\epsilon = 1.5$ and 2.0, we have a small jump in the swelling curve at T_{NI}^p [26]. The anisotropic interaction becomes an important factor on the conformation of a semi-flexible polymer.

In conclusion, we have predicted two different rodlike conformations of a polymer chain in a nematic solvent. The phase transition from a condensed-rodlike conformation to a swollen one is strongly affected by the stiffness of a polymer and the anisotropic interaction between polymer segments. The concept of the two different rodlike conformations is important to the modification of the mechanical and viscoelastic properties of liquid crystals by the dissolved polymers. The results will also be important to the conformation of DNA chains [17] and the volume phase transition of nematic gels [27] in nematic solvents.

This work was supported by a Grant-in-Aid from the Ministry of Education, Culture, Sports, Science and Technology, Japan.

- [1] B. Kronberg, I. Bassignana, and D. Patterson, *J. Phys. Chem.* **82**, 1714 (1978).
- [2] A. Dubault, C. Casagrande, M. Veyssie, and B. Deloche, *Phys. Rev. Lett.* **45**, 1645 (1980).
- [3] F. Brochard, J. Jouffroy, and P. Levinson, *J. Phys. (France)* **45**, 1125 (1984).
- [4] C. Shen and T. Kyu, *J. Chem. Phys.* **102**, 556 (1995).
- [5] J.C. Loudet, P. Barois, and P. Poulin, *Nature (London)* **407**, 611 (2000).
- [6] A. Dubault, R. Ober, M. Veyssie, and B. Cabane, *J. Phys. (France)* **46**, 1227 (1985).
- [7] *Liquid Crystalline and Mesomorphic Polymers*, edited by V.P. Shibaev and L. Lam (Springer-Verlag, New York, 1993).
- [8] J.F. D'Allest, P. Maissa, A. ten Bosch, P. Sixou, A. Blumstein, R. Blumstein, J. Teixeira, and L. Noirez, *Phys. Rev. Lett.* **61**, 2562 (1988); *Mol. Cryst. Liq. Cryst.* **155**, 581 (1988).
- [9] F. Volino, M.M. Gauthier, A.M. Giroud-Godquin, and R.B. Blumstein, *Macromolecules* **18**, 2620 (1985).
- [10] D.J. Photinos, E.T. Samulski, and H. Toriumi, *J. Phys. Chem.* **94**, 4688 (1990).
- [11] Y.C. Chiang, A.M. Jamieson, M. Kawasumi, and V. Percec, *Macromolecules* **30**, 1992 (1997).
- [12] A. ten Bosch, P. Maissa, and P. Sixou, *J. Chem. Phys.* **79**, 3462 (1983).
- [13] M. Warner, J.M.F. Gunn, and A. Baumgartner, *J. Phys. A* **18**, 3007 (1985); X.J. Wang and M. Warner, *ibid.* **19**, 2215 (1986).
- [14] V.V. Rusakov and M.I. Shliomis, *J. Phys. (France) Lett.* **46**, 935 (1985).
- [15] A.J. Liu and G.H. Fredrickson, *Macromolecules* **28**, 2817 (1993).
- [16] P.J. Flory, *Macromolecules* **11**, 1141 (1978).
- [17] T. Odijk, *J. Chem. Phys.* **105**, 1270 (1996).
- [18] G.A. Carri and M. Muthukumar, *J. Chem. Phys.* **109**, 11 117 (1998).
- [19] P.D. Olmsted and S.T. Milner, *Macromolecules* **27**, 6648 (1994).
- [20] A. Matsuyama and T. Kato, *Phys. Rev. E* **59**, 763 (1999).
- [21] A. Matsuyama and T. Kato, *J. Chem. Phys.* **114**, 3817 (2001).
- [22] P.J. Flory, *Proc. R. Soc. London, Ser. A* **234**, 60 (1956).
- [23] P.J. Flory, *Principles of Polymer Chemistry* (Cornell University, Ithaca, 1953).
- [24] W. Maier and A. Saupe, *Z. Naturforsch. A* **14a**, 882 (1959).
- [25] P.G. de Gennes and J. Prost, *The Physics of Liquid Crystals*, 2nd ed. (Oxford Science, London, 1993).
- [26] Details will be published elsewhere.
- [27] K. Urayama, Y. Okuno, T. Kawamura, and S. Kohjiya, *Macromolecules* **35**, 4567 (2002).