

Original citation:

Joubert, Fanny, Musa, Osama M., Hodgson, David R. W. and Cameron, Neil R. (2014) The preparation of graft copolymers of cellulose and cellulose derivatives using ATRP under homogeneous reaction conditions. *Chemical Society Reviews*, 43 (20). pp. 7217-7235.

Permanent WRAP URL:

<http://wrap.warwick.ac.uk/85231>

Copyright and reuse:

The Warwick Research Archive Portal (WRAP) makes this work of researchers of the University of Warwick available open access under the following conditions. Copyright © and all moral rights to the version of the paper presented here belong to the individual author(s) and/or other copyright owners. To the extent reasonable and practicable the material made available in WRAP has been checked for eligibility before being made available.

Copies of full items can be used for personal research or study, educational, or not-for-profit purposes without prior permission or charge. Provided that the authors, title and full bibliographic details are credited, a hyperlink and/or URL is given for the original metadata page and the content is not changed in any way.

Publisher statement:

First published by Royal Society of Chemistry 2014

<http://dx.doi.org/10.1039/C4CS00053F>

A note on versions:

The version presented here may differ from the published version or, version of record, if you wish to cite this item you are advised to consult the publisher's version. Please see the 'permanent WRAP URL' above for details on accessing the published version and note that access may require a subscription.

For more information, please contact the WRAP Team at: wrap@warwick.ac.uk



The Preparation of Graft Copolymers of Cellulose and Cellulose Derivatives Using ATRP Under Homogeneous Reaction Conditions


Journal:	<i>Chemical Society Reviews</i>
Manuscript ID:	CS-REV-01-2014-000053.R2
Article Type:	Review Article
Date Submitted by the Author:	n/a
Complete List of Authors:	Joubert, Fanny; Durham University, Department of Chemistry Musa, Osama; Ashland Inc., Hodgson, David; Durham University, Department of Chemistry Cameron, Neil; University of Durham, Department of Chemistry

Chemical Society Reviews – Referee Guidelines

Chemical Society Reviews publishes succinct and reader-friendly articles on topics at the forefront of the chemical sciences. **Our aim is to only publish reviews of the very highest quality and international impact.**

Questions to consider when reviewing this article:

- Is the subject of broad general interest?
- Is it timely? Does it genuinely add to/complement the existing literature?
- Does it give an authoritative and state-of-the-art account?
- Are the authors qualified to write this review?
- Would it be more suitable for a specialised journal?

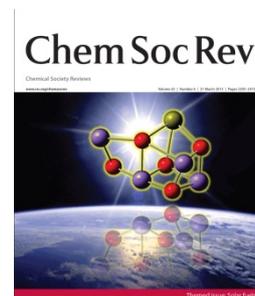

2012 Impact Factor: 24.89

Chemical Society Reviews publishes two article types:

Tutorial Reviews

Tutorial Reviews are short, authoritative overviews of important topics in the chemical sciences. They are of relevance to both the general research chemist who is new to the field as well as the expert. They should outline the development of a subject, its current standing and implications for the wider scientific community.

Tutorial Reviews must be:

- **Accessible:** to graduate students and beyond.
- **An essential introduction to the field:** serving as a springboard to further reading.
- **Short:** Maximum 12,000 word equivalents; 12 journal pages; approx. 35 pages of A4 (double-spaced).
- **Lightly referenced:** Strict maximum 50 citations; authors should credit the major contributors only.
- **Jargon free:** Specialist terms and symbols should be defined and fundamental ideas simply explained.

Key Learning Points: Tutorial Reviews should now include up to five key learning points that a reader should expect to gain from reading the review.

Review Articles

Review Articles provide an authoritative and in-depth understanding of important topics in the chemical sciences. They give a very high quality state-of-the-art account and a balanced assessment of the current primary literature.

Not suitable?

If you do not recommend publication of this article in *Chemical Society Reviews*, please indicate whether it might be suitable for a more specialised RSC journal (see <http://pubs.rsc.org/en/journals>).

With best wishes,

A handwritten signature in black ink, appearing to be 'R. Eagling', written in a cursive style.

Dr Robert D Eagling CSi CChem MRSC
Editor, *Chemical Society Reviews*

We appreciate your time in serving as a reviewer. To acknowledge this, the RSC offers a **25% discount** on its books.

The Preparation of Graft Copolymers of Cellulose and Cellulose Derivatives Using ATRP Under Homogeneous Reaction Conditions

Fanny Joubert ^{a,b}, Osama M. Musa ^c, David R. W. Hodgson ^{a,b}, Neil R. Cameron ^{a,b}

^aDepartment of Chemistry, Durham University, Science Laboratories, Durham DH1 3LE, UK

^bBiophysical Sciences Institute, Durham University, Durham DH1 3LE, UK

^cAshland Speciality Ingredients, 1005 Route 202/206, Bridgewater, NJ 08807, USA

Abstract

In this comprehensive review, we report on the preparation of graft-copolymers of cellulose and cellulose derivatives using atom transfer radical polymerization (ATRP) under homogeneous conditions. The review is divided into four sections according to the cellulosic material that is graft-copolymerised; i) cellulose, ii) ethyl cellulose, iii) hydroxypropyl cellulose and iv) other cellulose derivatives. In each section, the grafted synthetic polymers are described as well as the methods used for ATRP macro-initiator formation and graft-copolymerisation. The physical properties of the graft-copolymers including their self-assembly in solution into nanostructures and their stimuli responsive behaviour are described. Potential applications of the self-assembled graft copolymers in areas such as nanocontainers for drug delivery are outlined.

I. Introduction

Cellulose is the most abundant biopolymer on earth as it represents about fifty per cent of biomass, with an annual production estimated to be 10^{11} tons per year¹⁻³. Cellulose is

synthesised by some plants, animals, bacteria and also algae. In plants, cellulose is a major component of the rigid cell walls⁴⁻⁶. Cellulose is defined as long polymer chains of β -D-anhydroglucopyranose units (AGU units). The β -D-glucoses are covalently bonded together by the linkage between the C1 anomeric carbon and the C4 oxygen atom, providing β -1,4-glycosidic bonds⁷. The structural aspect of cellulose defines its properties. The supra-molecular aspect is mainly characterised by two hydrogen-bonding networks: the intramolecular and intermolecular H-bonding networks which are respectively between and within chains. These networks are responsible for the insolubility of cellulose in common solvents^{3, 8-10}. Although cellulose is a low cost material with low density (in its unpurified state), biodegradability, high strength and high thermal stability, its applications have been mainly limited to the paper and textile industries due to its poor solubility. Cellulose has been chemically modified to impart new properties such as solubility in organic solvents, crease resistance, dimensional stability, thermoplasticity and antimicrobial properties^{6, 9, 11}. The reactivity of cellulose arises from the presence of hydroxyl groups. Two secondary alcohols are present at the C2 and C3 positions and one primary alcohol at the C6 position, where the –OH reactivity follows the order: $-\text{OH}_{\text{C6}} \gg -\text{OH}_{\text{C2}} > -\text{OH}_{\text{C3}}$ ^{12, 13}. Etherification, esterification and oxidation reactions of the hydroxyl groups have been used to create a range of new cellulosic materials. These commercial derivatives include hydroxyethyl cellulose (HEC), carboxymethyl cellulose (CM Cell), ethyl cellulose (EC), hydroxypropyl cellulose (HPC) and others (Figure 1). They are defined by the degree of substitution (DS) which ranges from 0 to 3 depending on the number of hydroxyl groups in the AGU units that have been modified. Different methods, including NMR spectroscopy^{14, 15} and elemental analysis¹⁶, have been used to measure DS. For instance, DS is directly calculated from the ¹H NMR integral ratio of one of the protons assigned to the added functional group to a proton assigned to the cellulose backbone. Meanwhile, the content of carbon, hydrogen, nitrogen or any other

halogens present in the newly prepared derivatives can be measured by elemental analysis and the resulting elemental content permits further the estimation of the DS.

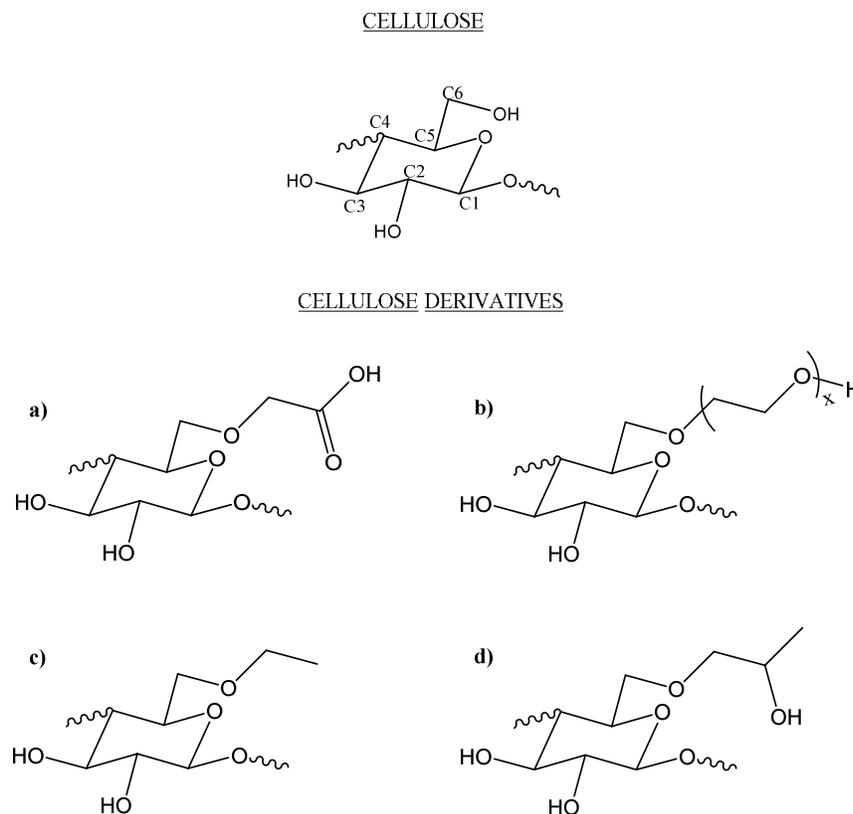


Figure 1: Molecular structure of cellulose and cellulose derivatives (considering a DS of 1 at the C6 position); a) CM Cell b) HEC c) EC and d) HPC

The chemical modification of cellulose and its derivatives has been performed under both heterogeneous and homogeneous conditions. Heterogeneous conditions refer to situations where cellulose is not dissolved in the reaction medium so the reaction occurs at the interface between the solid and liquid phases resulting in modification only at the surface. Cellulose fibers^{17, 18}, membranes^{19, 20} and nano-whiskers^{21, 22} have all been modified under heterogeneous conditions. Homogeneous conditions are defined by the dissolution or, at least, by the swelling of cellulose in the reaction medium resulting in modification of the entire cellulose molecular structure. This remains extremely challenging because of both the high

molecular weight of cellulose and the intra/inter-H bonding networks which define the cellulose solid-state structure and limit considerably its solubility in common solvents. Recently, Olsson and Westman²³ reviewed advances in methods for the dissolution of cellulose. Water swells cellulose because the water molecules interact with the cellulose backbone but do not break fully the H-bonding interactions. Cellulose is partially soluble in alkali solution where the concentration of the solution needs to be at least 10 % w/w. The addition of species including PEG, urea or thiourea enhances the solubility of cellulose in alkali solution at low temperature by limiting the aggregation of cellulose chains. Furthermore, the DMAc/LiCl system has been used commonly to dissolve cellulose. It involves interaction between the hydroxyl groups of cellulose and the Cl anion, resulting in the formation of “bridges” between cellulose and the macro-cation [DMAc-Li]⁺. However, this process requires the prior-elimination of water which prevents its use in industry. Ionic liquids (ILs) such as BMIMCl dissolve cellulose due penetration of the anion into the cellulose structure, breaking the H- bonding networks.

Recently, chemical modification of cellulose by polymer grafting has generated much interest because it combines two polymers, one of which is a bio-polymer, in one unique material, where the combination is expected to produce new materials properties. Different grafting approaches are described in the literature^{13, 24, 25}: the “grafting through” approach is characterised by the polymerisation of a macro-monomer in the presence of a low molecular weight monomer; the “grafting to” approach involves attaching a pre-synthesised polymer chain to the cellulose backbone; the “grafting from” approach involves the polymerisation of monomeric species from the backbone. The “grafting from” approach is the most popular for modifying cellulose. Free radical polymerisation is the main method used to graft synthetic polymers onto cellulose, where the backbone has been initiated by hydrogen abstraction^{26, 27}, single electron transfer²⁸, irradiation^{29, 30} or other methods^{13, 24, 31}. However, these methods

also result in the formation of ungrafted homopolymer chains and give no control over the density or the length of the grafts. In recent years, controlled radical polymerisation (CRP) processes have been used to create well-defined cellulose-based graft-copolymers including a narrow molecular weight distribution of the grafts. The most commonly used CRP process is Atom Transfer Radical Polymerisation (ATRP)^{32, 33} because of the straightforward preparation of cellulose macro-initiators from the reaction between one of hydroxyl groups present on the cellulose backbone and commercially available acyl chlorides or bromides. Compared to other CRP techniques, ATRP produces polymers with the narrowest molecular weight distribution and the required reagents such as catalysts and ligands are commercially available at low cost. On the other hand, commercially available transfer agents for Reversible Addition Fragmentation Transfer (RAFT) polymerisation³⁴ can be quite expensive and may have to be synthesised for specific targets, which adds steps to the fabrication process. Furthermore, the use of RAFT polymerisation produces polymers with possibly undesirable colour and/or odour, due to the presence of sulphur from the chain transfer agent³⁵. This could be a constraint in some applications. However, this problem can potentially be solved by removing RAFT agent residues from chain ends; recently, Willcock *et al.*³⁶ reviewed the different methods by which this can be achieved, including for instance thermal elimination, aminolysis and hetero-Diels-Alder reactions. It should be pointed out that ATRP also has some inherent disadvantages; it has to be conducted in a rigorously oxygen-free environment and the use of copper can be a problem as it can be difficult to remove. Furthermore, some solvents and vinyl monomers deactivate the catalyst resulting in unsuccessful or uncontrolled polymerisation.

The modification of cellulose and its derivatives by ATRP is reviewed in this article, with a focus on ATRP under homogeneous conditions. This has received much less attention than the alternative approach of grafting onto the surface of solid cellulosic materials (selected

relevant references are cited here^{37, 38, 39}). The review is arranged into sections based on the parent cellulose derivative undergoing chemical modification. The modifications involve principally two steps. The first is the preparation of macro-initiators with a certain DS which determines the graft-density of the resulting graft-copolymer. In the second step, these macro-initiators were used to initiate the ATRP of various monomers resulting in the formation of graft-copolymers of cellulose and cellulose derivatives. The efficiency of the polymerisation has been highlighted using the monomer conversion (%) which permits a determination of the chain length, and the livingness of the polymerisation has been evaluated by measuring dispersity (D_M).

II. Graft-copolymers of cellulose

In this section, studies on the graft-copolymerisation from cellulose will be reviewed. The process of the activation of the cellulose backbone will be described, and the influence of the reaction conditions on the DS will be highlighted, for instance the choice of solvents used to dissolve the cellulose starting material. Moreover, the preparation in a controlled manner of graft-copolymers from monomers such as methyl methacrylate (MMA), N,N-dimethyl acrylamide (DMA), 3-ethyl-3-methacryloyloxy-methyloxetane (EMO), styrene (St), N-isopropyl acrylamide (NIPAAM) and N,N-dimethylamino-2-ethyl methacrylate (DMAEMA) and the characterisation of the resulting polymers will be detailed. Ring Opening Polymerisation (ROP) will be mentioned as it was used in combination with ATRP for preparing graft block copolymers from ϵ -caprolactone (CL) or L-lactide (LLA). The properties of these graft-copolymers including aggregation and responses to external stimuli will be discussed.

The first work related to cellulose modification using the ATRP process under homogeneous conditions was reported by Chang *et al.*⁴⁰ in 2008, who described the graft-copolymerisation of various monomers. The macro-initiator, Cl-Cell was synthesised from an excess of chloroacetyl chloride in a mixture of dimethylacetamide (DMAc)/LiCl in the presence of pyridine. The use of DMAc/LiCl enhanced the homogeneity of the reaction medium due to the interruption of the H-bonding networks of the cellulose structure, and led to a DS value of 2.1 after 10 h of reaction at room temperature. The ATRP of methyl methacrylate (MMA) or 3-ethyl-3-methacryloyloxy-methyloxetane (EMO) was performed using multidentate amines as ligands such as *N,N,N',N',N''*-pentamethyldiethylenetriamine (PMDETA) and tetramethylethylenediamine (TMEDA) and copper (I) bromide (CuBr) as catalyst. The influence of the solvent on the process was investigated using solvents including DMSO, anisole and DMF. DMSO and anisole were found to be less suitable than DMF for the ATRP process because they interacted with the CuBr/ligand system resulting in deactivation of the polymerisation process. Polymerisation of MMA and EMO was conducted at 130 °C for around 20 h, long reaction times being necessary to reach the maximum yield. The ratio of initiator to catalyst, ligand and monomer ($[I]/[C]/[L]/[M]$) required to give maximum yield was 1/1/3/9 and 1/1/3/60 for the polymerisation of EMO and MMA respectively. The chloride at the chain end of PMMA-g-Cell and PEMO-g-Cell was used to activate the ATRP of EMO and MMA respectively to form copolymers (Figure 2), however, the ATRP of EMO onto PMMA-g-Cell was more efficient than that of MMA onto PEMO-g-Cell. The catalyst was copper (I) chloride (CuCl) for both graft-copolymerisations; TMEDA was used for graft-copolymerising EMO onto Cl-PMMA-Cell whereas PMDETA was chosen for graft-copolymerising MMA onto Cl-PEMO-Cell. For an optimum yield, a temperature of 70 °C and a ratio $[I]/[C]/[L]/[M]$ of 1/1/3/60 were used for both polymerisations, however, the

reaction time was twice as long for graft-copolymerising EMO than MMA. The extent of control of the polymerisations was not determined.

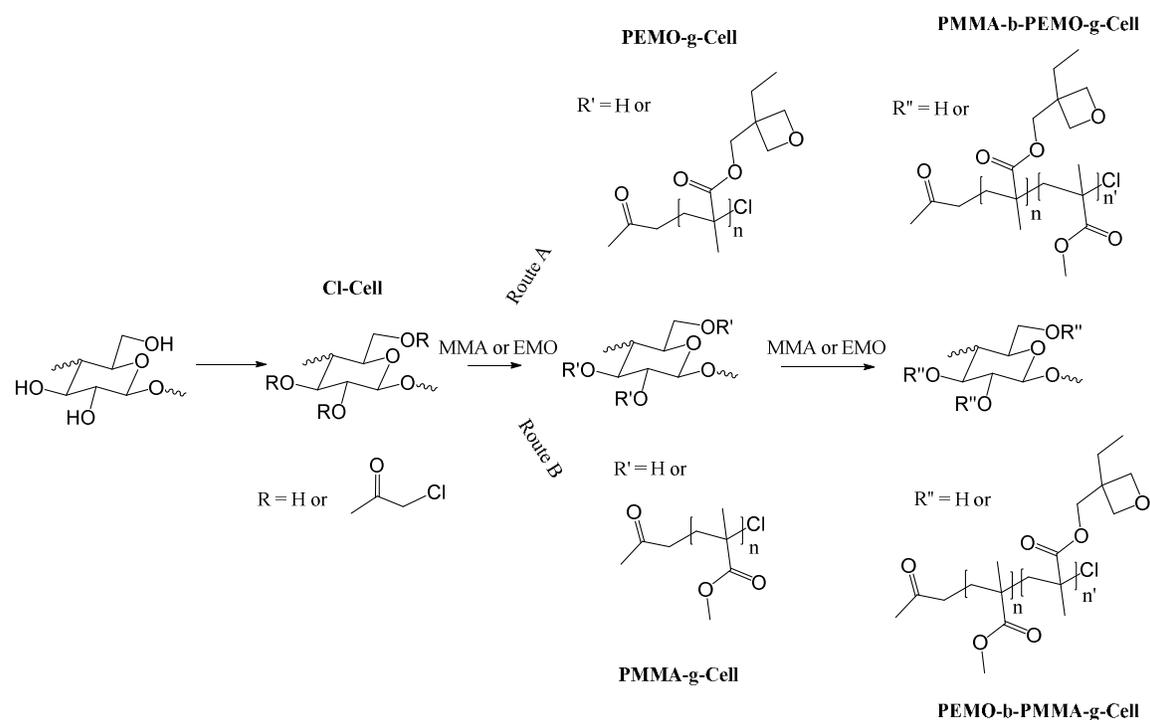


Figure 2: Preparation of graft-copolymers PMMA-b-P(MMA-g-Cell) (Route A) and P(EMO-b-P(MMA-g-Cell)) (Route B) from the macro-initiator, Cl-Cell.

The same authors investigated the preparation of copolymers by ROP and ATRP. The ROP of CL or LLA and ATRP of MMA or EMO were performed simultaneously by using a Cl-Cell, PMMA-g-Cell or P(EMO-g-Cell) initiator (Figure 3). Modification of cellulose was confirmed by Thermal Gravimetric-Differential Thermal Analysis (TG-DTA), Differential Scanning Calorimetry (DSC) and Wide-Angle X-ray Diffraction (WAXD) analyses.

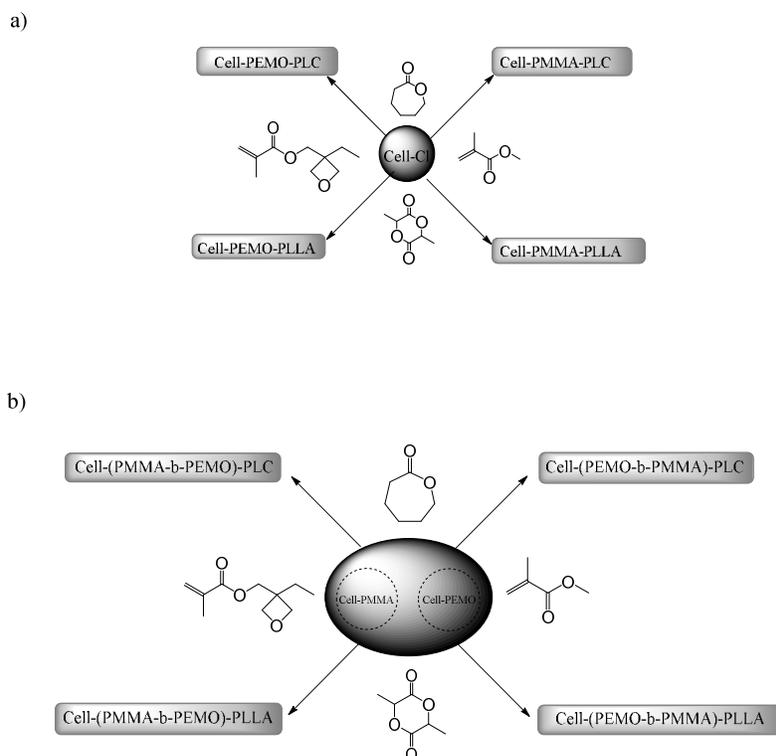


Figure 3: Preparation of graft-copolymers combining ATRP and ROP processes using macro-initiators a) Cl-Cell b) PMMA-g-Cell and PEMO-g-Cell.

Chun-xiang *et al.*⁴¹ reported the preparation of the macro-initiator Cl-Cell (from chloroacetyl chloride) and subsequent graft-copolymerisation of MMA using an ionic liquid as the reaction medium. The DS of the macroinitiator increased when the temperature was increased, however, above 50 °C there was evidence of hydrolysis of the cellulose backbone. The highest DS reached was 1.8 which is lower than that achieved by the method of Chang *et al.*⁴⁰. This is explained by the decrease of the amount of reactant chloroacetyl chloride compared to AGU. MMA was graft-copolymerised under mild reaction conditions, and the D_M of the product ranged from 1.5 to 1.8, depending on the reaction conditions, which were chosen to limit the radical-radical coupling of the propagating chains. A bidentate ligand, bpy, was also used and the first time the polymerisation was conducted in an ionic liquid at 70 °C for 5 h. A maximum of 15% of monomer conversion was reached with a D_M of 1.5 for a ratio

[I]/[C]/[L]/[M] equal to 1/1/1/300. The graft copolymers were able to form aggregates in solution.

Further work was carried out by Meng *et al.*⁴² who reported the graft-copolymerisation of MMA and styrene (St) onto cellulose. The macro-initiator Br-Cell was prepared from bromoisobutyryl bromide under homogeneous conditions using 1-allyl-3-methyl-imidazolium chloride ([AMIM]Cl) and the influence of the reaction conditions on the DS were evaluated. Increases in both the molar ratio of AGU/Br and reaction time led to an increase in substitution of the hydroxyls with bromo-ester groups, and thus, the degree of functionalization, which affected the graft-copolymer solubility. The highest DS for Br-Cell was 0.72 using a ratio of AGU to Br equal to 1/5. This is lower than that reported by Ifuku *et al.*⁴³ because of a lower amount of reactant, a shorter reaction time and/or absence of catalyst. MMA and/or St were then graft-copolymerised from the macro-initiator by ATRP under optimised experimental conditions using bpy/CuCl, butanone as solvent, 3h reaction time, a temperature of 70 °C and a ratio [I]/[C]/[L]/[M] of 1/1/2/200. These conditions resulted in a monomer conversion of 28% and a D_M of 1.4 as determined by GPC of the hydrolysed grafted chains, which is the lowest value of D_M obtained for the ATRP of MMA onto cellulose under homogeneous conditions. The authors were the first to report the ATRP of styrene onto cellulose, using the same catalyst system. However, the reaction time was shorter (2 h), the temperature was higher (110 °C) and the polymerisation was conducted in dioxane as reaction medium. A relatively low monomer conversion, approximately 14%, and a D_M of 1.5 were obtained. The authors investigated the diameter, conformation and morphology of PMMA-g-Cell aggregates using static and dynamic light scattering (SLS and DLS) and transmission electron microscopy (TEM) respectively.

In 2011 Xin *et al.*⁴⁴ prepared the graft-copolymer PMMA-g-Cell with the highest monomer conversion reported in the literature. The macro-initiator, Br-Cell with a DS of 0.7

was synthesised following the same procedure of Sui *et al.*⁴⁵ and thus ATRP of MMA onto Br_{0.7}-Cell was investigated in DMF. The importance of both concentration and temperature on the extent of control was demonstrated; a high dilution and low temperature limited the radical-radical coupling responsible for gel formation and enhanced the polymerisation control. However, a low temperature (50 °C) reduced the graft ratio, and thus a compromise between reaction time, temperature and concentration was required to achieve a 38% monomer conversion, a D_M and graft ratio of 1.65. Compared to the work of Meng *et al.*⁴² and Chun-xiang *et al.*⁴¹, this increase in monomer conversion could be due to the use of a tridentate ligand which has a higher K_{ATRP} , responsible for the higher polymerisation rate. The graft-copolymer was thermally more stable than PMMA and aggregated into spheres of 500 nm and 100 nm diameters respectively in DMF and in acetone (Figure 4) as shown by TEM and Atomic Force Microscopy (AFM).

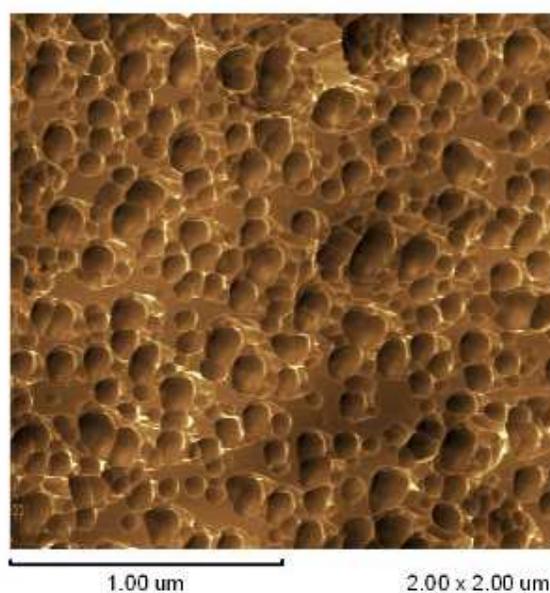


Figure 4: AFM image for the aggregates formed from PMMA-g-Cell in acetone⁴⁴.

Zhong *et al.*⁴⁶ developed a full evaporation headspace gas chromatographic (HS-GC) method⁴⁷ to analyse graft-copolymers produced from cellulosic materials by determining the

residual monomer in the graft-copolymer. In order to validate their analytical system, the homogeneous grafting of PMMA onto Cl-Cell was performed. Cl-Cell was prepared from chloroacetyl chloride in the presence of catalyst and the functionalization reaction was performed for 5 h at 50 °C in a mixture of DMAc/LiCl. The Activator Generated by Electron Transfer (AGET) ATRP process⁴⁸ was used to polymerise MMA onto cellulose and the control of the polymerisation was highlighted using the HS-GC method. Contrary to conventional ATRP, AGET ATRP uses Cu (II) and a reducing agent such as ascorbic acid to reduce Cu (II) to Cu (I). The main advantage of AGET ATRP is its ability to be carried out in the presence of air. The graft-copolymerisation was conducted in DMAc at temperatures of 50-70 °C. The authors suggested that the most efficient temperature was 50 °C as it limits MMA homopolymerisation. However, the monomer conversion was only 13% and the D_M of the grafts was 1.4. Compared to previous work with MMA, the monomer conversion is relatively low. A plausible reason could be the low amount of catalyst, especially with TMEDA, a bidentate ligand, for which it is required to have a high concentration of catalyst to improve the rate of polymerisation.

The synthesis of PDMA-g-Cell was investigated by Yan and Tao⁴⁹, who used a DMAc/LiCl system to dissolve cellulose prior to further modifications. The macro-initiator was synthesised from 2-bromoisobutyryl bromide leading to Br-Cell of DS 0.2. The ATRP of *N,N*-dimethylacrylamide (DMA) was successfully performed using the Br-Cell macro-initiator. 2,2'-Bipyridine (bpy), a bidentate ligand, was used with CuBr and DMSO as solvent. The polymerisation was conducted at room temperature for 7 h using a ratio of [I]/[C]/[L]/[M] equal to 1/2.9/1.3/90. Compared to the work of Chang *et al.*⁴⁰, a higher amount of catalyst was used to decrease the reaction time i.e. 7 h instead of approximately 20 h. In the ATRP process, the choice of the ligand is crucial as it determines both the rate of reaction and the extent of control of the polymerisation. Compared to tetramethylethylenediamine (TMEDA)

and pentamethyldiethylenetriamine (PMDETA), bpy has a lower ATRP equilibrium constant (K_{ATRP}) which means that a greater amount of catalyst is needed to achieve the same rate of polymerisation. The DMA grafts of PDMA-g-Cell were removed by hydrolysis and were analysed by Gel Permeation Chromatography (GPC), which revealed a linear increase of molecular weight with monomer conversion, indicating a high level of polymerisation control. After 7 h of reaction, the monomer conversion reached 50% and the D_M of PDMA was 1.5. The graft-copolymer PDMA-g-Cell was coated onto a cellulose membrane to produce a material that showed dramatically reduced protein adsorption compared to the uncoated membrane (Figure 5). This represents an improvement in the membrane hemocompatibility and therefore shows potential for use in hemodialysis.

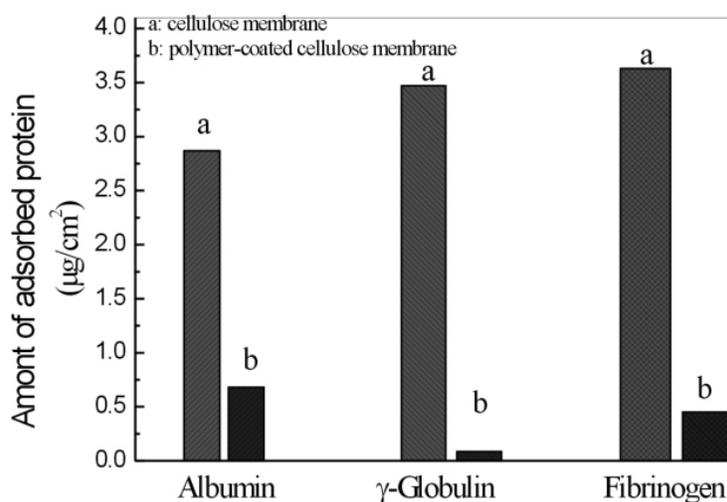


Figure 5: Adsorption of proteins onto (a) uncoated cellulose membrane and (b) cellulose membrane coated with PDMA-g-Cell⁴⁹

In order to produce a cellulose-based stimuli-responsive material, Ifuku *et al.*⁴³ investigated the graft-copolymerisation of *N*-isopropylacrylamide (NIPAAm) onto cellulose (Figure 6). PNIPAAm is a thermo-responsive material with a lower critical solution temperature (LCST) of 32 °C. Below the LCST, the chains are present as unimers in solution

whereas the chains collapse above the LSCT, resulting in the precipitation of the polymer from the solution.

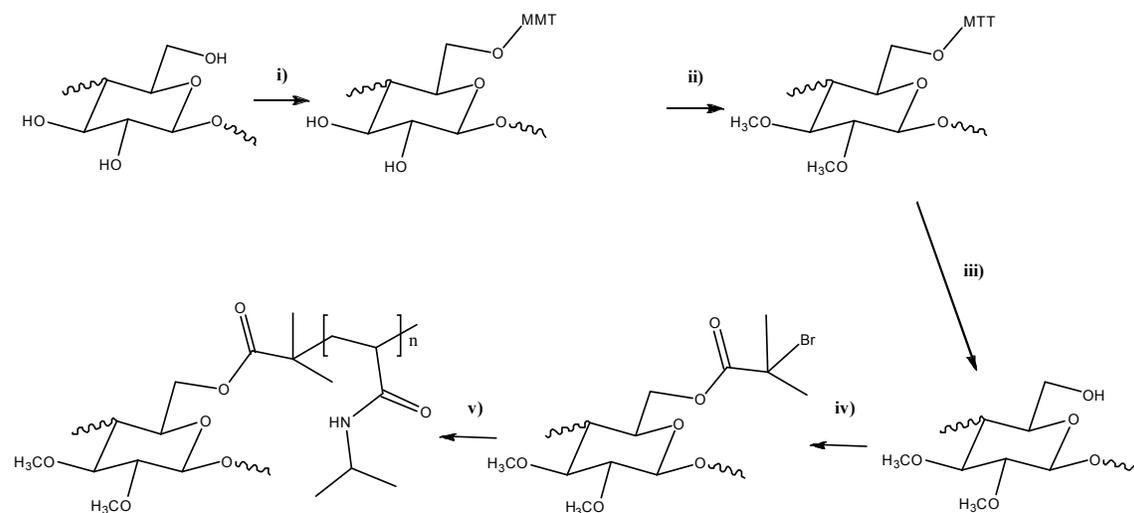


Figure 6: Reaction scheme showing the preparation of PNIPAAm-g-Cell; i) protection of the C6-OH, ii) methylation of the -OH groups at C2 and C3 positions, iii) deprotection of the OH at C6 position, iv) acylation of the OH and v) ATRP of NIPAAm; MMT= monomethoxy trityl-.⁴³

The macro-initiator Br-Cell was prepared following the procedure described by Yan and Tao⁴⁹, yielding a DS of 1 indicating complete functionalization of the -OH group at the C6 position. For the ATRP of NIPAAm, a tridentate ligand, PMDETA was used to complex CuBr and a mixture DMF/H₂O was used as reaction medium. During polymerisation, both dispersity (D_M) and monomer conversion increased when the amount of ligand and catalyst were increased compared to monomer. The D_M increase indicates a loss of polymerisation control. For a ratio [I]/[C]/[L]/[M] of 1/4/4/200 and a reaction time of 12 h at room temperature, an optimum monomer conversion of 17% and a D_M of 2.3 were measured indicating a relatively broad molecular weight distribution. The increased degree of polymerisation (DP) led to increases in both the thermal stability and the glass transition

temperature of the product. The graft-copolymer was insoluble in water, but the PNIPAAm chains permitted the suspension of graft-copolymers in water to form a cloudy solution. Above 30 °C, the PNIPAAm chains collapsed resulting in the precipitation of the graft-copolymers, leaving the aqueous solution clear.

Further investigations were conducted to produce dually responsive materials. Sui *et al.*⁴⁵ investigated the graft-copolymerisation of 2-(dimethylamino)ethyl methacrylate (DMAEMA) onto cellulose. For the first time, the preparation of the macro-initiator was performed in an ionic liquid which enhanced the solubility of cellulose. The macro-initiator was prepared from 2-bromopropionyl bromide with a ratio of AGU to Br equal to 1/5 and the functionalization reaction led to a DS of 0.7. This DS value was obtained after a reaction time of 8 h whereas the functionalization reactions reported by Tao and Ifuku were run overnight to reach a DS of 0.2 and 1 respectively. Regarding the ATRP of DMAEMA onto cellulose, a maximum conversion of 35% and a D_M of 2.3 were measured after one hour of reaction at 60 °C in DMF using PMDETA as ligand. These conditions were optimal for limiting radical-radical coupling, and thus preserving the “livingness” of the polymerisation. The pH- and thermo-responsive properties were comparable to the homopolymer PDMAEMA which is known to be a dually responsive material. The graft-copolymer aggregated above 42 °C, as shown by an increase in its hydrodynamic radius (R_h). Moreover, the graft copolymer chains gradually collapsed as the pH was increased from 2 to 12.

Gupta⁵⁰ subsequently developed additional stimuli-responsive materials, by graft-copolymerisation of acrylic acid (AA) and/or dimethyl acrylamide (DMA) onto cellulose. Methyl-2-bromopropionate was used to prepare the macro-initiator Br-Cell in THF in the presence of dimethylaminopyridine (DMAP) employing a ratio of AGU to Br of 1/30. Regarding the ATRP, toluene, tris[2-(dimethylamino) ethyl] amine (Me_6TREN) and CuBr were used as solvent, ligand and catalyst respectively. The presence of AA improved the

reactivity of DMA monomers and facilitated its graft copolymerisation onto Br-Cell. Moreover, the AA monomer showed greater propensity towards graft-copolymerisation onto cellulose than DMA. The LCST of the P(AA-co-DMA)-g-Cell was lower than that of PDMA-g-Cell, and the thermal stability of the graft-copolymer increased compared to cellulose itself.

More recently, Cui *et al.*⁵¹ prepared a PNIPAAm/Eu(III)-g-Cell complex which had both thermosensitive and fluorescence properties. NIPAAm was graft-copolymerised onto cellulose in a controlled manner. Cellulose was functionalized with chloropropionyl chloride in DMF and a DS above 1 was achieved. The ATRP of NIPAAm onto cellulose used a tetradentate ligand, Me₆TREN, which resulted in an increased monomer conversion compared to the previous work of Yan and Tao⁴⁹. Furthermore, the use of this ligand permits a decrease of the quantity of copper in the reaction mixture which makes the ATRP process more environmentally friendly. A 1.4 value of D_M for the grafts was measured, indicating that this polymerisation is the most successful ATRP graft polymerisation onto cellulose under homogeneous conditions. PNIPAAm-g-Cell complexed to Eu(III) was prepared via a chelation process with europium ions, and this led to an increased LCST for the complex compared to PNIPAAm-g-Cell. Furthermore, the complex showed an increase in emission intensity at 613 nm compared to that of uncomplexed Eu(III) ions (Figure 7).

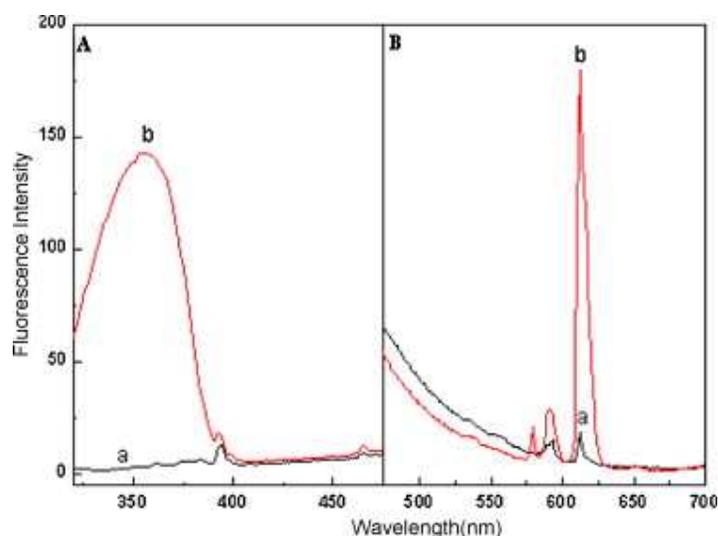


Figure 7: Excitation (A) and emission (B) spectra of (a) EuCl_3 and (b) PNIPAAm/Eu(III)-g-Cell⁵¹. Reproduced with permission, copyright Elsevier 2013.

To summarise, graft-copolymers were successfully prepared from either Cl-Cell or Br-Cell (Table S1 in ESI) in a controlled manner. The use of DMAc/LiCl or ionic liquids allowed the dissolution of the cellulose resulting in homogeneous conditions for performing ATRP. The preparation of the macro-initiators was mainly conducted at room temperature, using pyridine or dimethylaminopyridine (DMAP) as catalysts. The reaction time and the ratio of AGU to reactant were varied to determine their effect on the degree of functionalization. An increase of the amount of reactant relative to AGU and/or a longer reaction time increased the DS, while the presence of catalyst may not be necessary to reach a high DS. Different polymers have been successfully grafted onto cellulose using the ATRP method (Table S2 in ESI). The efficiency of the grafting takes into account both the monomer conversion and the control of the polymerisation. The latter was highlighted by measuring the D_M of the grafts after removal by hydrolysis. The importance of the ligand structure on both the rate of polymerisation and the D_M was discussed. For instance, a tetradentate ligand increased the rate of polymerisation and thus an increase of the monomer conversion was observed. The influence of the reaction parameters, including solution

concentration and choice of solvent on the success of the reaction were also investigated. Overall, the chemical modification of cellulose changed the behaviour of the raw materials. Depending on the monomers, the graft-copolymers aggregated into nanoparticles and had stimuli-responsive or dual stimuli-responsive properties which could result in potential applications in areas such as nanocontainers for drug delivery.

III. Graft-copolymer of ethyl cellulose

Ethyl cellulose (EC; Figure 1) is prepared via a Williamson etherification of cellulose with ethyl chloride. The modification takes place preferentially at the C6 and C2 position with a DS ranging from 2.1 to 2.6. The remaining free hydroxyls are therefore at positions C3 and C2, hence reactivity of EC towards further functionalisation can be low. EC is known for its thermoplasticity, chemical stability, resistance to degradation by alkali and salt, and its capability to absorb only a small amount of water. Owing to these properties, EC has been used in the formulations of paints, varnishes and lacquers and is used as an ingredient in hair sprays^{6, 52}. The solubility of EC in organic solvents makes it a good candidate for graft-copolymerisation under homogeneous conditions. Due to the biocompatibility of EC and its self-assembly properties, there has been interest in possible biotechnology applications, with the formation of amphiphilic graft-copolymers being a central theme. Here, we will report the preparation of graft-copolymers from EC which have been prior-functionalized with bromo-ester bromide. Br-EC was synthesised from either 2-bromoisobutyryl bromide or 2-bromopropionyl bromide in the presence of a catalyst such triethylamine (TEA) or pyridine. The solvent commonly used was THF and the reaction was carried out at room temperature for a desired time. The importance of the reaction time and the ratio of AGU to Br on the DS of Br-EC will be discussed. Graft-copolymerisation with acrylic acid (AA), St, MMA and 2-hydroxyethyl methacrylate (HEMA) will be described and the self-assembly of the products into micelles will be discussed. The graft copolymerisation of other monomers such as methacrylate-containing azobenzene groups (MMAzo), poly(ethylene glycol) methyl ether methacrylate (PEGMA), 2-(diethylamino)ethyl methacrylate (DEAMA), and *N,N*-dimethylaminoethyl methacrylate (DMAEMA) onto Br-EC and the photo-, thermo- and/or pH-responsiveness properties of the products will be summarised. We will compare the

influence of the density and the length of the grafts on the behaviour of micelles produced from the self-assembly of the graft copolymers.

In 2005, Shen *et al.*⁵³ were the first to report the graft-copolymerisation from ethyl cellulose using ATRP. Densely grafted PSt-g-EC and PMMA-g-EC copolymers were prepared, where the macro-initiator Br-EC was synthesised under mild conditions using EC with a DS of 2.1. For a ratio of AGU to Br equal to 1/3 and a reaction time of 48 h, a maximum DS of 0.5 was obtained. This low value was explained by the low reactivity of the free –OH groups at the C2 and C3 positions. Polymerisation of St and MMA from Br_{0.5}-EC were performed at optimized temperatures of 110 °C and 70 °C respectively for 16 h using CuBr/PMDETA as catalyst system and toluene as reaction medium. The targeted degree of polymerisation was 300 and the ratio [I]/[C]/[L] was equal to 1/0.5/1. After 16 h of reaction, the monomer conversion was 12% and 11% for MMA and St respectively and a relatively narrow D_M of 1.35 for both graft copolymers was measured by GPC. A rod-like shape of PSt₃₀-g-EC_{0.5} in toluene was proven using light scattering and AFM experiments. Repulsion between PSt chains enhanced the extension of the EC backbone resulting in the formation of rods. Shen *et al.*⁵⁴ investigated the graft-copolymerisation of St onto EC, using macro-initiator Br_{0.04}-EC and Br_{0.5}-EC synthesised, respectively, with DS values of 0.04 and 0.5. To synthesise Br_{0.5}-EC, the same procedure of Shen *et al.*⁵³ was used, whereas to prepare Br_{0.04}-EC, a higher ratio of AGU to Br (1/0.2) was used. St was polymerised onto these macro-initiators resulting in various graft lengths and graft densities. The authors used the same catalyst system, solvent and temperature as reported in their previous publication⁵³. However, different reaction times, targeted degrees of polymerisation and ratio of [I]/[C]/[L] were chosen depending on the DS of the Br-EC used. For Br_{0.5}-EC, where the authors intended to prepare graft-copolymers PSt₆₀-g-EC_{0.5} of high graft density with a short graft length, a low DP of 300 was targeted using a ratio [I]/[C]/[L] equal to 1/0.5/1. A monomer conversion of

20% was reached after 21.5 h and the D_M of the grafts was equal to 1.3 which confirmed the controlled/living nature of the polymerisation process. In order to produce longer length of grafts in a shorter reaction time, the targeted DP was increased to 6000 and the amount of catalyst was increased by a factor 2. A 10% monomer conversion and a D_M of 1.2 were obtained resulting in the formation of the graft-copolymer $PSt_{600-g-EC_{0.04}}$. At a high concentration in acetone, the densely grafted copolymer $PSt_{60-g-EC_{0.5}}$ self-assembled into nanoparticles (Figure 8) whereas at a low concentration, graft-copolymers were present as unimers in solution. At a solution concentration of 25 $\mu\text{g/ml}$ in acetone, the diameter of particles reached 200-300 nm and the size distribution was narrow. The PSt grafts are not soluble in acetone whereas EC backbone is soluble, thus PSt and EC formed the core and shell respectively of the nanoparticles.

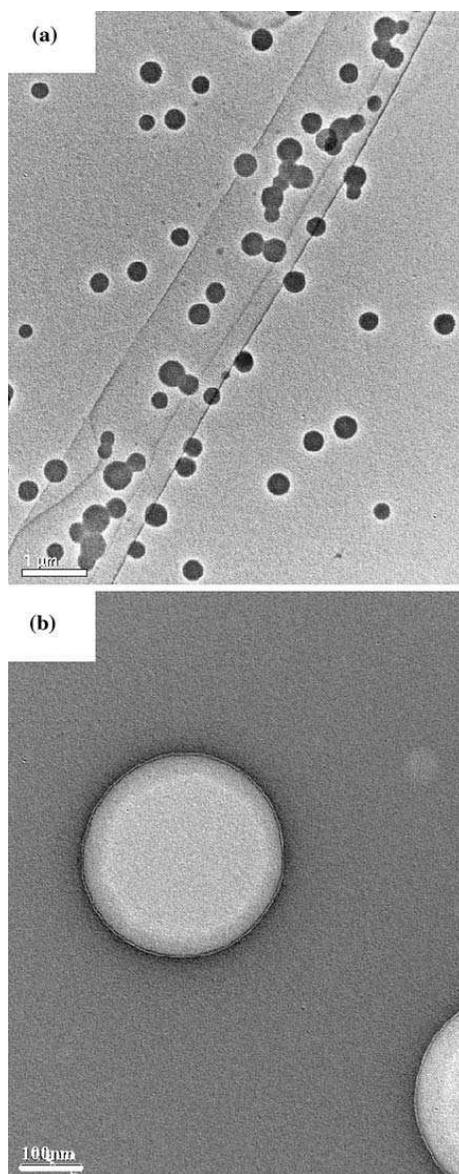


Figure 8: TEM image of spherical aggregates formed from $\text{PSt}_{60}\text{-g-EC}_{0.5}$ in acetone solution with acetone (concentration $25 \mu\text{g/ml}$)⁵⁴. Reproduced with permission, copyright Springer 2006.

Qinmei *et al.*⁵⁵ recently developed new graft-copolymers such as $(\text{PSt-co-PEG})\text{-g-EC}$ and PSt-g-PEG-g-EC combining click and ATRP processes. Two Br-EC macro-initiators with DS of 0.28 and 0.54 respectively were prepared from EC with a DS of 2.5. The variation of DS can be explained by the change of the ratio of AGU to Br; a decrease of the ratio results in

an increase of the DS of Br-EC. The ATRP procedure used to graft St onto Br-ECs was the same as that reported by Shen *et al.*⁵³. Different lengths of PSt chains were achieved by varying for instance the reaction time, and/or the targeted DP.

Kang *et al.*⁵⁶ used Br-EC macro-initiators with DS of 0.04 and 0.09 to graft-polymerise 2-hydroxyethyl methacrylate (HEMA). The functionalization reaction of EC with DS of 2.1 using bromoisobutyryl bromide was carried out for 24 h in the presence of pyridine. To obtain a DS of 0.04, a ratio of AGU to Br equal to 1/1 was used whereas a lower ratio of 1/2 permitted an increase of the DS to 0.09. ATRP performed at 40 °C was found to give better control of the polymerisation process than at 30 °C. Different ratios of [I]/[C]/[L] for Br_{0.09}-EC and Br_{0.04}-EC were chosen and CuBr₂ was additionally used to slow down the initiating step of the polymerisation with EC_{0.09}-Br, helping to maintain the “livingness”. The targeted DP was 510 and 1000 for Br_{0.09}-EC and Br_{0.04}-EC respectively. The length and the dispersity of the PHEMA grafts were determined using both ¹H NMR spectroscopy and GPC. A common D_M of approximately 1.2 was measured indicating a narrow molecular weight distribution of the grafts and the length of the grafts was equal to 66 and 83 monomeric units of HEMA for PHEMA₆₆-g-EC_{0.09} and PHEMA₈₃-g-EC_{0.04} respectively. The self-assembly of similar graft-copolymers (PHEMA₁₃₁-g-EC_{0.09} and PHEMA₁₀-g-EC_{0.04}), for which the synthesis was not described, was reported. These graft copolymers were self-assembled into micelles by dialysis of a solution of these graft-copolymers in DMF against water and both R_h and size distribution were determined using DLS. The average of R_h was around approximately 70 nm and a narrow size distribution was observed for a concentration of the graft-copolymers in water ranging from 5-25 µg/ml.

Amphiphilic graft-copolymers were developed by Kang *et al.*⁵⁷ who reported the graft-copolymerisation of t-butyl acrylate (t-BA) onto EC using macro-initiators (Br-EC) with DS values of 0.04 and 0.25. The reaction time used to prepare the macroinitiators was 50% lower

compared to previous work^{53,54} and this could be an explanation of the low DS values. t-BA was then polymerised in a controlled manner using CuBr/PMDETA as catalyst and a mixture of toluene/cyclohexanone as solvent at 80 °C. The targeted DP was 3750 and 300 for Br_{0.04}-EC and Br_{0.25}-EC respectively. A high amount of catalyst was used for Br_{0.04}-EC to increase the rate of polymerisation whereas CuBr₂ was used in conjunction with CuBr for the polymerisation of t-BA onto Br_{0.25}-EC to control the rate of polymerisation by reducing the number of radicals in the reaction mixture. At the end of the polymerisation, monomer conversions were equal to 6% and 21% for Br_{0.04}-EC and Br_{0.25}-EC respectively and a common D_M of 1.2 was measured by GPC after hydrolyzing the P(t-BA) grafts from the EC backbone. Two different graft-copolymers were produced; PSt₆₃-g-EC_{0.25} with a high density of short grafts and PSt₂₂₅-g-EC_{0.04} with low density of long grafts. Further, PAA-g-EC was successfully prepared by hydrolysis of P(t-BA) chains. The amphiphilic graft-copolymer PAA₁₃-g-EC_{0.25} self-assembled in water (1.0 mg/ml), and the size of the aggregates varied from 5 to 100 nm, depending on the number of chains involved in the aggregate formation. Recently, the influence of the graft density on PAA-g-EC molecular conformation was studied by Liu *et al.*⁵⁸; a high graft density led to a rod conformation whereas a low graft density generated a coil conformation (Figure 9).

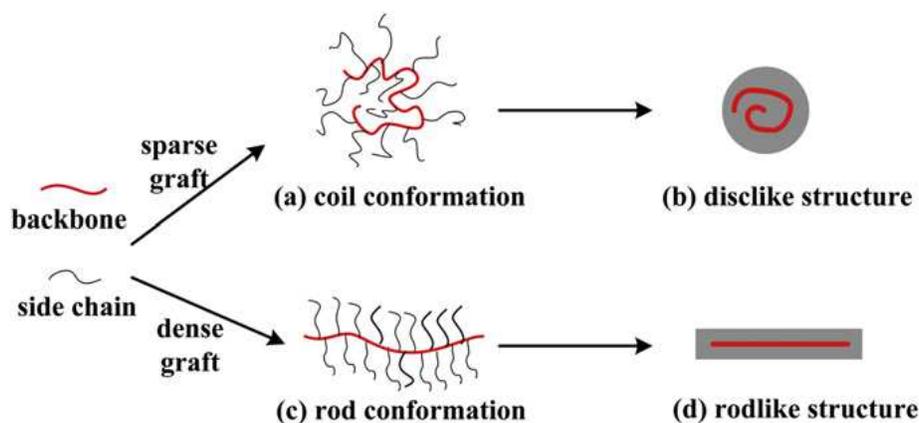


Figure 9: Molecular conformation and single chain structure of the graft copolymers⁵⁸.

Reproduced with permission, copyright Elsevier 2012.

In 2007, a range of amphiphilic photo-responsive self-assembling graft-copolymers were developed by Tang *et al.*⁵⁹ by grafting an azobenzene-containing methacrylate onto EC. The monomer containing azobenzene was successfully prepared and Br-EC with a DS of 0.52 was synthesised in the presence of TEA as catalyst. The functionalization reaction of EC was performed at room temperature overnight and the ratio of AGU to Br was equal to 1/3. Compared to Br_{0.5}-EC prepared by Shen *et al.*^{53,54}, the change of catalyst from pyridine to triethylamine allowed a reduction of the reaction time to obtain the same DS. The graft-copolymerisation of azobenzene-containing methacrylate monomers onto Br_{0.5}-EC proceeded at 85 °C for 20 h in anisole with PMDETA/CuBr as catalyst system. [I]/[C]/[L] equal to 1/2/4 was chosen and two different DPs were targeted in order to prepare graft-copolymers with different length grafts. To highlight the grafting of PMMAzo onto Br_{0.5}-EC, the molecular weight (M_n) of the graft copolymers was measured by GPC. The increase of M_n indicated successful grafting and M_n was found to increase with graft length. The graft-copolymerisation gave a product with two phase transitions at 94 °C and 134 °C corresponding, respectively, to the smectic-to-nematic and nematic-to-isotropic transition

temperatures. Furthermore, a reversible trans to cis isomerisation of azobenzene groups under UV-vis light was observed by spectrophotometry.

Subsequently, in 2008, Li *et al.*⁶⁰ prepared the thermally responsive graft-copolymer PPEGMA-g-EC, using macro-initiators of DS 0.2 and 0.02 to initiate the ATRP of poly(ethylene glycol) methyl ether methacrylate (PEGMA). To avoid the radical-radical coupling responsible for gel formation, conversions were kept low; 56% and 62% with Br_{0.2}-EC and Br_{0.02}-EC respectively, using ratios of monomer to initiator of 50 and 300, respectively. The polymerisation proceeded in toluene with a 4,4'-Di-5-nonyl-2,2'-bipyridine (dN bpy)/CuCl as catalyst system at 60 °C. A common ratio of [I]/[C]/[L] equal to 1/0.75/1.5 was chosen for each polymerisation, however the polymerisation using Br_{0.2}-EC proceeded for a shorter time compared to that from Br_{0.02}-EC because of a higher possibility of radical-radical coupling in the former polymerisation. Furthermore, CuCl₂ was used in conjunction with CuCl for the ATRP of PEGMA onto Br_{0.2}-EC in order to slow down the initiation rate and maintain polymerisation control. The resulting graft-copolymers, P(PEGMA)₂₇-g-EC_{0.2} and P(PEGMA)₁₈₅-g-EC_{0.02} were dissolved in THF and dialyzed against water resulting in the formation of micellar solutions with a concentration of 1 mg/ml. The R_h of graft-copolymers P(PEGMA)₂₇-g-EC_{0.2} and P(PEGMA)₁₈₅-g-EC_{0.02} as determined by DLS was 140 nm and 73 nm respectively, which indicates that micelle size increases with the graft density but the length of the grafted chains has no influence on the micelle size. Moreover, the graft-copolymers were found to have thermo-responsive behavior defined by an LCST of 65 °C, however, the graft density and length did not influence the LCST. Above the LCST, the micelles aggregated, resulting in an increase in R_h to 180 nm and 120 nm for P(PEGMA)₂₇-g-EC_{0.2} and P(PEGMA)₁₈₅-g-EC_{0.02} respectively and solution turbidity, and these phenomena were shown to be reversible.

More recently, in 2011, Wang *et al.*⁶¹ investigated the pH responsive graft copolymer PDEAEMA-g-EC prepared from Br-EC macro-initiators with a DS of 0.06, 0.1 and 0.2. These were used to polymerise 2-(diethylamino)ethyl methacrylate (DEAEMA), and based on ¹H NMR spectra, the degree of polymerisation ranged from 15 to 90, depending on the feed ratio and reaction time. The ATRP proceeded in DMF at 20 °C using bpy/CuBr as catalyst system and a common [I]/[C]/[L] ratio of 1/0.75/1.5 was chosen. The graft-copolymers were dissolved in THF and dialyzed against acidic aqueous solution to form a micelle solution of a concentration of 0.5 mg/ml. The size of the micelles was determined by DLS and their behaviour at different pH was studied (Figure 10). At a constant pH of 3.2, the critical micelle concentration (CMC) decreased when the graft length and density increased. When the pH was increased from 6 to 6.9, the R_h of the micelles decreased as the PDEAEMA chains collapsed. Above a pH of 6.9, the micelles aggregated together resulting in an increase of R_h . For instance, the size of the micelles formed by the graft-copolymer PDEAEMA₈₅-g-EC_{0.1} was 200 nm at 3.2 of pH, when the pH increased to 6.9, R_h strongly decreased to ~75 nm because of the shrinkage of the synthetic chains and above a pH of 7, R_h slightly re-increased to ~90 nm due to the aggregation of micelles together. The authors have also studied the importance of both the graft density and the chain length on the size of the micelles. In fact, the size of the micelles formed from graft-copolymers prepared from Br_{0.1}-EC increased with the chain length of PDEAEMA. At a pH of 3.2, the micelle size increased from 140 nm to 200 nm when chain length was increased from 35 to 85 monomer units. However, the graft density did not affect the size of micelles for a constant chain length of 90 monomer units. Furthermore, the aggregated structure at pH above 6.9 prolonged the drug release over time compared to the structure generated at pH 6.6.

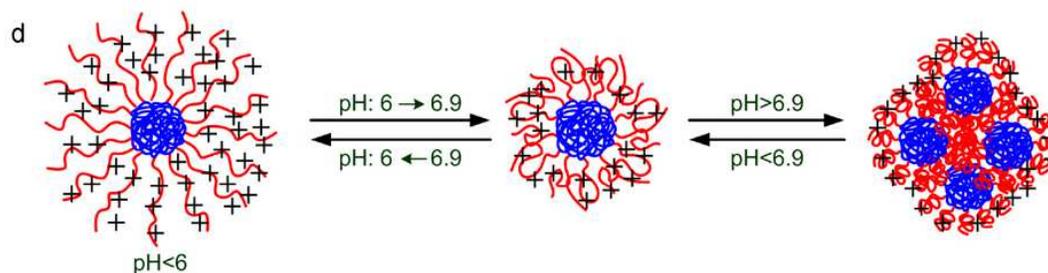


Figure 10: Proposed mechanism of the pH-responsive micelle formation from PDEAEMA-g-EC copolymers⁶¹. Reproduced with permission, copyright Elsevier 2011.

Yan *et al.*⁶² prepared the dual graft copolymer PCL-g-PDMAEMA-g-EC by combining ATRP and ROP processes. EC was functionalized with 2-bromopropionyl bromide in presence of triethylamine for 24 h with a ratio AGU to Br equal to 1/3. After this, ROP of CL was performed then the DMAEMA was polymerised onto Br-PCL₃₀-g-EC in THF at 60 °C using PMDETA/CuBr and a [I]/[C]/[L] ratio of 1/1/1. The longest chain length was reached after 30 h of polymerisation with a monomer conversion of 23% resulting in the formation of brush-copolymer PDMAEMA₂₃-g-PCL₃₀-g-EC. The dual graft-copolymer displayed similar behaviour in terms of micellization, micelle structure and pH responsiveness as PDEAEMA-g-EC. At low pH, the brush copolymer formed micelles of 36 nm radius whereas the size of the micelles increased to 81 nm at high pH indicating an aggregation phenomenon. Compared to PDEAEMA₈₅-g-EC_{0.1} where the micelle size decreased when pH increased, the shrinkage of PDMAEMA₂₃ resulted to the formation of a micellar aggregate which was indicated by an increase of the R_h . This phenomenon can be explained by the brush structure of the graft copolymer and thus by the presence of the grafts of PCL. PDMAEMA₂₃-g-PCL₃₀-g-EC was also analyzed using DSC and WAXD and it proved to be amorphous because the EC and especially the PDMEAMA chains disturbed the order of the PCL.

Tang *et al.*⁶³ aimed to develop more complex responsive graft-copolymers, through simultaneous graft-copolymerisation of MMAzo and NIPPAM to generate a dual responsive material. Br-EC was synthesised from 2-bromosiobutyryl bromide in presence of triethylamine as catalyst because TEA had been shown to decrease the reaction time. Br-EC was then used to copolymerize NIPAAM and MMAzo monomers in a mixture of DMF/H₂O using the tetradentate ligand tris[2-(dimethylamino)ethyl]amine (Me₆TREN)/CuCl as catalyst system at 80 °C for 9 h with a ratio of [I]/[C]/[L] equal to 1/1/1. A ratio of NIPAAM to MMAzo equal to 50/1 was chosen. The grafting efficiency was not discussed and no data have been reported to confirm the formation of the graft-copolymer. However, the solubility properties of the graft-copolymer were discussed; it was found to be insoluble in water, but instead formed an emulsion. When the temperature was increased above 30 °C, the graft-copolymer side chains collapsed resulting in precipitation from the solution. Furthermore, the presence of PMMAzo chains induced changes in the solubility behavior of the graft-copolymer caused by the reversible trans/cis isomerization under UV-vis light of the azobenzene groups. Under UV light, the polarity of the graft-copolymer increased resulting in an increase of the LSCT.

In summary, amphiphilic graft-copolymers were successfully prepared from the macro-initiator Br-EC (Table S3 in ESI) for which the DS ranged from 0.06 to 0.5 depending on the reaction time, choice of catalyst and ratio of AGU to Br. For instance, the DS value was higher for a longer reaction whereas the DS decreased for a higher ratio of AGU to Br. Furthermore, the use of triethylamine as catalyst decreased the reaction time compared to the use of pyridine. The graft-copolymers of EC are listed in Table S4 (ESI) where experimental conditions and the grafting efficiency defined by the monomer conversion and/or D_M are reported. The monomer conversion was kept low to avoid radical-radical coupling which results in the loss of livingness. Furthermore, Cu (II) was sometimes used to regulate the

production of radicals and thus enhance the control of the polymerisation. The use of a tridentate ligand such as PMDETA permitted both a reduction of the amount of catalyst and an increase of the polymerisation rate compared to the use of a bidentate ligand such as bpy. D_M was determined after hydrolyzing the synthetic chains from the backbone and ranged from 1.1 to 1.3 which indicated a relatively good control of the polymerisation. The R_h values of graft-copolymers of EC that have been self-assembled in aqueous solution are summarized in Table S5 (ESI) and were found to range from 5 to 300 nm. For each graft-copolymer, the chain length and the graft density are indicated because of their importance for understanding of the graft copolymer structure. Graft-copolymers that had either a low graft-density with a long chain length or a high graft-density with a short chain length formed micelles in aqueous solution. However, the graft-copolymer with a low graft density and a long chain length formed larger micelles compared to graft-copolymer with a high graft-density and short chain length. Furthermore, the chain length influenced more the micelle size than the graft-density; R_h increased when the chain length increased. The use of thermo-, pH- or photo-responsive polymers such as PPEGMA, PDEAEMA and PMMAzo allowed the creation of smart self-assembled materials. Under external stimulus (temperature, pH or light) the micelles formed by the graft-copolymers collapsed together resulting in increases in R_h . All of the self-assembled graft-copolymers are potentially valuable materials as nanocontainers, and more precisely as drug delivery systems when these materials are produced from a stimuli-responsive polymer which is capable of modulating the release of a drug over time.

IV. Graft-copolymers of hydroxypropyl cellulose

Hydroxypropyl cellulose (HPC) is produced by the reaction of cellulose with propylene oxide, with reaction taking place preferentially at the C6-OH position of the glucose units to give a new hydroxyl group in addition to the propyl unit (Figure 1). This side chain can be further extended through sequential additions of propylene oxide units onto the newly formed hydroxyl group. Observed DS values range from 2.2 to 2.8, and HPC is soluble only in cold water and in most polar organic solvents^{6, 64}. HPC has proven uses as an emulsion stabilizer, coating excipient, binding agent and film former in many industrial applications such as food, pharmaceuticals and personal care⁶⁵⁻⁶⁷. Owing to its solubility, the use of HPC supports and facilitates the preparation of graft-copolymers under homogeneous conditions. Furthermore, HPC has a lower critical solution temperature at approximately 42 °C. HPC derivatives present a strong potential in biotechnology applications such as functioning as drug nanocontainers. Thus, graft-copolymers of HPC were targeted in order to decrease the LCST to physiological temperature, and to add stimulus-responsive and self-assembly properties. In the following section, the activation of the HPC backbone will be reviewed; the strategies used to influence the DS of Br-HPC are summarised in Table S6 (ESI). We will discuss also the preparation of graft-copolymers from monomers such as DMAEMA, NIPAAm, 4-vinylpyridine (4VP) and oligo(ethylene glycol) methacrylate (OEMA). Their physical properties will be described and their responsiveness to external stimuli will be discussed. We will see that some graft-copolymers were further cross-linked to control the sizes of the micelles or to form gel particles resulting in prolonged drug release profiles.

The first reported work with HPC was by Östmark *et al.*⁶⁸ in 2007, who synthesized PMMA-g-HPCs from a conventional- and a dendronized-macro-initiator (Figure 11), Br-HPC

and Br-G1-HPC, with DS values of up to 2.26 and 0.88, respectively. The polymerisation of MMA was performed using these two macro-initiators in highly dilute solutions of toluene and PMDETA as ligand, in the presence of CuBr_2 with a minimum ratio $\text{CuBr}_2/\text{CuBr}$ equal to 1/4. Reaction conditions of 80 °C and 19 h were chosen for the polymerisation with $\text{Br}_{2.26}$ -HPC whereas the polymerisation of MMA with the dendronized macro-initiator was performed at a lower temperature, 50 °C for a shorter time, 2 h. The polymerisation of MMA onto the conventional macro-initiator $\text{Br}_{2.26}$ -HPC was less controlled than that of MMA onto the dendronized macro-initiator. However, the monomer conversion was higher using $\text{Br}_{2.26}$ -HPC than $\text{Br}_{0.88}$ -GI-HPC with values of 39% and 18% for PMMA-g-HPC_{2.26} and PMMA-g-GI-HPC_{0.88} obtained respectively. Both macro-initiators were also used to polymerise hexadecyl methacrylate (HDMA), but only the polymerisation onto $\text{Br}_{0.88}$ -GI-HPC was successful. $\text{Br}_{2.26}$ -HPC produced a high concentration of radicals resulting in the formation of a gel due to the radical-radical coupling phenomenon between chains. The bromides at the chain end of PMMA-g-HPC_{2.26} were then used to activate the polymerisation of t-BA with similar reaction conditions to those that were used for the polymerisation of PMMA onto $\text{Br}_{2.66}$ -HEC. After 22 h of reaction, a low conversion of 3.5% was reached leading to a second block in a ratio of 1/0.58 MMA to t-BA. The t-butyl ester groups of P(t-BA) were then hydrolysed to form a PAA block. PHDMA-g-G1-HPC_{0.88}, PMMA-g-G1-HPC_{0.88} and PMMA-g-HPC_{2.26} formed particles in THF and their sizes were measured using DLS. D_h values of 96 and 195 nm were observed for particles from PMMA-g-HPC_{2.26} and PMMA-g-G1-HPC_{0.88} respectively and the particles formed from PHDMA-g-G1-HPC_{0.88} were similar in size to those of PMMA-g-G1-HPC_{0.88}. However, chain extension of PMMA-g-HPC_{2.26} with t-BA permitted the formation of larger particles of $D_h = 280$ nm.

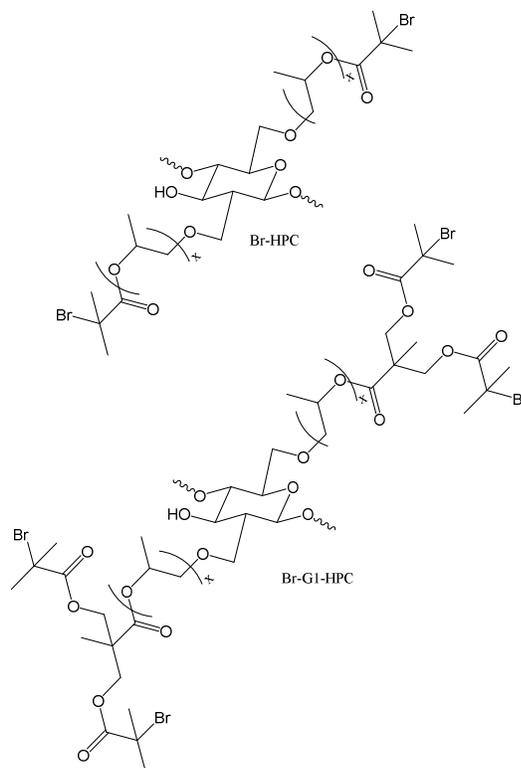


Figure 11: Molecular structure of macro-initiators Br-HPC and Br-G1-HPC

Recently (2013), Bagheri *et al.*⁶⁹ investigated the graft-copolymerisation of MMA and the simultaneous graft-copolymerisation of MMA and cholesteryl methacrylate (CMA) onto HPC. Br-HPC, the macro-initiator, with a DS of 2.04 was successfully prepared in a conventional manner and both MMA and the complex MMA/CMA were polymerized onto it in the presence of CuBr_2 to improve the polymerisation control. Bidentate ligand, bpy and toluene as solvent were used at a temperature of 70 °C and after 19 h of polymerisation, the monomer conversion was 25% and 30% for the ATRP of MMA and the simultaneous polymerisation of MMA and CMA respectively. Graft-copolymers (PMMA-ran-PCMA)-g-HPC were produced with graft lengths of 100 and 357, and the ratio of PMMA to PCMA was determined to be 1/0.11. The thermal stability and glass transition temperature (T_g) of each graft-copolymer were reduced compared to HPC itself, and these observations were attributed to a reduction of the crystallinity of HPC. Compared to HPC-g-MMA, the thermal stability

and T_g of (PMMA-ran-PCMA)-g-HPC graft-copolymers were also decreased. Furthermore, the T_g decreased with increased PMMA-ran-PCMA graft length, plus, the solubility behavior of the graft-copolymers was different. The (PMMA-ran-PCMA)-g-HPC formed nanoparticles of D_h below 570 nm (DLS experiments) in water/ethyl acetate solution with narrow size distribution.

Östmark *et al.*⁷⁰ investigated the preparation of the graft-copolymer PAA-b-PCL-g-HPC. The CL was polymerised onto HPC via a ROP process resulting in a degree of polymerisation (DP) of 10. The chain ends were further functionalized with bromoisobutyryl bromide using DMAP/TEA as catalyst system in DMF. After 2 h of reaction at room temperature, the Br-PCL-HPC was successfully prepared with a DS greater than 1.1 and Br_{>1.1}-PCL-HPC was further used for initiating the polymerisation of t-BA monomers. The chain length of P(t-BA) was controlled by varying the polymerisation time, and the monomer conversion was kept under 35% in order to maintain true living polymerisation conditions. The reaction conditions used were similar to those used for polymerising MMA onto Br_{2.26}-HPC and a maximum conversion of 32% was reached after 22 h of reaction. Furthermore, the t-butyl ester groups were successfully hydrolysed to form PAA-block-PCL-g-HPC. This block graft-copolymer was then cross-linked using a diamine. The three graft-copolymers self-assembled into particles in THF and their sizes were determined using DLS. The cross-linked graft-copolymers produced particles with the largest D_h of 235 nm while the size of the particles formed from PtBA-b-PCL-HPC was smaller than those from PAA-b-PCL-g-HPC (D_h of 86 and 129 nm respectively).

PAA-b-PLLA-g-HPC graft copolymers were developed by Berthier *et al.*⁷¹ following a five step procedure (Figure 12). The macro-initiator was prepared from bromopropionyl bromide using the chain end -OH of PLLA following the ROP polymerisation of LLA onto HPC. After 2 days at room temperature in the presence of TEA, all hydroxyl group chain ends

of PLLA were functionalized to bromo-ester groups. For the first time, the ATRP was carried out without the use of solvent; instead the monomer t-BA was used as reaction medium. The polymerisation was conducted at 100 °C in the presence of PMDETA/CuBr as catalyst system. A relatively high conversion was reached after only 30 min. The reaction time had to be short to avoid gel formation from radical-radical coupling.

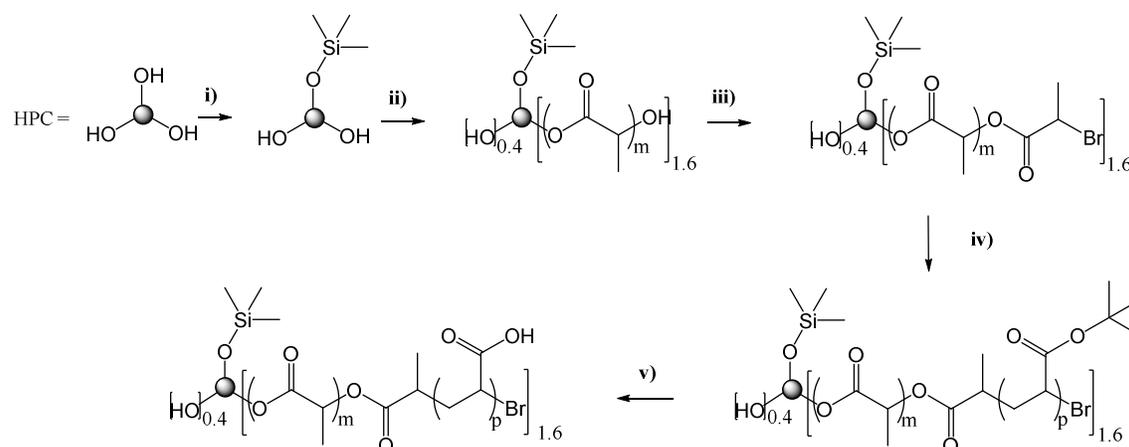


Figure 12: Preparation of the graft-copolymer PAA-b-PLLA-g-HPC: i) protection of OH via HDMS ii) ROP of LLA iii) macro-initiator preparation from chain ends of PLLA iv) ATRP of t-BA and v) deprotection of P(t-BA) to PAA.⁷¹

The amphiphilic graft-copolymers formed micelles of diameter approximately 64 nm in a mixture of ethanol/water, however the micelles which have been loaded with Romascone, a perfume ingredient, had an extended D_h of 203 nm and were shown to be capable of controlling the release of the volatile compound.

Stimuli-responsive graft copolymers of HPC have also been developed. Xu *et al.*⁷² reported the preparation of PNIPAAm-g-HPC from Br_{0.14}-HPC using dioxane as reaction solvent because it is known to be a good solvent for polymerisation of NIPAAm. The graft-length was controlled via the polymerisation time and after 24 h, a high monomer conversion of 64% was achieved due to the use of tetradentate ligand. A graft efficiency ranging from 35

to 64% of PNIPAAM (LCST of 32 °C) onto HPC (LCST of 42 °C) provided a material where the LCST fell below 37 °C, and the cytotoxicity of the graft-copolymer was reduced compared to that of ungrafted PNIPAAM homopolymer. The presence of residual -OH groups permitted cross-linking of PNIPAAM-g-HPC using divinylsulfone (DVS), and this resulted in hydrogel formation. This result is significant because above a temperature of 37 °C, PNIPAAM grafts collapsed completely, releasing their payloads, whereas the hydrogel based-PNIPAAM-g-HPC showed slower, more controlled drug release than the hydrogel based on HPC (Figure 13).

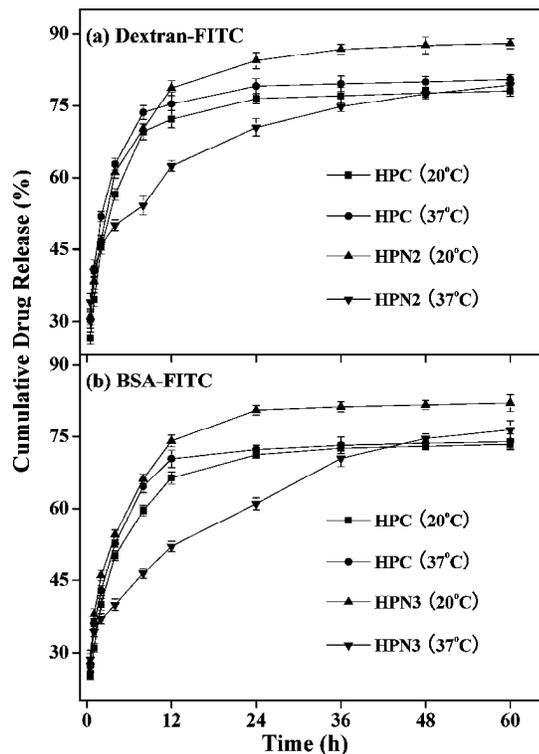


Figure 13: Release profiles of (a) dextran-FITC from HPC and HPN2 hydrogels and (b) BSA-FITC from HPC and HPN3 hydrogels at 20 and 37 °C⁷². Reproduced with permission, copyright American Chemical Society 2010.

In 2011 Porsch *et al.*⁷³ described the preparation of thermally responsive HPC-based graft-copolymers using a variant of ATRP known as Activators ReGenerated by Electron Transfer (ARGET) ATRP⁴⁸. Br-HPC macro-initiators with DS values of 0.6 and 1.4 were synthesised using a procedure described above^{68, 74}. Oligo(ethylene glycol) methacrylate (OEGMA₃₀₀), 2-(hydroxyethoxy)ethyl methacrylate (DEGMA) and OEGMA₃₀₀-co-DEGMA were polymerised onto Br-HPC using a bidentate ligand, bpy and CuBr₂/ascorbic acid as catalyst system. Polymerisation was performed at 40 °C for 4 h and anisole and methanol were used as solvent for Br_{1.4}-HPC and Br_{0.6}-HPC respectively. High dilution and low monomer conversion were maintained to limit side reactions such as cross-linking and termination reactions. Even under these conditions, Br_{1.4}-HPC did not give successful ARGET ATRP of OEGMA₃₀₀ and OEGMA₃₀₀-co-DEGMA due to the high concentration of radical species in solution resulting in the formation of gel. At the end of polymerisation, the monomer conversion varied from 20 to 35% depending on the choice of monomer. These graft-copolymers presented both thermo-responsive and self-assembly properties. The grafting of such materials onto HPC influenced its LCST because these synthetic polymers have LCST values from 29-90 °C depending on their chain length (Figure 14). The grafting of PDEGMA onto HPC decreased the LCST to 22 °C whereas the LCST increased to 62 °C when POEGMA was grafted from HPC. However, the grafting of P(OEGMA₅₂-co-DEGMA₄₈) onto HPC did not affect the LCST which remained at 42 °C. Furthermore, the graft-density of PEGMA-g-HPC did not influence the LCST as the same value was determined for both PEGMA-g-HPC_{1.4} and PEGMA-g-HPC_{0.6}. Below their LCST, the graft-copolymers were self-assembled into micelles in water with R_h ranging from 20-40 nm. Above their LCST, the micelles aggregated resulting in an increase of R_h to 150-250 nm.

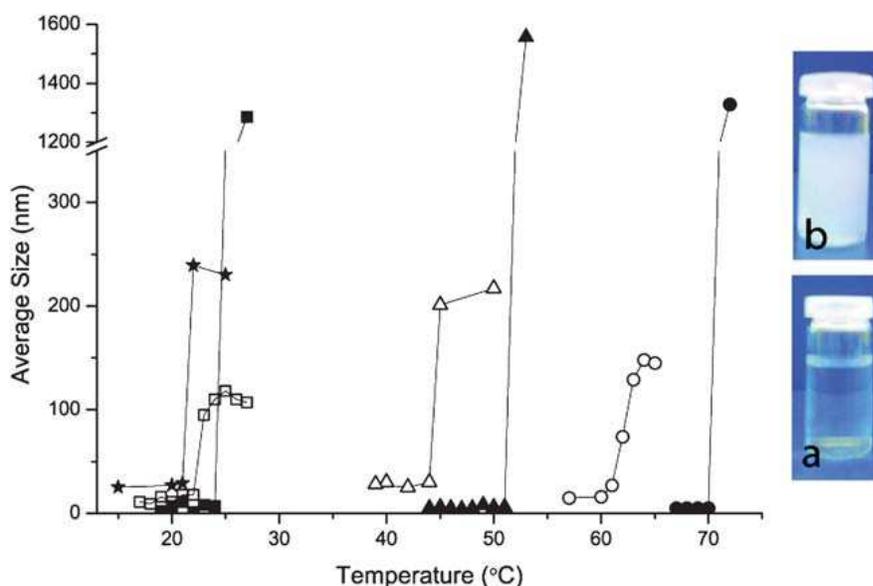


Figure 14: Size of HPC-based graft copolymers and their linear analogues as a function of temperature: PDEGMA (■), PDEGMA-g-HPC_{1.4} (★), PDEGMA-g-HPC_{0.6} (□), P(OEGMA₅₄-co-DEGMA₄₆) (▲), P(OEGMA₅₂-co-DEGMA₄₈)-g-HPC_{0.6} (Δ), POEGMA (●), and POEGMA-g-HPC_{0.6} (○). Insets: (a) polymer sample below LCST in aqueous solution and (b) polymer sample above LCST in aqueous solution⁷³.

Dually responsive materials were produced by Ma *et al.*⁷⁵ who reported the preparation of the graft-copolymer P4VP-g-HPC. The macro-initiator Br-HPC with a DS of 0.05 was synthesised from bromoisobutryl bromide in THF using pyridine as catalyst and was used for the graft-copolymerisation of 4VP. The low DS of Br_{0.05}-HPC allowed the minimization of cross-linking reactions during the polymerisation while preserving the thermo-responsive properties of HPC. The authors highlighted the “livingness” of the polymerisation of 4VP onto HPC. The graft-copolymerization proceeded for 6 h at 30 °C in isopropanol and Me₆TREN was used as ligand. The monomer conversion was 35 % resulting in a chain length of 35 monomeric units. The resulting graft-copolymer, P4VP₃₅-g-HPC_{0.05} was found to be dually responsive because P4VP and HPC are, respectively, pH- and thermo-

responsive materials. At $\text{pH} > 6$, the graft-copolymer self-assembled into micelles with R_h of 190 nm due to the collapse of the P4VP chains forming the micelle core whereas the HPC backbone formed the micelle shell. Similar behavior was observed when the temperature was raised to 45 °C, however HPC this time formed the micelle cores while P4VP provided the shell that stabilized the micelles. The cloud point of the graft-copolymers was found to depend on the graft length; 4VP of $\text{DP}=3$ grafted onto HPC was not insufficient to give micelle formation.

Xu *et al.*⁷⁴ reported the preparation of a quaternised PDMAEMA grafted onto HPC to produce a cationic material. In the first step, Br-HPC with a DS of approximately 0.14 was synthesised in dichloromethane (DCM). This low value can be explained by a short reaction time of 5 h and/or the absence of catalyst. 2-(Dimethylaminoethyl)methacrylate (DMAEMA) was polymerised onto the $\text{Br}_{0.14}$ -HPC at room temperature in an isopropanol/water mixture using CuBr and HMTETA which is known to lead to both high monomer conversion and low D_M , but which had not been used previously in homogeneous ATRP onto cellulose or cellulose derivatives. It resulted in 62% of monomer conversion after only 8 h. The PDMAEMA grafts were then partially quaternised by treating PDMAEMA-g-HPC with 1-bromohexane. The unmodified, neutral and quaternised graft-copolymers were tested as vectors for gene delivery. The DNA and both graft-copolymers (neutral and quaternised) were complexed into nanoparticles of 150-200 nm in diameter. The neutral graft-copolymer presented a lower cytotoxicity and better gene transfection properties compared to the linear PDMAEMA polymer. Moreover, on quaternisation of the PDMAEMA portion of the graft-copolymer, improved complexation with DNA was observed.

To summarise, HPC was modified using various bromo-ester bromides to form Br-HPC with DS ranging from 0.14 to 2.04 (Table S6 in ESI). DMF, THF and DCM were the commonly used solvents and the reaction time varied from 2.5 h to 2 days. Catalysts such as

TEA, pyridine and/or DMAP were used for enhancing the degree of functionalization. A dendronized macro-initiator permitted the preparation of graft-copolymers of HPC with a high graft density. Bromoisobutyryl anhydride as the reagent for functionalizing HPC produced a macro-initiator with the highest DS of 2.26. These macro-initiators were used for graft-copolymerising various monomers; Table S7 (ESI) summarises the reaction conditions used for each graft-copolymerisation. CuBr_2 has been used extensively with CuBr to control the production of radicals thus enhancing the control of the polymerisation. High dilution also permitted a reduction of radical-radical coupling. Furthermore, the use of tridentate ligands such as PMDETA was favoured over bidentate ligands such as bpy because of both the enhanced polymerisation rate and the lower required amount of Cu (I). To maintain the livingness of the polymerisation, the monomer conversion was kept below 64 %. Depending on the nature of the grafted polymers, the physical properties of HPC were changed. NIPAAM, OEGMA and DEGMA were polymerised onto HPC and the resulting graft-copolymers self-assembled into particles above their LCST. The presence of PNIPAAM and PDEGMA grafts decreased the LCST of HPC to 37 °C and 22 °C respectively whereas the grafting of POEGMA increased the LCST to 62 °C. Moreover, the graft-copolymerisation of 4VP introduced pH responsiveness making the resulting HPC dually responsive with a cloud point at a temperature greater than 45 °C or a pH > 6. The grafting of a quaternised PDMAEMA to the HPC backbone extended its potential uses to that of a vector for gene delivery. The preparation of graft-block copolymers such as P(t-BA)-b-PMMA-g-HPC, PMMA-g-G1-HPC and (PMMA-ran-PCMA)-g-HPC produced micelles with different sizes. The cross-linking of NIPAAM and PAA-b-PLC-g-HPC prolonged payload release over time and increased the size of its micelles, respectively. The graft-copolymers of HPC which self-assembled into particles are summarised in Table S8 (ESI). The size of particles varied from 64 nm to 570 nm depending on the length and density of the grafts. An increase in the graft

length resulted in the formation of larger particles; however the graft density is responsible for the shapes of particles as previously discussed in the part concerning graft-copolymers.

V. Graft-copolymers of other cellulose derivatives

Other cellulose derivatives such as cellulose diacetate (CDA), cellulose acetate (CA) and hydroxyethyl cellulose (HEC) have been used for graft-copolymerisation via ATRP processes in homogeneous media. Cellulose acetate and CDA are produced by esterification with acetic anhydride where the difference resides in the DS of the hydroxyl groups (1 and 2 respectively). These cellulose derivatives are used in the production of membranes, eyeglasses, adhesives and photography film. HEC is made by reacting cellulose with ethylene oxide, producing a DS ranging from 0.8 to 1.8^{6, 64}. HEC is used as a thickener, stabilizer, binder, suspending agent and a film former in the pharmaceutical, cosmetic, adhesive, and paint industries^{64, 76, 77}. In this section of the review, ATRP of these derivatives will be covered. First, we will overview the preparation of graft-copolymers from CDA. Second, the graft-copolymerisation of CA with methyl diethylene glycol methacrylate (MDEGA) will be summarised, including the influence of the graft length on the segregation state. Finally, the modification of HEC with polyacrylamide (PAM) and poly(N,N-dimethylacrylamide) (PDAM) will be described alongside the potential application of the resulting copolymer in capillary electrophoresis.

In 2004, Shen *et al.*⁷⁸ were the first researchers to use the CDA backbone for grafting MMA. A macro-initiator Br-CDA was successfully prepared from bromoisobutryl bromide in THF in the presence of pyridine. A ratio of AGU to Br equal to 1/0.5 was chosen and almost all Br reacted with the CDA backbone at the C6 position leading to a DS of 0.43. Br_{0.43}-CDA was used for graft-polymerising MMA in dioxane using CuBr/PMDETA as catalyst system. A ratio monomer to initiator, catalyst and ligand ([M]/[I]/[C]/[L]) equal to 300/1/0.5/1 was chosen and the reaction was conducted at 70 °C for 8 h. Kinetic studies

highlighted the control of the MMA polymerisation, however the monomer conversion was extremely low with a value of 4 %. Cleavage of PMMA grafts from the CDA backbone using a solution of sulphuric acid confirmed the narrow molecular weight distribution with a D_M of ~ 1.4 . Later on, Vlček *et al.*⁷⁹ showed interest in the preparation of CDA based graft-copolymers. Macro-initiators were synthesised from 2-bromoisobutyryl bromide in dioxane or dichloroacetyl chloride in acetone using both TEA/DMAP as a catalyst system. The DS of Br-CDA and Cl-CDA were varied depending on the molar ratio of functionalizing agent to CDA. For Br-CDA, a ratio AGU to Br equal to 1/0.3 led to a DS of 0.1 whereas a decrease of the ratio AGU/Br to 1/3.1 increased the DS to 0.52. The same was observed for Cl-CDA; a 1/1 and 1/4 ratio of AGU to Cl lead to a DS of 0.1 and 0.41 respectively. The resulting Br-CDAs and Cl-CDAs macro-initiators were used for graft-copolymerising MMA, t-BA and St. For the graft-copolymerisation of MMA and St, dioxane as solvent, CuCl/CuCl₂ as catalyst system and principally a tetradentate ligand, HMDETA, were used. Cl_{0.41}-DCA and Cl_{0.1}-DCA were used for the polymerisation of MMA at a temperature of 75 °C or 90 °C respectively whereas Br-CDAs were used for initiating the polymerisation of St at 110 °C. For a reaction time ranging from 6.5 to 18 h, MMA has been polymerised onto Cl_{0.41}-CDA with a monomer conversion between 5 to 10 % whereas the ATRP of MMA onto the Cl_{0.1}-CDA led to higher monomer conversion (18-21 %) in a shorter reaction time (1.5-2.5h) because the use of a low DS_{Cl} reduces the radical-radical coupling which is responsible for both loss of control and gelation. Regarding the polymerisation of St, the monomer conversion of 9-14 % was similar for both macro-initiators Br_{0.52}-CDA and Br_{0.12}-CDA. These two macro-initiators, Br-CDAs were further used to graft-copolymerise t-BA in acetone using a tridentate ligand, PMDETA. As for the polymerisation of MMA onto Cl-CDAs, Br_{0.12}-CDA was found to be a more efficient initiator than Br_{0.52}-CDA, with a monomer conversion of 25 % and 15 % after respectively 5 h and 8.5 h. The alkyl halide at

the chain end of PMMA₆₉-g-CDA_{0.1} and PSt₂₅-g-CDA_{0.12} graft-copolymers was also used to polymerise t-BA producing block graft-copolymers. The reaction conditions were similar to that for the ATRP of t-BA onto Br-CDAs, except that CuCl₂ was omitted most probably to increase the rate of the polymerisation. After 20 h of reaction for the polymerisation of t-BA onto Br_{0.12}-PSt₂₅-CDA, the monomer conversion was equal to 5 % whereas after 27 h, a monomer conversion of 10 % was reached for the polymerisation of t-BA onto Cl_{0.1}-PMMA₆₉-CDA. Overall, Vlček *et al.*⁷⁹ highlighted the versatility of ATRP process onto CDA i.e. from the grafting of a single polymeric chain to the grafting of block copolymers.

Vlček *et al.*⁸⁰ continued their investigation via the preparation of brush graft-copolymers combining ATRP and ROP processes. The CDA backbone was activated as described in their previous work, via bromination forming a macro-initiator with a DS value of 0.5. Thus, PCLs with a DP of 50 and 89 were grafted onto CDA via a ROP process. Thereafter, graft-copolymers of MMA, St, or t-BA were generated by ATRP where the length of the grafts was varied by adapting the reaction conditions which were similar to that in their previous work. The monomer conversion was relatively low ranging from 6 to 10 %, but it was found to be predictable when the graft-copolymerisation was performed with a high DS of macro-initiator.

Recently, Billy *et al.*⁸¹ chose to investigate graft-copolymerisation of methyl diethylene glycol methacrylate (MDEGMA) from CA. Br-CA macro-initiators with a DS of 0.06 and 0.01 were synthesised from bromoisobutryl bromide in the presence of TEA in THF, and the regioselectivity of substitution at the C6 position on the CA backbone was highlighted. A ratio of AGU to Br equal to 1/0.08 was used to synthesise Br_{0.01}-CA, however a decrease of the ratio AGU/Br produced a higher degree of functionalization of CA with bromo-ester bromide. The graft-copolymerisation of MDEGMA onto Br-CAs proceeded in cyclopentanone using PMDETA/CuCl as catalyst system at a temperature of 40 °C. For the

most substituted macro-initiator Br_{0.06}-CA, the reaction time used was shorter than that for Br_{0.01}-CA to limit radical-radical coupling and thus prevent gelation. After 2.5 and 7 h of polymerisation onto Br_{0.06}-CA and Br_{0.01}-CA respectively, the monomer conversion was equal to 16 and 19 % respectively. Due to the difference of targeted DP, Br_{0.06}-CA resulted in a high number of short grafts defined by 16 monomer units with a D_M of approximately 1.5, however, the less substituted macro-initiator Br_{0.01}-CA gave long PMDEGMA grafts constituting of 80 monomer units. Morphological studies showed that the PMEGMA-g-CAs with longer grafts segregated more than those with shorter grafts. Furthermore, the size of the segregated phase increased with the length of the grafts. For a DP of 98, the resulting graft-copolymer was fully segregated with sharp interfaces and a radius of gyration of 11.5 nm.

Yang and co-workers⁸² described the preparation of a PAM-g-HEC graft-copolymer in a controlled manner from macro-initiator Br-HEC which had been synthesised in a mixture of DMF/THF in the presence of TEA and DMAP as catalyst system (the degree of functionalization was not given). The graft-copolymerisation of AM onto Br-HEC was also conducted in a mixture of DMF/THF at 30 °C with CuBr/CuBr₂ as catalyst. An unusual tetradentate ligand, Me₆[14]aneN₄, was used and 40% of monomer conversion was reached after 3 days of polymerisation. Owing to its rheological behavior and its ability to suppress electroosmotic flow (EOF), the graft-copolymer found a potential application in capillary electrophoresis (CE) systems such as for DNA separation. The same group continued their investigation with the preparation of the graft-copolymer, PDMA-g-HEC⁸³ by polymerisation of DMA onto Br-HEC. The reaction conditions were similar, however, a mixture of DMF/toluene was used. A monomer conversion of 62% and a D_M of 4.2 were measured after 6 h of polymerisation suggesting a loss of polymerisation control. The graft-copolymer was

coated onto capillaries to investigate protein separation, and the results showed efficient protein separations at pH 2.2, 4.6 and 6.0 (Figure 15).

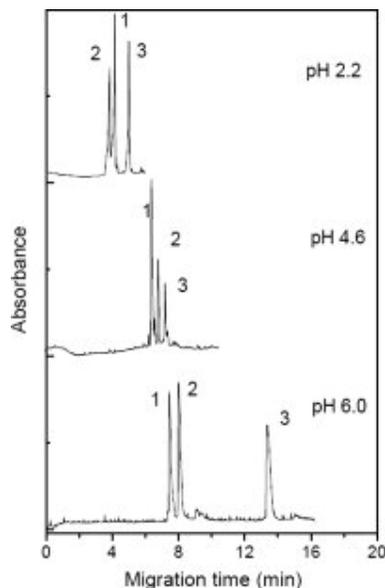


Figure 15: Effect of buffer pH on the separation of common proteins. Separation buffer: phosphate-citrate of pH 2.2, pH 4.6 and pH 6.0, separations were conducted in a PDMA-g-HEC coated capillary. Conditions: separation voltage, 20 kV; temperature, 25°C; detection, UV 214 nm; injection, 0.5 psi for 5 s; polymer concentration, 0.2% w/v. Sample: 0.5 mg/mL protein mixture, peak identification: 1, lysozyme; 2, cytochrome *c*; 3, ribonuclease A. Capillary, bare fused-silica of 40 cm total length (30 cm to the detector) $\times 75 \mu\text{m}$ id⁸³.

To summarise, CDA, CA and HEC have been successfully combined with synthetic polymers via graft-copolymerisation by ATRP. These derivatives were prior-functionalized using either bromoisobutryl bromide or dichloroacetyl chloride and DS ranged from 0.1 to 0.52 depending in both the number of free hydroxyl groups and the ratio AGU to alkyl halide. Further details regarding the preparation of the macro-initiators are summarised in Table S9 (ESI). Regarding the graft-copolymerisation, PMMA, PSt and P(*t*-BA) were grafted on CDA and PMMA-g-CDA and PSt-g-CDA were further used to polymerise *t*-BA to form block

graft-copolymers. Combining ROP and ATRP processes, a brush graft-copolymer from PCL was also obtained. CA was graft-copolymerised with MDEGMA, however, CA systems remain sparsely investigated. The resulting graft-copolymer phase-segregated depending on the lengths of the grafts. HEC was modified with DAM and PDAM and the resulting products showed potential for applications in capillary electrophoresis. The reaction conditions for all graft-copolymerisations described in this section are summarised in Table S10 (ESI). In the case of CDA, dioxane was used as solvent and principally tetradentate ligands were used for the graft-polymerisation of both MMA and St whereas acetone and tridentate ligand was used as reaction media and ligand respectively for polymerizing t-BA onto CDA. Furthermore, the DS of the backbone seemed to affect the monomer conversion; higher conversion was obtained from lower DS macro-initiator and vice versa, potentially explained by a higher concentration of radicals for higher DS macro-initiator leading to gelation at too high monomer conversion.

VI. Conclusions

Grafting synthetic polymers onto solid cellulosic substrates such as membranes and fibers has been described extensively, however, chemical modification of cellulose and cellulose derivatives with polymers under homogeneous conditions is less well explored. The use of ATRP processes to graft polymers onto cellulose and its derivatives is highly attractive because they permit grafting in a controlled manner to produce designed bio-based hybrid materials. Despite this, the area has been the subject of study only for the last ten years. Cellulose, ethyl cellulose and hydroxypropyl cellulose have received most attention as materials for the graft-copolymerisation of various monomers, including methyl methacrylate, N-isopropylacrylamide and styrene. In this review we have described the synthetic polymers which have been grafted onto cellulose and its derivatives, and these are summarized chronologically in Figure 16 and by cellulose backbone type in Table 1. The main purpose of the grafting was to create amphiphilic hybrid materials which could self-assemble into nanoscale species and/or which possess stimuli-responsive properties. These materials are being considered for applications in biotechnology given their cost effectiveness and their largely renewable origin.

Figure 16: Graft-copolymers of cellulose and cellulose derivatives arranged in chronological order of date of publication.

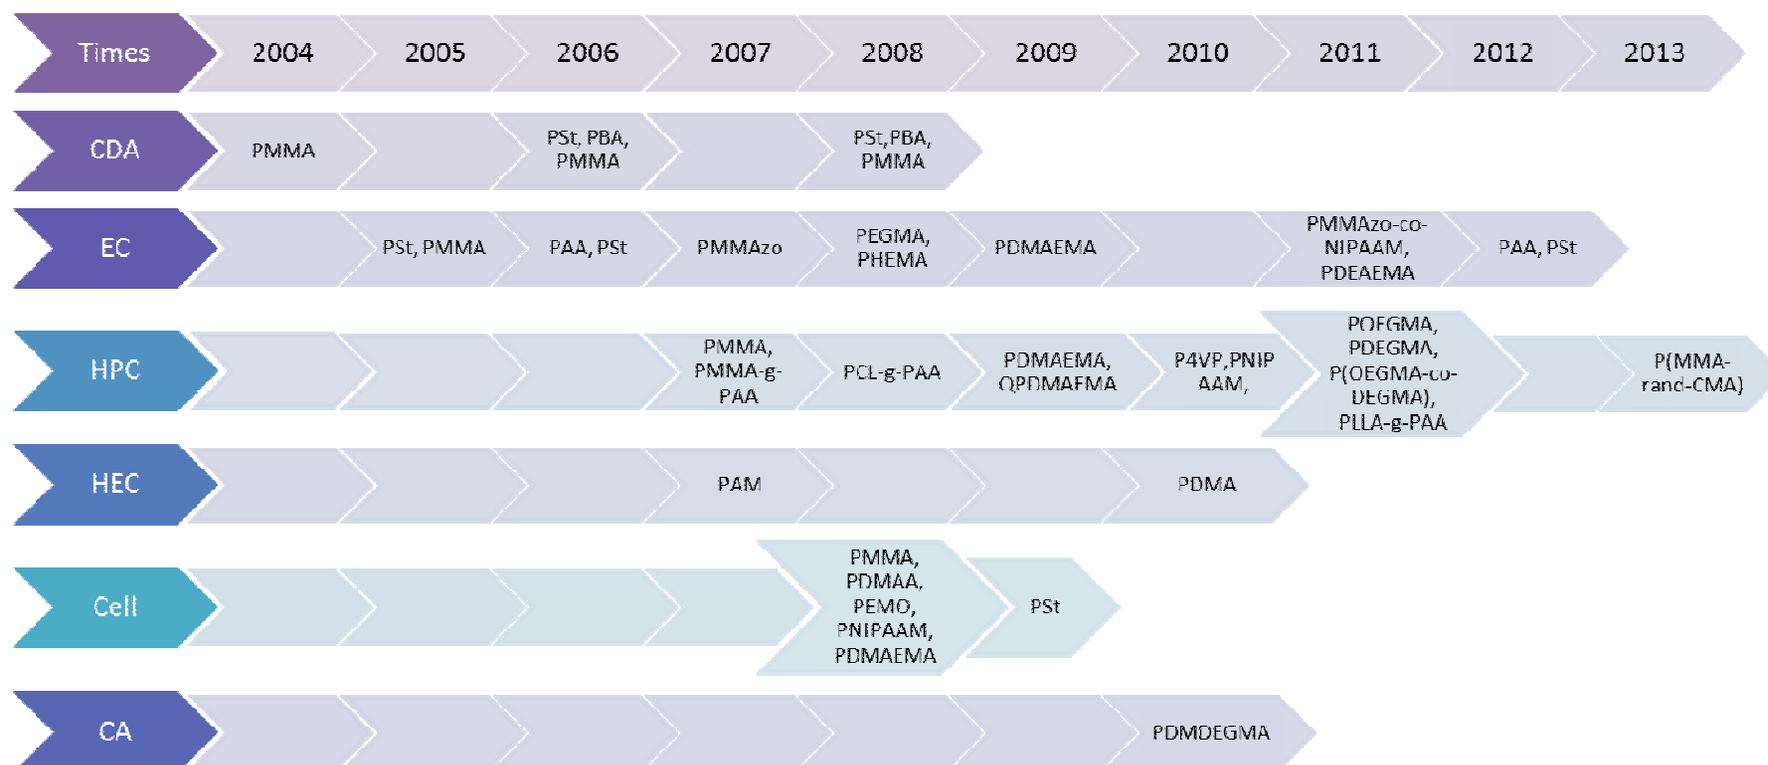


Table 1: Summary of the polymers grafted onto cellulose or its derivatives using ATRP under homogeneous conditions

From cellulose	From cellulose derivatives						
PMMA ^{40-42, 44, 46} PDMA ^{49, 50} PEO ⁴⁰ PNIPAAm ^{43, 51} PDMAEMA ⁴⁵ PSt ⁴²	EC		HPC		Others		
	Assembly	Smart-assembly	Single Brush	Brush copolymer	CDA	HEC	CA
	PAA ⁵⁷ PSt ⁵³⁻⁵⁴ PMMA ⁵³ PHEMA ⁵⁶	MMAzo ⁵⁹ PEGMA ⁶⁰ PDEAEMA ⁶¹ PDMAEMA ⁶² PMMAzo-co-NIPAAm ⁶³	POEGMA ⁷³ PDEGMA ⁷³ P4VP ⁷⁵ PMMA ^{68, 69} PDMAEMA ⁷⁴ QPDMAEMA ⁷⁴ NIPAAm ⁷²	PMMA-g-PAA ⁶⁸ P(OEGMA-co-DEGMA) ⁷³ P(MMA-ran-CMA) ⁶⁹ PLLA-g-PAA ⁷¹ PCL-g-PAA ⁷⁰	PSt ⁸⁰ PBuA ⁸⁰ PMMA ⁸⁰ PSt ⁷⁹ P(t-BA) ⁷⁹ PMMA ⁷⁹ PMMA ⁷⁸	PAm ⁸² PDMA ⁸³	PMDEGMA ⁸¹

References

1. D. Klemm, H.-P. Schmauder and T. Heinze, in *Biopolymers Online*, Wiley-VCH Verlag GmbH & Co. KGaA, 2005.
2. D. R. Nobles, Jr. and R. M. Brown, Jr., *Cellulose*, 2008, **15**, 691-701.
3. S. Dumitriu, *Polysaccharides: Structural Diversity And Functional Versatility*, Marcel Dekker, 2005.
4. D. Klemm, *Comprehensive Cellulose Chemistry: Fundamentals and analytical methods*, Wiley-VCH, 1998.
5. K. Kamide, *Cellulose And Cellulose Derivatives: Molecular Characterization and Its Applications*, Elsevier, Amsterdam, 2005.
6. J.-L. Wertz and J. P. Mercier, *Cellulose science and technology*, EPFL Press ; Taylor & Francis distributor, Lausanne; London, 2008.
7. A. O'Sullivan, *Cellulose*, 1997, **4**, 173-207.
8. D. Plackett, *Biopolymers: New Materials for Sustainable Films and Coatings*, John Wiley & Sons, 2011.
9. S. Kamel, N. Ali, K. Jahangir, S. M. Shah and A. A. El-Gendy, *Express Polym. Lett.*, 2008, **2**, 758-778.
10. H. Pereira, *Cork: Biology, Production and Uses*, Elsevier, 2007.
11. R. Myers, *The Basics of Chemistry*, Greenwood Press, Toledo, OH, 2003.
12. T. Heinze, H. Barsett and A. Ebringerová, *Polysaccharides I: Structure, Characterisation And Use*, Springer, 2005.
13. D. Roy, M. Semsarilar, J. T. Guthrie and S. Perrier, *Chem. Soc. Rev.*, 2009, **38**, 2046-2064.

14. A. W. T. King, J. Jalomaki, M. Granstrom, D. S. Argyropoulos, S. Heikkinen and I. Kilpelainen, *Anal. Methods*, 2010, **2**, 1499-1505.
15. F. F. L. Ho, R. R. Kohler and G. A. Ward, *Anal. Chem.*, 1972, **44**, 178-181.
16. C. Vaca-Garcia, M. E. Borredon and A. Gaseto, *Cellulose*, 2001, **8**, 225-231.
17. A. Reza Fareghi, P. Najafi Moghaddam, A. Akbar Entezami and M. Ensafi Avval, *Iran. Polym. J.*, 2013, **22**, 361-367.
18. A. Carlmark and E. Malmström, *J. Am. Chem. Soc.*, 2002, **124**, 900-901.
19. P.-S. Liu, Q. Chen, S.-S. Wu, J. Shen and S.-C. Lin, *J. Membrane Sci.*, 2010, **350**, 387-394.
20. N. Singh, Z. Chen, N. Tomer, S. R. Wickramasinghe, N. Soice and S. M. Husson, *J. Membrane Sci.*, 2008, **311**, 225-234.
21. G. Morandi, L. Heath and W. Thielemans, *Langmuir*, 2009, **25**, 8280-8286.
22. J. Majoinen, A. Walther, J. R. McKee, E. Kontturi, V. Aseyev, J. M. Malho, J. Ruokolainen and O. Ikkala, *Biomacromolecules*, 2011, **12**, 2997-3006.
23. C. Olsson and G. Westman, in *Cellulose - Fundamental Aspects*, eds. T. van de Ven and L. Godbout, InTech, 2013.
24. A. Bhattacharya and B. N. Misra, *Progr. Polym. Sci.*, 2004, **29**, 767-814.
25. M. B. K. Horie, R. B. Fox, J. He, M. Hess, J. Kahovec, T. Kitayama, P. Kubisa, E. Maréchal, W. Mormann, R. F. T. Stepto, D. Tabak, J. Vohlídal, E. S. Wilks and W. J. Work, *Pure App. Chem.*, 2004, **76**, 889-906.
26. E. M. Flefel, M. M. Ibrahim, W. K. El-Zawawy and A. M. Ali, *Polym. Adv. Technol.*, 2002, **13**, 541-547.
27. M. Yigitoglu, N. Isiklan and R. Ozmen, *J. Appl. Polym. Sci.*, 2007, **104**, 936-943.
28. M. M. Ibrahim, E. M. Flefel and W. K. El-Zawawy, *Polym. Adv. Technol.*, 2002, **13**, 548-557.

29. G. S. Chauhan, B. Singh and S. Kumar, *J. Appl. Polym. Sci.*, 2005, **98**, 373-382.
30. E. Takács, H. Mirzadeh, L. Wojnárovits, J. Borsa, M. Mirzataheri and N. Benke, *Nucl. Instr. Meth. B*, 2007, **265**, 217-220.
31. N. Inagaki and K. Katsuura, *J. Polym. Sci. Pt. A: Polym. Chem.*, 1980, **18**, 441-448.
32. J.-S. Wang and K. Matyjaszewski, *J. Am. Chem. Soc.*, 1995, **117**, 5614-5615.
33. J.-S. Wang and K. Matyjaszewski, *Macromolecules*, 1995, **28**, 7901-7910.
34. J. Chiefari, Y. K. Chong, F. Ercole, J. Krstina, J. Jeffery, T. P. T. Le, R. T. A. Mayadunne, G. F. Meijs, C. L. Moad, G. Moad, E. Rizzardo and S. H. Thang, *Macromolecules*, 1998, **31**, 5559-5562.
35. A. Postma, T. P. Davis, G. Moad and M. S. O'Shea, *Macromolecules*, 2005, **38**, 5371-5374.
36. H. Willcock and R. K. O'Reilly, *Polym. Chem.*, 2010, **1**, 149-157.
37. S. Li, M. Xiao, A. Zheng and H. Xiao, *Biomacromolecules*, 2011, **12**, 3305-3312.
38. A. Carlmark and E. E. Malmström, *Biomacromolecules*, 2003, **4**, 1740-1745.
39. O. Glaied, M. Dubé, B. Chabot and C. Daneault, *J. Colloid Interf. Sci.*, 2009, **333**, 145-151.
40. F. Chang, K. Yamabuki, K. Onimura and T. Oishi, *Polym. J.*, 2008, **40**, 1170-1179.
41. L. Chun-xiang, Z. Huai-yu, L. Ming-hua, F. Shi-yu and Z. Jia-jun, *Carbohydr. Polym.*, 2009, **78**, 432-438.
42. T. Meng, X. Gao, J. Zhang, J. Yuan, Y. Zhang and J. He, *Polymer*, 2009, **50**, 447-454.
43. S. Ifuku and J. F. Kadla, *Biomacromolecules*, 2008, **9**, 3308-3313.
44. T.-T. Xin, T. Yuan, S. Xiao and J. He, *Bioresources*, 2011, **6**, 2941-2953.
45. X. Sui, J. Yuan, M. Zhou, J. Zhang, H. Yang, W. Yuan, Y. Wei and C. Pan, *Biomacromolecules*, 2008, **9**, 2615-2620.
46. J.-F. Zhong, X.-S. Chai and S.-Y. Fu, *Carbohydr. Polym.*, 2012, **87**, 1869-1873.

47. J. F. Zhong, X. S. Chai, X. L. Qin and S. Y. Fu, *Carbohydr. Polym.*, 2011, **86**, 367-370.
48. W. Jakubowski, K. Min and K. Matyjaszewski, *Macromolecules*, 2005, **39**, 39-45.
49. Y. Lifeng and W. Tao, *J. Biomed. Sci. Eng.*, 2008, **01**, 37-43.
50. K. C. Gupta, *Abstr. Pap. Am. Chem. Soc.*, 2009, **50 (2)**, 174-175.
51. G. Cui, Y. Li, T. Shi, Z. Gao, N. Qiu, T. Satoh, T. Kakuchi and Q. Duan, *Carbohydr. Polym.*, 2013, **94**, 77-81.
52. E. Lokensgard, *Industrial Plastics: Theory and Applications*, Cengage Learning, Clifton Park, NY, 2008.
53. D. Shen, H. Yu and Y. Huang, *J. Polym. Sci. Pt. A: Polym. Chem.*, 2005, **43**, 4099-4108.
54. D. Shen, H. Yu and Y. Huang, *Cellulose*, 2006, **13**, 235-244.
55. Q. Li, H. Kang and R. Liu, *Chinese J. Chem.*, 2012, **30**, 2169-2175.
56. H. Kang, W. Liu, R. Liu and Y. Huang, *Macromol. Chem. Phys.*, 2008, **209**, 424-430.
57. H. Kang, W. Liu, B. He, D. Shen, L. Ma and Y. Huang, *Polymer*, 2006, **47**, 7927-7934.
58. W. Liu, Y. Liu, G. Zeng, R. Liu and Y. Huang, *Polymer*, 2012, **53**, 1005-1014.
59. X. Tang, L. Gao, X. Fan and Q. Zhou, *J. Polym. Sci. Pt. A: Polym. Chem.*, 2007, **45**, 1653-1660.
60. Y. Li, R. Liu, W. Liu, H. Kang, M. Wu and Y. Huang, *J. Polym. Sci. Pt. A: Polym. Chem.*, 2008, **46**, 6907-6915.
61. D. Wang, J. Tan, H. Kang, L. Ma, X. Jin, R. Liu and Y. Huang, *Carbohydr. Polym.*, 2011, **84**, 195-202.
62. Q. Yan, J. Yuan, F. Zhang, X. Sui, X. Xie, Y. Yin, S. Wang and Y. Wei, *Biomacromolecules*, 2009, **10**, 2033-2042.
63. X. Tang, D. Zhou and N. Han, *Mater. Sci. Forum*, 2011, **663-665**, 4.

64. A. A. Tracton, *Coatings Materials And Surface Coatings*, CRC Press, Boca Raton, FL, 2006.
65. R. L. Whistler and J. N. BeMiller, *Industrial Gums: Polysaccharides and Their Derivatives*, Academic Press, San Diego, CA, 1993.
66. D. B. Braun and M. R. Rosen, *Rheology Modifiers Handbook: Practical Use and Application*, William Andrew Pub., Norwich, NY, 2000.
67. C. Vasile and G. E. Zaikov, *New Trends in Natural And Synthetic Polymer Science*, Nova Science Publishers, New York, 2006.
68. E. Östmark, S. Harrisson, K. L. Wooley and E. E. Malmström, *Biomacromolecules*, 2007, **8**, 1138-1148.
69. M. Bagheri and L. Pourmirzaei, *Macromol. Res.*, 2013, **21**, 801-808.
70. E. Östmark, D. Nyström and E. Malmström, *Macromolecules*, 2008, **41**, 4405-4415.
71. D. L. Berthier, A. Herrmann and L. Ouali, *Polym. Chem.*, 2011, **2**, 2093-2101.
72. F. J. Xu, Y. Zhu, F. S. Liu, J. Nie, J. Ma and W. T. Yang, *Bioconjugate Chem.*, 2010, **21**, 456-464.
73. C. Porsch, S. Hansson, N. Nordgren and E. Malmstrom, *Polym. Chem.*, 2011, **2**, 1114-1123.
74. F. J. Xu, Y. Ping, J. Ma, G. P. Tang, W. T. Yang, J. Li, E. T. Kang and K. G. Neoh, *Bioconjugate Chem.*, 2009, **20**, 1449-1458.
75. L. Ma, H. Kang, R. Liu and Y. Huang, *Langmuir*, 2010, **26**, 18519-18525.
76. M. Glicksman, *Adv. Food Res.*, 1963, **12**, 283-366.
77. C. G. Wilson and P. J. Crowley, *Controlled Release in Oral Drug Delivery*, Springer, Boston, MA, 2011.
78. D. Shen and Y. Huang, *Polymer*, 2004, **45**, 7091-7097.

79. P. Vlček, M. Janata, P. Látalová, J. Kríž, E. Čadová and L. Toman, *Polymer*, 2006, **47**, 2587-2595.
80. P. Vlček, M. Janata, P. Látalová, J. Dybal, M. Špírková and L. Toman, *J. Polym. Sci. Pt. A: Polym. Chem.*, 2008, **46**, 564-573.
81. M. Billy, A. R. Da Costa, P. Lochon, R. Clément, M. Dresch, S. Etienne, J. M. Hiver, L. David and A. Jonquière, *Eur. Polym. J.*, 2010, **46**, 944-957.
82. R. Yang, Y. Wang and D. Zhou, *Electrophoresis*, 2007, **28**, 3223-3231.
83. R. Yang, Y. Liu and C. Zheng, *J. Appl. Polym. Sci.*, 2010, **116**, 3468-3472.

Electronic Supporting Information

The Preparation of Graft Copolymers of Cellulose and Cellulose Derivatives Using ATRP Under Homogeneous Reaction Conditions

Fanny Joubert ^{a,b}, Osama M. Musa ^c, David R. W. Hodgson ^{a,b}, Neil R. Cameron ^{a,b}

^a Department of Chemistry, Durham University, Science Laboratories, Durham DH1 3LE, UK

^b Biophysical Sciences Institute, Durham University, Durham DH1 3LE, UK

^c Ashland Speciality Ingredients, 1005 Route 202/206, Bridgewater, NJ 08807, USA

List of abbreviations

AM: Acrylamide

AA: Acrylic acid

[AMIM]Cl: 1-Allyl-3-methylimidazolium chloride

AGU: β -D-anhydroglucopyranose

AFM: Atomic Force Microscopy

ATRP: Atom Transfer Radical Polymerisation

BA: n-Butyl acrylate

BMIMCl: 1-Butyl-3-methylimidazolium chloride

Bpy: 2,2'-bipyridine

CL: ϵ -Caprolactone

CM Cell: Carboxymethyl cellulose

Cell: Cellulose

CA: Cellulose acetate

CDA: Cellulose diacetate

CMA: Cholesteryl methacrylate

CRP: Controlled Radical Polymerisation

CMC: Critical Micelle Concentration

D_h: Hydrodynamic diameter

D_M : Dispersity

DCM: Dichloromethane

DEAEMA: 2-(Diethylamino)ethyl methacrylate

DMAc: N,N-Dimethylacetamide

DMA: N,N-Dimethylacrylamide

DMAEMA: 2-(Dimethylamino)ethyl methacrylate

DMAP: 4-Dimethylaminopyridine

DMF: N,N-Dimethylformamide

DMSO: Dimethyl sulfoxide

DNpby: 4,4'-Di-5-nonyl-2,2'-bipyridine

DLS: Dynamic Light Scattering

DP: Degree of Polymerisation

DS: Degree of Substitution

DSC: Differential Scanning Calorimetry

DEGMA: 2-(Hydroxyethoxy)ethyl methacrylate

EC: Ethyl cellulose

EMO: 3-Ethyl-3-methacryloyloxy-methyloxetane

GPC: Gel Permeation Chromatography

HS-GC: Headspace gas chromatography

HDMA: Hexadecyl methacrylate

HEC: Hydroxyethyl cellulose

HEMA: 2-Hydroxyethyl methacrylate

HMTETA: 1,1,4,7,10,10-Hexamethyltriethylenetetramine

HPC: Hydroxypropyl cellulose

IL: Ionic liquid

LLA: L-lactide

LCST: Lower Critical Solution Temperature

Me₆TREN: Tris[2-(dimethylamino)ethyl]amine

MMAzo: azobenzene-containing methacrylate

MDEGMA: methyl diethylene glycol methacrylate

MMA: methylmethacrylate

NIPAAM: *N*-isopropylacrylamide

OEGMA: Oligo(ethylene glycol) methacrylate

PEG: Polyethylene glycol

PEGMA: Poly(ethylene glycol) methyl ether methacrylate

PMDETA: *N,N,N',N',N''*-pentamethyldiethylenetriamine

QDDMAEMA: Quaternized *N,N*-dimethylamino-2-ethyl methacrylate

RAFT: Reversible Addition Fragmentation Transfer

R_h : hydrodynamic radius

ROP: Ring Opening Polymerisation

St: Styrene

SLS: Static Light Scattering

T_g : Glass transition temperature

TEA: Triethylamine

TEM: Transmission Electron Microscopy

TG-DTA: Thermal Gravimetric-Differential Thermal Analysis

TMEDA: Tetramethylethylenediamine

4VP: 4-*N*-vinylpyridine

WAXD: Wide-Angle X-ray Diffraction

Table S1: Reaction conditions used to prepare cellulose ATRP macro-initiators

Ref.	Reactants	Catalyst	AGU:(Br/Cl)	Temperature (°C)	Time (h)	Solvent(s)	DS
40	Chloroacetyl chloride	pyridine	1:10	RT	10	DMAc/LiCl	2.1
41		/	1:5	50	5	BMIMCl	1.8
46		dimethylaminopyridine	..	50	5	DMAc/LiCl	..
51	2-Chloropropionyl chloride	dimethylaminopyridine	DMF	>1
49	2-Bromoisobutyryl bromide	pyridine	..	RT	~17	DMAc/LiCl	0.2
43		pyridine	1:20	RT	~17	DMAc	1
42		/	1:5	RT	8	AMIMCl/DMF	0.7
45	2-Bromopropionyl bromide	/	1:5	RT	8	AMIMCl/DMF	0.7
44		/	1:5	RT	10	AMIMCl/DMF	0.7
50	Methyl-2-bromopropionate	dimethylaminopyridine	1:30	25	..	THF	..

'..' = not reported; '/' = no catalyst

Table S2: Summary of the reaction conditions for preparing graft-copolymers of cellulose

Ref.	Monomer	Initiator	Catalyst	Ligand	Solvent(s)	Temperature (°C)	Time (h)	Ratio [I]/[C]/[L]/[M]	Conversion (%)	\bar{D}_M	Graft Ratio
40	EMO	Cl-Cell	CuBr	PMDETA	DMF	130	21	1/1/3/9	10
		Cell-PMMA-Cl	CuCl	TMEDA	..	70	46	1/1/3/60	28
40		Cl-Cell	CuBr	TMEDA	DMF	130	20	1/1/3/60	7
		Cell-PEMO-Cl	CuCl	PMDETA	..	70	21	1/1/1/3/60	49
41	MMA	Cl-Cell	CuBr	bpy	BMIMCl		70	5	1/1/1/300	15	1.5
42		Br-Cell	CuCl			butanone		3	1/1/2/200	28	1.4
44		Br-Cell	CuBr	PMDETA	DMF	60	3	1/1/1/200	38	1.6	1800
46		Cl-Cell	Cu(II)Br/ AsAc	TEMED	DMAc	50-70	3	1/0.1/1/100	13	1.4	553
49		Br-Cell	CuBr	bpy	DMSO	RT	7	1/2.9/1.3/90	50	1.5	2280
50	DMA	Br-Cell	CuBr	Me ₆ TREN	toluene1/1/(10 AA/20 DMA)
43	NIPAAM	Br-Cell	CuBr	PMDETA	DMF/H ₂ O	RT	12	1/4/4/200	17	2.3	14
51		Cl-Cell	CuCl	Me ₆ TREN	DMF/H ₂ O	80	48	1/1.2/1.2/100	79	1.4	..
45	DMAEMA	Br-Cell	CuBr	PMDETA	DMF	60	1	1/1/1/200	35	..	2670
42	St	Br-Cell	CuCl	bpy	dioxane	110	2	1/1/3/100	14	1.5	373

('..' = not reported) and Graft ratio = $(W_2 - W_1)/W_1 \times 100$ where W_2 and W_1 are weight of the graft-copolymers and macro-initiator respectively.

Table S3: Summary of the reaction conditions used to prepare ethyl cellulose ATRP macroinitiators

Ref.	DS _{EC}	Reactant	Catalyst	Time (h)	AGU:Br	DS _{Br-EC}		
63	2.1	2-bromoisobutyryl bromide	triethylamine	10	1:5	(50 %)		
53			pyridine	48	1:3	0.5		
54					1:3	0.5		
54					1:0.2	0.04		
56					24	..	0.04/0.25	
56			1:1	0.04				
59					triethylamine	~17	1:3	0.5
60					0.02/0.2
62	2.3	2-bromopropionyl bromide	triethylamine	24	1:3	(23 %)		
55	2.5	2-bromoisobutyryl bromide	pyridine	48	..	0.28/0.54		
61			0.1/0.06/0.2		

'..' = not reported

Table S4: Summary of reaction conditions for preparing graft-copolymers of EC

Ref.	Monomer	Solvent(s)	Ligand	Temperature (°C)	Ratio [I]/[C]/[L]	Catalyst (s)	Time (h)	DS _{Br-EC}	DP _{targeted}	Conversion (%)	\bar{D}_M	Graft Ratio (%)
53,	MMA	toluene	PMDETA	70	1/0.5/1	CuBr	16	0.5	300	11.8	1.35	1291
55	St			110	1/0.5/1					10.8	1.35	1227
54	St			Toluene	PMDETA					110	1/1/1	CuBr
		10.5	0.04			6000	10	1.2	1115			
57	tBA	toluene/ cyclohexan one	PMDETA	80	1/2/2		..	0.04	3750	6	1.16	518
					1/1/1	CuBr/ CuBr ₂	..	0.25	300	21	1.2	..
56	HEMA	methanol	bypyridine	40	1/1.5/2.6	CuBr/ CuBr ₂	12	0.09	510	13	1.15	401
					1/1/2	CuBr	10	0.04	1000	8.3	1.18	502
59	MMAzo	anisole	PMDETA	85	1/2/4	CuBr	20	0.5	25	18	..	325
									50
60	PEGMA	toluene	dN bpy	60	1/0.75/1.5	CuCl/ CuCl ₂	8	0.2	50	55.6	..	665

						CuCl	14	0.02	300	61.7
61	DEAEMA	DMF	bpy	20	1/1.5/2.5	CuBr	5	0.1	300	28	..	616
							4	0.2	450	24
							6.5	0.06	200	42
62	DMAEMA	THF	PMDETA	60	1/1/1	CuBr	30	23%	100	23	..	31
63	NIPAAM/ MMAzo	DMF/H ₂ O	Me ₆ TREN	80	1/1/1	CuCl	9	50%	50/1

'..' = not reported

Table S5: Summary of the R_h of micelles prepared from EC

Ref.	graft-copolymers	solvent	Concentration (mg/ml)	R_h^* (nm)
54	PSt ₆₀ -g-EC _{0.5}	acetone	0.02	200-300
57	PAA ₁₃ -g-EC _{0.25}	water	1	5-100
56	PHEMA ₁₃₁ -g-EC _{0.09}	water	0.01-0.05	66-73
	PHEMA ₁₀ -g-EC _{0.04}	water	0.01-0.05	79-83
60	P(PEGMA) ₂₇ -g-EC _{0.2}	water	1	73
	P(PEGMA) ₁₈₅ -g-EC _{0.02}	water	1	140
61	PDEAEMA ₍₃₅₋₈₅₎ -g-EC _{0.1}	acidic aqueous	0.5	140-200
	PDEAEMA ₉₀ -g-EC _(0.06-0.1)	acidic aqueous	0.5	200
62	PDMAEMA ₂₃ -g-PCL ₃₀ -g-EC	aqueous	0.5	36

* determined by DLS

Table S6: Reactions conditions for preparing macro-initiators of HPC

Ref.	Starting material	Reagents	Catalyst(s)	Solvent	Time (h)	DS
74	HPC	bromoisobutyryl bromide	..	DCM	5	0.14
72			..	DCM	6	0.14
75			Pyridine	THF	12	0.05
73			..	DCM	2.5	0.6
69			DMAP/Pyridine	DMF	5	2.04
68		bromoisobutyryl anhydride	DMAP/Pyridine	DMF	12	2.26
73						1.4
68		Br*	DMAP/TEA	DMF	12	0.88
70	HPC-PCL-I	bromoisobutyryl bromide	DMAP/TEA	THF	2	>1.1
71	HPC-PLLA-OH	bromopropionyl bromide	TEA	THF	48	1

*3(2-bromo-2-methylpropanoyloxy)2-((2-bromo-2-methylpropanoxy)methyl)2-methylpropanoic acid chloride; ‘..’ = not reported.

Table S7: Reaction conditions for the graft-copolymerisation onto HPC

Ref.	Monomer	Macro-initiator	Solvent(s)	Ligand	Temperature (°C)	Ratio [M]/[I]/[C]/[L]	Catalyst(s)	Time (h)	Conversion (%)	Graft Ratio (%)
68	MMA	Br _{2.26}	toluene	PMDETA	80	100/0.28/0.8/0.2/1	CuBr/CuBr ₂	19	39	4680
68		Br _{0.88} -G1	toluene	PMDETA	50	100/0.085/0.9/0.1/1	CuBr/CuBr ₂	2	18	..
69		Br _{2.04}	toluene	bpy	70	100/0.28/0.8/0.2/1	CuCl/CuBr ₂	19	25	3480
69	MMA/CMA	Br _{2.04}	toluene	bpy	70	100/0.28/0.8/0.2/1	CuCl/CuBr ₂	19	30	6288
68	HDMA	Br _{2.26}	toluene	PMDETA	50-80	..	CuBr/CuBr ₂	1-2	gelled	..
68		Br _{0.88} -G1	toluene	PMDETA	70	100/0.19/0.8/0.2/1	CuBr/CuBr ₂	20	23	..
68	t-BA	Br _{2.26} -PMMA	toluene	PMDETA	70	100/0.1/0.8/0.2/1	CuBr/CuBr ₂	22	3.5	210
70		Br _{>1.1} -PCL	toluene	PMDETA	70	..	CuBr/CuBr ₂	14	32	1920
71		Br ₁	/	PMDETA	100	152/1/1/1	CuBr	0,5	35	475
74	DMAEMA	Br _{0.14}	isopropanol/ H ₂ O	HMTETA	RT	60/1/1/1.2	CuBr	8	62	289
72	NIPAAM	Br _{0.14}	dioxane	HMTETA	RT	100/1/1.5	CuBr	24	64	320
75	4VP	Br _{0.05}	isopropanol	Me ₆ TREN	30	100/1/1	CuCl	6	35	55

73	DEGMA	Br _{1.4}	anisole	Bpy	40	425/1	CuBr ₂ / AcAsc	..	20	2368
73	DEGMA	Br _{0.6}	MeOH	bpy	40	850/1/./..		4	21	2487
73	OEGMA	Br _{0.6}	MeOH	bpy	40	850/1/./..		4	28	5712
73	OEGMA52- co- DEGMA48	Br _{0.6}	MeOH	bpy	40	850/1/./..		4	35	..

'..' = not reported

Table S8: Hydrodynamic radii (R_h) of the micelles formed with graft-copolymers of HPC

Ref.	Graft-copolymers	Solvent(s)	R_h^*
71	PAA-PLLA-g-HPC	EtOH/H ₂ O	64
70	PtBA-PCL-g-HPC	H ₂ O	43
68	PMMA-g-HPC _{2.26}	THF	96
73	PDEGMA-g-HPC _{0.6}	H ₂ O	120
70	PAA-PCL-g-HPC _{>1.1}	H ₂ O	129
73	POEGMA-g-HPC _{0.6}	H ₂ O	150
68	PHDMA-g-GI-HPC _{0.88}	THF	183
75	P4VP ₃₅ -g-HPC _{0.05}	H ₂ O	190
68	PMMA-g-GI-HPC _{0.88}	THF	195
73	P(OEGMA ₅₂ -co-DEGMA ₄₈)-g-HPC _{0.6}	H ₂ O	200
73	PDEGMA-g-HPC _{1.4}	H ₂ O	250
70	cross linked PAA-PCL-g-HPC _{>1.1}	H ₂ O	235.3
68	PtBA-PMMA-g-HPC _{2.26}	THF	280
69	P(MMA-rand-CMA)-g-HPC _{2.04}	H ₂ O	570

*determined using DLS

Table S9: Reaction conditions for preparing macro-initiators of derivatives

Ref.	Derivative	Reagents	Ratio AGU:Br	Catalyst(s)	Solvent(s)	DS
78	CDA	bromoisobutyryl bromide	01:0.5	pyridine	THF	0.43
79, 80			1/(0.3 or 3.1)	TEA/DMAP	dioxane	0.12-0.52
79		dichloroacetyl chloride	1/(1 or 4)	TEA/DMAP	acetone	0.10-0.41
81	CA	bromoisobutyryl bromide	1/0.08	TEA	THF	0.01
82, 83	HEC	bromoisobutyryl bromide	..	TEA/DMAP	DMF/THF	..


‘..’ = not reported

Table S10: Reaction conditions for synthesising graft-copolymers of other cellulose derivatives

	Monomer	Solvent	Ligand	Catalyst(s)	Macro-initiator	Ratio [M]/[I]/[C]/[L]	Temp. (°C)	Time (h)	Conversion (%)	Graft Ratio (%)	Ref.
CDA	MMA	dioxane	PMDETA	CuBr	Br _{0.43}	300/1/0.5/1	70	8	4	177	78
			bpy	CuCl/CuCl ₂	Cl _{0.41}	1240/1/(2/1)/4	75	6.5-18	5-10	..	79
			HMDETA		Cl _{0.1}	380/1/(1/0.5)/1	90	1.5	18	..	79
						710/1/(2/1)/2		2.5	21	..	79
			HMDETA		Br _{0.5} -PCL ₅₀	500/1/(1/0.5)/1	70	7	6	50	80
					Br _{0.12/0.52}	(230-680)/1/(1/0.5)/1	110	9-12	9-14	..	79
			St	Br _{0.5} -PCL ₅₀	500/1/(1/0.5)/1	110	8	7	..	80	
	BuA	acetone		PMDETA	CuCl/CuCl ₂	Br _{0.12}	410/1/(1/1)/2	70	5	25	..
			Br _{0.52}			440/1/(1/3)/2	60	8.5	15	..	79
			PMDETA	CuCl	Br _{0.12} -PSt ₂₅	720/1/1/2	60	20	5	..	79
					Cl _{0.1} -PMMA ₆₉	580/1/1/2	60	27	10	..	79
		anisole	Br _{0.5} -PCL ₈₉	750/1/1/2	70	8	10	..	80		

CA	MDEGMA	cyclopentanone	PMDETA	CuCl	Br _{0.06}	100/1/1/2	40	2.5	16	..	81
					Br _{0.01}	425/1/3/7		7	19	60.8	81
HEC	AM	DMF/THF	Me6[14]aneN4	CuBr/CuBr ₂	Br	200/1/(1/0.1)/3	30	72	40.5	..	82
	DMA	DMF/toluene				100/1/(1/0.1)/3		6	61.5	..	83

Graphical Abstract

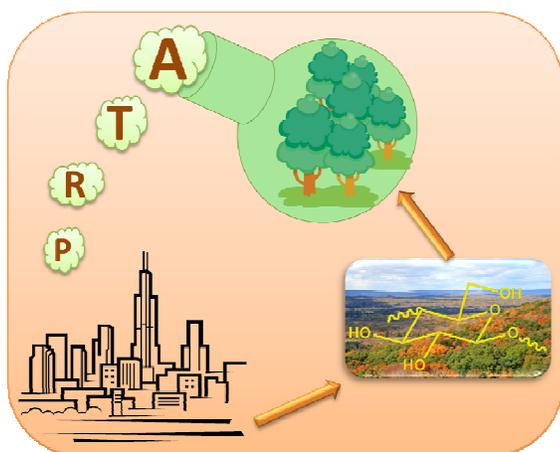

Atom transfer radical polymerisation (ATRP) is used to modify cellulose and cellulose derivatives under homogeneous conditions, yielding novel materials for application in areas such as drug delivery.

Response to Comments on CS-REV-01-2014-000053.R1

Reviewer(s)' Comments to Author:

>>> Referee: 3

>>>

>>> Comments to the Author

>>> The review has significantly improved from the previous version and I

>>> am a lot happier with the current version. I do however have some

>>> additional comments, mostly related to some of the changes the

>>> authors made. When these are addressed, I would be happy for this to

>>> be published in ChemSocRev.

>>>

>>> Introduce method for calculating DS (or explain for the non-expert

>>> reader). Also, when reporting DS it needs to be made clear when it

>>> concerns DS of the initiator, or DS after polymerization.

>>> **This has been discussed on p.2-3 and to make sure that the notion of DS is clear a paragraph was added on p. 6.**

>>> It would be good to report weight or mol ratio of grafted

>>> polymer/cellulose in the final product. How much of the final product

>>> is cellulose, how much is synthetic polymer? This is extremely

>>> important from a materials and a colloidal behaviour point of view

>>> (given that there are such examples given in the review).

>>> **One column called Graft ratio (%) has been added to the Tables (which were moved to ESI) and these report the ratio of the synthetic polymer to the cellulose.**

>>> The Tables are very informative and useful to directly compare

>>> results. I would however place them in ESI as they are a little too

>>> big for the actual article. So it is good to have them in ESI to

>>> refer to and to be used as a fast reference.

>>> **This has been done.**

>>> Page 6 : ³Cellulose fibers, membranes and nano-whiskers have all been

>>> modified under heterogeneous conditions.² This needs references.

>>> **This has been done.**

>>> Page 7: discoloration of RAFT polymers: The RAFT agent can be

>>> cleaved quite effectively after polymerization which removes the discoloration.

>>> **This has been discussed p.5 where a relevant review was cited.**

>>> Page 8: ³This has received much less attention than the alternative

>>> approach of grafting onto the surface of solid cellulosic materials

>>> (selected relevant references are cited here^{26, 27, 28, 29, 30}).²

>>> Many of these references are quite obscure and not the main works at

>>> all (quite derivative work), and most on regenerated cellulose

>>> membranes which are not the most common. I would suggest selecting

>>> more selecting high-impact work and/or some real reviews in the


>>> leading polymer/surface science journals.

>>> **References have been replaced with more significant articles.**

>



RightsLink®

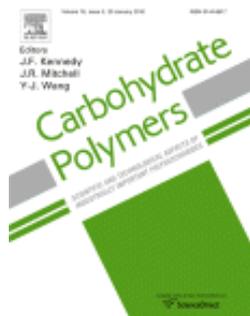[Home](#)
[Account Info](#)
[Help](#)


Title: Synthesis and characterization of Eu(III) complexes of modified cellulose and poly(*N*-isopropylacrylamide)

Author: Guihua Cui, Yanhui Li, Tiantian Shi, Zhengguo Gao, Nannan Qiu, Toshifumi Satoh, Toyoji Kakuchi, Qian Duan

Publication: Carbohydrate Polymers

Publisher: Elsevier

Date: 15 April 2013

Copyright © 2013, Elsevier

Logged in as:
Neil Cameron
Account #:
3000201095

[LOGOUT](#)

Order Completed

Thank you very much for your order.

This is a License Agreement between Neil R Cameron ("You") and Elsevier ("Elsevier"). The license consists of your order details, the terms and conditions provided by Elsevier, and the [payment terms and conditions](#).

[Get the printable license.](#)

License Number	3391921191478
License date	May 18, 2014
Licensed content publisher	Elsevier
Licensed content publication	Carbohydrate Polymers
Licensed content title	Synthesis and characterization of Eu(III) complexes of modified cellulose and poly(<i>N</i> -isopropylacrylamide)
Licensed content author	Guihua Cui, Yanhui Li, Tiantian Shi, Zhengguo Gao, Nannan Qiu, Toshifumi Satoh, Toyoji Kakuchi, Qian Duan
Licensed content date	15 April 2013
Licensed content volume number	94
Licensed content issue number	1
Number of pages	5
Type of Use	reuse in a journal/magazine
Requestor type	author of new work
Intended publisher of new work	Royal Society of Chemistry
Portion	figures/tables/illustrations
Number of figures/tables/illustrations	1
Format	both print and electronic
Are you the author of this Elsevier article?	No
Will you be translating?	No
Title of the article	The Preparation of Graft Copolymers of Cellulose and Cellulose Derivatives Using ATRP Under Homogeneous Reaction Conditions
Publication new article is in	Chemical Society Reviews
Publisher of the new article	Royal Society of Chemistry
Author of new article	Fanny Joubert, Osama M. Musa, David R. W. Hodgson, Neil R. Cameron
Expected publication date	Dec 2014
Estimated size of new article	15

Estimated size of item article (number of pages)	25
Elsevier VAT number	GB 494 6272 12
Permissions price	0.00 GBP
VAT/Local Sales Tax	0.00 GBP / 0.00 GBP
Total	0.00 GBP

[ORDER MORE...](#)[CLOSE WINDOW](#)

Copyright © 2014 [Copyright Clearance Center, Inc.](#) All Rights Reserved. [Privacy statement](#).
Comments? We would like to hear from you. E-mail us at customercare@copyright.com




RightsLink®

Home

Account
Info

Help

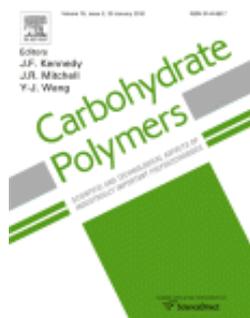

Title: Synthesis and characterization of Eu(III) complexes of modified cellulose and poly(*N*-isopropylacrylamide)

Author: Guihua Cui, Yanhui Li, Tiantian Shi, Zhengguo Gao, Nannan Qiu, Toshifumi Satoh, Toyoji Kakuchi, Qian Duan

Publication: Carbohydrate Polymers

Publisher: Elsevier

Date: 15 April 2013

Copyright © 2013, Elsevier

Logged in as:
Neil Cameron
Account #:
3000201095

LOGOUT

Order Completed

Thank you very much for your order.

This is a License Agreement between Neil R Cameron ("You") and Elsevier ("Elsevier"). The license consists of your order details, the terms and conditions provided by Elsevier, and the [payment terms and conditions](#).

[Get the printable license.](#)

License Number	3391921391178
License date	May 18, 2014
Licensed content publisher	Elsevier
Licensed content publication	Carbohydrate Polymers
Licensed content title	Synthesis and characterization of Eu(III) complexes of modified cellulose and poly(<i>N</i> -isopropylacrylamide)
Licensed content author	Guihua Cui, Yanhui Li, Tiantian Shi, Zhengguo Gao, Nannan Qiu, Toshifumi Satoh, Toyoji Kakuchi, Qian Duan
Licensed content date	15 April 2013
Licensed content volume number	94
Licensed content issue number	1
Number of pages	5
Type of Use	reuse in a journal/magazine
Requestor type	author of new work
Intended publisher of new work	Royal Society of Chemistry
Portion	figures/tables/illustrations
Number of figures/tables/illustrations	1
Format	both print and electronic
Are you the author of this Elsevier article?	No
Will you be translating?	No
Title of the article	The Preparation of Graft Copolymers of Cellulose and Cellulose Derivatives Using ATRP Under Homogeneous Reaction Conditions
Publication new article is in	Chemical Society Reviews
Publisher of the new article	Royal Society of Chemistry
Author of new article	Fanny Joubert, Osama M. Musa, David R. W. Hodgson, Neil R. Cameron
Expected publication date	Dec 2014
Estimated size of new article	15

Estimated size of item group (number of pages)	25
Elsevier VAT number	GB 494 6272 12
Permissions price	0.00 GBP
VAT/Local Sales Tax	0.00 GBP / 0.00 GBP
Total	0.00 GBP


[ORDER MORE...](#)

[CLOSE WINDOW](#)

Copyright © 2014 [Copyright Clearance Center, Inc.](#) All Rights Reserved. [Privacy statement](#).
Comments? We would like to hear from you. E-mail us at customercare@copyright.com



RightsLink®

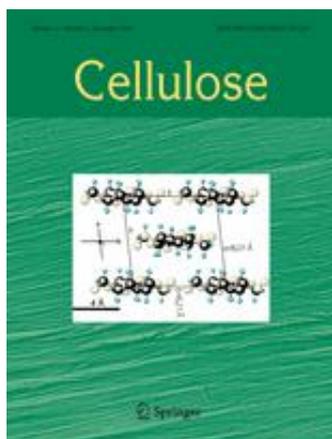[Home](#)
[Account Info](#)
[Help](#)


Title: Synthesis of graft copolymer of ethyl cellulose through living polymerization and its self-assembly

Author: Dawa Shen

Publication: Cellulose

Publisher: Springer

Date: Jan 1, 2006

Copyright © 2006, Springer

Logged in as:
Neil Cameron
Account #:
3000201095

[LOGOUT](#)

Order Completed

Thank you very much for your order.

This is a License Agreement between Neil R Cameron ("You") and Springer ("Springer"). The license consists of your order details, the terms and conditions provided by Springer, and the [payment terms and conditions](#).

[Get the printable license.](#)

License Number	3392151472780
License date	May 18, 2014
Licensed content publisher	Springer
Licensed content publication	Cellulose
Licensed content title	Synthesis of graft copolymer of ethyl cellulose through living polymerization and its self-assembly
Licensed content author	Dawa Shen
Licensed content date	Jan 1, 2006
Volume number	13
Issue number	3
Type of Use	Journal/Magazine
Requestor type	Publisher
Publisher	Royal Society of Chemistry
Portion	Figures
Format	Print and Electronic
Number of figures	1
Print run	10000
Author of this Springer article	No
Original figure numbers	figure 9
Title of new article	The Preparation of Graft Copolymers of Cellulose and Cellulose Derivatives Using ATRP Under Homogeneous Reaction Conditions
Publication the new article is in	Chemical Society Reviews
Publisher of new article	Royal Society of Chemistry
Author of new article	Fanny Joubert, Osama M. Musa, David R. W. Hodgson, Neil R. Cameron
Expected publication date of new article	Dec 2014
Estimated size of new	15


Estimated size of item	0.00
article (pages)	
Total	0.00 GBP

CLOSE WINDOW

Copyright © 2014 [Copyright Clearance Center, Inc.](#) All Rights Reserved. [Privacy statement.](#)
Comments? We would like to hear from you. E-mail us at customercare@copyright.com



RightsLink®

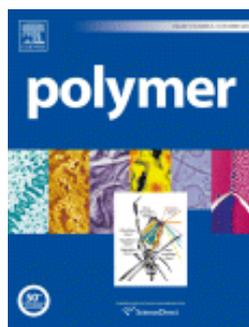[Home](#)
[Account Info](#)
[Help](#)


Title: Coil-to-rod conformational transition and single chain structure of graft copolymer by tuning the graft density

Author: Wenyong Liu, Yuejun Liu, Guangsheng Zeng, Ruigang Liu, Yong Huang

Publication: Polymer

Publisher: Elsevier

Date: 17 February 2012

Copyright © 2012, Elsevier

Logged in as:
Neil Cameron
Account #:
3000201095

[LOGOUT](#)

Order Completed

Thank you very much for your order.

This is a License Agreement between Neil R Cameron ("You") and Elsevier ("Elsevier"). The license consists of your order details, the terms and conditions provided by Elsevier, and the [payment terms and conditions](#).

[Get the printable license.](#)

License Number	3391930667487
License date	May 18, 2014
Licensed content publisher	Elsevier
Licensed content publication	Polymer
Licensed content title	Coil-to-rod conformational transition and single chain structure of graft copolymer by tuning the graft density
Licensed content author	Wenyong Liu, Yuejun Liu, Guangsheng Zeng, Ruigang Liu, Yong Huang
Licensed content date	17 February 2012
Licensed content volume number	53
Licensed content issue number	4
Number of pages	10
Type of Use	reuse in a journal/magazine
Requestor type	author of new work
Intended publisher of new work	Royal Society of Chemistry
Portion	figures/tables/illustrations
Number of figures/tables/illustrations	1
Format	both print and electronic
Are you the author of this Elsevier article?	No
Will you be translating?	No
Title of the article	The Preparation of Graft Copolymers of Cellulose and Cellulose Derivatives Using ATRP Under Homogeneous Reaction Conditions
Publication new article is in	Chemical Society Reviews
Publisher of the new article	Royal Society of Chemistry
Author of new article	Fanny Joubert, Osama M. Musa, David R. W. Hodgson, Neil R. Cameron
Expected publication date	Dec 2014
Estimated size of new article (number of pages)	15
Elsevier VAT number	GR 494 6777 17

Permissions price	0.00 GBP
VAT/Local Sales Tax	0.00 GBP / 0.00 GBP
Total	0.00 GBP

[ORDER MORE...](#)

[CLOSE WINDOW](#)

Copyright © 2014 [Copyright Clearance Center, Inc.](#) All Rights Reserved. [Privacy statement.](#)
Comments? We would like to hear from you. E-mail us at customercare@copyright.com




RightsLink®

Home

Account
Info

Help

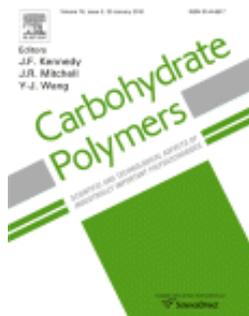

Title: Synthesis, self-assembly and drug release behaviors of pH-responsive copolymers ethyl cellulose-*graft*-PDEAEMA through ATRP

Author: Deqian Wang, Junjun Tan, Hongliang Kang, Lin Ma, Xin Jin, Ruigang Liu, Yong Huang

Publication: Carbohydrate Polymers

Publisher: Elsevier

Date: 11 February 2011

Copyright © 2011, Elsevier

Logged in as:
Neil Cameron
Account #:
3000201095

LOGOUT

Order Completed

Thank you very much for your order.

This is a License Agreement between Neil R Cameron ("You") and Elsevier ("Elsevier"). The license consists of your order details, the terms and conditions provided by Elsevier, and the [payment terms and conditions](#).

[Get the printable license.](#)

License Number	3392120001931
License date	May 18, 2014
Licensed content publisher	Elsevier
Licensed content publication	Carbohydrate Polymers
Licensed content title	Synthesis, self-assembly and drug release behaviors of pH-responsive copolymers ethyl cellulose- <i>graft</i> -PDEAEMA through ATRP
Licensed content author	Deqian Wang, Junjun Tan, Hongliang Kang, Lin Ma, Xin Jin, Ruigang Liu, Yong Huang
Licensed content date	11 February 2011
Licensed content volume number	84
Licensed content issue number	1
Number of pages	8
Type of Use	reuse in a journal/magazine
Requestor type	author of new work
Intended publisher of new work	Royal Society of Chemistry
Portion	figures/tables/illustrations
Number of figures/tables/illustrations	1
Format	both print and electronic
Are you the author of this Elsevier article?	No
Will you be translating?	No
Title of the article	The Preparation of Graft Copolymers of Cellulose and Cellulose Derivatives Using ATRP Under Homogeneous Reaction Conditions
Publication new article is in	Chemical Society Reviews
Publisher of the new article	Royal Society of Chemistry
Author of new article	Fanny Joubert, Osama M. Musa, David R. W. Hodgson, Neil R. Cameron
Expected publication date	Dec 2014
Estimated size of new article	15

(number of pages)	
Elsevier VAT number	GB 494 6272 12
Permissions price	0.00 GBP
VAT/Local Sales Tax	0.00 GBP / 0.00 GBP
Total	0.00 GBP

[ORDER MORE...](#)[CLOSE WINDOW](#)

Copyright © 2014 [Copyright Clearance Center, Inc.](#) All Rights Reserved. [Privacy statement.](#)
Comments? We would like to hear from you. E-mail us at customercare@copyright.com



RightsLink®

Home

Account
Info

Help



Title: Comb-Shaped Conjugates
Comprising Hydroxypropyl
Cellulose Backbones and Low-
Molecular-Weight Poly(N-
isopropylacryamide) Side Chains
for Smart Hydrogels: Synthesis,
Characterization, and Biomedical
Applications

Logged in as:
Neil Cameron
Account #:
3000201095

LOGOUT

Author: F. J. Xu, Y. Zhu, F. S. Liu, J. Nie,
J. Ma, and W. T. Yang

Publication: Bioconjugate Chemistry

Publisher: American Chemical Society

Date: Mar 1, 2010

Copyright © 2010, American Chemical Society

PERMISSION/LICENSE IS GRANTED FOR YOUR ORDER AT NO CHARGE

This type of permission/license, instead of the standard Terms & Conditions, is sent to you because no fee is being charged for your order. Please note the following:

- Permission is granted for your request in both print and electronic formats, and translations.
- If figures and/or tables were requested, they may be adapted or used in part.
- Please print this page for your records and send a copy of it to your publisher/graduate school.
- Appropriate credit for the requested material should be given as follows: "Reprinted (adapted) with permission from (COMPLETE REFERENCE CITATION). Copyright (YEAR) American Chemical Society." Insert appropriate information in place of the capitalized words.
- One-time permission is granted only for the use specified in your request. No additional uses are granted (such as derivative works or other editions). For any other uses, please submit a new request.

If credit is given to another source for the material you requested, permission must be obtained from that source.

BACK

CLOSE WINDOW

Copyright © 2014 [Copyright Clearance Center, Inc.](#) All Rights Reserved. [Privacy statement.](#)
Comments? We would like to hear from you. E-mail us at customercare@copyright.com

