



Contents lists available at [ScienceDirect](#)

Japanese Dental Science Review

journal homepage: www.elsevier.com/locate/jdsr



Review Article

Ultrastructural and biochemical aspects of matrix vesicle-mediated mineralization

Tomoka Hasegawa (DDS, Ph.D)^{a,*}, Tomomaya Yamamoto^a,
Erika Tsuchiya^{a,b}, Hiromi Hongo^a, Kanako Tsuboi^{a,b}, Ai Kudo^a,
Miki Abe^a, Taiji Yoshida^a, Tomoya Nagai^{a,c}, Naznin Khadiza^{a,d},
Ayako Yokoyama^{a,e}, Kimimitsu Oda^f, Hidehiro Ozawa^g,
Paulo Henrique Luiz de Freitas^h, Minqi Liⁱ, Norio Amizuka^a

^a Department of Developmental Biology of Hard Tissue, Graduate School of Dental Medicine, Hokkaido University, Sapporo, Japan

^b Department of Oral Diagnosis and Medicine, Graduate School of Dental Medicine, Hokkaido University, Sapporo, Japan

^c Department of Oral Functional Prothodontics, Graduate School of Dental Medicine, Hokkaido University, Sapporo, Japan

^d Department of Dentistry for Children and Disabled Person, Graduate School of Dental Medicine, Hokkaido University, Sapporo, Japan

^e Department of Gerodontology, Graduate School of Dental Medicine, Hokkaido University, Sapporo, Japan

^f Division of Biochemistry, Graduate School of Medical and Dental Sciences, Niigata University, Niigata, Japan

^g Institute for Oral Science, Graduate School of Oral Medicine, Matsumoto Dental University, Shiojiri, Japan,

^h Department of Dentistry, Federal University of Sergipe at Lagarto, Brazil

ⁱ Division of Basic Science of Stomatology, The School of Stomatology, Shandong University, Jinan, China

Received 10 June 2016; received in revised form 14 September 2016; accepted 21 September 2016

KEYWORDS

Matrix vesicle;
Mineralization;
TNAP;
ENPP1;
Mineralized nodule

Summary Matrix vesicle-mediated mineralization is an orchestrated sequence of ultrastructural and biochemical events that lead to crystal nucleation and growth. The influx of phosphate ions into the matrix vesicle is mediated by several proteins such as TNAP, ENPP1, Pit1, annexin and so forth. The catalytic activity of ENPP1 generates pyrophosphate (PPi) using extracellular ATPs as a substrate, and the resultant PPi prevents crystal overgrowth. However, TNAP hydrolyzes PPi into phosphate ion monomers, which are then transported into the matrix

* Corresponding author at: Department of Developmental Biology of Hard Tissue, Graduate School of Dental Medicine, Hokkaido University, Kita 13, Nishi 7, Kita-Ku, Sapporo, Hokkaido 060-8586, Japan. Fax: +81 11 706 4226.
E-mail address: hasegawa@den.hokudai.ac.jp (T. Hasegawa).

<http://dx.doi.org/10.1016/j.jdsr.2016.09.002>

1882-7616/© 2016 The Author(s). Published by Elsevier Ltd on behalf of Japanese Association for Dental Science. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

Please cite this article in press as: Hasegawa T, et al. Ultrastructural and biochemical aspects of matrix vesicle-mediated mineralization. Japanese Dental Science Review (2016), <http://dx.doi.org/10.1016/j.jdsr.2016.09.002>

vesicle through Pit1. Accumulation of Ca^{2+} and PO_4^{3-} inside matrix vesicles then induces crystalline nucleation, with calcium phosphate crystals budding off radially, puncturing the matrix vesicle's membrane and finally growing out of it to form mineralized nodules.

© 2016 The Author(s). Published by Elsevier Ltd on behalf of Japanese Association for Dental Science. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

Contents

1. Introduction.....	00
2. Ultrastructural aspects of matrix vesicle-mediated mineralization in bone	00
2.1. Ultrastructural properties of the matrix vesicles under electron microscopy.....	00
2.2. Mineralized nodules developed from matrix vesicles.....	00
3. Enzymes and membrane transporter are necessary for matrix vesicle-mediated mineralization in bone	00
3.1. Biological function of tissue nonspecific alkaline phosphatase (TNAP) in matrix vesicle-mediated mineralization ...	00
3.2. Biological action of ecto-nucleotide pyrophosphatase/phosphodiesterase 1, ENPP 1 in bone mineralization	00
3.3. Putative function of ankylosis protein (ANK) in pyrophosphate transport in cells.....	00
3.4. Ca^{2+} transport through annexins.....	00
4. Ultrastructure of collagen mineralization.....	00
5. Concluding remarks.....	00
Conflict of interest	00
Acknowledgments	00
References	00

1. Introduction

Bone is a living mineralized tissue composed of calcium phosphates and a variety of organic materials, with collagen being the most abundant. Bone mineralization has two phases: primary and secondary. Primary mineralization is orchestrated by osteoblasts; osteoblasts secrete a large amount of collagen fibrils, non-collagenous proteins, and matrix vesicles, which are extracellular vesicles that trigger mineralization *via* membrane transporters and enzymes. The degree of the primary mineralization is controlled by fine-tuning bone formation and mineral apposition rates. In contrast, secondary mineralization is a phenomenon whereby there is a gain in bone mineral density after primary mineralization. It is hypothesized that secondary mineralization is regulated physicochemically, *i.e.*, through crystal maturation, and by the osteocytic network inside the mineralized bone matrix. Still, the mechanisms behind secondary mineralization are relatively untapped.

In bone, primary mineralization can be divided into two phases: first, matrix vesicle-mediated mineralization, and second, collagen mineralization. During the process of the matrix vesicle-mediated mineralization, osteoblasts regulate vesicle synthesis as well as the activity of membrane transporters and enzymes with which matrix vesicles are equipped. Discovery of matrix vesicles was a breakthrough in the field of bone mineralization [1–7]. Long before that, it was proposed that alkaline phosphatase may supply phosphates by hydrolyzing phosphate substrates and then help forming crystalline calcium phosphates [8]. However, this theory is based on the physicochemical regulation of bone mineralization. In contrast, the theory behind matrix vesicle-mediated mineralization sustains that the processes are mainly under the control of osteoblasts through the regulation of membrane transporters/enzymes and surrounding extracellular organic materials. Knowledge

of the ultrastructure and biological activities of membrane transporters/enzymes may clarify the cellular mechanisms of matrix vesicle-mediated mineralization and explain, for instance, why mineral appositional rate is higher in regions of accelerated bone turnover.

In this review, we will present the ultrastructural and biochemical aspects of matrix vesicle-mediated mineralization in bone.

2. Ultrastructural aspects of matrix vesicle-mediated mineralization in bone

Matrix vesicles are extracellular vesicles enveloped by a plasma membrane (ranging 30–1000 nm in diameter) secreted by osteoblasts [2] (Fig. 1). Matrix vesicles bear several membrane transporters and enzymes on their membranes and in their interior, providing a nurturing microenvironment for calcium phosphate nucleation and subsequent crystal growth. Mineralization begins when a crystalline calcium phosphate, *i.e.*, hydroxyapatite [$\text{Ca}_{10}(\text{PO}_4)_6(\text{OH})_2$], appears inside the matrix vesicles, growing and eventually breaking through the vesicle's membrane to form mineralized nodules—also known as calcifying globules (Figs. 1 & 2). Under transmission electron microscopy (TEM), each hydroxyapatite crystal has a small, ribbon-like structure profile approximately 25 nm wide, 10 nm high and 50 nm long [9,10].

2.1. Ultrastructural properties of the matrix vesicles under electron microscopy

Some of these incipient mineral crystals were initially found associated with the inner leaflet of the matrix vesicle membranes, and it seems plausible that crystal nucleation would begin at that specific site. Matrix vesicle membranes are

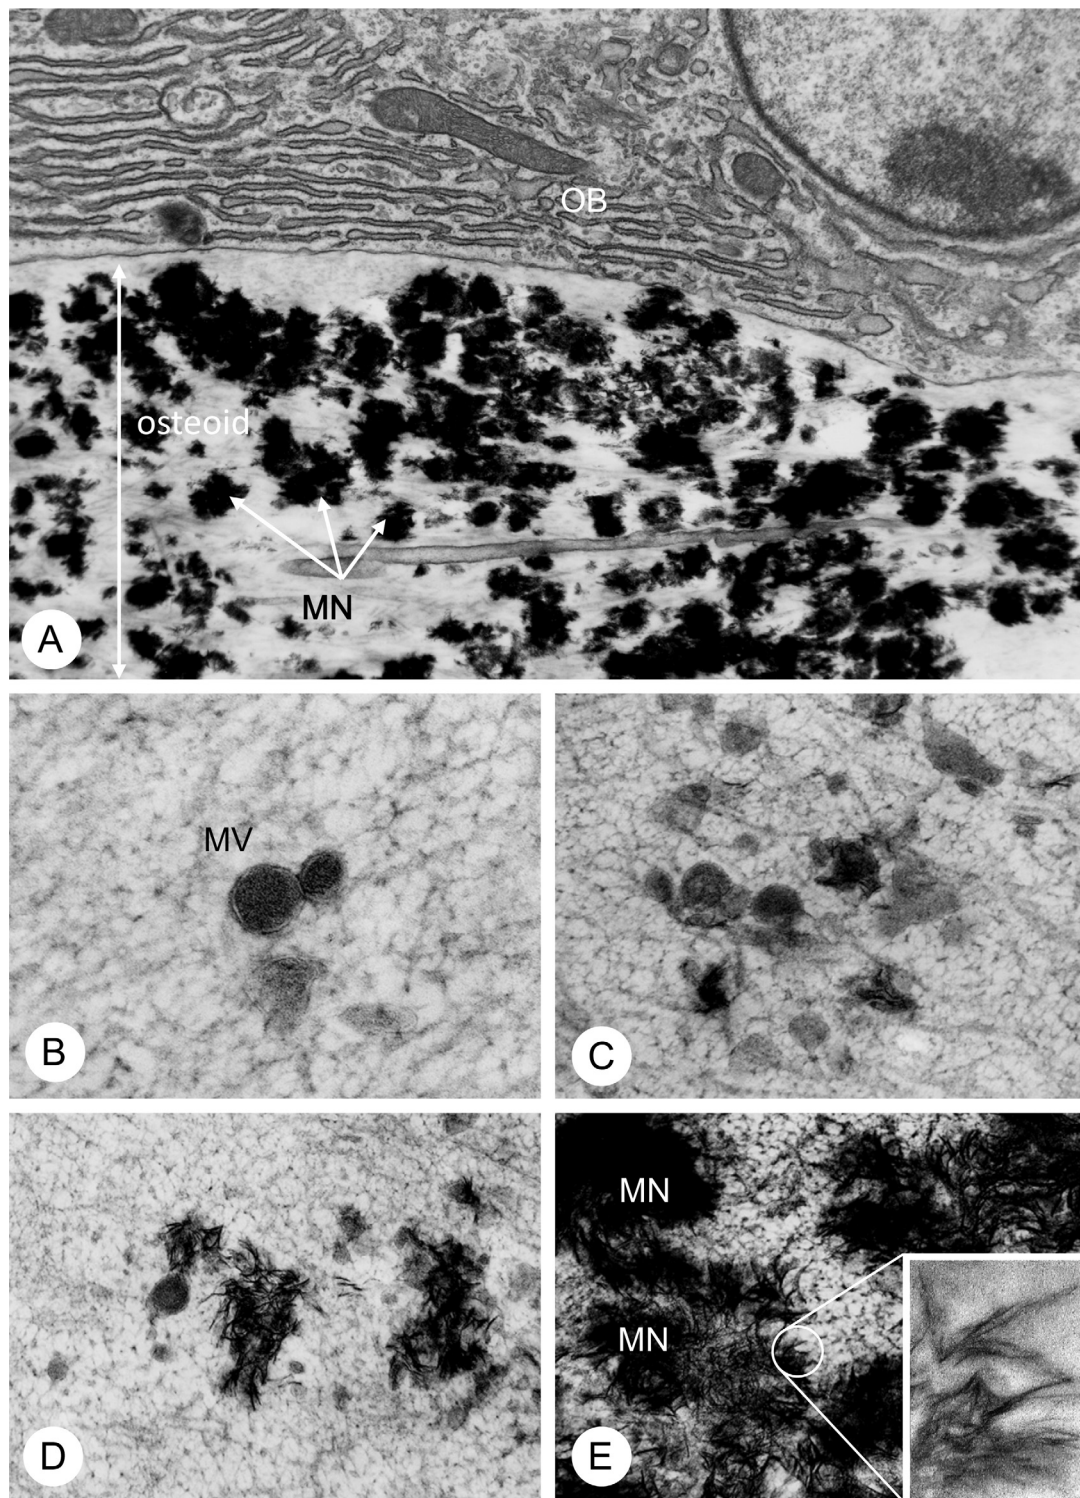


Figure 1 TEM observation of matrix vesicles and mineralized nodules in osteoid.

(A) TEM image of ultrastucture of osteoid underlying mature osteoblasts (OB). Notice many mineralized globular structures referred to as mineralized nodule (MN) in the osteoid. (B–E) TEM images of matrix vesicles (MV) (B), appearance of mineral crystals in the matrix vesicles (C), exposure of mineral crystals out of the matrix vesicles (D) and mineralized nodule (MN) formation (E). An inset demonstrate a highly-magnified image of needle-shape of mineral crystals.

Panel A is derived from Ref. [71] (Amizuka and Ozawa), while panels B–F are modified from Ref. [72] (Amizuka et al.).

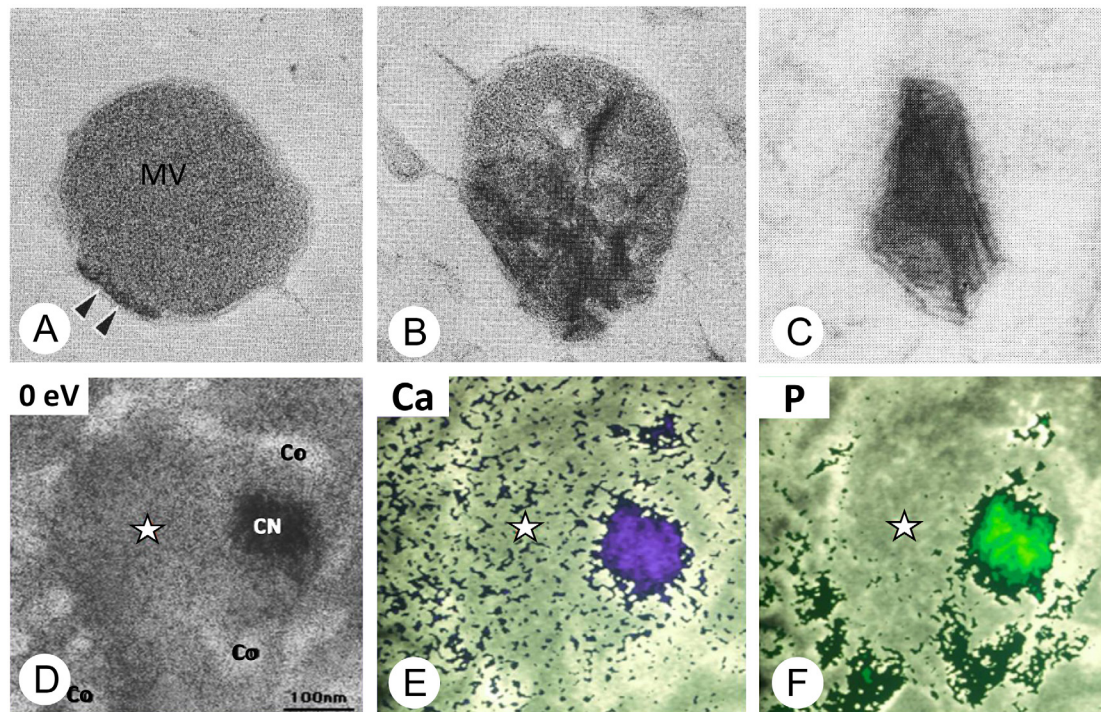


Figure 2 Highly-magnified images of matrix vesicles and elemental mapping of calcium and phosphate ions. (A–C) TEM images of matrix vesicles (MV). (A) amorphous electron-dense structure (double arrows, black) are shown to be associated with plasma membrane of the matrix vesicle. (B) The grown mineral crystals (black structures) are seen inside the matrix vesicles. (C) Mineral crystals are getting out of the matrix vesicles. (D–F) TEM image (D) and elemental mapping of calcium (Ca, panel E) and phosphorus (P, panel F) assessed by electron energy loss spectroscopy. Note that calcium (Ca) was evenly distributed in the peripheral region of matrix vesicles, while phosphorus (P) is predominant in collagen fibrils. The images of A–C are modified from Ref. [73] (Ozawa et al.), and D–F are from Ref. [17] (Hoshi et al.).

rich in acidic phospholipids such as phosphatidylserine and phosphatidylinositol, which have high affinity for Ca^{2+} . The affinity of phosphatidylserine for Ca^{2+} is particularly high and can produce a stable calcium phosphate–phospholipid complex associated with the inner leaflet of the vesicle’s membrane [7] (Fig. 2A). The possibility that such complexes may play an important role in crystal nucleation has been pointed out before [11,12]. However, the early phases of calcium phosphate nucleation inside the matrix vesicles may be rather amorphous [13], but gradually become crystalline (hydroxyapatite) in later stages. Calcium phosphate crystals formed inside matrix vesicles can grow through the addition of Ca^{2+} and PO_4^{3-} , which enter the vesicles through the action of membrane transporters and enzymes. Inside the matrix vesicle, “needle-shaped” crystalline calcium phosphates form a stellate assembly, bud off radially from the vesicle’s interior, and then, rip through the plasma membrane to form mineralized nodules, also referred to as calcifying globules [6] (Figs. 1E and 2D). While the needle-shaped crystals are identified as crystalline structures by electron diffraction, freeze-substitution and cytochemical calcium detection methods such as κ -pyroantimonate combined with energy-dispersive X-ray spectroscopy may show them as non-crystalline structures containing calcium and phosphate [14–16].

According to observations of the osteoid in bone derived from the quick frozen-freeze substitution technique with electron energy loss spectroscopy, which enables elemen-

tal mapping at the molecular level, calcium was evenly distributed in the proteoglycan-rich, peripheral region of matrix vesicles, whereas phosphate was detected predominantly in collagen fibrils [17] (Fig. 2D–F). Therefore, it seems feasible that, in non-calcified sites, the extracellular meshwork of organic substances limits the production of hydroxyapatite and inhibits precipitation of calcified crystals by controlling the spatial distribution of Ca^{2+} and PO_4^{3-} , even if the extracellular fluid is supersaturated with those ions. In addition, a biological mechanism of PO_4^{3-} supplementation and subsequent transport into matrix vesicles must be in place, since PO_4^{3-} is not abundant in the periphery of matrix vesicles. Later in the text, we will discuss about the biological actions of membrane transporters and enzymes to produce PO_4^{3-} and to warrant the influx of Ca^{2+} and PO_4^{3-} into the matrix vesicles.

2.2. Mineralized nodules developed from matrix vesicles

Matrix vesicles and developing mineralized nodules can be observed in the osteoid below mature osteoblasts (Fig. 1A). It seems that the osteoid provides an adequate microenvironment for the development of mineralized nodules in bone. Even though the vesicle’s membrane is ripped during the process of crystal growth, the mineralized nodules might

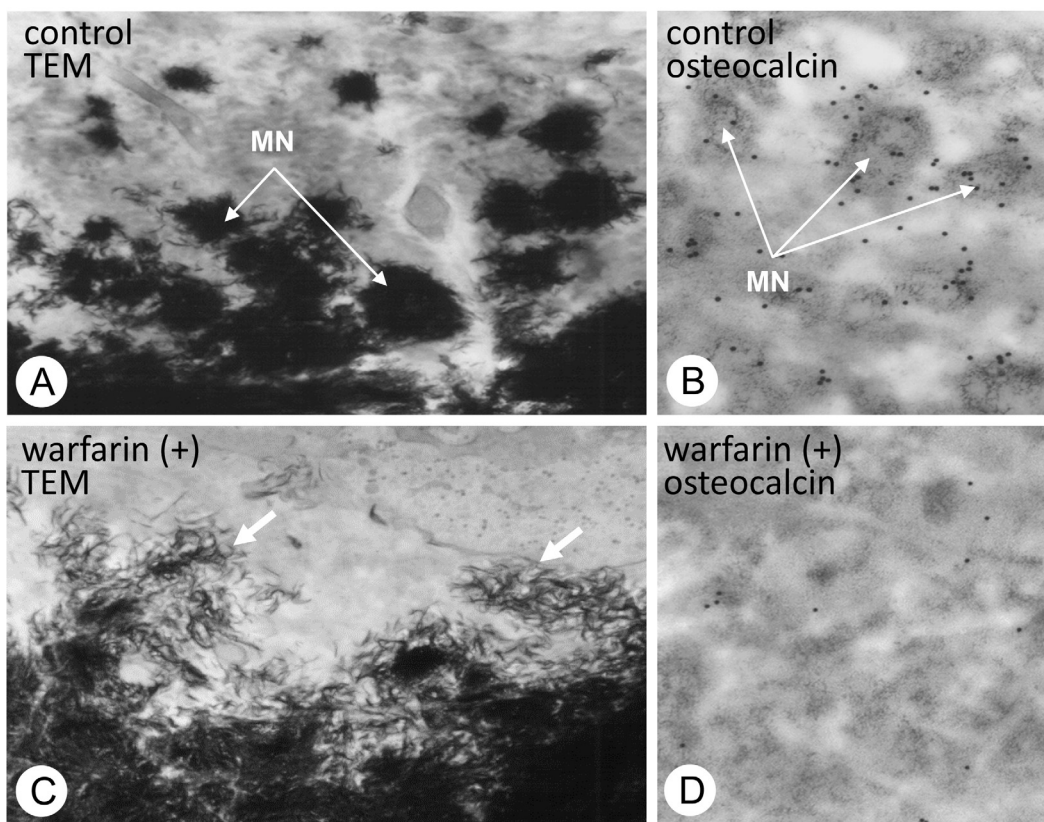


Figure 3 TEM observation on mineralized nodules of normal rats and warfarin-treated rats.

Panels A and C demonstrate the ultrastructure of mineralized nodules in the osteoid of normal and warfarin-administered rat bones. In control group, globular mineralized nodules (MN) are shown to be composed of many needle-shaped mineral crystals (A). However, the warfarin-administered osteoid shows dispersed mineral crystals throughout the osteoid (C). (B and D) Immunoelectron microscopy for osteocalcin localization. Osteocalcin immunoreactivity (black particles) can be seen on the mineralized nodules (MN, grey colored globular structures) of the control osteoid (B), while little immunoreactivity for osteocalcin is seen in the warfarin-administered osteoid (D).

The images are derived from Ref. [29] (Amizuka et al.).

retain the membrane-associated enzymes and transporters, which will be mentioned later in this text.

Mineralized nodule is a globular assembly of numerous needle-shaped mineral crystals that has been exposed to extracellular environment (Fig. 1E). It seems likely that the growth of mineralized nodules is regulated by a large number of extracellular organic materials in the osteoid. Among them, osteopontin is especially suited to the task of regulating mineralization, because it effectively inhibits apatite formation and growth [18,19]. Osteopontin is localized in the periphery of mineralized nodules, where it might act as a blocker of excessive mineralization [20]. Since other organic materials can combine with osteopontin [21], they can form the so-called “crystal ghosts” [22–24]. Among these materials, osteocalcin is known for containing γ -carboxyglutamic acid and for their ability to bind to mineral crystals [25–27]. Warfarin, which is an inhibitor for γ -carboxylation of glutamine residues, induces an embryopathy consisting of nasal hypoplasia, stippled epiphyses and distal extremity hypoplasia when given to women in the first trimester of pregnancy [25,28]. In our observations, the administration of warfarin resulted in the dispersion of numerous fragments of needle-shaped crystal minerals throughout the osteoid [29] (Fig. 3).

Recently, γ -carboxylase-deficient mice revealed the same abnormality with disassembled, scattered crystal minerals in bone [30]. Therefore, osteocalcin may play an important role in the globular assembly of needle-shaped mineral crystals, probably binding the organic components of the crystal sheath together.

3. Enzymes and membrane transporter are necessary for matrix vesicle-mediated mineralization in bone

Several enzymes and proteins found in the matrix vesicles are involved in the metabolism of proteoglycans and pyrophosphate. Among these enzymes and membrane transporters, tissue nonspecific alkaline phosphatase (TNAP), ecto-nucleotide pyrophosphatase/phosphodiesterase 1 (ENPP1), and others, e.g., annexin and ankylin protein (ANK) and sodium/phosphate co-transporter type III (Pit1) appear to play a pivotal role in matrix vesicle-mediated mineralization.

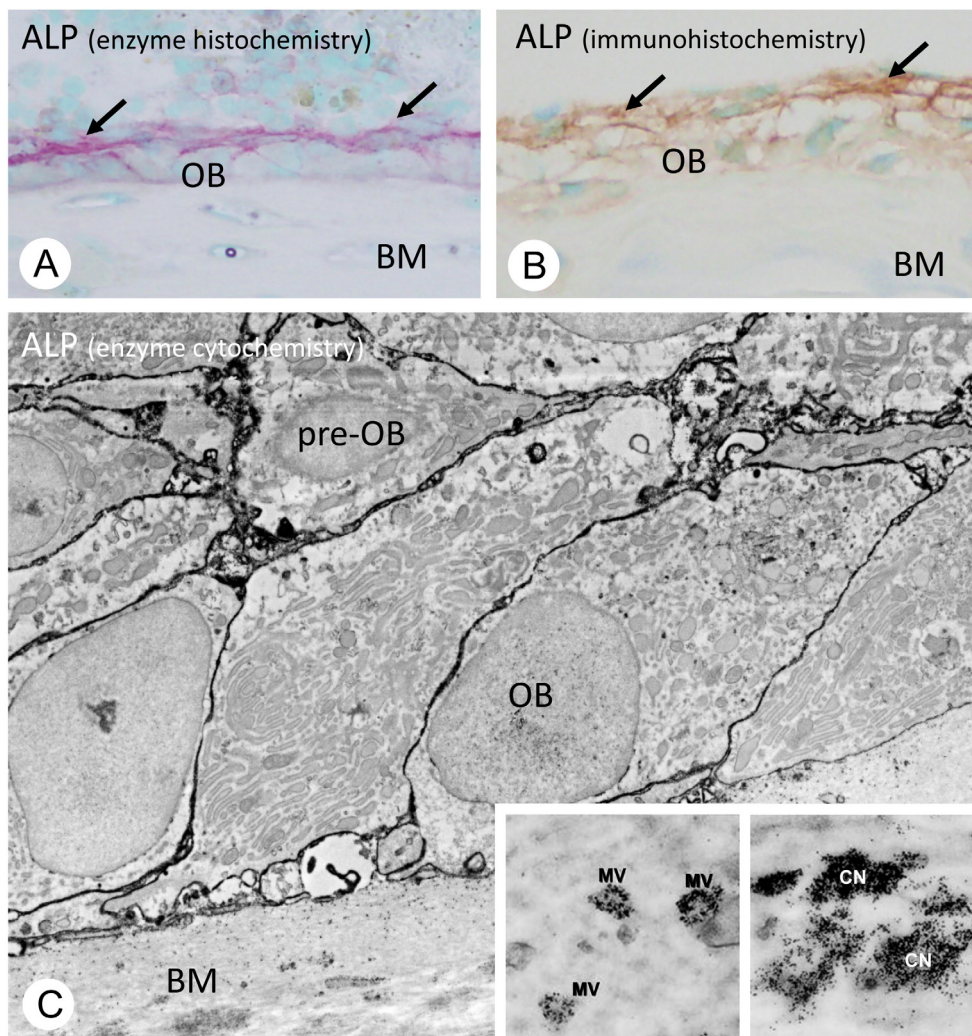


Figure 4 Histochemical localization of alkaline phosphatase in bone. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

(A and B) Enzyme histochemistry of alkaline phosphatase (ALPase, red color) and tissue nonspecific ALPase (TNAP, brown color) immunohistochemistry. Both histochemical technique consistently reveal an intense enzymatic activity of ALPase and immunoreactivity of TNAP in the regions of preosteoblasts (arrows, in A and B), rather than mature osteoblast (OB) located on bone matrix (BM). (C) TEM image of ALPase enzyme cytochemistry. Note the ALPase activity (black) can be seen on cell membranes of preosteoblasts (pre-OB) and mature osteoblasts (OB) on the bone surfaces. Insets demonstrate the ALPase enzyme activity on matrix vesicle (MV) and mineralized nodule referred to as calcified nodules (black, CN).

Panels A and B are derived from Ref. [72] (Amizuka et al.), while panel C is from Ref. [71] (Amizuka and Ozawa).

3.1. Biological function of tissue nonspecific alkaline phosphatase (TNAP) in matrix vesicle-mediated mineralization

One of the most important enzymes to initiate mineralization in bone is TNAP, a glycosylphosphatidylinositol anchor enzyme associated with cell membranes (Fig. 4). TNAP can hydrolyze various phosphate esters, especially pyrophosphate (PPi), and is responsible for the production of inorganic phosphate, *i.e.*, TNAP serve as pyrophosphatase to generate PO_4^{3-} monomer. The resultant PO_4^{3-} is transported into the matrix vesicles by means of sodium/phosphate cotransporter type III (Pit1). Therefore, many believe TNAP is a potent inducer of mineralization.

In bone, TNAP activity has been detected on osteoblasts and matrix vesicles [31,32]. Interestingly, the distribution of TNAP on the cell membrane is not uniform in osteoblasts, which reflect the cell polarity with distinct basolateral and secretory (osteoidal) domains (Fig. 4). It has been reported that the plasma membrane Ca^{2+} transport ATPase was restricted to the osteoidal domain of the osteoblastic cell membrane, while TNAP was predominantly present on the basolateral domain [33]. Consistently, using specific antiserum to TNAP [34], we could observe relatively intense immunoreactivity and enzymatic activity for TNAP on preosteoblasts and on the basolateral aspect of mature osteoblasts' membranes [35]. Thus, in bone, the membranes featuring intense activity of TNAP are not identical to those that serve as sites for matrix vesicle formation, for matrix

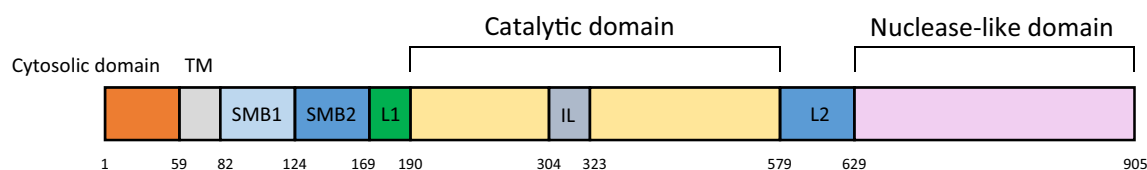


Figure 5 Domain organization of mouse ENPP1.

Modified from Ref. [44] (Kato et al.).

vesicles derive from the secretory (osteoidal) cell membrane of osteoblasts—which show weak TNAP enzymatic activity. While the actual reason for that difference is still a matter of debate, it could be that high levels of TNAP activity in the matrix vesicles would induce mineral crystals overgrowth within the osteoid.

Mice homozygous for *Tnap* gene depletion have been generated [36,37] and mimic severe hypophosphatasia, indicating that TNAP is likely involved in mineralization. While TNAP might act as a pyrophosphatase [38], other pyrophosphatases may exist. *Tnap*^{-/-} mice are born with intact bones, but gradually develop growth retardation and other skeletal deformities. Although the absence of endogenous TNAP activity did not result in complete lack of mineral uptake in skeletal tissues [37], *Tnap*^{-/-} mice revealed a severe disturbance of the growth plate, suggesting abnormal endochondral ossification [39]. It was shown that depletion of *Tnap* gene results not only in hypomineralization of the skeleton, but also in a severe disorder of mineral crystal alignment in growing long bones with a disordered bone matrix architecture [40]. Murshed et al. have reported that transgenic mice expressing *Tnap* in the dermis showed extracellular mineralization consisting of hydroxyapatite crystals [41]. Given the evidence, it seems that TNAP activity is essential for mineralization in bone, but it is still unknown why the cell membranes with intense TNAP activity in bone are not identical to those forming matrix vesicles.

Recently, basic research on TNAP provided a promising tool for clinicians. The FDA approved asfotase alfa (Strensiq) in 2015 for the treatment of hypophosphatasia caused by a rare hereditary mutation in the alkaline phosphatase gene. Patients with either perinatal or infant onset of the disease who were treated with asfotase alfa showed improvement in overall survival: 97% patients receiving the drug were alive at age 1 year compared with 42% of control patients selected from a natural history study group. Patients with juvenile-onset hypophosphatasia also experienced improved growth and bone health compared with patients in a natural history database [42,43].

3.2. Biological action of ecto-nucleotide pyrophosphatase/phosphodiesterase 1, ENPP 1 in bone mineralization

ENPP 1 is a member of the ENPP family of proteins, which are conserved in vertebrates and hydrolyze pyrophosphate or phosphodiester bonds in various extracellular compounds such as nucleotides and phospholipids. ENPP1 is composed of two N-terminal somatomedin B-like domains (SMB1 and SMB2), a catalytic domain and nuclease-like domain (Fig. 5). ENPP1 participates in different biological processes through distinct sets of domains: the catalytic and nuclease-like

domains act in bone mineralization, while the SMB-like domains for insulin signaling. The crystalline structure analysis of ENPP1 suggests that the nucleotides are able to be accommodated in a pocket formed by an insertion loop in the catalytic domain, explaining why ATPs are ENPP1's preferred substrate [44].

In bone mineralization, ENPP1's catalytic activity generates Ppi – presumably using extracellular ATPs – and the resultant Ppi inhibits mineralization by binding to incipient hydroxyapatite crystals and preventing their overgrowth [45–47] (Fig. 6). In our observations, ENPP1 immunoreactivity was seen throughout the cytoplasm and on the secretory (osteoidal) pole of mature osteoblasts, as well as in osteocytes (*data not shown*). The localization of ENPP1 predominantly on the osteoidal surface of osteoblasts may suggest that it inhibits the overgrowth of mineral crystals. The histological evidence that TNAP is not intensely localized on the osteoidal surface appears to be consistent with the distribution of ENPP1 on osteoblasts.

Severe ENPP1 deficiency was recently shown to be related to a syndrome of spontaneous infantile arterial and periarticular mineralization [48,49]. They suggested that the Ppi generated by ENPP1 activity in vascular smooth muscle cells and chondrocytes disrupts the growth of hydroxyapatite crystals. In addition, the linkage of genetic ENPP1 dysfunction to infantile arterial mineralization suggests abnormal Ppi metabolism seems to be an important regulatory factor or inducer of osteoblastic differentiation in vascular smooth muscle cell.

Mice with *Enpp1* gene depletion (*Enpp1*^{-/-} mice), also known as tiptoe walking (*ttw/ttw*) mice, develop progressive ankylosing intervertebral and peripheral joint hyperostosis and articular cartilage mineralization [50–54]. Mackenzie et al. [54] have recently reported on the details of the skeletal deformities seen in *Enpp1*^{-/-} mice: mineralization in arteries and in the kidney, ectopic formation of cartilage in the joints and spine, despite the reduced circulating calcium and phosphate levels. Also, there was hypermineralization of the talocrural joint and hypomineralization of the femur and tibia with reduced trabecular number, trabecular bone volume and trabecular/cortical thickness. Consistent with the marked increase in fibroblast growth factor (FGF) 23 mRNA, circulating FGF23 was significantly elevated in *Enpp1*^{-/-} mice [54].

3.3. Putative function of ankylosis protein (ANK) in pyrophosphate transport in cells

ENPP1 can be found not only on the cell surface but also in cytoplasmic regions, generating Ppi in the both regions of the cell (Fig. 6). Ankylosis protein, ANK, which is encoded by the mouse progressive ankylosis (*Ank*) gene, appears to

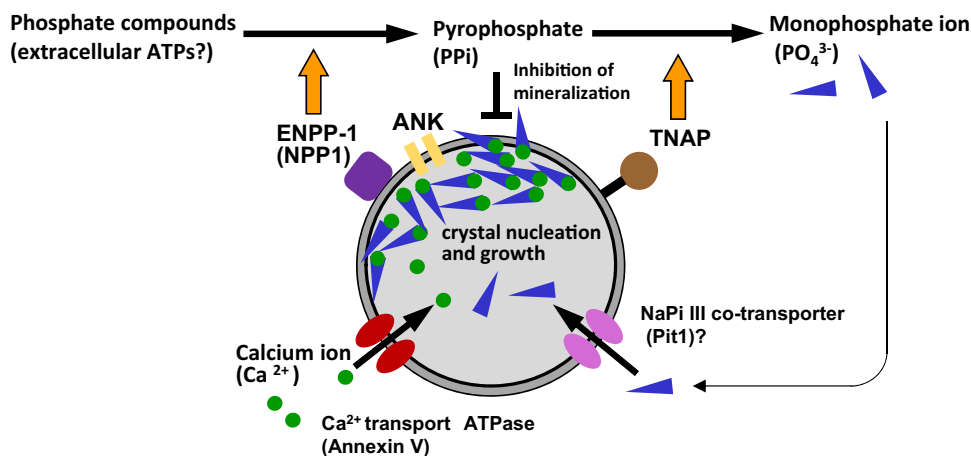


Figure 6 Schematic design of matrix vesicle-mediated mineralization.

Matrix vesicles provide adequate micro-circumstance for initiation of mineralization. Membrane transporters and enzymes including TNAP, ENPP1, annexins, ANK and Pit1 equipped on matrix vesicles play a pivotal role in Ca^{2+} and PO_4^{3-} transport into the vesicles. Phosphatidylserine and so forth in the plasma membrane has a high affinity to produce a stable calcium phosphate–phospholipid complex associated with the inner leaflet of the vesicle’s membrane. Thereafter, amorphous calcium phosphates develop hydroxyapatite to form needle-shaped mineral crystals. Many mineral crystals penetrate the vesicles’ membranes to form a globular assembly of numerous mineral crystals, *i.e.*, mineralized nodules.

function as a multiple-pass, transmembrane PPI-channelling protein, allowing PPI molecules to pass through the plasma membrane from the cytoplasm to the outside of the cell [55,56]. In mice, *Ank* mRNA is expressed in several tissues including the heart, brain, liver, spleen, lung, muscle and kidney, as well as in bone and cartilage such as the articular cartilage in the shoulder, elbow, wrist and digits. Since PPI and its derivatives are naturally potent mineralization inhibitors both *in vivo* and *in vitro*, ANK-mediated regulation of PPI levels provides a room for inhibition of excessive mineralization in several tissues [55]. Considering that infants carrying *Ank* mutations display a three- to five-fold decrease in extracellular PPI, the *Ank* gene appears to regulate both intra- and extracellular levels of an important inhibitor of hydroxyapatite crystal formation [55]. Thus, local PPI production naturally inhibits hydroxyapatite deposition, blocking undesirable mineralization in articular cartilage and other tissues. With loss of ANK activity, however, extracellular PPI levels attenuate, intracellular PPI levels rise, and unregulated mineralization takes place.

3.4. Ca^{2+} transport through annexins

Matrix metalloproteinase (MMP)-3 [57], TNAP [5,16,17,32,57–60], annexins [61], phospholipase A2, carbonic anhydrase II and lactate dehydrogenase [62] are some of the relevant enzymes and proteins involved in matrix vesicle-mediated mineralization.

Among these molecules, annexins are Ca^{2+} - and lipid-binding proteins involved in Ca^{2+} transport and serving as ion channels in the matrix vesicles (Fig. 6). Three annexins were identified in the matrix vesicles: annexin A2, A5 and A6 [63–66]. In the first phase of matrix vesicle-mediated mineralization, mineral complexes appears on the inner leaflet of the matrix vesicle’s membrane. The affinity of

phosphatidylserine for Ca^{2+} is quite strong in the inner leaflet of the matrix vesicle membrane, which is enriched with anionic lipids [67,68]. The annexin A5 shows Ca^{2+} -dependent phosphatidylserine-binding properties and may play a central role in mineralization. However, *Annexin A5*^{-/-} mice did not demonstrate abnormal skeletal development; thus, other annexins could replace the biological functions of annexin A5 in knockout mice. Thus, further studies seem to be necessary to clarify the precise role of annexins during bone mineralization.

4. Ultrastructure of collagen mineralization

After the onset of matrix vesicle-mediated mineralization, mineralized nodules would contact the surrounding collagen fibrils. The collagen fibrils mineralization begins at the point of contact with mineralized nodules (Fig. 7). There are at least two theories explaining collagen mineralization: one is the hole zone theory, and another is the one supporting that mineralization takes place along the superhelix of collagen fibrils, which are arranged in parallel, but shifted at certain intervals. According to the hole zone theory, during the non-mineralizing phase, the gaps within the collagen fibrils are occupied by small proteoglycans such as decorin and biglycan. However, after elimination of these proteoglycans, extracellular Ca^{2+} and PO_4^{3-} fill in the gap to generate calcium phosphate nuclei and mineralize the collagen fibrils. Thus, the initial mineralization begins in the collagen fibrils’ “holes”.

However, while decorin/biglycan-double knockout mice revealed osteopenia as a result of impaired GAG-linking to decorin and biglycan core proteins, mineralization was not stimulated [69]. Still, collagen mineralization based on the process of removal of small proteoglycans may need further investigation. On the other hand, TEM observations demon-

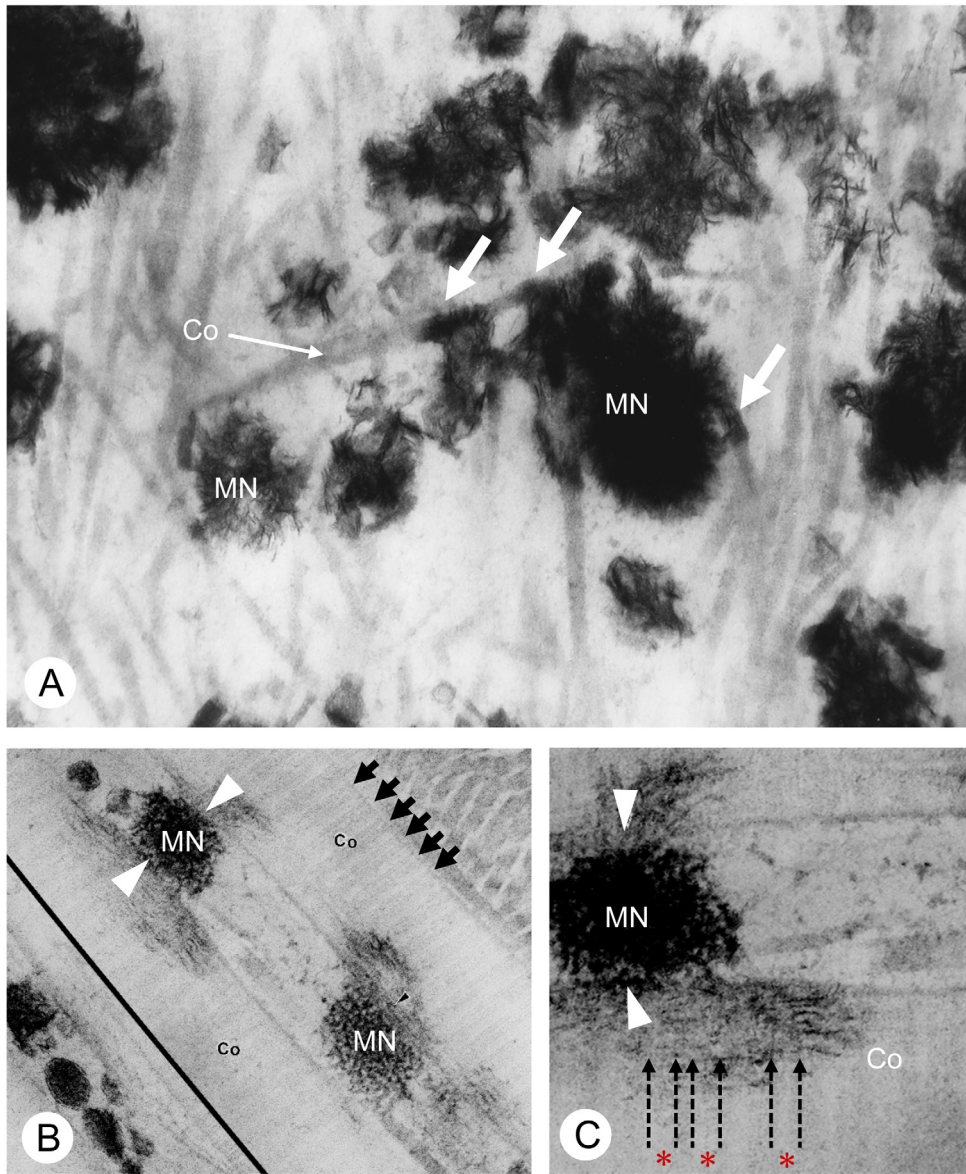


Figure 7 TEM images of the contact between collagen fibrils and mineralized nodules.

(A) In osteoid, several mineralized nodules (MN) are shown to make contact with surrounding collagen fibrils (Co) (arrows). (B) In other region, mineralized nodules spread out minerals to neighboring collagen fibrils. Thus, collagen mineralization seems to be associated with mineralized nodules. In contrast, however, collagen striation (short arrows) do not show any mineral deposition. (C) At a higher magnification, laddering structures of mineral deposition are parallel to the longitudinal axis of the collagen fibrils, and the length of mineral crystal seems to be identical to that of superhelix.

Panel A is from Ref. [74] (Amizuka et al.), and panels B and C are modified from Ref. [73] (Ozawa et al.).

strated that mineralization spread out from the contact point of mineralized nodules towards the periphery of collagen fibrils (Fig. 7B and C). This finding suggests that collagen mineralization is association with mineralized nodules. At a higher magnification, the spicules of calcium phosphate crystals are seen on the fibrillar structures identical to the superhelix of collagen fibrils, which indicates that mineral crystals are deposited on the superhelix, which serves as a scaffold for collagen mineralization.

We also examined mineralization on osteogenic disorder shionogi (ODS) rats, which carry a hereditary defect

in ascorbic acid synthesis [70]. Fragile, fibrillar collagenous structures without evident striation were found in ODS rat bones, which may be a result of misassembly of the triple helices of collagenous α -chains secondary to ascorbic acid deprivation. However, that seemed to bear no effect on mineralization: fine needle-shaped mineral crystals extended from mineralized nodules, and were apparently bound to collagenous fibrillar structures (Fig. 8).

Taken together, these two postulations (the hole zone theory and mineralization on the superhelix of collagen fib-

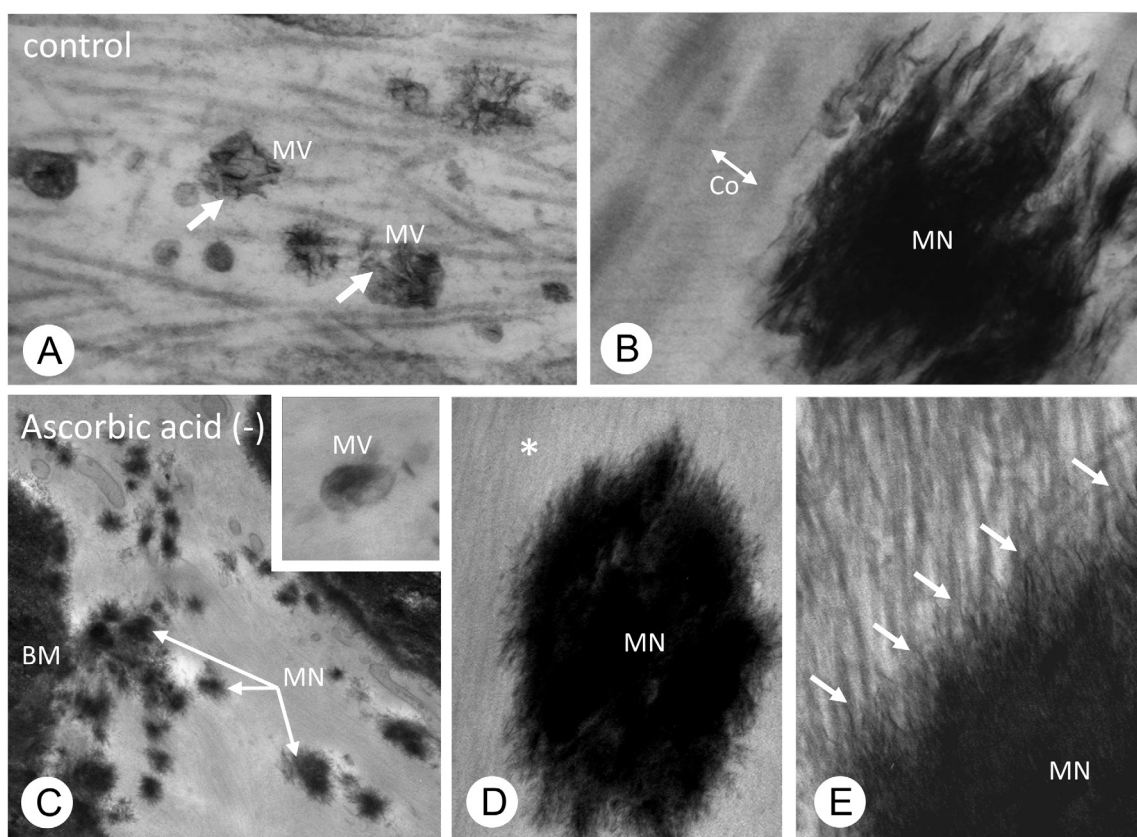


Figure 8 Matrix vesicles and collagen mineralization in ascorbic acid insufficient circumstance.

In a normal state, TEM observations demonstrate numerous matrix vesicles (A) and mineralized nodules (B). At a higher magnification, mineral crystals extending from the mineralized nodules ran along the collagen fibrils (B). In an insufficient circumstance of ascorbic acid, which is necessary for collagen synthesis, TEM observations verified the presence of matrix vesicles and mineralized nodules (C). At a higher magnification, however, collagen fibrils are shown by very fine, but, the fine mineral crystals from the mineralized nodule extended along fine fibrillar structures of collagen fibrils (D and E). All the images are modified from Ref. [70] (Hasegawa et al.).

rils) are both without proper foundations, and therefore, need further scientific scrutiny.

5. Concluding remarks

Matrix vesicle-mediated mineralization causes a series of orchestrated ultrastructural and biochemical events in bone. To achieve proper mineralization, a variety of membrane transporters and enzymes are put at work in matrix vesicles. Of particular importance is the influx of phosphate ions into matrix vesicles, which involves a complex interplay among ENPP1, ANK, TNAP and Pit1. Mineralized nodules, the globular assembly of needle-shaped mineral crystals, are derived from matrix vesicles and may retain some activity of those transporters and enzymes. However, crystal growth is likely regulated by surrounding organic materials prior to subsequent collagen mineralization.

Conflict of interest

None declared.

Acknowledgments

This study was partially supported by the Grants-in Aid for Scientific Research (Amizuka N, Hasegawa T) and Promoting International Joint Research (Bilateral Collaborations) of JSPS and NSFC (Amizuka N, Li M).

References

- [1] Ali SY, Sajdera SW, Anderson HC. Isolation and characterization of calcifying matrix vesicles from epiphyseal cartilage. *Proc Natl Acad Sci U S A* 1970;67:1513–20.
- [2] Anderson HC. Vesicles associated with calcification in the matrix of epiphyseal cartilage. *J Cell Biol* 1969;41:59–72.
- [3] Bonucci E. Fine structure of early cartilage calcification. *J Ultrastruct Res* 1967;20:33–50.
- [4] Bonucci E. Fine structure and histochemistry of “calcifying globules” in epiphyseal cartilage. *Z Zellforsch Mikrosk Anat* 1970;103:192–217.
- [5] Ozawa H, Yamada M, Yajima T. The ultrastructural and cytochemical aspects of matrix vesicles and calcification processes. In: Talmage RV, Ozawa H, editors. *Formation and calcification of hard tissues*. Tokyo: Shakai Hoken Pub; 1978. p. 9–57.

- [6] Ozawa H, Yamada M, Yamamoto T. Ultrastructural observations on the location of lead and calcium in the mineralizing dentine of rat incisor. In: Ascenzi A, Bonucci E, de Bernard B, editors. *Matrix vesicles*. Milano: Wicking Editore srl; 1981. p. 179–87.
- [7] Wuthier RE. Lipid composition of isolated epiphyseal cartilage cells, membranes and matrix vesicles. *Biochim Biophys Acta* 1975;409:128–43.
- [8] Robison R, Soames KM. The possible significance of hexosephosphoric esters in ossification. *Biochem J* 1924;17:286–93.
- [9] Weiner S. Organization of extracellularly mineralized tissues: a comparative study of biological crystal growth. *CRC Crit Rev Biochem* 1986;20:365–408.
- [10] Ozawa H. Ultrastructural concepts on biological calcification; focused on matrix vesicles. *J Oral Biosci* 1985;27:751–74.
- [11] Boskey AL, Posner AS. The role of synthetic and bone extracted Ca-phospholipid-PO₄ complexes in hydroxyapatite formation. *Calcif Tissue Res* 1977;23:251–8.
- [12] Boyan BD, Schwartz Z, Swain LD, Khare A. Role of lipids in calcification of cartilage. *Anat Rec* 1989;224:211–9.
- [13] Mahamid J, Sharir A, Gur D, Zelzer E, Addadi L, Weiner S. Bone mineralization proceeds through intracellular calcium phosphate loaded vesicles: a cryo-electron microscopy study. *J Struct Biol* 2011;174:527–35.
- [14] Ozawa H. Current concepts of the morphophysiology of matrix vesicle calcification. *Connect Tissue* 1983;15:1–12.
- [15] Ozawa H. Ultrastructural aspects on the biological calcification with special reference to freeze-substitution at liquid helium temperature. In: *Proceedings of the 11th International Congress on Electron Microscopy*. 1986. p. 57–60.
- [16] Yamada M. Ultrastructural and cytochemical studies on the calcification of the tendon-bone joint. *Arch Histol Jpn* 1976;39:347–78.
- [17] Hoshi K, Ejiri S, Ozawa H. Localizational alterations of calcium, phosphorus, and calcification-related organics such as proteoglycans and alkaline phosphatase during bone calcification. *J Bone Miner Res* 2001;16:289–98.
- [18] Bosky AL, Maresca M, Ulrich W, Doty SB, Butler WT, Prince CW. Osteopontin-hydroxyapatite interactions in vitro: inhibition of hydroxyapatite formation and growth in a gelatin-gel. *Bone Miner* 1993;22:147–59.
- [19] Hunter GK, Hauschka PV, Poole AR, Rosenberg LC, Goldberg HA. Nucleation and inhibition of hydroxyapatite formation by mineralized tissue proteins. *Biochem J* 1996;317:59–64.
- [20] Mark MP, Butler WT, Prince CW, Finkleman RD, Ruch J-V. Developmental expression of 44-kDa phosphoprotein (osteopontin) and bone-carboxylglutamic acid (Gla)-containing protein (osteocalcin) in calcifying tissues of rat. *Differentiation* 1988;37:123–36.
- [21] Ritter NM, Farach-Carson MC, Butler WT. Evidence for the formation of a complex between osteopontin and osteocalcin. *J Bone Miner Res* 1992;7:877–85.
- [22] Bianco P, Hayashi Y, Silvestrini G, Termine JD, Bonucci E. Osteonectin and Gla-protein in calf bone: ultrastructural immunohistochemical localization using the Protein A-gold method. *Calcif Tissue Int* 1985;37:684–6.
- [23] Bonucci E. The locus of initial calcification in cartilage and bone. *Clin Orthop Relat Res* 1971;78:108–39.
- [24] Bonucci E, Gherardi G. Histochemical and electron microscopy investigations on medullary bone. *Cell Tissue Res* 1975;163:81–97.
- [25] Hall JG, Pauli RM, Wilson KM. Maternal and fetal sequelae of anti-coagulation during pregnancy. *Am J Med* 1980;68:122–40.
- [26] Hauschka PV, Lian JB, Gallop PM. Direct identification of the calcium-binding amino acid, gamma-carboxylglutamate, in mineralized tissue. *Proc Natl Acad Sci U S A* 1975;72:3925–9.
- [27] Price PA, Otsuka AA, Poser JW, Kristaponis J, Raman N. Characterization of a gamma-carboxylglutamic acid-containing protein from bone. *Proc Natl Acad Sci U S A* 1976;73:1447–51.
- [28] Pauli RM, Lian JB, Mosher DF, Suttie JW. Association of congenital deficiency of multiple vitamin K-dependent coagulation factors and the phenotype of the warfarin embryopathy: clues to the mechanism of teratogenicity of coumarin derivatives. *Am J Hum Genet* 1987;41:566–83.
- [29] Amizuka N, Li M, Hara K, Kobayashi M, de Freitas PH, Ubaidus S, et al. Warfarin administration disrupts the assembly of mineralized nodules in the osteoid. *J Electron Microsc* 2009;58:55–65.
- [30] Azuma K, Shiba S, Hasegawa T, Ikeda K, Urano T, Horie-Inoue K, et al. Osteoblast-specific γ -glutamyl carboxylase-deficient mice display enhanced bone formation with aberrant mineralization. *J Bone Miner Res* 2015;30:1245–54.
- [31] de Bernard B, Bianco P, Bonucci E, Costantini M, Lunazzi GC, Martinuzzi P, et al. Biochemical and immunohistochemical evidence that in cartilage an alkaline phosphatase is a Ca²⁺-binding glycoprotein. *J Cell Biol* 1986;103:1615–23.
- [32] Matsuzawa T, Anderson HC. Phosphatases of epiphyseal cartilage studied by electron microscopic cytochemical methods. *J Histochem Cytochem* 1971;19:801–8.
- [33] Nakano Y, Beertsen W, van den Bos T, Kawamoto T, Oda K, Takano Y. Site-specific localization of two distinct phosphatases along the osteoblast plasma membrane: tissue non-specific alkaline phosphatase and plasma membrane calcium ATPase. *Bone* 2004;35:1077–85.
- [34] Oda K, Amaya Y, Fukushi-Irie M, Kinameri Y, Ohsuye K, Kubota I, et al. A general method for rapid purification of soluble versions of glycosylphosphatidylinositol-anchored proteins expressed in insect cells: an application for human tissue-nonspecific alkaline phosphatase. *J Biochem* 1999;126:694–9.
- [35] Hoshi K, Amizuka N, Oda K, Ikehara Y, Ozawa H. Immunolocalization of tissue non-specific alkaline phosphatase in mice. *Histochem Cell Biol* 1997;107:183–91.
- [36] Narisawa S, Fröhlander N, Millian JL. Inactivation of two mouse alkaline phosphatase genes and establishment of a model of infantile hypophosphatasia. *Dev Dyn* 1997;208:432–46.
- [37] Waymire KG, Mahuren JD, Jaje JM, Guilarte TR, Coburn SP, MacGregor GR. Mice lacking tissue non-specific alkaline phosphatase die from seizures due to defective metabolism of vitamin B-6. *Nat Genet* 1995;11:45–51.
- [38] Anderson HC, Sipe JB, Hesse L, Dhanyamraju R, Atti E, Camacho NP, et al. Impaired calcification around matrix vesicles of growth plate and bone in alkaline phosphatase-deficient mice. *Am J Pathol* 2004;164:841–7.
- [39] Fedde KN, Blair L, Silverstein J, Coburn SP, Ryan LM, Weinstein RS, et al. Alkaline phosphatase knock-out mice recapitulate the metabolic and skeletal defects of infantile hypophosphatasia. *J Bone Miner Res* 1999;14:2015–26.
- [40] Tesch W, Vandenbos T, Roschgr P, Fratzi-Zelman N, Klaushofer K, Beertsen W, et al. Orientation of mineral crystallites and mineral density during skeletal development in mice deficient in tissue nonspecific alkaline phosphatase. *J Bone Miner Res* 2003;18:117–25.
- [41] Murshed M, Harmey D, Millán JL, McKee MD, Karsenty G. Unique coexpression in osteoblasts of broadly expressed genes accounts for the spatial restriction of ECM mineralization to bone. *Genes Dev* 2005;19:1093–104.
- [42] Whyte MP, Greenberg CR, Salman NJ, Bober MB, McAlister WH, Wenkert D, et al. Enzyme-replacement therapy in life-threatening hypophosphatasia. *N Engl J Med* 2012;366:904–13.
- [43] Whyte MP, Rockman-Greenberg C, Ozono K, Riese R, Moseley S, Melian A, et al. Asfotase alfa treatment improves survival for perinatal and infantile hypophosphatasia. *J Clin Endocrinol Metab* 2016;101:334–42.
- [44] Kato K, Nishimasu H, Okudaira S, Mihara E, Ishitani R, Takagi J, et al. Crystal structure of Enpp1, an extracellular glycoprotein

- involved in bone mineralization and insulin signaling. *Proc Natl Acad Sci U S A* 2012;109:16876–81.
- [45] Terkeltaub R, Rosenbach M, Fong F, Goding J. Causal link between nucleotide pyrophosphohydrolase overactivity and increased intracellular inorganic pyrophosphate generation demonstrated by transfection of cultured fibroblasts and osteoblasts with plasma cell membrane glycoprotein-1. *Arthritis Rheum* 1994;37:934–41.
- [46] Johnson K, Vaingankar S, Chen Y, Moffa A, Goldring M, Sano K, et al. Differential mechanisms of inorganic pyrophosphate production by plasma cell membrane glycoprotein-1 and B10 in chondrocytes. *Arthritis Rheum* 1999;42:1986–97.
- [47] Johnson K, Moffa A, Chen Y, Pritzker K, Goding J, Terkeltaub R. Matrix vesicle plasma membrane glycoprotein-1 regulates mineralization by murine osteoblastic MC3T3 cells. *J Bone Miner Res* 1999;14:883–92.
- [48] Rutsch R, Vaingankar S, Johnson K, Goldfine I, Maddux B, Schauerte P, et al. PC-1 nucleoside triphosphate pyrophosphohydrolase deficiency in idiopathic infantile arterial calcification. *Am J Pathol* 2001;158:543–54.
- [49] Rutsch F, Ruf N, Vaingankar S, Toliat MR, Suk A, Höhne W, et al. Mutations in ENPP1 are associated with 'idiopathic' infantile arterial calcification. *Nat Genet* 2003;34:379–81.
- [50] Okawa A, Nakamura I, Goto S, Moriya H, Nakamura Y, Ikegawa S. Mutation in Npps in a mouse model of ossification of the posterior longitudinal ligament of the spine. *Nat Genet* 1998;19:271–3.
- [51] Johnson K, Pritzker K, Goding J, Terkeltaub R. The nucleoside triphosphate pyrophosphohydrolase isozyme PC-1 directly promotes cartilage calcification through chondrocyte apoptosis and increased calcium precipitation by mineralizing vesicles. *J Rheumatol* 2001;28:2681–91.
- [52] Johnson K, Hashimoto S, Lotz M, Pritzker K, Goding J, Terkeltaub R. Up-regulated expression of the phosphodiesterase nucleotide pyrophosphatase family member PC-1 is a marker and pathogenic factor for knee meniscal cartilage matrix calcification. *Arthritis Rheum* 2001;44:1071–81.
- [53] Johnson K, Goding J, Van Etten D, Sali A, Hu SI, Farley D, et al. Linked deficiencies in extracellular inorganic pyrophosphate (PPi) and osteopontin expression mediate pathologic ossification in PC-1 null mice. *J Bone Miner Res* 2003;18:994–1004.
- [54] Mackenzie NC, Zhu D, Milne EM, van't Hof R, Martin A, Darryl Quarles L, et al. Altered bone development and an increase in FGF-23 expression in *Enpp1*($-/-$) mice. *PLoS One* 2012;7:e32177.
- [55] Ho AM, Johnson MD, Kingsley DM. Role of the mouse ank gene in control of tissue calcification and arthritis. *Science* 2000;289:265–70.
- [56] Gurley KA, Reimer RJ, Kingsley DM. Biochemical and genetic analysis of ANK in arthritis and bone disease. *Am J Hum Genet* 2006;79:1017–29.
- [57] Schmitz JP, Schwartz Z, Sylvia VL, Dean DD, Calderon F, Boyan BD. Vitamin D3 regulation of stromelysin-1 (MMP-3) in chondrocyte cultures is mediated by protein kinase C. *J Cell Physiol* 1996;168:570–9.
- [58] Fleish H, Neuman WF. Mechanisms of calcification: role of collagen, polyphosphates, and phosphatase. *Am J Physiol* 1961;200:1296–300.
- [59] Fleish H, Neuman W. The role of phosphatase and polyphosphates in calcification of collagen. *Helv Physiol Pharmacol Acta* 1961;19:C17–8.
- [60] Takano Y, Ozawa H, Crenshaw MA. Ca-ATPase and ALPase activities at the initial calcification sites of dentine and enamel in the rat incisor. *Cell Tissue Res* 1986;243:91–9.
- [61] Kirsch T, Nah HD, Shapiro IM, Pacifici M. Regulated production of mineralization-competent matrix vesicles in hypertrophic chondrocytes. *J Cell Biol* 1997;137:1149–60.
- [62] Anderson HC. Molecular biology of matrix vesicles. *Clin Orthop Relat Res* 1995;314:266–80.
- [63] Cao X, Genge BR, Wu LN, Buzzi WR, Showman RM, Wuthier RE. Characterization, cloning and expression of the 67-kDa annexin from chicken growth plate cartilage matrix vesicles. *Biochem Biophys Res Commun* 1993;197:556–61.
- [64] Kirsch T, Nah HD, Demuth DR, Harrison G, Golub EE, Adams SL, et al. Annexin V-mediated calcium flux across membranes is dependent on the lipid composition: implications for cartilage mineralization. *Biochemistry* 1997;36:3359–67.
- [65] Kirsch T, Nah HD, Shapiro IM, Pacifici M. Regulated production of mineralization-competent matrix vesicles in hypertrophic chondrocytes. *J Cell Biol* 1997;137:1149–60.
- [66] Kirsch T, Claassen H. Matrix vesicles mediate mineralization of human thyroid cartilage. *Calcif Tissue Int* 2000;66:292–7.
- [67] Majeska RJ, Holwerda DL, Wuthier RE. Localization of phosphatidylserine in isolated chick epiphyseal cartilage matrix vesicles with trinitrobenzenesulfonate. *Calcif Tissue Int* 1979;27:41–6.
- [68] Taylor MG, Simkiss K, Simmons J, Wu LN, Wuthier RE. Structural studies of a phosphatidyl serine-amorphous calcium phosphate complex. *Cell Mol Life Sci* 1998;54:196–202.
- [69] Corsi A, Xu T, Chen XD, Boyde A, Liang J, Mankani M, et al. Phenotypic effects of biglycan deficiency are linked to collagen fibril abnormalities, are synergized by decorin deficiency, and mimic Ehlers-Danlos-like changes in bone and other connective tissues. *J Bone Miner Res* 2002;17:1180–9.
- [70] Hasegawa T, Li M, Hara K, Sasaki M, Tabata C, de Freitas PH. Morphological assessment of bone mineralization in tibial metaphyses of ascorbic acid-deficient ODS rats. *Biomed Res* 2011;32:259–69.
- [71] Amizuka N, Ozawa H. In: Nishizawa Y, Shiraki M, Ezawa I, Hirota T, editors. *Bone and calcium, calcium—basic science, clinics, nutrition*. Tokyo: Life Science Publishing Co. Ltd.; 1999. p. 20–34 [in Japanese].
- [72] Amizuka N, Hasegawa T, Oda K, Luiz de Freitas PH, Hoshi K, Li M, et al. Histology of epiphyseal cartilage calcification and endochondral ossification. *Front Biosci* 2012;4:2085–100.
- [73] Ozawa H, Hoshi K, Amizuka N. Current concepts of bone mineralization. *J Oral Biosci* 2008;50(1):1–14.
- [74] Amizuka N, Li M, Kobayashi M, Hara K, Akahane S, Takeuchi K, et al. Vitamin K2, a gamma-carboxylating factor of gla-proteins, normalizes the bone crystal nucleation impaired by Mg-insufficiency. *Histol Histopathol* 2008;23(11):1353–66.