



King Saud University
Arabian Journal of Chemistry

www.ksu.edu.sa
www.sciencedirect.com



ORIGINAL ARTICLE

Synchronous role of coupled adsorption and photocatalytic degradation on CAC–TiO₂ composite generating excellent mineralization of alizarin cyanine green dye in aqueous solution



P. Muthirulan, C. Nirmala Devi, M. Meenakshi Sundaram *

Centre for Research and Post-Graduate Studies in Chemistry, Ayya Nadar Janaki Ammal College, Sivakasi 626 124, Tamil Nadu, India

Received 26 April 2012; accepted 29 April 2013
Available online 10 May 2013

KEYWORDS

Photocatalytic degradation;
ACG dye;
TiO₂;
Commercial activated carbon;
Synergistic effect

Abstract The synchronous role of coupled adsorption and photocatalytic degradation of alizarin cyanine green dye (ACG) in aqueous solution on porous Commercial Activated Carbon (CAC)–titanium dioxide (TiO₂) mixture have been studied under UV irradiation. The CAC–TiO₂ composite was prepared by simple chemical route and the as prepared composite was characterized using Scanning Electron Microscopy (SEM) and X-ray Diffraction (XRD) analysis. The photodegradation rate constant (*k*) for ACG dye on CAC–TiO₂ is (0.0666 min^{−1}), which is very much higher than that of pure TiO₂ 0.00368 min^{−1}. The photodegradation efficiency of the CAC–TiO₂ composite was eighteen order magnitudes higher than that of pure TiO₂ for ACG dye degradation. The total mineralization of ACG, through the combination of adsorption and degradation was achieved in a reasonable time, and can therefore be suggested as an efficient, cost-effective and environment friendly water treatment methodology.


© 2013 Production and hosting by Elsevier B.V. on behalf of King Saud University. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/3.0/>).

1. Introduction

Pigments and dyes are widely used in various industries (Robinson et al., 2001), and a considerable percentage of these go into the effluent during the dyeing process. The toxicity and potentially carcinogenic nature of these represent an increasing danger for aquatic life. Therefore, many physicochemical methods such as adsorption, coagulation, precipitation, filtration and oxidation have been attempted for dye removal. The adsorption process has been found to be the most effective. Numerous adsorbents such as activated carbon

* Corresponding author. Tel.: +91 9486028616; fax: +91 4562254970.

E-mail addresses: chemistryanjac@gmail.com (M. Meenakshi Sundaram), drmmmsundaram61@gmail.com (M. Meenakshi Sundaram).
Peer review under responsibility of King Saud University.



(Demirbas et al., 2008; Al-Degs et al., 2008), alumina (Salem and El-Maazawi, 2000), and zeolite (Karadag et al., 2007) are widely used. However, they only simply transfer the dye from one medium to another and still leave the pollutants in the environment.

Photocatalytic oxidation represents an attractive solution due to the ability to completely oxidize organic contaminants to carbon dioxide, water and mineral acids hence it degraded the pollutants rather than transferring them (Lodha et al., 2011; Velmurugan et al., 2012; Barka et al., 2010). TiO_2 , a well-known photocatalyst, has been extensively investigated for the degradation of organic pollutants under ultraviolet irradiation in wastewater and in air because of its photostability, nontoxicity, high activity and relatively low cost (Ding et al., 1999; Li et al., 2002, 2007). However, problems with the use of TiO_2 powder is also well recognized; specifically, (1) the difficulty in separating the TiO_2 powder from the solution after reaction is complete, (2) aggregation of particles in suspension, especially at high loadings and (3) difficulty in application to continuous flow systems (Leary and Westwood, 2011).

The incorporation of photocatalysts with adsorbents offers a new design of a photocatalytic system. Some nanocomposites which have a high adsorbing capacity as well as a high efficiency for the photocatalytic degradation have been prepared such as TiO_2 /zeolite, TiO_2 /activated carbon, $\text{TiO}_2/\text{Al}_2\text{O}_3$ and $\text{TiO}_2/\text{SiO}_2$. Because of the adsorbents adsorbing the substances selectively, exploring new adsorbents for the application in more industrial purposes is expected (Chen et al., 2010; Fernandez et al., 1995; Velasco et al., 2010; Tryba et al., 2003). However, reports on both physical-adsorbing properties and photocatalytic properties of the CAC– TiO_2 mixtures are scanty. The present study designates the photodecolorization of ACG dye on TiO_2 in the presence of CAC. The influence of various process parameters on the photodecolorization was also studied.

2. Experimental procedure

2.1. Materials

AnalaR grade Alizarin Cyanine Green (ACG) dye purchased from E. Merck, India was used in the present study. Figure 1 shows the structure (Fig. 1a), UV–vis absorption spectrum

(Fig. 1b) and wavelength for maximum absorption (λ_{max}) of ACG dye. The catalyst used in the present work is TiO_2 supplied by May & Baker Ltd., Dagenham, England. CAC was supplied by BDH, India. All the other chemicals and reagents were of AnalaR grade supplied by BDH, India, Ranboxy and SD fine chemicals. Deionized water was used for the preparation of all the solutions and reagents.

2.2. Preparation of CAC– TiO_2 composite

The CAC– TiO_2 composite was prepared by infiltration of a suspension in ethanol of commercial TiO_2 particles on the CAC in a rotary evaporator under vacuum for 45 min. After the rotation, ethanol was evaporated out and dried. Before each photocatalysis experimental studies, the CAC– TiO_2 mixture is activated and dried at 110 °C overnight. Mere TiO_2 was also used as a standard for comparison purposes.

2.3. Photodegradation studies

The photocatalytic activities of the photocatalysts were evaluated by photodegradation of ACG dye in aqueous solution at room temperature. Stock solution of ACG dye was suitably diluted to the required initial concentration with DD water. 100 ml of the dye solution of known initial concentration (C_i) was taken in a photo reactor vessel. The required amount of catalyst (TiO_2 or CAC– TiO_2 composite) was exactly weighted and then transferred into the photo reactor vessel. The photo reactor vessel was placed in the safety wood. Before illumination, it was turned on. The suspension was stirred with a magnetic stirrer. After a definite period of time, the solution was taken from the photo reactor vessel and centrifuged immediately for separation of the suspended solids. The solution was analyzed by a spectrophoto colorimetric technique by measuring the absorbance using spectrophoto colorimeter. Preliminary dark experiments without irradiation were also performed to establish the period of time needed to achieve the adsorption–desorption equilibrium of all the prepared materials and to determine $t = 0$ for the photocatalytic reactions (instant to turn on the irradiation). Although ACG dye may absorb light itself, such a self-degradation is negligible when compared with degradation catalyzed by photocatalysts.

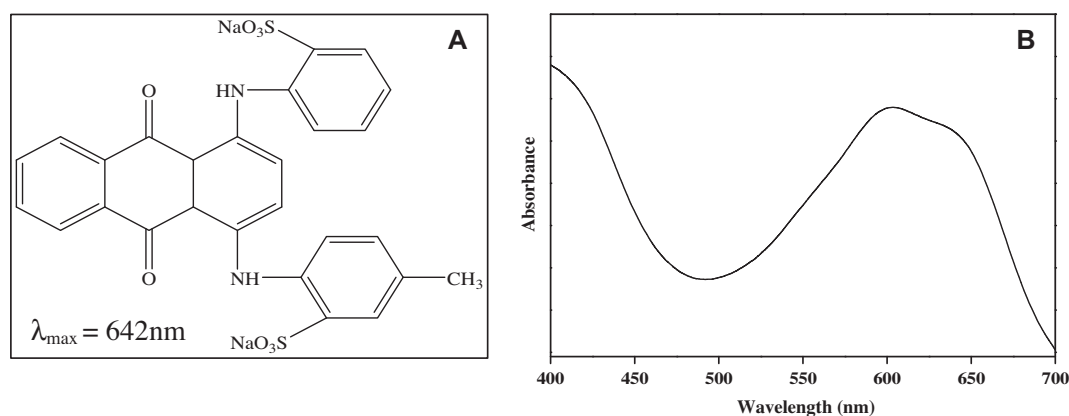


Figure 1 Structure (a) and UV–vis spectra of ACG dye.

2.4. Equipments

High irradiation was performed with a UV – high pressure (“HEBER” photoreactor, model HIPR compact-MP-8/125/400) mercury lamp ($\lambda_{\text{max}} = 365 \text{ nm}$; 400 W). The X-ray diffraction pattern of the PoPD film was taken with an analytical (Model PW 3040/60) X-ray diffractometer using Cu K α radiation. UV–visible spectra were recorded using “TECHCOMP” UV–visible spectrometer model 8500 with a matched pair of Teflon stoppard quartz cuvettes. Scanning Electron Microscopy (SEM) image was obtained using LEO 440 I model. The X-ray diffraction pattern of the PoPD film was taken with an analytical (Model PW 3040/60) X-ray diffractometer using Cu K α radiation. Concentration of dye was determined with Spectrophotometer (Systronics-115). The pH of the dye solution was measured by using digital pen pH meter (Hanna instrument, Portugal).

3. Results and discussion

3.1. Scanning electron microscope analysis

SEM studies provide useful information regarding the surface morphology of the materials. Fig. 2 shows SEM images of the surface morphology of the mere TiO₂, Mere CAC and CAC–TiO₂ composites. The surfaces of the TiO₂ particles appeared spherical in shape and the particles are agglomerated (Fig. 2A). SEM photograph exhibits mere CAC to be porous in nature with uniform morphology (Fig. 2B). The surface structure of the CAC–TiO₂ composite clearly reveals the surface texture and porosity nature (Fig. 2C). The immobilization of TiO₂ in the carbon matrix partially blocked the porosity of the carbon surface, although the composite still displays a porous character with a relatively large pore volume and surface area. These results suggested that TiO₂ did not enter the inner pores of the carbon during the immobilization, remaining on the outer surface and most accessible pores. Consequently, the pores of smaller sizes remained unblocked. Besides, due to the synthetic route followed in the preparation of the AC–TiO₂ composite no chemical bonding is expected between TiO₂ and the carbon support, it seems that there exists a weak interaction.

3.2. XRD measurement

In order to confirm the crystalline nature of TiO₂ on CAC–TiO₂ composite, XRD pattern has been carried out for pristine CAC and 1:4 ratio of CAC:TiO₂ mixture (Fig. 3). The XRD pattern of the pure CAC shows two broad diffraction peaks at 25.9° and 41.2°, which can be indexed to (002) and (100) diffraction for typical graphite carbons. For CAC–TiO₂ composite catalysts, all the sharp peaks observed in the XRD patterns belong to the anatase phase of TiO₂ [JCPDS No. 21 = 1272]. The peaks at $2\theta = 25.3^\circ, 37.8^\circ, 48.0^\circ, 53.9^\circ,$ and 55.1° can be assigned to the diffractions of (101), (004), (200), (105) and (211) crystal planes of the anatase phase. It is noteworthy that the characteristic peaks of CAC can hardly be identified from all the patterns of the composite catalysts. The reason may be that the main peak of CAC at 24.9° is overlapped with the main

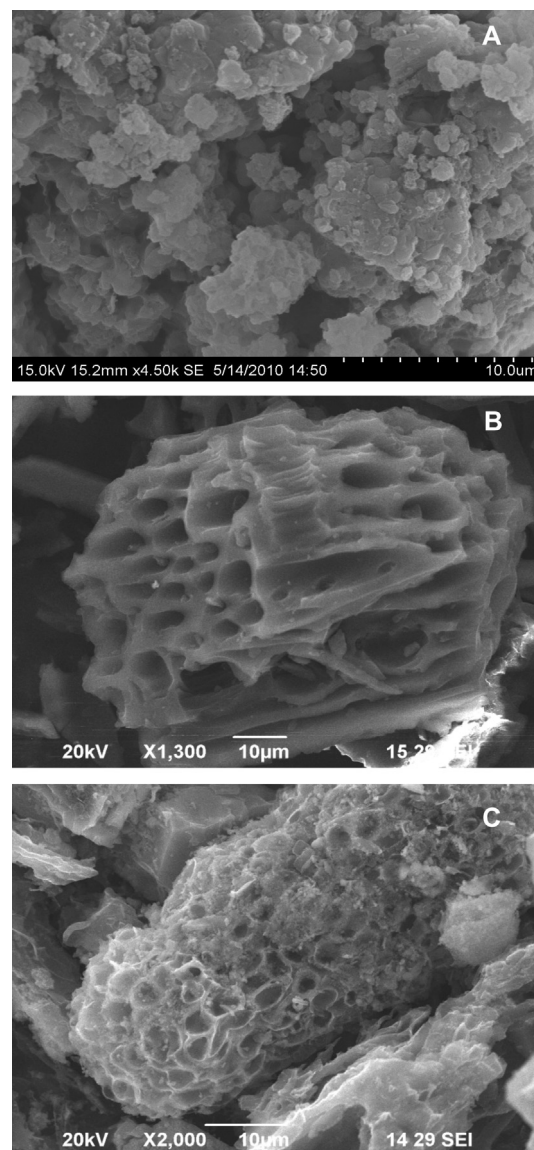


Figure 2 Surface morphology of the (A) pure TiO₂; (B) pure CAC and (C) CAC–TiO₂ mixture.

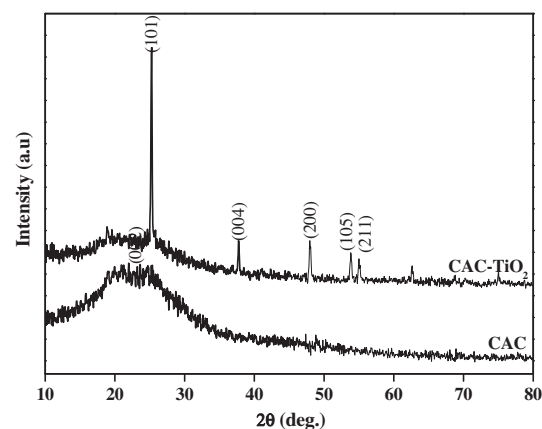


Figure 3 XRD pattern of Mere CAC and CAC–TiO₂ composites.

peak of anatase TiO_2 at 25.3° (Liu et al., 2007; Velasco et al., 2010; Muthirulan et al., 2012a).

3.3. Effect of initial concentration on photodegradation of ACG

The effect of dye concentration on the degradation rate was studied by keeping the mass of composite and irradiation time constant while the concentration of the dye varies in the range 10–40 ppm. Similarly, the photocatalytic degradation of ACG dye was also carried out under same experimental conditions in the presence of CAC.

The extent of removal of the dye, in terms of the values of percentage removal of dye has been calculated using the following relationship:

$$\text{Percentage removal} = 100(C_i - C_f)/C_i \quad (1)$$

where, C_i = initial concentration of dye (ppm); C_f = final concentration of dye (ppm) at given time.

It was observed from Fig. 4, that the percentage removal (%R) of ACG dye decreases exponentially with the increase in the initial concentration. An important step in the photocatalytic process of the present system is the adsorption of reacting substances onto the surface of the catalyst. AC has a well-developed pore structure, very large surface area with strong adsorption capacity and is widely used as an adsorbent and catalyst support. AC in the CAC– TiO_2 catalysts can act as an active center where dye molecules can be adsorbed before transferring to the decomposition center, illuminated by TiO_2 , which is located on the AC surface, because of the concentration difference. Meanwhile anatase nanocrystals generate $\bullet\text{OH}$ radicals by UV irradiation, which simultaneously attack the pre-enriched ACG dye from many different directions. As a result, the ACG dye is in no time cleaved into small molecules. Subsequently, the resultants diffuse out of the pores into the solution. In this process, the $\bullet\text{OH}$ radicals are highly efficiently utilized because of the synchronous role of adsorption and photocatalytic oxidation, generating the excellent activity (Muthirulan et al., 2012a,b).

On the other hand, using activated carbon as a catalyst support will help increase the photodegradation rate by progressively allowing an increased quantity of substrate to come in

contact with TiO_2 through means of adsorption. This is important because researchers have established that the oxidizing species ($\bullet\text{OH}$) generated by the photocatalyst, does not migrate very far from the active centers of TiO_2 and therefore degradation takes place virtually on the catalyst surface. In this respect, activated carbon will prove to be an invaluable support in promoting the photocatalytic process in providing a synergistic effect by creating a common interface between both the activated carbon phase and the TiO_2 particle phase. The synergistic effect can be explained as an enhanced adsorption of the target pollutant onto the activated carbon phase followed closely by a transfer through an interphase to the TiO_2 phase, giving a complete photodegradation process.

3.4. Effect of irradiation time on photodegradation of ACG

In order to study the effect of irradiation time (range 15–120 min) on the extent of removal of ACG dye, the photodegradation experiments were carried out at constant dose of the catalysts (200 mg) and constant dose of the CAC (40 mg) and optimum initial concentration of dye (30 ppm). Fig. 5 represents that as the irradiation time increases the %R also increases. UV–vis absorption spectrum of ACG with different reaction times under UV irradiation in the presence CAC– TiO_2 composites is illustrated in Fig. 6a. UV irradiation leads to a continuous decrease in the absorbance of ACG in the presence of photocatalyst and the decrease of the absorption band intensities of the dye indicated that dye has been degraded. As can be seen in this figure, the disappearance of the characteristic band of ACG dye at 642 nm after 90 min under UV light irradiation indicates that ACG has been degraded completely.

The following pseudo-first order kinetic equation was used to study the kinetics of photodegradation of ACG dye.

$$\ln(C_0/C_f) = Kt \quad (2)$$

where, C_0 = initial concentration of dye solution (in ppm), C_f = final concentration of dye solution at time t (in ppm), k = pseudo-first order rate constant for degradation of dye (in min.^{-1}).

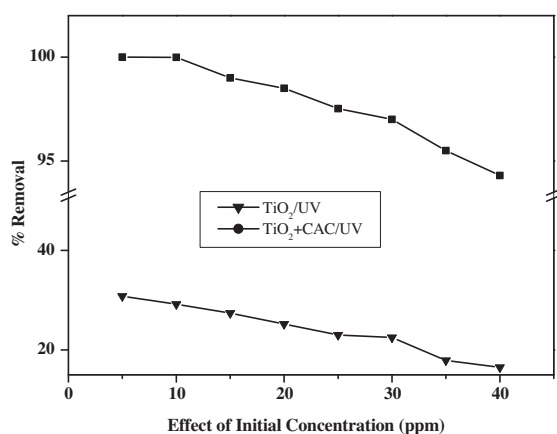


Figure 4 Effect of initial concentration of ACG dye in the presence and absence of CAC [Contact time: 90 min; Dose of the catalyst: TiO_2 -200 mg and CAC-40 mg].

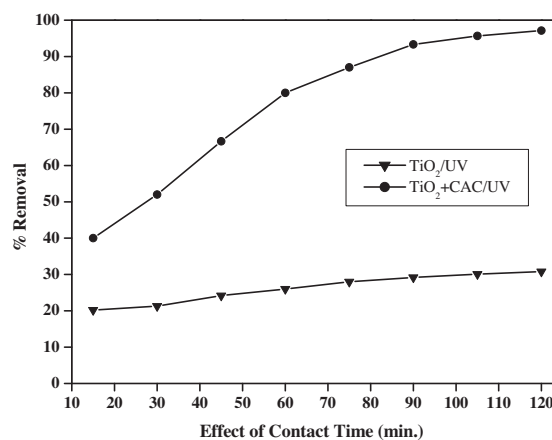


Figure 5 Effect of Irradiation time of ACG dye in the presence and absence of CAC [Initial concentration of ACG: 30 ppm; Dose of the catalyst: TiO_2 -200 mg and CAC-40 mg].

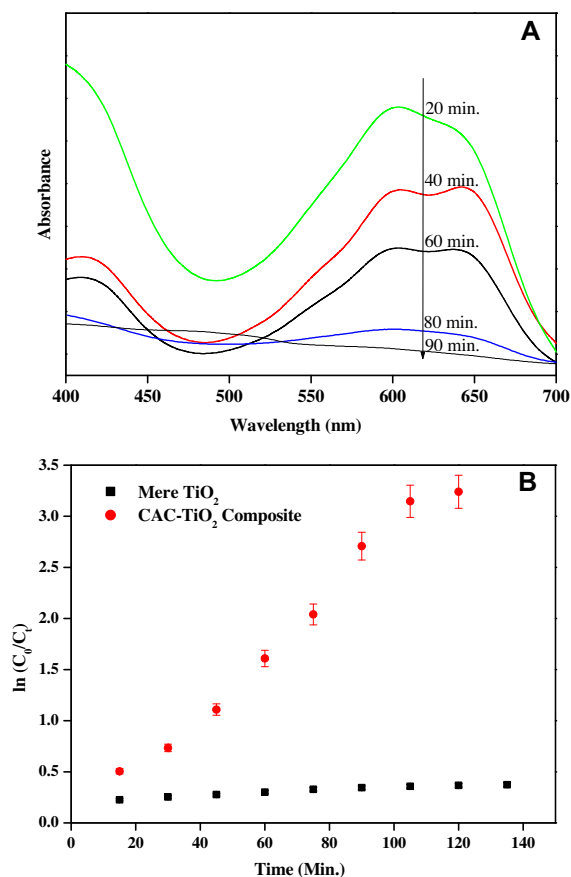


Figure 6 UV-vis absorption spectra (A) and Kinetics (B) of ACG dye degradation in the presence and absence of CAC.

The degradation experiments by UV irradiation of ACG dye containing TiO₂ in the presence and absence of CAC follow pseudo-first-order kinetics with respect to the irradiation time (t) (Fig. 6b). The value of $\ln(C_0/C_t)$ is plotted against time (in min.,) and the plots were found to be linear. From the slope, the rate constants were calculated for the degradation of ACG dye in the presence and absence of CAC. The pseudo first order rate constant (k in min^{-1}) for TiO₂ in the absence of CAC is 0.00368 and for CAC-TiO₂ is 0.0666. The degradation efficiency of the ACG dye on CAC-TiO₂ composite is eighteen times higher than that of mere TiO₂. These results indicate the synchronous role of CAC on the photocatalytic degradation of ACG in the presence of TiO₂. The enormous enhancement in the photodegradation efficiency for CAC-TiO₂ is due to porous frameworks which link mutually and coexist to form unique composite-walls, providing unprecedented spaces for “the synchronous role of coupled adsorption and photocatalytic oxidation”. CAC is an excellent adsorbent, providing better adsorption centers and enriching dye pollutant molecules; while TiO₂ behaves as photocatalytic active sites to oxidize the dye molecules pre-enriched by the surrounding CAC. Moreover, the high accessible surface areas can provide more adsorptive and photocatalytically active sites; and the pore channels allow the reactive molecules to diffuse more easily both into and out of the inner surfaces before and after photocatalytic reactions (Muthirulan et al., 2012a,b).

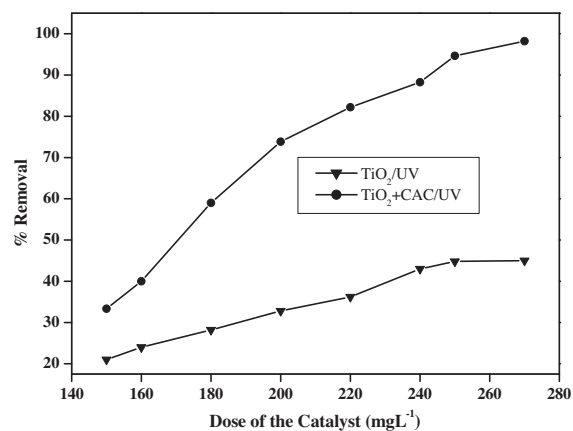


Figure 7 Effect of dose of ACG dye in the presence and absence of CAC [Initial concentration of ACG: 30 ppm; Contact time: 90 min].

3.5. Effect of dose of the catalyst on photodegradation of ACG

The effect of ACG dye decolorization using both the catalyst (CAC and TiO₂) separately (alone) by varying their amount in the AC-TiO₂ mixture. Fig. 7 shows the optimized condition of the effect of dose of the catalyst. The plot of percentage removal versus dose of the catalyst is found to be exponential for both the ACG-TiO₂ and ACG-TiO₂-CAC systems. Increasing the dose of CAC and keeping the dose of TiO₂ as constant in the CAC-TiO₂ mixture leads adsorption of ACG dye and this process is favor and limited only certain level of concentrations (at low concentrations) and tends to become saturated (at higher concentrations). This may be due to reduction in immediate solute adsorption, owing to the lack of available active sites on the adsorbents' surface compared to the relatively large number of active sites required for high concentrations of dye.

Moreover, it should be pointed out that, the catalyst loading affects number of active sites on the photocatalyst and the penetration of radiation through the suspension. As the catalyst loading increases the % removal of ACG dye decreases due to the enhancement of light reflectance by CAC. The number of active sites increases but the penetration of radiation decreases due to shielding effect. Photocatalytic degradation rate, which is influenced by both the number of active sites and the penetration of irradiation light, must therefore pass through a maximum at optimum amount of catalyst. Also, the decrease in adsorption density with an increase in adsorbent amount is due to the high number of unsaturated adsorption sites. However, strong adsorption of pollutant molecules may inhibit subsequent photocatalytic reactions. But, increasing the dose of TiO₂ and keeping the dose of CAC in the CAC-TiO₂ mixture as constant, the photodegradation favors predominantly not only at lower concentrations but also at higher concentrations up to optimum level (1:5 ratio of CAC and TiO₂). This observation is understandable because too high loading of TiO₂ commonly results in the formation of agglomerated particles that have small active surfaces for catalytic performance (Muthirulan et al., 2012a,b).


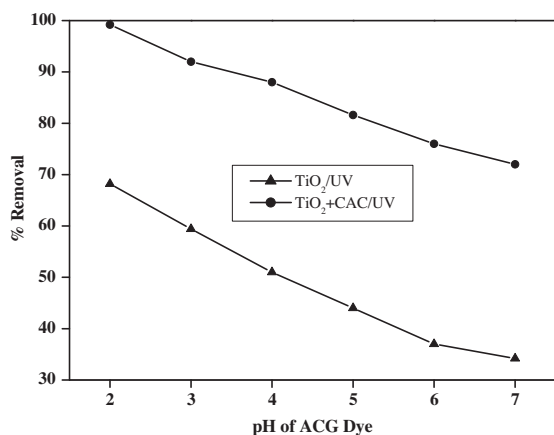


Figure 8 Effect of pH of ACG dye in the presence and absence of CAC [C_i : 30 ppm; Dose of the catalyst: TiO₂-200 mg and CAC-40 mg; Contact time: 90 min.].

3.6. Influence of solution pH on photodegradation of ACG

Wastewaters from textile industries usually have a wide range of pH values. Usually, pH plays an important role in the characteristics of dye wastewaters and is one of the most important parameters that influence the photo-oxidation processes. The effect of the initial solution pH on the photocatalytic decolorization is presented in Fig. 8. The ACG dye decolorization percentages increase with a decrease in the initial pH of the dye solution at optimum concentration of dye, dose of the catalyst and time of irradiation under UV irradiation. The effect of pH on the dye photocatalytic decolorization is difficult to explain since it had multiple roles. First, it was related to the surface-charge properties of the photocatalysts, and could be explained based on the point of zero charge (pzc).

The point of zero charge (pzc) of TiO₂ is 6.2. In acidic media (pH < 6.2) the surface of TiO₂ is positively charged, whereas, it is negatively charged under alkaline conditions (pH > 6.2) according to Eqs. (3) and (4),



ACG is negatively charged due to the sulfonated groups which are ionized in water; their electrostatic attraction to the composite surface is favorable in acidic solution and forbidden in alkaline media due to the columbic repulsion between the negatively charged surface of TiO₂ and the negatively charged dye molecules. Thus, the reaction rate reached a maximum value at very low pH. Moreover, the generation of OH⁻ radicals by the effect of UV-light on TiO₂ of the composite may also be the factor responsible for increasing reaction rate in an acidic environment. In strong alkaline medium (pH < 7) such radical species are rapidly scavenged and therefore the reaction rate decreases. Hence, the degradation is very efficient at low pH on both TiO₂/UV and TiO₂ + CAC/UV systems (Muthirulan et al., 2012a,b).

3.7. Decolorization mechanism

The ACG removal by photodegradation in the presence of CAC is higher than that obtained by the sum of the contribu-


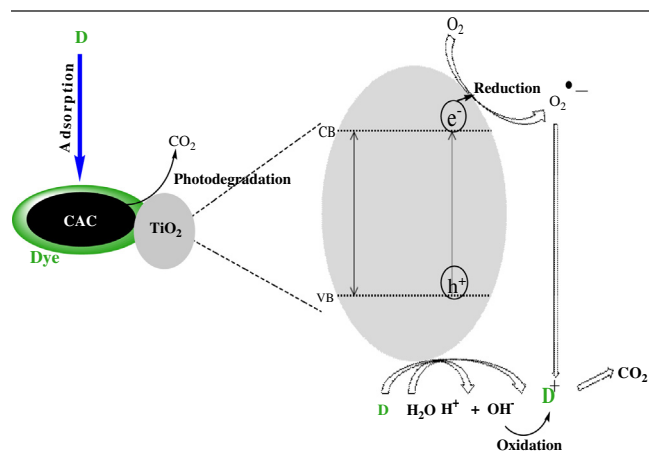


Figure 9 Photodegradation mechanism of ACG degradation on CAC-TiO₂.

tion of photodegradation and subsequent adsorption indicating, a synergistic effect. The mechanism of photodegradation on TiO₂ in the presence of CAC is shown in Fig. 9. In heterogeneous photocatalysis, the liquid phase organic compounds are degraded to its corresponding intermediates and further mineralized to carbon dioxide and water, if the irradiation time is extended.

The overall photocatalysis reaction as portrayed as follows

- Mass transfer of the organic contaminant(s) in the liquid phase to the TiO₂ surface.
- Adsorption of the organic contaminant(s) onto the photon activated TiO₂ surface photocatalysis reaction for the adsorbed phase on the TiO₂ surface.
- Desorption of the intermediate(s) from the TiO₂ surface.
- Mass transfer of the intermediate(s) from the interface region to the bulk fluid.



The proposed mechanism of synergistic enhancement in AC-TiO₂ composites is shown in Fig. 9 and the explanations are as follows: (i) Adsorption onto the AC provides a high concentration of reactants near TiO₂, which may then be photocatalyzed, possibly passing through intermediate stages; (ii) In the absence of adsorbent AC, reactants must collide with TiO₂ by chance, and remain in contact for the photocatalysis to proceed. When this is not achieved, the reactants or intermediate products will pass back into solution and can only react further when they collide with TiO₂ again. In other words, CAC and TiO₂, which link mutually and coexist to form unique mixtures, owning coupled performances of “adsorption-photocatalysis oxidation” and providing unprecedented spaces for the “synchronous role” (Muthirulan et al., 2012a,b), Leary and Westwood, 2011; Velasco et al., 2010; Tryba et al., 2003).

3.8. Desorption studies

After 90 min of photodegradation experiment, the residue of CAC-TiO₂ composite was separated and immersed in 4 mL of ethanol under ultrasonication for 20 min. Then the filtrate

was collected and analyzed by UV–vis spectrophotometer. The UV–vis spectrum (figure not shown) of filtrate in ethanol solution does not show any significant peak corresponding to ACG dye (disappearance absorption peak), which confirms that the removal of color is due to photodegradation and not by adsorption. This result clearly illustrates that molecules of ACG that have been adsorbed and accumulated on CAC during the initial photocatalytic degradation are able to be transferred to TiO₂ where they are decomposed under irradiation. Continuous migration and subsequent photocatalytic oxidation on the surface of TiO₂ accelerated ACG removal efficiency greatly. This transfer occurs through the CAC–TiO₂ interface with the concentration gradient as the driving force.

From the above studies we conclude that the decolorization of ACG dye is due to the photodegradation process and not by pure adsorption and the enhancement of photodegradation efficiency is due to synergistic or cooperative effect.

4. Conclusions

In conclusion, our results showed that the synergetic roles of coupled adsorption and photocatalytic oxidation remarkably enhance the activities, but the synchronous role generates excellent degradation activity of ACG, which is much lower than that of commercial TiO₂ photocatalyst. The results depict that the pores frameworks consist of CAC and TiO₂, which link mutually and coexist to form unique mixtures, possessing coupled performances of “adsorption-photocatalysis oxidation” and providing unprecedented spaces for the “synchronous role”. The results of the present study imply the rational viability of using CAC–TiO₂ in the presence of UV light for ecofriendly mineralization of ACG dye in textile waste water treatment.

Acknowledgement

The authors thank the Management and Principal of Ayya Nadar Janaki Ammal College for providing research facilities and constant encouragement.

References

Al-Degs, Y.S., El-Barghouthi, M.I., El-Sheikh, A.H., Walker, G.M., 2008. Effect of solution pH, ionic strength, and temperature on adsorption behavior of reactive dyes on activated carbon. *Dyes Pigm.* 77, 16–23.

Barka, N., Qourzal, S., Assabbane, A., Nounah, A., Ichou, Y.A., 2010. Photocatalytic degradation of an azo reactive dye reactive yellow 84, in water using an industrial titanium dioxide coated media. *Arab. J. Chem.* 3, 279–283.

Chen, K., Li, J., Li, J., Zhang, Y., Wang, W., 2010. Synthesis and characterization of TiO₂-montmorillonites doped with vanadium and/or carbon and their application for the photodegradation of

sulphorhodamine B under UV–vis irradiation. *Colloids Surf., A* 367, 47–56.

Demirbas, E., Kobya, M., Sulak, M.T., 2008. Adsorption kinetics of a basic dye from aqueous solutions onto apricot stone activated carbon. *Bioresour. Technol.* 99, 5368–5373.

Ding, Z., Zhu, H.Y., Lu, G.Q., Greenfield, P.F., 1999. Photocatalytic properties of titania pillared clays by different drying methods. *J. Colloid Interface Sci.* 209, 193–199.

Fernandez, A., Lassaletta, G., Jimenez, V.M., Justo, A., Gonzalez-Elipe, A.R., Herrmann, J.M., 1995. Preparation and characterization of TiO₂ photocatalysts supported on various rigid supports (glass, quartz and stainless steel): comparative studies of photocatalytic activity in water purification. *Appl. Catal., B* 7, 49–63.

Karadag, D., Akgul, E., Tok, S., Erturk, F., Kaya, M.A., Turan, M., 2007. Basic and reactive dye removal using natural and modified zeolites. *J. Chem. Eng. Data* 52 (2007), 2436–2441.

Leary, R., Westwood, A., 2011. Carbonaceous nanomaterials for the enhancement of TiO₂ photocatalysis. *Carbon* 49, 741–772.

Li, J.Y., Chen, C.C., Zhao, J.C., Zhu, H.Y., Orthman, J., 2002. Photodegradation of dye pollutants on TiO₂ nanoparticles dispersed in silicate under UV–vis irradiation. *Appl. Catal., B* 37, 331–338.

Li, J.Y., Ma, W.H., Lei, P.X., Zhao, J.C., 2007. Detection of intermediates in the TiO₂-assisted photodegradation of rhodamine B under visible light irradiation. *J. Environ. Sci.* 19, 892–896.

Liu, S.X., Chen, X.Y., Chen, X., 2007. A TiO₂/AC composite photocatalyst with high activity and easy separation prepared by a hydrothermal method. *J. Hazard. Mater.* 143, 257–263.

Lodha, S., Jain, A., Pinki, B., Punjabi, 2011. A novel route for waste water treatment: photocatalytic degradation of rhodamine B. *Arab. J. Chem.* 4, 383–387.

Muthirulan, P., Kannan, N., Meenakshi Sundaram, M., 2012a. Beneficial role of ZnO photocatalyst supported with porous activated carbon for the mineralization of alizarin cyanin green dye in aqueous solution. *J. Adv. Res.*, <http://dx.doi.org/10.1016/j.jare.2012.08.005>.

Muthirulan, P., Naganathan, G., Kannan, N., Meenakshi Sundaram, M., 2012b. Beneficial role of commercial activated carbon for the decoloration of Safranin dye on TiO₂ and ZnO/UV system for the application of effluents treatment from wastewater. *Indian J. Environ. Prot.* 32, 546–553.

Robinson, T., McMullan, G., Marchant, R., Nigam, P., 2001. Remediation of dyes in textile effluent: a critical review on current treatment technologies with a proposed alternative. *Bioresour. Technol.* 77, 247–255.

Salem, I.A., El-Maazawi, M.S., 2000. Kinetics and mechanism of colour removal of methylene blue with hydrogen peroxide catalyzed by some supported alumina surfaces. *Chemosphere* 41, 1173–1180.

Tryba, B., Morawski, A.W., Inagaki, M., 2003. Application of TiO₂-mounted activated carbon to the removal of phenol from water. *Appl. Catal., B* 4, 427–433.

Velasco, L.F., Parra, J.B., Ania, C.O., 2010. Role of activated carbon features on the photocatalytic degradation of phenol. *Appl. Surf. Sci.* 256, 5254–5258.

Velmurugan, R., Krishnakumar, B., Kumar, R., Swaminathan, M., 2012. Solar active nano-TiO₂ for mineralization of reactive red 120 and trypan blue. *Arab. J. Chem.* 5, 447–452.