



# Adsorption of isophorone and trimethyl-cyclohexanone on Pd(111): A combination of infrared reflection absorption spectroscopy and density functional theory studies



Karl-Heinz Dostert<sup>a</sup>, Casey P. O'Brien<sup>a</sup>, Wei Liu<sup>a,c</sup>, Wiebke Riedel<sup>a</sup>, Aditya Savara<sup>a</sup>, Alexandre Tkatchenko<sup>a</sup>, Swetlana Schauer mann<sup>a,b,\*</sup>, Hans-Joachim Freund<sup>a</sup>

<sup>a</sup> Fritz-Haber-Institut der Max-Planck-Gesellschaft, Faradayweg 4-6, 14195 Berlin, Germany

<sup>b</sup> Institut für Physikalische Chemie, Christian-Albrechts-Universität zu Kiel, Max-Eyth-Str. 2, 24118 Kiel, Germany

<sup>c</sup> Nano Structural Materials Center, School of Materials Science and Engineering, Nanjing University of Science and Technology, Nanjing 210094, Jiangsu, China

## ARTICLE INFO

Available online 4 February 2016

### Keywords:

Infrared spectroscopy

Density functional calculations

Palladium

Isophorone

Trimethylcyclohexanone

## ABSTRACT

Understanding the interaction of  $\alpha,\beta$ -unsaturated carbonyl compounds with late transition metals is a key prerequisite for rational design of new catalysts with desired selectivity towards C = C or C = O bond hydrogenation. The interaction of the  $\alpha,\beta$ -unsaturated ketone isophorone and the saturated ketone TMCH (3,3,5-trimethylcyclohexanone) with Pd(111) was investigated in this study as a prototypical system. Infrared reflection-absorption spectroscopy (IRAS) and density functional theory calculations including van der Waals interactions (DFT + vdW<sup>surf</sup>) were combined to form detailed assignments of IR vibrational modes in the range from 3000  $\text{cm}^{-1}$  to 1000  $\text{cm}^{-1}$  in order to obtain information on the binding of isophorone and TMCH to Pd(111) as well as to study the effect of co-adsorbed hydrogen. IRAS measurements were performed with deuterium-labeled ( $d_5$ -) isophorone, in addition to unlabeled isophorone and unlabeled TMCH. Experimentally observed IR absorption features and calculated vibrational frequencies indicate that isophorone and TMCH molecules in multilayers have a mostly unperturbed structure with random orientation. At sub-monolayer coverages, strong perturbation and preferred orientations of the adsorbates were found. At low coverage, isophorone interacts strongly with Pd(111) and adsorbs in a flat-lying geometry with the C = C and C = O bonds parallel, and a CH<sub>3</sub> group perpendicular, to the surface. At intermediate sub-monolayer coverage, the C = C bond is strongly tilted, while the C = O bond remains flat-lying, which indicates a prominent perturbation of the conjugated  $\pi$  system. Pre-adsorbed hydrogen leads to significant changes in the adsorption geometry of isophorone, which suggests a weakening of its binding to Pd(111). At low coverage, the structure of the CH<sub>3</sub> groups seems to be mostly unperturbed on the hydrogen pre-covered surface. With increasing coverage, a conservation of the in-plane geometry of the conjugated  $\pi$  system was observed in the presence of hydrogen. In contrast to isophorone, TMCH adsorbs in a strongly tilted geometry independent of the surface coverage. At low coverage, an adsorbate with a strongly distorted C = O bond is formed. With increasing exposure, species with a less perturbed C = O group appear.

© 2016 The Authors. Published by Elsevier B.V. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

## 1. Introduction

Chemo- and enantioselectivity in hydrogenation of  $\alpha,\beta$ -unsaturated carbonyls on transition metals is a widely discussed topic in the field of heterogeneous catalysis. Particularly important is the possibility to control the selective hydrogenation of  $\alpha,\beta$ -unsaturated ketones and aldehydes, which represent a broad class of valuable intermediates for

practically important processes [1–3]. For molecules containing both a C = C and a C = O  $\pi$ -bond, such as the  $\alpha,\beta$ -unsaturated ketone isophorone (3,3,5-trimethylcyclohex-2-enone), hydrogenation can yield either a saturated ketone, an unsaturated alcohol or a saturated alcohol. To avoid the formation of undesired products and thereby an often difficult and costly separation of the different products, a high selectivity towards hydrogenation of either the C = C or C = O bonds is desirable. Over Pd catalysts, the hydrogenation of the C = C bond of isophorone is strongly favored, yielding the saturated ketone TMCH (3,3,5-trimethylcyclohexanone) in high selectivity ( $\approx 100\%$ ) and almost no alcohols [4–6]. The origin of this chemoselectivity is, however, not fully understood.

\* Corresponding author at: Fritz-Haber-Institut der Max-Planck-Gesellschaft, Faradayweg 4-6, 14195 Berlin, Germany.

E-mail address: [schauer mann@fhi-berlin.mpg.de](mailto:schauer mann@fhi-berlin.mpg.de) (S. Schauer mann).

Not only a high chemoselectivity, but even a high enantioselectivity in hydrogenation reactions can be achieved over heterogeneous catalysts using chiral modifiers [7–10]. Compared to homogeneous catalysts traditionally applied for enantioselective reactions, the use of heterogeneous catalysts has operational, economical and often environmental advantages, so that heterogeneously catalyzed enantioselective hydrogenation has been recognized as a promising field of research. A number of different modifiers have been tested for the enantioselective hydrogenation of isophorone, which is a model compound for enantioselective hydrogenation of enones [7,11–18]. Although the origin of the enantioselective hydrogenation of isophorone is not well understood, Lambert et al. [19,20] have proposed a mechanism in which the stereochemistry of the chiral modifier and the adsorption geometry of isophorone on the Pd catalyst play a decisive role. More specifically, strong tilting of the unsaturated bonds on Pd was put forward to explain the enantioselective interaction of isophorone with the chiral modifier. To the best of our knowledge, the effects of isophorone coverage and co-adsorbed hydrogen on the isophorone adsorption geometry have not been investigated so far in surface science studies.

In our previous work we found that isophorone adsorbs in a flat-lying geometry with the C = C and C = O bonds parallel to the Pd(111) surface at low coverage [21,22]. Coverage dependent NEXAFS studies showed that the angles of both unsaturated bonds with respect to the surface increased with increasing isophorone coverage. The tilting is considerably more pronounced for the C = C bond, indicating a perturbation and strong structural distortion of the conjugated  $\pi$  system [22].

In this work, infrared reflection-absorption spectroscopy (IRAS) and density functional theory studies including van der Waals interactions (DFT + vdW<sup>surf</sup> [23]) were used to assign vibrational modes of isophorone, *d*<sub>5</sub>-isophorone, and TMCH as well as to study the effects of hydrogen co-adsorption. IRAS is a powerful tool not only for determining the vibrational frequencies of chemical bonds, but also – making use of the metal surface selection rule [24–26] – for probing their orientation with respect to the metal surface. Thus, the combination of IRAS studies at sub-monolayer coverages with DFT hold great potential to provide detailed insights into the interaction of isophorone and TMCH with Pd(111).

Our results show that IR absorption features of molecules at multi-layer coverages agree well with the calculated vibrational frequencies for unperturbed molecules. At sub-monolayer coverages, isophorone is strongly perturbed by interacting with the Pd(111) surface. Both the C = C and C = O bonds are oriented parallel to the surface and the CH<sub>3</sub> groups are oriented perpendicular to the surface. Strong perturbations of the isophorone molecule are observed on pristine Pd(111), however, this effect is reduced by preadsorbing hydrogen on Pd(111). In contrast to isophorone, TMCH adsorbs on Pd(111) with a strongly tilted C = O bond at low coverages.

## 2. Experimental details and methods

IRAS experiments were performed at the Fritz-Haber-Institut, Berlin, in a UHV apparatus that has been described in detail before [27]. Isophorone, *d*<sub>5</sub>-isophorone, or TMCH were dosed onto the sample cooled to 120 K through a doubly differentially pumped multi-channel array source controlled by valves and shutters. The surface was pre-covered with hydrogen by dosing 100 L of H<sub>2</sub> through a second doubly differentially pumped multi-channel array source controlled by valves and shutters. The sources were operated at room temperature, and the beam diameter was chosen to exceed the sample size. The Pd(111) single crystal was cleaned prior to use by repeated cycles of Ar<sup>+</sup> ion bombardment at room temperature, annealing at 1000 K and oxidation in  $1 \cdot 10^{-6}$  mbar O<sub>2</sub> at 750 K to remove residual carbon. The final cleaning cycle was stopped after annealing. The flatness and cleanliness of the Pd(111) single crystal surface were checked by low

energy electron diffraction (LEED) and infrared reflection-absorption spectroscopy (IRAS) of adsorbed CO. IRAS data were acquired using a vacuum Fourier-Transform infrared (FT-IR) spectrometer (Bruker IFS 66v/S) with a spectral resolution of 2 cm<sup>-1</sup> and using a mid-infrared (MIR) polarizer and p-polarized IR light. Isophorone (Acros Organics, 98%), *d*<sub>5</sub>-isophorone (Quotient Bioresearch (Radiochemicals) Limited, 90%) and TMCH (Aldrich, 98%) were purified prior to the experiments by repeated freeze–pump–thaw cycles. The stated exposures for IRAS experiments are given in fractions of a monolayer (ML) that were determined by TPD experiments.

The DFT calculations were carried out using the PBE + vdW<sup>surf</sup> method [28], as implemented in the FHI-aims all-electron code [29]. The PBE + vdW<sup>surf</sup> method, which accurately and effectively include the vdW interactions and dielectric screening within the bulk, has been demonstrated to perform very well for both strongly and weakly bound adsorption systems [30–32]. The “tight” settings were employed for integration grids and standard numerical atom-centered orbitals basis sets in FHI-aims code. The scaled zeroth-order regular approximation [33] was used to treat relativistic effects for Pd atoms. We built up four-layer Pd slabs with a (4 × 4) unit cell, and each slab was separated by a 20 Å vacuum. The bottom two metal layers were constrained, whereas the uppermost two metal layers and the adsorbate were allowed to fully relax during geometry relaxations. For slab calculations, we used a 3 × 3 × 1 k-points mesh. Based on the most stable geometries, infrared vibrational spectra were calculated by a second derivative of the energy from the numerical change of the forces arising from small finite displacements. Six finite displacements were applied to each of the atoms with a value of 0.005 Å. It should also be noted that our calculations were based on the harmonic approximations, while the experimental spectra were measured at 120 K. To scrutinize the feasibility of the calculated structures, we have also computed the *anharmonic* IR spectra for isophorone on Pd(111) using *ab initio* molecular dynamics simulations at 130 K. The simulations were run for up to 73 ps, and the calculated spectra on Pd(111) agree very well with the experimentally measured IR spectra showing a vanishing of C = O and C = C stretching modes as expected for a flat-lying isophorone [22].

For isophorone and TMCH molecules in gas phase, the infrared vibrational spectra were calculated based on the fully relaxed structures from the PBE + vdW method, as implemented in the FHI-aims code. In this code the infrared spectra were calculated by a second derivative of the energy from the numerical change of the forces arising from small finite displacements. Six finite displacements were applied to each of the atoms with a value of 0.005 Å.

## 3. Results and discussion

The adsorption of the unsaturated ketone isophorone (3,5,5-trimethylcyclohex-2-enon), deuterium substituted (*d*<sub>5</sub>-) isophorone, and the saturated ketone TMCH (3,5,5-trimethylcyclohexanone) on Pd(111) at 120 K was studied under well-defined UHV conditions by infrared reflection-absorption spectroscopy (IRAS). IR vibrational frequencies were calculated by the DFT + vdW<sup>surf</sup> method. The structural formulae of normal and *d*<sub>5</sub>-isophorone are shown in Fig. 1a and b. In *d*<sub>5</sub>-isophorone, the five hydrogen atoms attached to the C<sub>6</sub> ring are substituted by deuterium atoms, while the hydrogen atoms on the CH<sub>3</sub> groups were unlabeled. The structure of TMCH is shown in Fig. 1c). Molecular vibrations will be discussed according to the labeling of the ring positions and methyl groups as illustrated in Fig. 1. Ring positions are labeled with numbers 1 to 6, methyl groups are labeled with A, B, and C.

To the best of our knowledge, no detailed assignment of IR vibrations of isophorone or TMCH is available in literature. Therefore, we compare our experimental and theoretical assignments of IR vibrations to those of the same functional groups in other molecules. Among a large number of IR studies on hydrocarbons with identical groups, we chose some of the most fundamental investigations [35–52] for comparison.

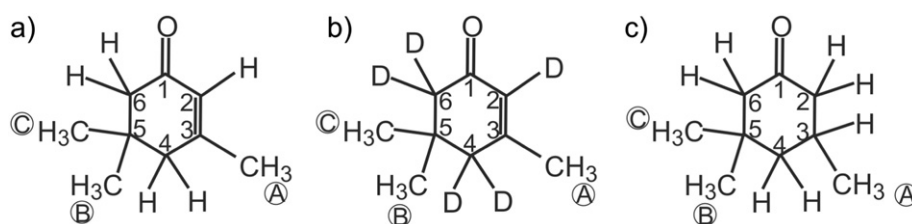


Fig. 1. Structures of the isophorone (a),  $d_5$ -isophorone (b) and TMCH (c).

We will briefly summarize only the most relevant results. An overview of typical vibrational frequencies of hydrocarbons can be found in a textbook by Colthup, Daly, and Wiberley [53]. In very early studies, Fox and Martin investigated CH<sub>3</sub>, CH<sub>2</sub>, and CH stretching vibrational modes from an experimental and theoretical point of view. The authors achieved a clear assignment of vibrational frequencies to CH<sub>3</sub>, CH<sub>2</sub>, and CH stretching modes in a large number of molecules. For instance, strong CH<sub>3</sub> stretching modes have been identified in several compounds near 2962 cm<sup>-1</sup> and 2872 cm<sup>-1</sup>. CH<sub>2</sub> stretching modes were typically observed near 2926 cm<sup>-1</sup> and 2853 cm<sup>-1</sup>. A CH stretching mode in olefins was assigned near 3019 cm<sup>-1</sup>, while the CH vibration in saturated compounds was observed at 2890 cm<sup>-1</sup> [35,36]. By using partially deuterium-labeled molecules, MacPhail et al. could distinguish CH<sub>3</sub> from CH<sub>2</sub> stretching modes in *n*-alkyl chains [38]. Studies on stretching modes of deuterium-labeled CD<sub>2</sub> groups are relatively rare. Nolin and Jones studied the IR absorption of normal and deuterium-substituted diethyl ketone. The authors assign CH<sub>3</sub> and CH<sub>2</sub> stretching and deformation vibrations as well as CD<sub>3</sub>, CD<sub>2</sub> and C = O stretching modes. CH<sub>3</sub> asymmetric stretching appeared at 2977 cm<sup>-1</sup> and 2936 cm<sup>-1</sup>, while the symmetric stretching was observed at 2883 cm<sup>-1</sup>. A CH<sub>2</sub> stretching mode was identified at 2902 cm<sup>-1</sup> and CD<sub>2</sub> stretching at 2173 cm<sup>-1</sup>. Moreover, the carbonyl (C = O) stretching mode was observed at 1720 cm<sup>-1</sup>. CH<sub>3</sub> asymmetric bending modes were assigned at 1461 cm<sup>-1</sup> and 1454 cm<sup>-1</sup> and the symmetric bending mode was observed at 1379 cm<sup>-1</sup>. The scissor vibrational mode of the CH<sub>2</sub> group was identified at 1414 cm<sup>-1</sup> and thus, at relatively low frequency. This is of particular interest for our study, since in both cases the CH<sub>2</sub> groups are located next to a C = O group [45]. More general, Snyder and Schachtschneider presented very extensive interpretations of IR spectra of *n*-alkanes at 3000–2800 cm<sup>-1</sup> and 1500–700 cm<sup>-1</sup> in an experimental [40] and a theoretical [39] study. Lavalley and Sheppard investigated IR absorption features in the C–H stretching region, which result from Fermi resonance between CH<sub>3</sub> asymmetric deformation overtones and CH<sub>3</sub> symmetric stretching fundamentals [52]. A detailed study on the vibrational modes of linear and branched aliphatic hydrocarbons in the range below 1500 cm<sup>-1</sup> was published by Sheppard et al. Some characteristic features were observed for non-linear molecules, such as a splitting of the CH<sub>3</sub> symmetric deformation into two bands for two CH<sub>3</sub> groups attached to the same saturated C atom [37]. Colthup found that this splitting is the result of an interaction force between two or three neighboring CH<sub>3</sub> groups. The same study shows that the exact wavenumber of CH<sub>3</sub>, CH<sub>2</sub>, and CH deformation vibrations is in general determined by the electron density at the respective C atom [41]. These references, along with DFT calculations from this work, form the basis for our assignment of infrared vibrational modes of isophorone and TMCH adsorbed on Pd(111).

In the following sections, we will first discuss the IR spectra of molecules in multilayers before focusing on coverage-dependent IR vibrations from multilayer to sub-monolayer coverage, where the interaction with the underlying palladium substrate becomes more important. Finally, the sub-monolayer structures of isophorone and TMCH will be compared. The comparison of the binding properties of isophorone and TMCH is of particular interest for catalysis, since hydrogenation of the C = C bond in isophorone yields TMCH.

### 3.1. IR vibrations in isophorone multilayers

In this section, we briefly discuss the IR spectra of multilayer-coverages of isophorone and  $d_5$ -isophorone on Pd(111). A more detailed assignment of molecular vibrations can be found in SI. The spectra are dominated by molecules organized in an ice structure, providing a reference for mainly non-perturbed molecules. DFT + vdW<sup>surf</sup> calculations were performed for non-perturbed molecules in the gas-phase. Fig. 2 displays the IR spectra of 3 ML of isophorone and  $d_5$ -isophorone on Pd(111) at 120 K. For both molecules, three main spectral regions can be distinguished: C–H stretching (3200–2800 cm<sup>-1</sup>), C = C and C = O stretching (1850–1550 cm<sup>-1</sup>), and C–H, C–D and C–C deformation (<1500 cm<sup>-1</sup>). C–D stretching vibrations (2300–2000 cm<sup>-1</sup>) in  $d_5$ -isophorone are not shown in Fig. 2.

The DFT-calculated vibrational frequencies agree well with those observed experimentally in the C = O stretching region, but the DFT-calculated IR spectrum was scaled by a factor of 0.945 with the origin at 1661 cm<sup>-1</sup> in order to compare the calculated vibrational frequencies to those observed experimentally in the 3100 cm<sup>-1</sup> to 1000 cm<sup>-1</sup> range. It has been observed before that calculated harmonic vibrational frequencies systematically deviate from experimental results, since effects of anharmonicity of the interaction potential are not taken into account and frequency scaling factors of  $\approx 0.9$  to 0.95 are typical [54]. For simplicity, we will give only the scaled DFT results in the text. The unscaled calculated DFT values are listed in Table 1 and Table 2. Note that a normal mode of a polyatomic molecule is a linear combination of several internal coordinates, such as bond angle bending and stretching. Since it is quite difficult to fully correctly describe a normal vibration consisting of a number of changing internal coordinates in a concise way, we decided to describe each calculated normal mode via the most pronounced internal coordinate(s) contributing to this vibration. It should be also noted that the experimentally measured IR spectra of the molecules adsorbed in the multilayers are compared to the

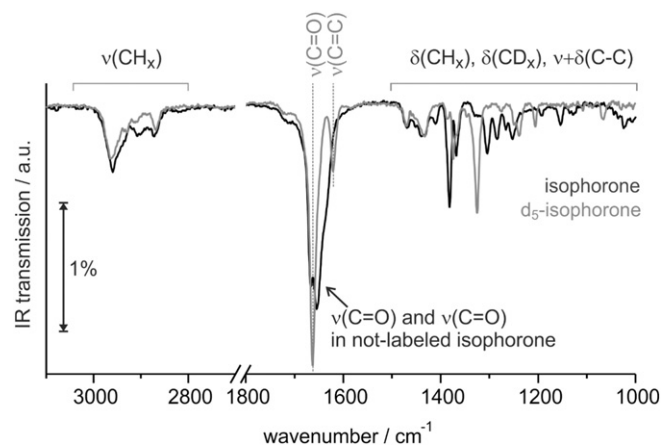


Fig. 2. IR spectra of 3 ML isophorone (black) and  $d_5$ -isophorone (gray) at 120 K on Pd(111). The region characteristic for C–H stretching vibrations (3100–2800 cm<sup>-1</sup>), C = O and C = C stretching vibrations (1800–1600 cm<sup>-1</sup>), and C–H and C–D deformation and C–C deformation and stretching vibrations (1500–1000 cm<sup>-1</sup>).

**Table 1**

Assignment of IR vibration frequencies from DFT calculations and IRAS experiments of normal isophorone and  $d_5$ -isophorone in the range of C = O, C = C, and C–H stretching vibrations (3100–1600  $\text{cm}^{-1}$ ). Vibration modes that strongly change when switching from normal to  $d$ -labeled isophorone are printed in bold. Vibration modes that are mostly independent from deuterium-labeling are printed with normal intensity.

	Most pronounced internal coordinate(s) of the normal mode	Vibrations isophorone/ $\text{cm}^{-1}$			Vibrations $d_5$ -isophorone/ $\text{cm}^{-1}$		
		DFT	DFT scaled	IRAS	DFT	DFT scaled	IRAS
	$\nu(\text{C} = \text{O})$	1661	1661	1665	1661	1661	1665
	$\nu(\text{C} = \text{C})$	<b>1624</b>	<b>1626</b>	<b>1655</b>	<b>1608</b>	<b>1610</b>	<b>1620</b>
A1	$\nu(\text{CH})$	3085	3006		2287	2253	
A2	$\nu_a(\text{CH}_3(\text{A}))$	3046	2970	2975–2930	3047	2971	2975–2930
A3	$\nu_a(\text{CH}_3(\text{C}))$	3032	2957		3034	2958	
A4	$\nu_a(\text{CH}_3(\text{B}))$	3021	2946		3024	2949	
A5	$\nu_a(\text{CH}_3(\text{B,C}))$	3016	2941		3021	2946	
A6	$\nu_a(\text{CH}_3(\text{B,C}))$ * + $\nu_a(\text{CH}_2(6))$	3011*	2937		3015	2941	
A7	$\nu_a(\text{CH}_3(\text{A}))$	2990	2917	2910	2990	2917	2910
A8	$2\delta(\text{CH}_3)$			2920–2890			2920–2890
A9	$\nu_a(\text{CH}_2(6))$ * + $\nu_a(\text{CH}_3(\text{B,C}))$	<b>3008*</b>	<b>2934</b>	$\approx 2940$	<b>2229</b>	<b>2198</b>	<b>2202</b>
A10	$\nu_a(\text{CH}_2(4))$	<b>2955</b>	<b>2884</b>	$\approx 2885$	<b>2187</b>	<b>2158</b>	<b>2184</b>
A11	$\nu_s(\text{CH}_3)$ (B,C) (in phase)	2949	2878	2874–2865	2957	2886	2874–2865
A12	$\nu_s(\text{CH}_3)$ (B,C) (out-of-phase)	2945	2874		2948	2877	
A13	$\nu_s(\text{CH}_3)$ (A)	2942	2872		2945	2874	
A14	$\nu_s(\text{CH}_2(6))$	<b>2928</b>	<b>2858</b>	$\approx 2820$	<b>2130</b>	<b>2104</b>	<b>2087–2079</b>
A15	$\nu_s(\text{CH}_2(4))$	<b>2908</b>	<b>2839</b>		<b>2124</b>	<b>2098</b>	

$\nu$ : stretch,  $\nu_a$ : asymmetric stretch,  $\nu_s$ : symmetric stretch.  
DFT scaling factor = 0.945.

DFT results obtained for the gas phase. Here, we made an approximation that the differences between the vibrational modes of the unperturbed molecules in the multilayers and in the gas phase are only minor. More accurate calculations should include effects arising from e.g. site symmetry effects, hydrogen-bonding etc., which will be subject of our future investigations.

The stretching modes are labeled with A1 to A15 and the deformation modes with B1 to B20. We will refer to the respective labels in the following discussion, in the tables, as well as in the IR spectra.

### 3.1.1. C = C and C = O stretching vibrations

The stretching modes of the C = O and the C = C bonds show very pronounced bands in the spectra displayed in Fig. 2. In normal isophorone, the most intense vibration is the C = O stretching mode at 1665  $\text{cm}^{-1}$ , which overlaps with the C = C stretching mode at 1655  $\text{cm}^{-1}$ . The C = C and C = O stretching bands are clearly separated in the IR spectrum of  $d_5$ -isophorone, in which the C = C stretching band appears at 1620  $\text{cm}^{-1}$ , exhibiting a shift of 35  $\text{cm}^{-1}$  compared to the unsubstituted molecule. The C = O stretching mode appears to be hardly affected by the substitution and remains essentially at the same frequency of 1665  $\text{cm}^{-1}$ . The DFT study indicates that the C = O stretching frequency is at 1661  $\text{cm}^{-1}$  for both molecules, while the C = C stretching is predicted to shift from 1624  $\text{cm}^{-1}$  in normal isophorone to 1608  $\text{cm}^{-1}$  in  $d_5$ -isophorone. Previously it has been reported that the C = O and C = C stretching vibrations in  $\alpha,\beta$ -unsaturated ketones overlap if the two bonds have *trans* orientation, such as in isophorone. The vibrational frequencies found in gas-phase studies of unlabeled molecules agree well with our results; C = O vibrations have been observed in the range of 1690–1655  $\text{cm}^{-1}$  and C = C stretching modes were observed in the 1649–1618  $\text{cm}^{-1}$  range [49,50,53]. Furthermore, the lower C = C stretching frequency in  $d_5$ -isophorone agrees well with previous studies, which found that the C = C stretching vibration is lowered by 10–20  $\text{cm}^{-1}$  for each substituted H atom at the C = C bond [51].

### 3.1.2. C–H and C–D Stretching Vibrations

Fig. 3 illustrates the experimental IR spectra of normal isophorone and  $d_5$ -isophorone in the range of the C–H and C–D stretching

vibrations. The C–H and C–D stretching modes show multiple bands and their assignment is more complex due to overlapping bands and weak dynamic dipole moments. A detailed discussion of the C–H and C–C asymmetric modes is presented in the SI. Briefly, our DFT study predicts six asymmetric and three symmetric stretching modes for the three  $\text{CH}_3$  groups, one asymmetric and one symmetric stretching vibration for each  $\text{CH}_2$  or  $\text{CD}_2$  groups, and one stretching mode for the CH or CD group. The computed frequencies and the experimentally observed IR vibrations are summarized in Table 1.

The DFT and IRAS results indicate that the stretching vibrations of the  $\text{CH}_3$  groups are mostly unaffected by the deuterium-substitution of the ring H atoms. The scaled DFT results show asymmetric stretching vibrations of the  $\text{CH}_3$  groups in normal isophorone between 2970  $\text{cm}^{-1}$  and 2917  $\text{cm}^{-1}$  (from 2971  $\text{cm}^{-1}$  to 2817  $\text{cm}^{-1}$  in  $d_5$ -isophorone) and symmetric stretching vibrations of the same groups in the range from 2878  $\text{cm}^{-1}$  to 2972  $\text{cm}^{-1}$  (2886–2874  $\text{cm}^{-1}$  in  $d_5$ -isophorone). Experimentally, broad IR absorption bands are observed from 2975  $\text{cm}^{-1}$  to 2930  $\text{cm}^{-1}$  and from 2874  $\text{cm}^{-1}$  to 2864  $\text{cm}^{-1}$  for both molecules.

Vibrational modes of the deuterium-substituted  $\text{CD}_2$  groups are found at much lower frequencies than those of the  $\text{CH}_2$  groups. The DFT-calculated frequencies of asymmetric  $\text{CH}_2$  stretching vibrations are 2934  $\text{cm}^{-1}$  and 2884  $\text{cm}^{-1}$ , while the same modes of the  $\text{CD}_2$  groups are 2198  $\text{cm}^{-1}$  and 2158  $\text{cm}^{-1}$ . Experimentally, IR absorption bands are found at 2940  $\text{cm}^{-1}$  and 2885  $\text{cm}^{-1}$  in normal isophorone as well as at 2202  $\text{cm}^{-1}$  and 2184  $\text{cm}^{-1}$  in  $d_5$ -isophorone. The symmetric stretching vibrations of the  $\text{CH}_2$  groups are found at 2858  $\text{cm}^{-1}$  and 2839  $\text{cm}^{-1}$  by DFT, while those of the  $\text{CD}_2$  groups appear at 2104  $\text{cm}^{-1}$  and 2098  $\text{cm}^{-1}$ . By IRAS, vibrations are observed near 2820  $\text{cm}^{-1}$  in normal isophorone and at 2087–2079  $\text{cm}^{-1}$  in  $d_5$ -isophorone.

### 3.1.3. Region of C–H and C–D deformation vibrations (<1500 $\text{cm}^{-1}$ )

IR spectra in the range of the deformation vibrations are illustrated in Fig. 4. The vibrational modes are summarized in Table 2. A detailed discussion can be found in the SI.

Asymmetric bending modes of the  $\text{CH}_3$  groups B and C are found between 1475  $\text{cm}^{-1}$  and 1445  $\text{cm}^{-1}$ , while the same modes of group A are observed between 1440  $\text{cm}^{-1}$  and 1430  $\text{cm}^{-1}$  for both molecules. Symmetric bending vibrations of all three  $\text{CH}_3$  groups appear between

**Table 2**

Assignment of IR vibration frequencies from DFT calculations and IRAS experiments of normal isophorone and  $d_5$ -isophorone in the C–H, C–D and C–C deformation and C–C stretching vibrations ( $1500\text{--}1000\text{ cm}^{-1}$ ). Vibration frequencies that strongly change when switching from normal to  $d$ -labeled isophorone are printed in bold. Vibration modes that are mostly independent from deuterium-labeling are printed with normal intensity.

	Most pronounced internal coordinate(s) of the normal mode	Vibrations isophorone/ $\text{cm}^{-1}$			Vibrations isophorone- $d_5/\text{cm}^{-1}$		
		DFT	DFT scaled	IRAS	DFT	DFT scaled	IRAS
B1	$\delta_a(\text{CH}_3(\text{B,C}))$	1458 1453	1469 1464	1475–1445	1457 1455	1468 1466	1475–1445
B2	$\delta_a(\text{CH}_3(\text{B,C}))$ * + $\delta_a(\text{CH}_2(4,6))$	1440* 1432*	1452 1445		1432 1429	1445 1442	
B3	$\delta_a(\text{CH}_3(\text{A}))^1$	1427 1423	1440 1436	1440–1430	1421 1419	1434 1432	1440–1430
<b>B4</b>	<b><math>\delta(\text{CH}_2(4,6))</math> (in-phase) * + <math>\delta_a(\text{CH}_3(\text{B,C}))</math></b>	<b>1409*</b>	<b>1423</b>	<b>1418–1408</b>	<b>1044</b>	<b>1078</b>	<b>1067</b>
<b>B5</b>	<b><math>\delta(\text{CH}_2(4,6))</math> (out-of-phase)</b>	<b>1397</b>	<b>1412</b>		<b>1035</b>	<b>1069</b>	
B6	$\delta_s(\text{CH}_3(\text{B,C}))$ (open-open)	1368	1384	1382	1365	1381	1385 1372
B7	$\delta_s(\text{CH}_3(\text{A}))$	1355	1372	1368	1351	1368	1368
B8	$\delta_s(\text{CH}_3(\text{B,C}))$ (open-close)	1347	1364		1344	1361	
B9	$\nu(\text{C6-C1-C2})$ $\nu(\text{C3-C4-C5})$				1290	1312	1325(?)
B10	$\Omega(\text{CH}_2(4))$ $\delta(\text{CH})$ $\nu(\text{C3-C4})$	1334	1352				
B11	$\Omega(\text{CH}_2(4,6))$ $\delta(\text{CH bend})$ $\nu(\text{C1-C2})$	1297	1317	1304			
B12	$\tau(\text{CH}_2(4))$ $\nu(\text{C6-C1-C2})$	1271	1292	1283			
<b>B13</b>	<b><math>\nu(\text{C-C})</math> in ring</b> <sup>a</sup> + $\Omega(\text{CH}_2(4))$ <sup>b</sup> + $\Omega(\text{CH}_2(6))$ <sup>c</sup> + $\delta(\text{CH})$ <sup>d</sup> + $\tau(\text{CH}_2(4))$ <sup>e</sup> + $\tau(\text{CH}_2(6))$	<b>1251<sup>a</sup></b> <b>1234<sup>a,b,c</sup></b> <b>1221<sup>c,d,e</sup></b>	<b>1274</b> <b>1257</b> <b>1245</b>	<b>1266</b> <b>1253</b>	<b>1223</b> <b>1214</b>	<b>1247</b> <b>1239</b>	<b>1250</b> <b>1239</b>
B14	$\nu(\text{C6-C1-C2})$ $\nu(\text{C5-CH}_3(\text{C}))$				1178	1205	1205
B15	$\nu(\text{C5-CH}_3(\text{B}))$ $\delta(\text{C-C})$ $\tau(\text{CH}_2(4))$	1170	1197	1192			
B16	$\tau(\text{CH}_2(4,6))$	1131	1159	1154			
B17	$\delta(\text{C-C})$ all bonds	1113	1143				
B18	$\tau(\text{CH}_2(6))$	1101	1131	1133–1123	889 774	931 822	
B19	$\tau(\text{CH}_2(4))$				832 821	878 867	
B20	$\rho(\text{CH}_3(\text{A,B,C}))$	1016 1002 988 972 929 920	1051 1038 1025 1010 969 961		1024 1011 989 933 920 909	1059 1047 1026 973 961 950	

$\nu$ : stretch,  $\delta$ : bend,  $\delta_a$ : asymmetric bend,  $\delta_s$ : symmetric bend,  $\omega$ : wag,  $\tau$ : twist,  $\rho$ : rock.  
DFT scaling factor = 0.945.

<sup>1</sup> Note that this band strongly shifts in the saturated ketone TMCH in which the immediate environment of  $\text{CH}_3(\text{A})$  is changed (see Table 4).

$1382\text{ cm}^{-1}$  and  $1368\text{ cm}^{-1}$ . The bending modes of the  $\text{CH}_2$  groups, however, are strongly affected by the deuterium substitution. In normal isophorone, DFT results show  $\text{CH}_2$  bending vibrations at  $1423\text{ cm}^{-1}$  and  $1412\text{ cm}^{-1}$ , while  $\text{CD}_2$  bending vibrations are  $1078\text{ cm}^{-1}$  and  $1069\text{ cm}^{-1}$ . Experimentally, IR absorption bands are observed at  $1418\text{--}1408\text{ cm}^{-1}$  for normal isophorone and near  $1067\text{ cm}^{-1}$  for  $d_5$ -isophorone.


### 3.2. Isophorone at sub-monolayer coverage

#### 3.2.1. Isophorone on pristine Pd(111)


Fig. 5 displays IR spectra of  $d_5$ -isophorone adsorbed on Pd(111) at 120 K at coverages ranging from the multilayer to the sub-monolayer regime. While the IR spectra of isophorone at multilayer coverages are

dominated by molecules in isophorone ice, the sub-monolayer spectra show the vibrations of isophorone molecules directly interacting with the Pd surface. The adsorption geometry of molecules on metal surfaces can be deduced from their IR spectra based on the metal surface selection rule (MSSR) [24,26]. According to the MSSR, only the component of a dynamic dipole moment perpendicular to the metal surface can be detected, while vibrations parallel to the surface are strongly attenuated by an image dipole in the metal substrate. Changes in the intensity distribution between C = C, C = O and C–H vibrations with decreasing isophorone coverage indicate the transition from a more random orientation in multilayers to a favored geometry of molecules attached to Pd(111).


At the lowest coverage of  $d_5$ -isophorone on Pd(111) (1/6 ML), there are significant absorption bands detected in the C–H stretching and

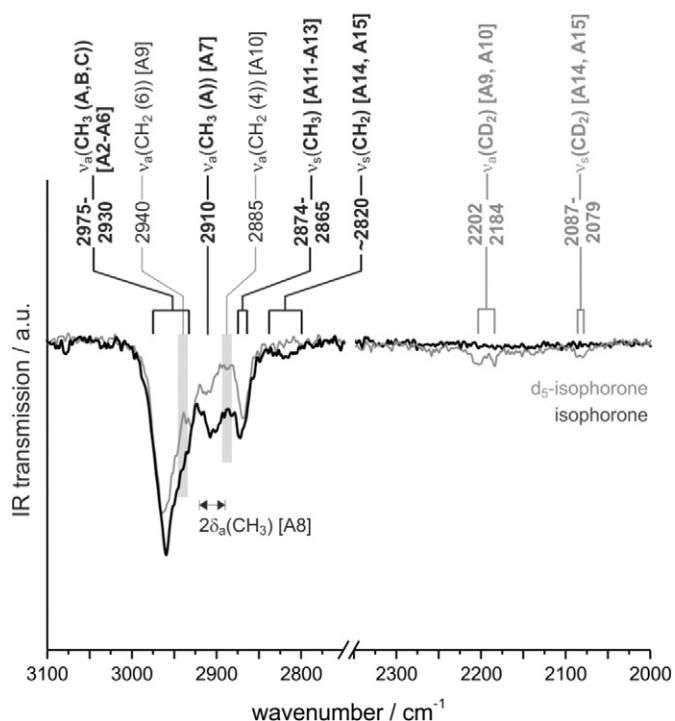

**Fig. 3.** IR spectra of 3 ML of normal and  $d_5$ -isophorone adsorbed at 120 K on Pd(111) from 3100 to 2750  $\text{cm}^{-1}$  (C–H stretching) and 2400–2000  $\text{cm}^{-1}$  (C–D stretching). Clearly assigned vibrations are indicated with bold printed labels, more tentative assignments are labeled with normal thickness.

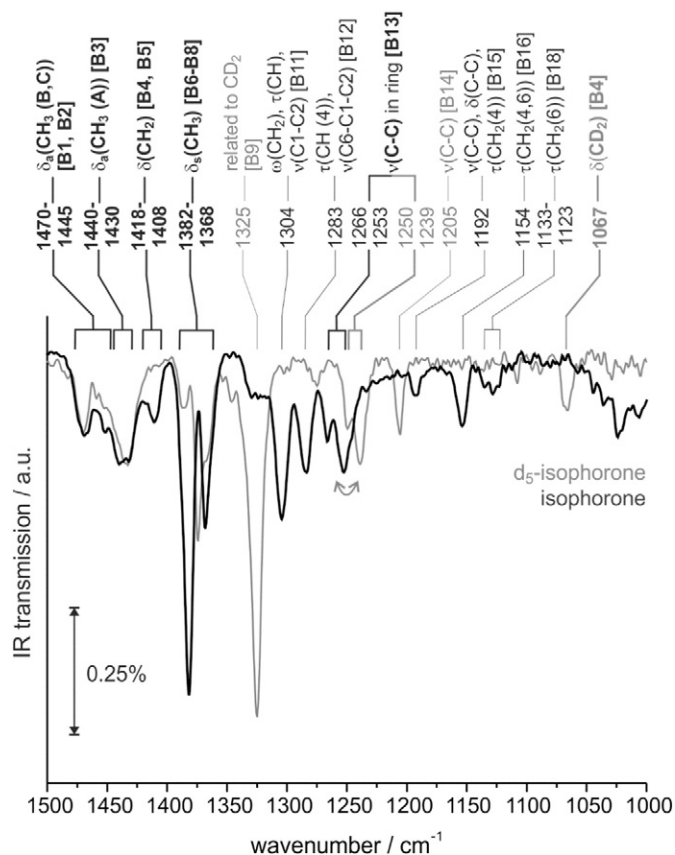


**Fig. 4.** IR spectra of 3 ML of normal and  $d_5$ -isophorone adsorbed at 120 K on Pd(111) from 1500 to 1000  $\text{cm}^{-1}$ . Clearly assigned vibrations are indicated with bold printed labels, more tentative assignments are labeled with normal thickness.

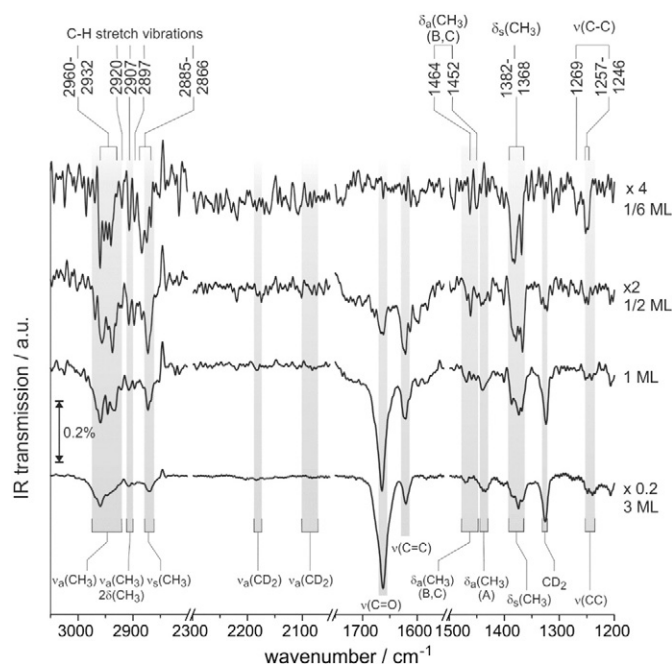

**Fig. 5.** IR spectra  $d_5$ -isophorone adsorbed at 120 K on Pd(111) from 3050 to 2800  $\text{cm}^{-1}$  (C–H stretching), 2300–2050  $\text{cm}^{-1}$  (C–D stretching), 1800–1600  $\text{cm}^{-1}$  (C = C and C = O stretching), and 1500–1000  $\text{cm}^{-1}$  (C–H, C–D, C–C deformation and C–C stretching) at different coverages. Vibrations in isophorone ice are indicated close to 3 ML spectrum (lowest trace). The wavenumbers of the IR vibrations at the lowest coverage (1/6 ML) (topmost trace) are given on top.

deformation regions; however, there are no band detected for the C = O or C = C stretching modes. This intensity distribution is in sharp contrast to the observation at multilayer coverage, where the most intense vibration is the C = O stretching mode. The absence of IR absorption in the C = O and C = C stretching region indicates that these bonds are either orientated parallel to the metal surface and cannot be seen in IRAS because of the MSSR or are strongly perturbed by the interaction with the Pd(111) surface. The orientation of the unsaturated C = C and C = O bonds has been studied in more detail by previous NEXAFS and IRAS experiments [22]. NEXAFS experiments confirmed that the C = C and C = O bonds stay intact, but are oriented parallel to the Pd(111) surface plane at a coverage of 0.2 ML. With increasing coverage, the intensities of the IR bands assigned to the C = O and C = C stretching vibrations strongly increase. For a coverage of 1/2 ML, the C = C stretching peak at 1620  $\text{cm}^{-1}$  is more pronounced than the C = O stretching band around 1665  $\text{cm}^{-1}$ . With further increasing coverage, the C = O stretching band increases rapidly and becomes the most intense peak at full monolayer coverage and above. The ratio of the C = O to C = C stretching vibration at multilayer coverage is ~6–8. The strong C = C stretching band and the low intensity of the C = O stretching band at 1/2 ML point to a strongly tilted C = C bond, while the orientation of C = O bond remains nearly parallel to the surface – this observation is in excellent agreement with our earlier NEXAFS study.

At sub-monolayer coverage, pronounced IR absorption is observed at 2960–2932  $\text{cm}^{-1}$  and at 2885–2866  $\text{cm}^{-1}$  and thus in the range of the CH<sub>3</sub> (and CH<sub>2</sub>) asymmetric and symmetric stretching modes. IR absorption was not been observed at 2885–2874  $\text{cm}^{-1}$  in multilayer isophorone. Further IR absorption features can be recognized at 2920  $\text{cm}^{-1}$ , 2907  $\text{cm}^{-1}$ , and 2897  $\text{cm}^{-1}$ . The absorption band at 2907  $\text{cm}^{-1}$  is most likely related to an overtone of a CH<sub>3</sub> asymmetric bending mode and will be discussed further in Section 3.2.2. Among the CH<sub>3</sub> bending modes, symmetric modes are intense at 1382–1368  $\text{cm}^{-1}$ , while the asymmetric modes are hardly detectable at

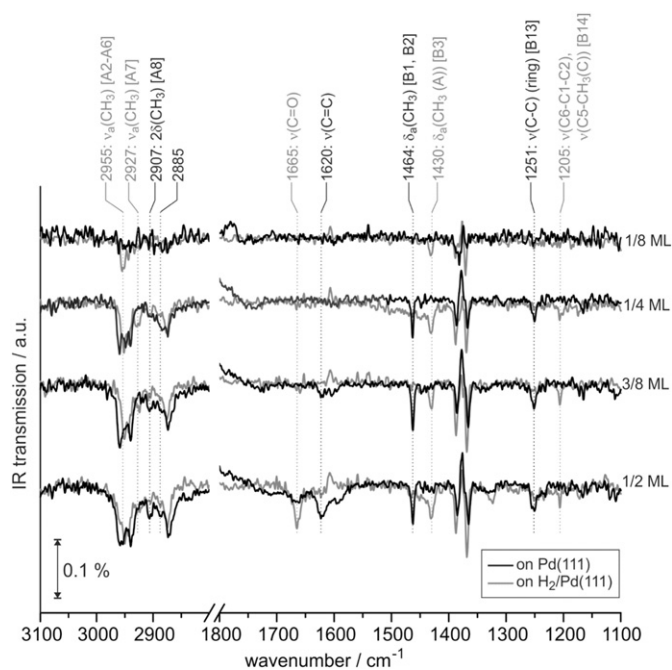

**Fig. 6.** IR spectra  $d_5$ -isophorone adsorbed at 120 K on Pd(111) (black traces) and on hydrogen pre-covered Pd(111) (gray traces) in the frequency range 3100–2800  $\text{cm}^{-1}$  (C–H stretching) and 1800–1600  $\text{cm}^{-1}$  (C = C and C = O stretching), 1500–1100  $\text{cm}^{-1}$  (C–H, C–D, C–C deformation and C–C stretching at sub-monolayer coverages). Vibrations that are more pronounced in isophorone on pristine Pd(111) are indicated with black labels, vibrations that are more pronounced on hydrogen pre-covered Pd(111) are indicated with gray labels.

1464  $\text{cm}^{-1}$  and 1452  $\text{cm}^{-1}$ . This intensity distribution between vibrations of the same functional group points to a strongly favored adsorption geometry, with some  $\text{CH}_3$  dynamic dipole moments parallel to the metal surface and others strongly inclined with respect to the surface plane. In fact, a strong dynamic dipole perpendicular to the surface for the symmetric bending mode and parallel dipole moment for the asymmetric bending mode points to a  $\text{CH}_3$  group which is facing away from the surface and is strongly inclined with respect to the C = C = O plane of isophorone. IR absorption bands near 2885–2874  $\text{cm}^{-1}$ , which are unique for low coverage, could either point to a shifted  $\text{CH}_3$  symmetric stretching frequency and thus to a perturbation of a  $\text{CH}_3$  group; or to a  $\text{CH}_2$  asymmetric stretching mode and thus to dehydrogenation of a  $\text{CH}_3$  group. Note that intact  $d_5$ -isophorone molecules do not have unlabeled  $\text{CH}_2$  groups.

### 3.2.2. Isophorone on hydrogen pre-covered Pd(111)

In order to study the effect of co-adsorbed hydrogen on the interaction of isophorone with Pd(111), the Pd(111) surface was pre-exposed to 100 L  $\text{H}_2$  at 120 K. Previously it has been shown that  $\text{H}_2$  rapidly dissociates on the Pd(111) surface, forming a  $1 \times 1$  overlayer of H atoms adsorbed on threefold-hollow sites (formal surface coverage: 1 H atom per 1 Pd surface atom) [55–57]. Note that no subsurface hydrogen species can be formed under these conditions. Fig. 6 shows IR spectra of  $d_5$ -isophorone adsorbed on pristine Pd(111) (black traces) and on hydrogen-saturated Pd(111) (red traces) at 120 K, with  $d_5$ -isophorone coverages ranging from 1/8 ML to 1/2 ML. While the spectra of  $d_5$ -isophorone multilayers on pristine and hydrogen pre-covered Pd(111) are similar, significant differences are observed at sub-monolayer coverages. Black labels indicate IR absorption bands that are more pronounced on the clean Pd(111) surface, gray labels mark peaks having higher intensity on hydrogen pre-covered Pd(111) in the low coverage limit.

At the lowest coverages, clearly different C–H vibrational modes appear on pristine and hydrogen pre-covered Pd(111). Stronger IR absorption of isophorone on hydrogen pre-covered Pd(111) is observed at 2955  $\text{cm}^{-1}$  and 2927  $\text{cm}^{-1}$  ( $\text{CH}_3$  asymmetric stretching modes) and at 1430  $\text{cm}^{-1}$  (the  $\text{CH}_3$  asymmetric bending mode of group A). In contrast, on pristine Pd(111), peaks appear in the C–H stretching region at 2907  $\text{cm}^{-1}$  and 2885  $\text{cm}^{-1}$ . The vibrational band at 2907  $\text{cm}^{-1}$  is most likely related to the overtone of the  $\text{CH}_3$  asymmetric bending mode at 1464  $\text{cm}^{-1}$ , which is also unique for molecules on pristine Pd(111). Moreover, the C–C stretching modes near 1251  $\text{cm}^{-1}$  are more pronounced on the clean surface, while the mode at 1205  $\text{cm}^{-1}$  is more intense on the hydrogen pre-covered surface.

According to the MSSR we conclude that the different distribution of IR absorption intensities on pristine and  $\text{H}_2$  pre-covered Pd(111) point to different adsorption geometries of isophorone on both surfaces. Especially the differences in the C–H stretching modes indicate significant changes in the orientation of the  $\text{CH}_3$  groups with respect to the surface in the presence of hydrogen. Furthermore, not only geometric effects, but also perturbation and/or chemical transformation of isophorone could yield different spectroscopic signatures on each surface. The IR absorption near 2885  $\text{cm}^{-1}$ , which is unique for isophorone on pristine Pd(111) at low coverage, might point to conversion of a  $\text{CH}_3$  to a  $\text{CH}_2$  group. This pathway seems to be suppressed in the presence of  $\text{H}_2$ .

Note that the relative intensities of the C–H vibrational bands might slightly differ for different measurements at nominally the same surface coverage, which might be due to the strong dipole coupling effects and/or variation of the surface coverage.

### 3.3. IR vibrations and adsorption of TMCH

The product of C = C bond hydrogenation in isophorone is the saturated ketone 3,3,5-trimethylcyclohexanone (TMCH). In this section, we assign the IR vibrational modes of TMCH adsorbed on Pd(111) for comparison to isophorone.

#### 3.3.1. Assignment of vibrations in TMCH multilayers

As discussed above, scaling the DFT-calculated IR spectra is necessary to fit the calculated values to the experimentally observed IR vibrations. In the following discussion, DFT results are scaled by the factor 0.954 around 1630  $\text{cm}^{-1}$ . The unscaled values can be found in Table 3 and Table 4. Stretching modes of TMCH are labeled with C1 to C15 and deformation modes with D1 to D28. We refer to the respective labels in the following discussion, in the tables, as well as in the IR spectra. A comparison of the IR spectra of TMCH and isophorone multilayers is shown in Fig. 7. Most importantly, there are two different peaks in the C = O stretching region that likely result from different TMCH species. We assign the strong peak at 1713  $\text{cm}^{-1}$  to C = O stretching in TMCH ice since it grows continuously with increasing exposure, and the band at 1648  $\text{cm}^{-1}$  to a C = O stretching mode from sub-monolayer TMCH. These peaks will be discussed in more detail in the following section.

The vibrational modes of TMCH are summarized in Table 3. The IR spectrum of multilayer TMCH on Pd(111) is plotted together with the IR spectrum of the same coverage of isophorone in Fig. 7. Fig. 7 also shows the assignment of selected vibrational modes. For a detailed discussion of the vibrational modes of TMCH we refer to the SI.

#### 3.3.2. TMCH at sub-monolayer coverage

Fig. 8 shows IR spectra of TMCH on Pd(111) at 120 K from 1800  $\text{cm}^{-1}$  to 1200  $\text{cm}^{-1}$  at different coverages. The coverage-dependent evolution of IR absorption features gives detailed insights into the binding and the geometry of TMCH on Pd(111). According to the MSSR, only the projection of the dynamic dipole moment perpendicular to the surface can be measured by IRAS.

The IR absorption intensities in the C–H stretching (not shown here) and the C–H deformation regions grow roughly monotonically with

**Table 3**Assignment of IR vibrations of TMCH from DFT and IRAS studies in the range of the C = C, C = O, and C–H stretching vibrations (3100–1600 cm<sup>-1</sup>).

	Most pronounced internal coordinate(s) of the normal mode	Vibrations TMCH/cm <sup>-1</sup>		
		DFT	DFT scaled	IRAS
C1	$\nu(\text{C}=\text{O})$	1693	1690	1713
	$\nu(\text{C}=\text{O})$			1648
C2	$\nu_a(\text{CH}_3(\text{B}))$	3026	2962	2975–2940
C3	$\nu_a(\text{CH}_3(\text{A}))$	3023	2959	
C4	$\nu_a(\text{CH}_3(\text{B}))$	3021	2957	
	$\nu_a(\text{CH}_3(\text{C}))$			
C5	$\nu_a(\text{CH}_2(6))$			
	$\nu_a(\text{CH}_2(2))$	3018	2954	
C6	$\nu_a(\text{CH}_3(\text{A,C}))$			
	$\nu(\text{CH}(3))$			
C7	$\nu_a(\text{CH}_3(\text{B}))$	3016	2952	
	$\nu_a(\text{CH}_3(\text{C}))$			
C8	$\nu_a(\text{CH}_2(2,6))$			
	$\nu_a(\text{CH}_3(\text{C}))$	3013	2949	
C9	$\nu_a(\text{CH}_3(\text{B}))$			
	$\nu_a(\text{CH}_2(6))$			
C10	$\nu_a(\text{CH}_3(\text{A}))$	3012	2948	
	$\nu_a(\text{CH}_2(6))$			
C11	$\nu_a(\text{CH}_3(\text{C}))$			
	$\nu_a(\text{CH}(3))$			
C12	$\nu_a(\text{CH}_2(2))$			
	$\nu_a(\text{CH}_2(4))$	2967	2905	2913
C13	$\nu(\text{CH}(3))$			
	$\nu_s(\text{CH}_3(\text{B}))$	2953	2892	2880–2865
C14	$\nu_s(\text{CH}_3(\text{A}))$	2946	2885	
C15	$\nu(\text{CH}(3))$			
	$\nu_s(\text{CH}_3(\text{C}))$	2943	2883	
C16	$\nu(\text{CH}(3))$	2936	2876	
	$\nu_s(\text{CH}_2(2,4,6))$			
C17	$\nu_s(\text{CH}_2(6))$	2931	2871	
	$\nu_s(\text{CH}_2(2))$	2916	2857	
C18	$\nu_s(\text{CH}_2(4))$			
	$\nu(\text{CH}(3))$			
C19	$\nu_s(\text{CH}_2(4))$	2912	2853	≈ 2840
	$\nu_s(\text{CH}(3))$			
C20	$\nu_s(\text{CH}_2(2))$			
	$\nu_s(\text{CH}_2(2))$			

 $\nu$ : stretch,  $\nu_a$ : asymmetric stretch,  $\nu_s$ : symmetric stretch.

DFT scaling factor = 0.954.

increasing TMCH exposure. In the C = O stretching region, however, there are non-trivial changes in the bands observed with increasing TMCH exposure. At the lowest TMCH exposure (1/12 ML), a sharp band at 1648 cm<sup>-1</sup> is detected and a smaller, broad band is observed at 1747 cm<sup>-1</sup>. The band at 1648 cm<sup>-1</sup> grows slightly with increasing exposure and is saturated at 1/6 ML exposure. The band at 1747 cm<sup>-1</sup> does not change intensity up to 1/3 ML, and then disappears at coverages greater than 1/3 ML. A small band at 1701 cm<sup>-1</sup> appears at 1/6 ML exposure and increases slightly in intensity up to 1/3 ML, but does not appear to grow further with increasing exposure. At 1/2 ML exposure, a bands at 1713 cm<sup>-1</sup> appears and continues to grow with increasing exposure.

The IRAS series shown in Fig. 8 gives valuable information about the interaction of TMCH with the Pd(111) substrate. First, there are several different peaks in the C = O stretching region that likely result from different TMCH species. We can assign the strong band at 1713 cm<sup>-1</sup>, which grows continuously with increasing exposure beyond 1/2 ML, to C = O stretching in TMCH ice. We assign the band at 1648 cm<sup>-1</sup>, which is observed at the lowest exposure (1/12 ML) and is saturated by 1/6 ML, to a C = O stretching mode from sub-monolayer TMCH. The C = O stretching modes at 1701 cm<sup>-1</sup> and 1747 cm<sup>-1</sup> are most likely related to TMCH species in the intermediate coverage range between sub-monolayer and multilayer ice, probably the second layer. Finally, the strong intensity of the C = O vibration at 1648 cm<sup>-1</sup> even at the lowest TMCH exposure (1/12 ML) indicates that the C = O bond in TMCH is strongly tilted with respect to the Pd(111) surface plane at sub-

monolayer coverage. These results indicate that at low coverage TMCH adsorbs close to perpendicularly to Pd(111) plane through the C = O group, strongly perturbing the C = O stretching vibration. With increasing TMCH coverage, several more TMCH species are formed, giving rise to new C = O vibrational bands. Second, the bands in the C–H stretching and the C–H deformation regions grow roughly monotonically with increasing TMCH exposure, and there is no indication that these vibrational modes are strongly affected by the Pd(111) substrate.

Below 1500 cm<sup>-1</sup>, all IR absorption features of TMCH become weaker with decreasing coverage. In contrast to isophorone, a selective disappearance of only some vibrations modes is not observed; the decrease in intensity is evenly distributed through all IR absorption features.

To better understand the influence of the Pd(111) substrate on the C = O stretching modes of TMCH, we have performed DFT calculations of the IR spectra of TMCH in the gas phase and of an isolated TMCH molecule adsorbed on Pd(111), which are shown in Fig. 9. The position of the calculated C = O stretching mode of gas-phase TMCH (1694 cm<sup>-1</sup>) is 83 cm<sup>-1</sup> higher in wavenumber than that of TMCH adsorbed on Pd(111) (1611 cm<sup>-1</sup>), indicating a strong perturbation of the C = O vibrational mode of TMCH by interaction with the Pd(111) surface. Also shown in Fig. 9 are the IR spectra of gas-phase TMCH from the NIST Chemistry WebBook [58] and TMCH (1.5 ML exposure at 120 K) adsorbed on Pd(111). The position of the calculated C = O vibrational band in gas-phase TMCH (1694 cm<sup>-1</sup>) is not the same as that of gas-phase TMCH from the NIST database (1730 cm<sup>-1</sup>). Also, the



**Table 4**Assignment of IR vibration modes of TMCH in the range from 1500 cm<sup>-1</sup> to 1000 cm<sup>-1</sup>.

	Most pronounced internal coordinate(s) of the normal mode	Vibrations TMCH/cm <sup>-1</sup>		
		DFT	DFT scaled	IRAS
D1	$\delta_s(\text{CH}_3(\text{B,C}))$	1457	1465	1475–1445
	$\delta_s(\text{CH}_3(\text{A}))$	1452	1459	
D2	$\delta_s(\text{CH}_3(\text{A}))$	1446	1455	
	$\delta_s(\text{CH}_3(\text{B,C}))$	1445	1454	
D3	$\delta_s(\text{CH}_3(\text{B,C}))$	1441	1450	
	$\delta_s(\text{CH}_3(\text{A}))$	1433	1442	
D4	$\delta(\text{CH}_2(4,6))$	1426	1435	1435–1410
	$\delta(\text{CH}_2(4))$			
	$\delta(\text{CH}_2(2,6))$			
D5	$\delta_s(\text{CH}_3(\text{B,C}))$	1410	1420	
	$\delta(\text{CH}_2(2,6))$			
	(in-phase)			
	$\delta(\text{CH}_2(4))$			
	(out-of-phase)			
D6	$\delta(\text{CH}_2(2,6))$	1403	1413	
	(out-of-phase)			
D7	$\delta_s(\text{CH}_3(\text{B,C}))$	1369	1381	1388
	(open-open)			1376
D8	$\delta_s(\text{CH}_3(\text{A}))$	1359	1371	1364
D9	$\delta_s(\text{CH}_3(\text{B,C}))$	1348	1361	
	(open-close)			
D10	$\delta(\text{CH}(3))$	1333	1347	1336
	$\omega(\text{CH}_2(2,4))$			
D11	$\delta(\text{CH}(3))$	1314	1329	1316
	$\tau(\text{CH}_2(2,4))$			
D12	$\nu(\text{C5-CH}_3(\text{C}))$	1289	1305	1300
	$\omega(\text{CH}_2(4,6))$			
	$\delta(\text{CH}(3))$			
D13	$\nu(\text{C5-CH}_3(\text{B}))$	1274	1290	
	$\tau(\text{CH}_2(2,4,6))$			
	$\delta(\text{CH}(3))$			
D14	$\nu_s(\text{C6-C1-C2})$	1259	1276	1282–1254
	$\omega(\text{CH}_2(2,4,6))$			
	$\delta(\text{CH}(3))$			
D15	$\nu_s(\text{C6-C1-C2})$	1242	1260	
	$\omega(\text{CH}_2(2,4,6))$			
D16	$\nu(\text{C-C}) + \delta(\text{C-C})$	1233	1251	
	$\tau(\text{CH}_2(2,4,6))$			
D17	$\nu(\text{C-C in ring})$	1207	1226	1235–1222
	$\tau(\text{CH}_2(2,4,6))$			
D18	$\nu(\text{C4-C5-C6})$	1197	1217	
	$\omega(\text{CH}_2(2,4,6))$			
D19	$\nu(\text{C5-CH}_3(\text{B}))$	1154	1177	
	$\rho(\text{CH}_3(\text{A,B,C}))$			
	$\omega(\text{CH}_2(6))$			
D20	$\nu(\text{C3-C4})$	1134	1157	1150–1130
	$\tau(\text{CH}_2(2,4,6))$			
	$\rho(\text{CH}_3(\text{A,B,C}))$			
D21	$\nu(\text{C2-C3-C4})$	1117	1141	
	$\rho(\text{CH}_3(\text{A}))$			
D22	$\nu(\text{C5-C6-C1-C2})$	1061	1087	1095–1078
	$\tau(\text{CH}_2(2,4,6))$			
	$\rho(\text{CH}_3(\text{A,C}))$			
D23	$\nu(\text{C3-CH}_3(\text{A}))$	1050	1077	
	$\rho(\text{CH}_3(\text{A,B,C}))$			
D24	$\rho(\text{CH}_3(\text{A,C}))$	1018	1046	
	$\delta(\text{C-C}) + \nu(\text{C-C})$			
	$\tau(\text{CH}_2(2,6))$			
D25	$\rho(\text{CH}_3(\text{B,C}))$	988	1018	
D26	$\rho(\text{CH}_3(\text{A}))$	962	993	
	$\rho(\text{CH}_3(\text{B,C}))$	943	975	
D27	$\rho(\text{CH}_3(\text{B,C}))$	917	950	
	$\rho(\text{CH}_3(\text{A}))$	909	942	
D28	$\rho(\text{CH}_3(\text{A,B,C}))$	887	921	
	$\nu(\text{C3-C4})$			

$\nu$ : stretch,  $\delta$ : bend,  $\delta_s$ : asymmetric bend,  $\delta_s$ : symmetric bend,  $\omega$ : wag,  $\tau$ : twist,  $\rho$ : rock.  
DFT scaling factor = 0.954.

position of the calculated C = O stretching mode for an isolated TMCH molecule adsorbed on Pd(111) (1611 cm<sup>-1</sup>) is not the same as the C = O stretching mode from sub-monolayer TMCH on Pd(111) that we measured (1648 cm<sup>-1</sup>). However, the difference in the position of the calculated C = O stretching mode in gas-phase TMCH to the

calculated C = O stretching mode of an isolated TMCH molecule on Pd(111) (83 cm<sup>-1</sup>) is almost exactly the same as the difference in the position of the C = O stretching mode in gas-phase TMCH from the NIST database and sub-monolayer TMCH on Pd(111) from this work (82 cm<sup>-1</sup>).

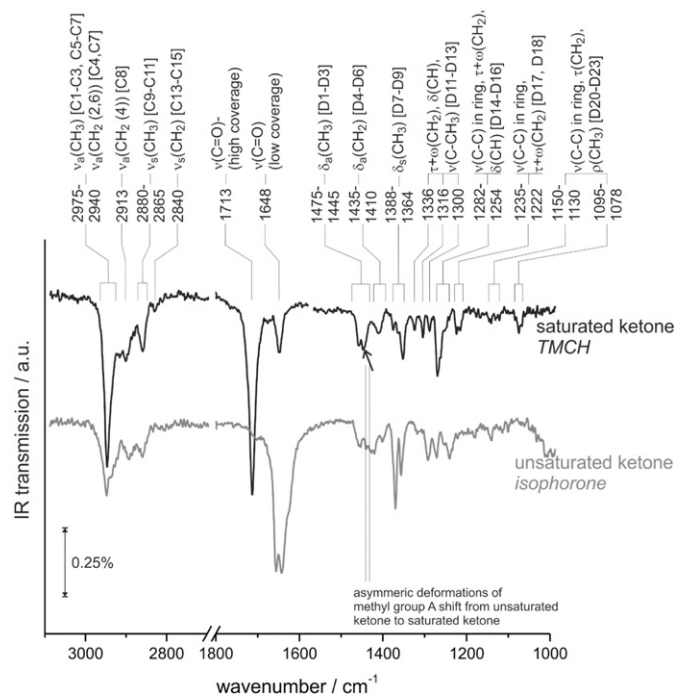


Fig. 7. IR spectra of 1.5 ML of TMCH (black) and isophorone (gray) adsorbed at 120 K on Pd(111) in the frequency range 3100–2700  $\text{cm}^{-1}$  (C–H stretching), 1800–1600  $\text{cm}^{-1}$  (C=C and C=O stretching), and 1500–1000  $\text{cm}^{-1}$  (C–H and C–C deformation and C–C stretching).

Combining the experimental IRAS results and DFT calculations, a clearer picture of the interaction between TMCH and Pd(111) emerges, which is very different from that of isophorone. The C–H stretching and C–H deformation regions grow roughly monotonically with increasing coverage, pointing to a possibly less strict ordering of molecules on the surface. TMCH interacts with the Pd(111) surface primarily through the C=O group. At low coverage, TMCH adsorbs roughly perpendicular to Pd(111) through the strongly perturbed C=O group, giving rise to a C=O vibrational band that is strongly shifted by  $\approx 82 \text{ cm}^{-1}$  to lower wavenumber relative to that of gas-phase TMCH. At intermediate coverage between sub-monolayer and multilayer ice, two new C=O vibrational bands appear at 1747  $\text{cm}^{-1}$  and 1701  $\text{cm}^{-1}$ . The origin of these peaks is not fully clear, however, they may arise from the second layer of TMCH molecules. A C=O vibrational band from multilayer TMCH ice appears at 1713  $\text{cm}^{-1}$ , which is 17  $\text{cm}^{-1}$  lower in wavenumber than the C=O stretching mode of gas-phase TMCH, and continues to grow with further increasing coverage.

#### 4. Conclusions

The adsorption of the unsaturated ketone isophorone and its hydrogenation product, the saturated ketone TMCH, on Pd(111) were investigated in this work. IR vibration modes of isophorone, deuterium-labeled ( $d_5$ -) isophorone and TMCH were studied in the range from 3000  $\text{cm}^{-1}$  to 1000  $\text{cm}^{-1}$  by IRAS and DFT studies. Detailed assignment of IR vibrations was achieved for the first time for normal and  $d_5$ -isophorone as well as TMCH at multilayers coverages.

Investigation of normal and  $d_5$ -isophorone allowed for better assignment of vibrational bands:

- C=C and C=O stretching modes are well-separated in  $d_5$ -isophorone, but are strongly overlapping in normal isophorone,
- $\text{CH}_2$  stretching and bending modes can be distinguished from  $\text{CH}_3$  stretching and bending vibrations, and

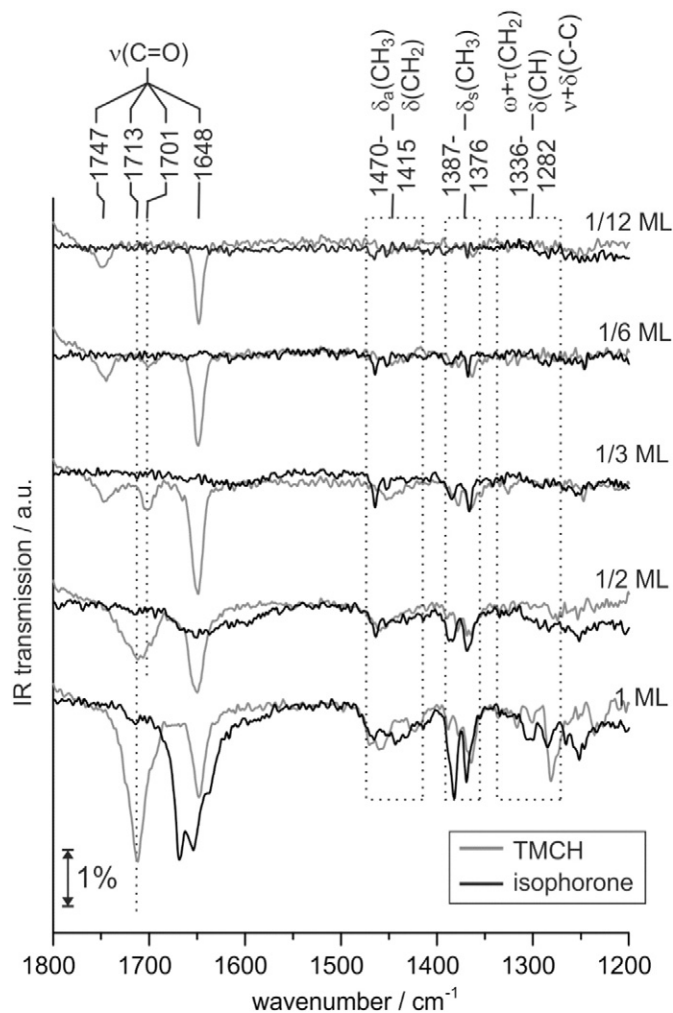



Fig. 8. IR spectra of TMCH and  $d_5$ -isophorone adsorbed at 120 K on Pd(111) at 1800–1600  $\text{cm}^{-1}$  (C=C and C=O stretching) and 1500–1000  $\text{cm}^{-1}$  (C–H, C–D, C–C deformation and C–C stretching) at coverages from 1/12 ML (topmost trace) to 1 ML (lowest trace).

- C–C stretching vibrations are separated from  $\text{CH}_2$  wag,  $\text{CH}_2$  twist, and CH bend modes.

Vibration frequencies of isolated isophorone and TMCH molecules from DFT + vdW calculations agree well with the experimentally observed IR absorption features at multilayer coverages. A detailed assignment of vibrational modes between 3000  $\text{cm}^{-1}$  and 1000  $\text{cm}^{-1}$  was presented for the three molecules.

The coverage dependent evolution of IR vibrational bands provides deep insights into the structure of isophorone on Pd(111):

- At the lowest isophorone coverage, we observed a flat-lying adsorption geometry with the C=C and C=O bonds being oriented parallel to the surface plane and at least one  $\text{CH}_3$  group facing away from the Pd. This observation suggests that isophorone preserves the in-plane configuration of the conjugated  $\pi$ -system in the low coverage limit. However, dehydrogenation of a  $\text{CH}_3$  group to  $\text{CH}_2$  appears to be possible.
- For intermediate sub-monolayer coverages, the in-plane structure of the isophorone ring adsorbed on pristine Pd(111) was observed to be strongly distorted. The C=C bond becomes noticeably tilted with respect to the surface plane, while the C=O bond remains still oriented flat on the surface.

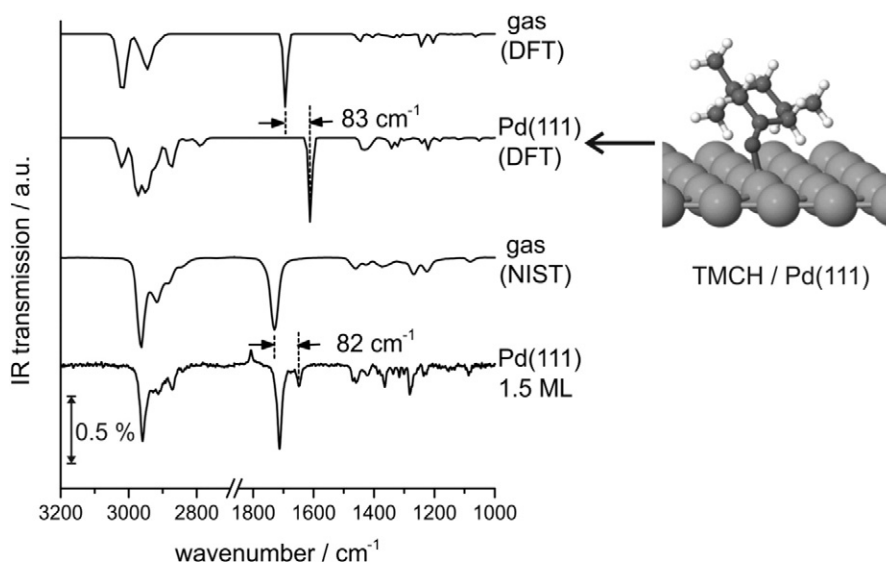

**Fig. 9.** Comparison of C = O stretching vibration in TMCH in different states (from top down): calculated by DFT in gas phase and adsorbed on Pd(111), gas phase spectrum according to NIST [58], and IRAS measurement on multilayer coverage of TMCH on Pd(111) at 120 K.

The IR spectra indicate that the adsorption of isophorone is significantly affected by the presence of pre-adsorbed hydrogen:

- At intermediate isophorone coverages, the molecular structure is similar to that of gas-phase isophorone.
- At low coverages of isophorone, the intensity ratio of the C–H vibrations strongly points to different orientation of the –CH<sub>3</sub> groups as compared to pristine Pd(111). The molecules appear to be more perturbed on the clean Pd(111) surface than on the hydrogen-precovered surface.
- The hydrogen-induced changes in the orientation of unsaturated bonds may have important implications for selective hydrogenation of either the C = C or the C = O bond, i.e. via changing the typical distances of the C = C vs. C = O bonds to the surface and thus effecting the degree of their perturbation and the hydrogenation probability.

We found pronounced differences in the structures of the saturated ketone TMCH and the unsaturated ketone isophorone adsorbed on Pd(111):

- TMCH adsorbs in a strongly tilted geometry with respect to the Pd(111) surface plane, interacting with the surface primarily through the C = O group.
- At the lowest TMCH coverage, the species give rise to a C = O vibrational band that points to a considerably weakened C = O bond.
- At intermediate TMCH coverage, species with less perturbed C = O bonds also appear.
- The C–H vibrational bands grow roughly monotonically with increasing coverage, which might point to less perturbed C–H bonds and a less strict ordering of molecules on the surface.
- The strong changes in the adsorbate's structure going from the unsaturated to the saturated ketone (isophorone to TMCH) may play a crucial role in the selectivity of C = C vs. C = O bond hydrogenation in  $\alpha,\beta$ -unsaturated carbonyl compounds.

## Acknowledgments

S.S. acknowledges support from the Fonds der Chemischen Industrie for the Chemiedozentenstipendium and the European Research Council

(ERC Starting Grant 335205 ENREMOS). A.T. acknowledges support from the European Research Council (ERC Starting Grant VDW-CMAT).

## References

- [1] M.T. Pirnot, D.A. Rankic, D.B.C. Martin, D.W.C. MacMillan, *Science* 339 (2013) 1593.
- [2] Y. Zhu, H.F. Qian, B.A. Drake, R.C. Jin, *Angew. Chem. Int. Ed.* 49 (2010) 1295.
- [3] S. Fleischer, S.L. Zhou, K. Junge, M. Beller, *Angew. Chem. Int. Ed.* 52 (2013) 5120.
- [4] M.G. Hitzler, F.R. Smail, S.K. Ross, M. Poliakoff, *Org. Process. Res. Dev.* 2 (1998) 137.
- [5] T. Sato, C.V. Rode, O. Sato, M. Shirai, *Appl. Catal. B Environ.* 49 (2004) 181.
- [6] D.I. Enache, G.J. Hutchings, S.H. Taylor, E.H. Stitt, *Catal. Today* 105 (2005) 569.
- [7] A. Tunzler, K. Fodor, T. Mathe, R.A. Sheldon, in: H.U. Blaser, A. Baiker, R. Prins (Eds.), *Heterogeneous Catalysis and Fine Chemicals* 4, 108, Elsevier Science Bv, Amsterdam 1997, p. 157.
- [8] M. Studer, H.U. Blaser, C. Exner, *Adv. Synth. Catal.* 345 (2003) 45.
- [9] H.U. Blaser, B. Pugin, F. Spindler, *J. Mol. Catal. A Chem.* 231 (2005) 1.
- [10] T. Mallat, E. Orglmeister, A. Baiker, *Chem. Rev.* 107 (2007) 4863.
- [11] A. Tunzler, G. Fogassy, *J. Mol. Catal. A Chem.* 173 (2001) 231.
- [12] T. Tarnai, A. Tunzler, T. Mathe, J. Petro, R.A. Sheldon, G. Toth, *J. Mol. Catal. A Chem.* 102 (1995) 41.
- [13] G. Farkas, K. Fodor, A. Tunzler, T. Mathe, G. Toth, R.A. Sheldon, *J. Mol. Catal. A Chem.* 138 (1999) 123.
- [14] A. Tunzler, Y. Nitta, K. Fodor, G. Farkas, T. Mathe, *J. Mol. Catal. A Chem.* 149 (1999) 135.
- [15] E. Sipos, A. Tunzler, *React. Kinet. Catal. Lett.* 80 (2003) 365.
- [16] E. Sipos, A. Tunzler, G. Fogassy, *J. Mol. Catal. A Chem.* 216 (2004) 171.
- [17] M. Fodor, A. Tunzler, L. Vida, *React. Kinet. Catal. Lett.* 90 (2007) 413.
- [18] S. Li, E.S. Zhan, Y. Li, Y.D. Xu, W. Shen, *J. Catal. Today* 131 (2008) 347.
- [19] S.K. Beaumont, G. Kyriakou, D.J. Watson, O.P.H. Vaughan, A.C. Papageorgiou, R.M. Lambert, *J. Phys. Chem. C* 114 (2010) 15075.
- [20] D.J. Watson, R. Jesudason, S.K. Beaumont, G. Kyriakou, J.W. Burton, R.M. Lambert, *J. Am. Chem. Soc.* 131 (2009) 14584.
- [21] W. Liu, A. Savara, X. Ren, W. Ludwig, K.-H. Dostert, S. Schauerermann, A. Tkatchenko, H.-J. Freund, M. Scheffler, *J. Phys. Chem. Lett.* 3 (2012) 582.
- [22] K.-H. Dostert, C.P. O'Brien, W. Riedel, A. Savara, W. Liu, M. Oehzelt, A. Tkatchenko, S. Schauerermann, *J. Phys. Chem. C* 118 (2014) 27833.
- [23] V.G. Ruiz, W. Liu, E. Zojer, M. Scheffler, A. Tkatchenko, *Phys. Rev. Lett.* (2012) 108.
- [24] F.M. Hoffmann, *Surf. Sci. Rep.* 3 (1983) 107.
- [25] S.A. Francis, A.H. Ellison, *J. Opt. Soc. Am.* 49 (1959) 131.
- [26] P. Hollins, J. Pritchard, *Prog. Surf. Sci.* 19 (1985) 275.
- [27] J.M. Libuda, J. Hartmann, H.J. Freund, *Rev. Sci. Instrum.* 71 (2000) 4395.
- [28] V.G. Ruiz, W. Liu, E. Zojer, M. Scheffler, A. Tkatchenko, *Phys. Rev. Lett.* 108 (2012) 146103.
- [29] V. Blum, R. Gehrke, F. Hanke, P. Havu, V. Havu, X. Ren, K. Reuter, M. Scheffler, *Comput. Phys. Commun.* 180 (2009) 2175.
- [30] W. Liu, A. Tkatchenko, M. Scheffler, *Acc. Chem. Res.* 47 (2014) 3369.
- [31] W. Liu, S.N. Filimonov, J. Carrasco, A. Tkatchenko, *Nat. Commun.* (2013) 4.
- [32] W. Liu, J. Carrasco, B. Santra, A. Michaelides, M. Scheffler, A. Tkatchenko, *Phys. Rev. B* (2012) 86.
- [33] E. van Lenthe, E.J. Baerends, J.G. Snijders, *J. Chem. Phys.* 101 (1994) 9783.
- [34] J.J. Fox, A.E. Martin, *Proc. R. Soc. Lond. A Math. Phys. Sci.* 175 (1940) 0208.
- [35] J.J. Fox, A.E. Martin, *Proc. R. Soc. Lond. A Math. Phys. Sci.* 167 (1938) 0257.

- [37] N. Sheppard, D.M. Simpson, Q. Rev. Chem. Soc. 7 (1953) 19.
- [38] R.A. Macphail, H.L. Strauss, R.G. Snyder, C.A. Elliger, J. Phys. Chem. 88 (1984) 334.
- [39] J.H. Schachtschneider, R.G. Snyder, Spectrochim. Acta 19 (1963) 117.
- [40] R.G. Snyder, J.H. Schachtschneider, Spectrochim. Acta 19 (1963) 85.
- [41] N.B. Colthup, Appl. Spectrosc. 34 (1980) 1.
- [42] R.G. Snyder, M.C. Goh, V.J.P. Srivatsavoy, H.L. Strauss, D.L. Dorset, J. Phys. Chem. 96 (1992) 10008.
- [43] M. Shimomura, K. Song, J.F. Rabolt, Langmuir 8 (1992) 887.
- [44] H.L. McMurry, V. Thornton, Anal. Chem. 24 (1952) 318.
- [45] B. Nolin, R.N. Jones, J. Am. Chem. Soc. 75 (1953) 5626.
- [46] N.B. Colthup, J. Opt. Soc. Am. 40 (1950) 397.
- [47] R.S. Rasmussen, J. Chem. Phys. 16 (1948) 712.
- [48] R.A. Meiklejohn, R.J. Meyer, S.M. Aronovic, H.A. Schuette, V.W. Meloch, Anal. Chem. 29 (1957) 329.
- [49] R. Mecke, K. Noack, Spectrochim. Acta 12 (1958) 391.
- [50] R. Barlet, M. Montagne, P. Arnaud, Spectrochim. Acta A: Mol. Spectrosc. A 25 (1969) 1081.
- [51] E.G. Hoffmann, Annalen Der Chemie-Justus Liebig, 6181958 276.
- [52] J.C. Lavalley, N. Sheppard, Spectrochim. Acta A: Mol. Spectrosc. 28 (1972) 2091.
- [53] N.B. Colthup, L.H. Daly, S.E. Wiberley, Introduction to Infrared and Raman Spectroscopy, third ed. Academic Press, San Diego and London, 1990.
- [54] M.L. Laury, M.J. Carlson, A.K. Wilson, J. Comput. Chem. 33 (2012) 2380.
- [55] K. Christmann, G. Ertl, O. Schober, Surf. Sci. 40 (1973) 61.
- [56] T.E. Felter, S.M. Foiles, M.S. Daw, R.H. Stulen, Surf. Sci. Lett. 171 (1986) L379.
- [57] W. Eberhardt, S.G. Louie, E.W. Plummer, Phys. Rev. B 28 (1983) 465.
- [58] Stein, S. E. In NIST Chemistry WebBook, NIST Standard Reference Database Number 69; Mallard, P. J. L. A. W. G., Ed.; National Institute of Standards and Technology: Gaithersburg MD, (August 1, 2014).