

# NASA Contractor Report 159137

(NASA-CR-159137) BEHAVIOR OF COMPOSITE  
BOLTED JOINTS AT ELEVATED TEMPERATURE  
(Delaware Univ.) 108 p HC A06/MF A01

N79-32574

CSSL 24K

Unclas

G3/39 35813

BEHAVIOR OF COMPOSITE BOLTED JOINTS AT  
ELEVATED TEMPERATURE

Dale W. Wilson and R. Byron Pipes

UNIVERSITY OF DELAWARE  
Center for Composite Materials  
Newark, Delaware 19711

NASA Grant NSG-1409  
September 1979

**NASA**  
National Aeronautics and  
Space Administration  
**Langley Research Center**  
Hampton, Virginia 23665



BEHAVIOR OF COMPOSITE BOLTED JOINTS  
AT ELEVATED TEMPERATURE

SUMMARY

Experimental results from an investigation which examines the combined effects of temperature, joint geometry and out-of-plane constraint upon the response of mechanically fastened composite joints are presented. Data are presented for simulated mechanically fastened joint conditions in two laminate configurations ( $[0/±45/90]_2$ s and  $[45/0/-45/0_2/-45/0/45/0_2/90]_2$ ) fabricated from Hercules AS/3501-6 graphite-epoxy. Strength and failure mode results are presented for the test temperatures of 21°C (70°F), 121°C (250°F) and 177°C (350°F) and for a range of the geometric parameters W/D and e/D from 3.71 to 7.43 and 1.85 to 3.69, respectively. A hole diameter, D of 5.16 mm (0.203 in.) was utilized for all tests. Pin bearing tests with out-of-plane constraint were conducted at room temperature only. All elevated temperature data were generated for pin bearing conditions. Three replicates of each test coupon geometry and laminate configuration were tested at each of three temperatures - totalling 126 tests in all. Ultrasonic "C" scan inspection of the failed specimens was employed to assess the damage region and to determine failure mode. Comparative data are presented for pin bearing and out-of-plane constraint conditions for the above mentioned joint configurations. The joint under pin loading was modeled by two-dimensional finite-element methods. Predicted net section strain concentrations were compared with experimental results.

## TABLE OF CONTENTS

| <u>Section</u> | <u>Title</u>  | <u>Page</u> |
|----------------|---|-------------|
|                | Summary   | i           |
|                | Table of Contents   | ii          |
|                | List of Tables  | iv          |
|                | List of Figures   | vi          |
|                | Nomenclature  | viii        |
| 1.0            | Introduction  | 1           |
| 2.0            | Experimental Procedure  | 4           |
|                | 2.1 Panel Fabrication   | 4           |
|                | 2.2 Test Coupon Fabrication   | 4           |
|                | 2.3 Fixture Design  | 5           |
|                | 2.4 Test Coupon Instrumentation   | 6           |
|                | 2.5 Test Methods and Procedures   | 6           |
|                | 2.6 NDE of Failed Specimens   | 8           |
|                | 2.7 Data Analysis   | 9           |
| 3.0            | Results and Discussion  | 10          |
|                | 3.1 Comparison of Pinned and Out-of-Plane<br>Constraint Loading Conditions                        | 10          |
|                | 3.2 Effects of Test Temperature on Bolted<br>Joint Strength                                       | 11          |
|                | 3.3 The Effect of Temperature on Modulus  | 12          |
|                | 3.4 Evaluation of e/D Effects on Strength   | 13          |
|                | 3.5 Evaluation of Combined e/D, W/D and<br>Temperature Effects on Joint Strength                  | 14          |
|                | 3.6 Comparison of Experimental and Finite<br>Element Modeled Net Section Strain<br>Concentrations | 15          |
|                | 3.7 Edge Deformation Predicted by Finite<br>Element Model   | 16          |
|                | 3.8 Bearing Stress Distribution Predicted<br>by Finite Element Model                              | 16          |

TABLE OF CONTENTS (Cont'd)

| <u>Section</u> | <u>Title</u>                                     | <u>Page</u> |
|----------------|--|-------------|
| 3.9            | NDE of and Damage Zone and Failure Mode Analysis | 17          |
| 3.10           | Delayed Test Strength Degradation Phenomena      | 19          |
| 4.0            | Conclusions                                      | 22          |
| 5.0            | References                                       | 25          |
| 6.0            | Acknowledgements                                 | 27          |
| 7.0            | Appendix A (Data Tables)                         | 28          |
| 8.0            | Figures  | 60          |

LIST OF TABLES

| TABLE | TITLE  | PAGE |
|-------|--|------|
| IA    | Pin Bearing Strength of laminate No. 1 at 70°F, e/D = 3.69, English Units  | 29   |
| IB    | Pin Bearing Strength of laminate No. 1 at 21°C, e/D = 3.69, S. I. Units    | 30   |
| IIA   | Pin Bearing Strength of laminate No. 1 at 70°F, e/D = 2.85, English Units  | 31   |
| IIB   | Pin Bearing Strength of laminate No. 1 at 21°C, e/D = 2.85, S. I. Units    | 32   |
| IIIA  | Pin Bearing Strength of laminate No. 1 at 250°F, e/D = 3.69, English Units | 33   |
| IIIB  | Pin Bearing Strength of laminate No. 1 at 121°C, e/D = 3.69, S. I. Units   | 34   |
| IVA   | Pin Bearing Strength of laminate No. 1 at 250°F, e/D = 1.85, English Units | 35   |
| IVB   | Pin Bearing Strength of laminate No. 1 at 121°C, e/D = 1.85, S. I. Units   | 36   |
| VA    | Pin Bearing Strength of laminate No. 1 at 350°F, e/D = 3.69, English Units | 37   |
| VB    | Pin Bearing Strength of laminate No. 1 at 177°C, e/D = 3.69, S. I. Units   | 38   |
| VIA   | Pin Bearing Strength of laminate No. 1 at 350°F, e/D = 1.85, English Units | 39   |
| VIB   | Pin Bearing Strength of laminate No. 1 at 177°C, e/D = 1.85, S. I. Units   | 40   |
| VIIA  | Pin Bearing Strength of laminate No. 2 at 70°F, e/D = 3.69, English Units  | 41   |
| VIIB  | Pin Bearing Strength of laminate No. 2 at 21°C, e/D = 3.69, S. I. Units    | 42   |
| VIIIA | Pin Bearing Strength of laminate No. 2 at 70°F, e/D = 1.85, English Units  | 43   |
| VIIIB | Pin Bearing Strength of laminate No. 2 at 21°C, e/D = 1.85, S. I. Units    | 44   |
| IXA   | Pin Bearing Strength of laminate No. 2 at 250°F, e/D = 3.69, English Units | 45   |
| IXB   | Pin Bearing Strength of laminate No. 2 at 121°C, e/D = 3.69, S. I. Units   | 46   |
| XA    | Pin Bearing Strength of laminate No. 2 at 250°F, e/D = 1.85, English Units | 47   |
| XB    | Pin Bearing Strength of laminate No. 2 at 121°C, e/D = 1.85, S. I. Units   | 48   |
| XIA   | Pin Bearing Strength of laminate No. 2 at 350°F, e/D = 3.69, English Units | 49   |
| XIB   | Pin Bearing Strength of laminate No. 2 at 177°C, e/D = 3.69, S. I. Units   | 50   |
| XIIA  | Pin Bearing Strength of laminate No. 2 at 350°F, e/D = 1.85, English Units | 51   |

| TABLE | TITLE   | PAGE |
|-------|---|------|
| XIIB  | Pin Bearing Strength of laminate No. 2 at 177°C,<br>e/D = 1.85, S. I. Units                       | 50   |
| XIIIA | Out-of-Plane Constraint Strengths of quasi-isotropic<br>laminate, e/D = 3.69, English Units       | 51   |
| XIIIB | Out-of-Plane Constraint Strengths of quasi-isotropic<br>laminate, e/D = 3.69, S. I. Units         | 54   |
| XIVA  | Out-of-Plane Constraint Strengths of quasi-isotropic<br>laminate, e/D = 1.85, English Units       | 55   |
| XIVB  | Out-of-Plane Constraint Strengths of quasi-isotropic<br>laminate, e/D = 1.85, S. I. Units         | 56   |
| XVA   | Out-of-Plane Constraint Strengths of 0° Dominated<br>laminate, e/D = 1.85, English Units          | 57   |
| XVB   | Out-of-Plane Constraint Strengths of 0° Dominated<br>laminate, e/D = 1.85, S. I. Units            | 58   |
| XVI   | Comparison of Experimental and Predicted Net<br>Section Strain Concentrations and Young's Modulus | 59   |

## LIST OF FIGURES

| <u>Figure</u> | <u>Title</u>  |
|---------------|---|
| 2.2.1         | Bolted Joint Test Coupon Geometry   |
| 2.3.1         | Bolted Joint Test Fixture Used for Pin Bearing Tests  |
| 2.3.2         | Inserts Used to Apply Out-of-Plane Constraint   |
| 2.4.1         | Instrumentation Locations on Test Coupon  |
| 2.6.1         | Ultrasonic "C" Scan Block Diagram   |
| 2.6.2         | Signal Waveforms Characteristic of Defects  |
| 3.1.1         | Comparison of Pin Loaded and Out-of-Plane Constraint Strength for AS/3501-6 Graphite Epoxy Quasi-isotropic Laminate, $e/D = 1.85$ |
| 3.1.2         | Comparison of Pin Loaded and Out-of-Plane Constraint Strength for AS/3501-6 Graphite Epoxy Quasi-isotropic Laminate, $e/D = 3.69$ |
| 3.1.3         | Comparison of Pin Loaded and Out-of-Plane Constraint Strength for AS/3501-6 Graphite Epoxy $0^\circ$ Dominated Laminate           |
| 3.2.1         | Failure Load Versus Temperature for AS/3501-6 Graphite Epoxy Quasi-isotropic Laminate, $e/D = 1.85$                               |
| 3.2.2         | Failure Load Versus Temperature for AS/3501-6 Graphite Epoxy Quasi-isotropic Laminate, $e/D = 3.69$                               |
| 3.2.3         | Failure Load Versus Temperature for AS/3501-6 Graphite Epoxy $0^\circ$ Dominated Laminate, $e/D = 1.85$                           |
| 3.2.4         | Failure Load Versus Temperature for AS/3501-6 Graphite Epoxy $0^\circ$ Dominated Laminate, $e/D = 3.69$                           |
| 3.3.1         | Variation of Laminate Modulus with Temperature for Quasi-isotropic Laminate   |
| 3.3.2         | Variation of Laminate Modulus with Temperature for $0^\circ$ Dominated Laminate   |
| 3.4.1         | Failure Load Versus $e/D$ for AS/3501-6 Graphite Epoxy Quasi-isotropic Laminate with Out-of-Plane Constraint                      |
| 3.4.2         | Pin Bearing Failure Load Versus $e/D$ for Quasi-isotropic Laminate, $W/D = 3.71$  |
| 3.4.3         | Pin Bearing Failure Load Versus $e/D$ for Quasi-isotropic Laminate, $W/D = 4.95$  |
| 3.4.4         | Pin Bearing Failure Load Versus $e/D$ for Quasi-isotropic Laminate, $W/D = 7.43$  |
| 3.5.1         | Pin Bearing Failure Load Versus $e/D$ for $0^\circ$ Dominated Laminate, $W/D = 3.71$  |
| 3.5.2         | Pin Bearing Failure Load Versus $e/D$ for $0^\circ$ Dominated Laminate, $W/D = 4.95$  |
| 3.5.3         | Pin Bearing Failure Load Versus $e/D$ for $0^\circ$ Dominated Laminate, $W/D = 7.43$  |
| 3.5.4         | Beam Bending Analogy for Pin Loaded Joint   |
| 3.6.1         | Finite Element Model of $e/D = 2$ Pin Loaded Joint  |
| 3.6.2         | Finite Element Model of $e/D = 4$ Pin Loaded Joint  |
| 3.7.1         | Deformation of Edge Under Pin Loading for AS/3501-6 Graphite Epoxy  |

| <u>Figure</u> | <u>Title</u>   |
|---------------|--|
| 3.8.1         | Comparison of Bearing Stresses in Quasi-isotropic Bolted Joint with e/D's of 1.85 and 3.69 |
| 3.8.2         | Comparison of Bearing Stresses in 0° Dominated Bolted Joint with e/D's of 2 and 4          |
| 3.9.1         | Typical Failure Modes of the Coupons   |
| 3.9.2         | "C" Scan of Quasi-isotropic Coupons Showing Damage Zones for e/D = 1.85                    |
| 3.9.3         | "C" Scan of Quasi-isotropic Coupons Showing Damage Zones for e/D = 3.69                    |
| 3.9.4         | "C" Scan of 0° Dominated Coupons Showing Damage Zones for e/D = 1.85                       |
| 3.9.5         | "C" Scan of 0° Dominated Coupons Showing Damage Zones for e/D = 3.69                       |
| 3.9.6         | "C" Scan of Coupons Tested with Out-of-Plane Constraint                                    |
| 3.10.1        | Decreased Strength Exhibited by Samples Tested After 4 mo. Delay, Quasi-isotropic Laminate |
| 3.10.2        | Decreased Strength Exhibited by Samples Tested After 4 mo. Delay, 0° Dominated Laminate    |



## NOMENCLATURE

| <u>Term</u>                            | <u>Description</u>   |
|--|--|
| edge distance (e)                      | Distance from center of hole to the end edge of the laminate.  |
| hole diameter (D)                      | The diameter of the fastener hole.   |
| width (W)                              | Width of the coupon which is equivalent to the half spacing between fasteners.   |
| pin loading                            | Reacting the joint loads with a pin which offers no out-of-plane restraint.  |
| out-of-plane constraint                | Reacting the joint loads through the pin while constraining the out-of-plane deformations (deformations normal to plane of laminate).  |
| bearing failure                        | A failure where localized crushing of the material reacting load leads to an elongation of the hole (see Fig. 4.91).   |
| shear-out failure                      | Failure which is characterized by extensive cleavage damage parallel to the loading extending from the two sides of the fastener hole to the edge of the coupon (see Fig. 4.91). |
| net tension failure                    | Normal tensile failure occurring in the material adjacent to the fastener hole.  |
| quasi-isotropic laminate               | Laminate with the $[0/\pm 45/90]_2$ configuration.   |
| bondable resistance temperature sensor | A strain insensitive resistive element which can be applied to the surface of a material to measure temperature.   |

Term

Description

0° dominated laminate

Referred to in this work as the laminate with the [45/0/-45/0<sub>2</sub>/-45/0/45/0<sub>2</sub>/90]<sub>s</sub> configuration.

ultrasonic "C" scan

A non-destructive inspection technique which uses ultrasonic waves to reveal information about the structure of the material.

gate

Electronic circuit used to selectively monitor a portion of the ultrasonic waveform.

## 1.0 INTRODUCTION

With increasing implementation of advanced composites in high technology aerospace applications, the understanding of bolted joint behavior remains a critical issue in the development of joining technology for composite materials. This is especially true for applications requiring high joint efficiency under extreme environmental conditions. Recent studies of bolted joint behavior have focused upon the development of analysis methods, the generation of design data, and the development of reinforcing techniques to improve joint strength [1-9].

Analytical studies have investigated the use of finite element methods to predict joint strength and determine failure modes in anisotropic materials [10, 11] and the use of numerical techniques for analyzing elastically orthotropic cases by modified elasticity theory [3]. Most of the analytical work to date models the joint system as two-dimensional, but a few efforts have been made in three-dimensional analysis of joint behavior [12].

Most of the information required for designing bolted joints with boron-epoxy or graphite-epoxy composite materials at ambient conditions is available from the Air Force Design Guide [9]. The design guide provides design allowables for single-lap and double-lap joints with

moisture exposure are reported by Wilkins (8) and Kim and Whitney [4] for the 21°C (70°F), 121°C (250°F) range.

The reduction in laminate strength associated with bolt penetrations has stimulated attempts to reinforce the region around the penetration with various stiffening and softening materials in order to increase joint strength and to avoid the catastrophic net tension failure mode [6, 7]. The laminate stacking sequence effects observed by Quinn and Matthews [5] for quasi-isotropic glass-epoxy bolted joints are of more fundamental interest in understanding bolted joint behavior.

Only a sampling of the research on bolted joints has been reviewed here, but a review of the literature has revealed that there is a general lack of fundamental knowledge of the load transfer and failure mechanisms in composite bolted joints. The present work is intended to examine elevated temperature performance of graphite-epoxy composites in the 127°C (350°F) temperature region while taking a more fundamental look at the behavior observed. Groundwork is laid for use of ultrasonic "C" scan inspection of failed joints to evaluate damage patterns and modes.

Elevated temperature pin bearing strength and failure

mode data were generated for joint geometries with W/D ranging from 3.71 to 7.43 and e/D ranging from 1.85 to 3.69. Room temperature tests were conducted with out-of-plane constraint over a controlled contact area for comparison with pin bearing data. Ultrasonic "C" scan inspection techniques were used in evaluating damage zone nature and extent in the failed specimens. The results were tabulated for two laminate configurations, a 16 ply  $[0/\pm 45/90]_{2S}$  (quasi-isotropic) laminate and a 22 ply  $[45/0/-45/0_2/-45/0/45/0_2/90]_S$  ( $0^\circ$  dominated) laminate, fabricated from Hercules AS/3501-6 graphite epoxy prepreg.

## 2.0 EXPERIMENTAL PROCEDURE

### 2.1 Panel Fabrication

The laminates were fabricated from Hercules AS/3501-6 graphite-epoxy 30 cm. (12 inch) wide prepreg tape. All panels in the test program were made from the same batch of prepreg material to avoid any variability between panels due to batch differences. The panels were autoclave cured according to the standard procedures recommended for the AS/3501-6 system by Hercules Inc.

### 2.2 Test Coupon Fabrication

The test coupon geometry shown in Fig. 2.2.1 was fabricated for each bolted joint test. The test coupon was 15 cm. (6 inches) in length. Load is introduced through beveled end tabs bonded to the laminate and reacted by a pin through the hole located approximately fifteen hole diameters from the tabs. This single hole coupon configuration was designed to eliminate load history as a test variable by allowing only one test per coupon and provided uniform load introduction without interaction with the joint area. Glass-epoxy end tab material was used for the 21°C (70°F) and 121°C (250°F) tests while glass polyimide<sup>1</sup> material was used

---

<sup>1</sup>Glass polyimide material obtained from Howe Industries, Inc. was used due to future intent to test graphite-polyimide material at temperatures of 600°F.

for the 177°C (350°F) tests. Standard room temperature curing epoxy was used to bond the end tabs on the 21°C (70°F) test coupons and an elevated temperature epoxy (Eccobond 104) was used for bonding tabs to the elevated temperature coupons. Coupons were cut to widths of 1.905 cm. (0.750 in.), 2.540 cm. (1.000 in.) and 3.810 cm. (1.500 in.) using a precision diamond saw. Holes were drilled using a diamond core drill and then reamed to a 0.516 cm. (0.203 in.) diameter. Visual and ultrasonic inspection of the holes after machining revealed negligible machining damage. The holes were centered with respect to the specimen width and located either .953 cm. (0.375 in.) or 1.905 cm. (0.750 in.) from the end of the coupon. Dimensions of each sample were recorded prior to testing. Upon completion of fabrication, all test coupons were stored in sealed plastic bags containing a dessicant.

### 2.3 Fixture Design

Standard Instron friction grips were used for load introduction at the tab end of the coupon while a special clevis fixture shown in Figure 2.3.1 was designed to simulate the bolted load reaction through the hole. The "V" groove inserts were used in pin bearing tests and the load reacted by a high strength tungsten carbide steel pin. For out-of-plane constraint the inserts shown in Figure 2.3.2 were used,

where the washers were machined to constrain a known contact area of 0.65 cm. (0.100 in.<sup>2</sup>) around the hole. The clevis fixture was mounted through a universal coupler to the load cell while friction grips were mounted on the crosshead. The fixture arrangement allowed a limited amount of self alignment capability.

#### 2.4 Test Coupon Instrumentation

One test coupon for each geometry and test temperature was instrumented with strain gages to monitor far field, net section, shear-out, and bearing strains. These gages were located as shown in Figure 2.4.1. Elevated temperature adhesive (M Bond 610) was used for all strain gages in the elevated temperature test program. A resistance temperature sensor mounted on a dummy coupon was used to monitor test chamber temperature during testing.

Temperature compensation for the strain gages was achieved by balancing the bridge circuit manually after the gages had reached equilibrium with the constant test temperature. Chamber temperatures were constant during testing thus causing no further need for temperature compensation.

#### 2.5 Test Methods and Procedures

Three replicates of each test coupon geometry and laminate were tested at each of the three temperatures -



totalling 126 tests in all. Tests were conducted within an environmental chamber providing temperature control over a  $-100^{\circ}\text{C}$  to  $+325^{\circ}\text{C}$  range. The test fixture was centered in the test chamber and all ports were sealed with insulation to assure a reasonably uniform chamber temperature. Temperature in close proximity to the test coupon was constantly monitored by the temperature gage mounted on the dummy sample. During all elevated temperature tests the coupon was "soaked" at temperature for 30 minutes to assure thermal equilibrium within the coupon during test.

Care was taken to align the test coupon in the grips and fixture so as not to introduce any eccentricities in load. Inspection of the grip marks on tested coupons revealed uniformity indicative of even load introduction. The tests were conducted with a crosshead speed of 0.05 cm/min. and the load versus crosshead displacement curve recorded for each test on the Instron x-y recorder. Failure load was determined as the maximum load attained before the load drop accompanying failure of the joint.

For pin bearing tests, clearance was left on each side of the laminate. The constraining washers were tightened finger tight for the out-of-plane constraint tests. The object was to simply inhibit out-of-plane deformation while applying minimal frictional load transfer. Strain data were

recorded at known load intervals for the instrumented tests. The far field strain gages were used to measure the effective longitudinal modulus of the laminates at the three test temperatures. The net section gage's strain output normalized by the far field strain was used to measure the strain concentration factor.

## 2.6 NDE of Failed Coupons

The failed coupons were subjected to ultrasonic "C" scan inspection and compared to the original "C" scans. While the undamaged regions compared identically, inspection of damage zone revealed information about the size and nature of damage inflicted at failure. All ultrasonic instrument settings were recorded. All coupons of the same laminate configuration were scanned under identical conditions to allow valid comparison of the damaged areas.

The "C" scan equipment is diagrammed in Figure 2.6.1. A wide band pulse of short duration is sent from a transducer through the specimen and the signal reflected from the specimen is received by the same transducer. This signal appears as a waveform shown in Figure 2.6.2 where the reflected signals from the front and back surfaces are characteristic of the material under test. In the peak amplitude "C" scan method, a gating circuit removes a specified portion of the waveform to be analyzed, usually the

back surface reflection. This gated portion of the waveform is then analyzed on a peak amplitude basis. The amplitude of the largest peak in the gated waveform is converted into a D. C. voltage which can be quantitized into 10 discrete regions. The recording amplifier then uses these discrete voltages to control the pen output which etches corresponding shades of grey on the recording paper.

Changes in thickness and delaminations cause changes in the waveform as shown in Figure 2.6.2. By adjusting the gate width and position it was possible to display delaminations as dark regions and changes in thickness as light regions. It should also be noted that the location of the delamination through the laminate thickness could be determined by examination of the waveform.

## 2.7 Data Analysis

A tabulation of data was compiled showing the sample dimensions, failure load, failure mode and the failure stresses (net tension, shear-out and bearing) and given in Appendix A. These stresses are simply the average stresses calculated using the following relationships.

$$F^{br} = P^{br}/(Dt) \quad (1)$$

$$F^{SO} = P^{SO}/[2t(e-D/2)] \quad (2)$$

$$F^{nt} = P^{nt}/((W-D)t) \quad (3)$$

where  $F^{br}$ ,  $F^{so}$  and  $F^{nt}$  are the failure stresses  
 $p^{br}$ ,  $p^{so}$  and  $p^{nt}$  are the failure loads.

### 3.0 RESULTS AND DISCUSSIONS

#### 3.1 Comparison of Pinned and Out-of-Plane Constraint Loading Conditions

The results showing the effect of out-of-plane constraint on pin bearing strength are summarized in Figures 3.1.1 - 3.1.3. These figures show failure load as a function of  $W/D$  for the pin bearing loads with and without out-of-plane constraint while eliminating test temperature, laminate type, failure mode and  $e/D$  as variables. As shown in Figures 3.1.1 and 3.1.2 the quasi-isotropic laminate exhibited bearing failure in all cases with the out-of-plane constraint providing a 30-50% increase in strength. Over the range investigated, the pin bearing tests were relatively insensitive to  $W/D$  effects, while the out-of-plane constraint tests showed definite  $W/D$  dependence in the form of increased strength with increasing  $W/D$ .

The failure mode of the  $0^\circ$  dominated laminate with an  $e/D = 1.85$  was shear-out and exhibited an 11% increase in strength with out-of-plane constraint. Both pin bearing and out-of-plane constraint tests exhibited decreasing strength with increasing  $W/D$  over the range of geometries investigated here as shown in Figure 3.1.3. These results suggest that

both the bearing and shear-out failure mechanisms are related to the out-of-plane deformation.

### 3.2 Effect of Test Temperature on Bolted Joint Strength

The effects of temperature on failure strength of bolted joints was investigated for pin bearing loading conditions only. The results are summarized for the two laminate configurations in Figures 3.2.1-3.2.4. In general, the strength diminished approximately 40% with a temperature increase from 21°C (70°F) to 177°C (350°F) for both laminate configurations. Figures 3.2.1 and 3.2.2 show failure load as a function of temperature for the quasi-isotropic laminate with e/D values of 1.85 and 3.69, respectively. It is apparent that W/D effects are insignificant for these cases. The test specimens with e/D of 1.85 were slightly more sensitive to temperature increases than the 3.69 geometry as indicated by a 50% decrease in strength with temperature for the e/D of 1.85 as compared to a 36% decrease for the e/D of 3.69.

The 0° dominated laminate results are presented in Figures 3.2.3 and 3.2.4. For this laminate the e/D effect on strength reduction with temperature is much less pronounced. An interesting result is the pronounced W/D effect for the e/D of 1.85 and little or no W/D effect for specimens of e/D 3.69. Examining the failed specimens it

was seen that the failure mode was predominantly shear-out for  $e/D$  of 1.85 while it was bearing for  $e/D$  of 3.69. Notice that for the  $0^\circ$  dominated laminate the difference in strength is very pronounced at  $21^\circ\text{C}$  ( $70^\circ\text{F}$ ), but decreases to an almost undetectable difference at  $177^\circ\text{C}$  ( $350^\circ\text{F}$ ).

### 3.3 The Effect of Temperature on Modulus

The effective initial longitudinal ( $E_x$ ) modulus of the laminate was determined from the far field stress-strain curve on the instrumented samples and defined as average laminate stress/average far field strain. Summarized in Figures 3.3.1 and 3.3.2 are the variations of these experimentally determined modulus values with temperature. For the quasi-isotropic laminate, the modulus varied from 46.8 G Pa ( $6.8 \times 10^6$  psi) at  $21^\circ\text{C}$  ( $70^\circ\text{F}$ ) to 40.0 G Pa ( $5.8 \times 10^6$  psi) at  $177^\circ\text{C}$  ( $350^\circ\text{F}$ ). This translates to a 15% decrease in stiffness over the temperature interval. The  $0^\circ$  dominated laminate showed a similar 15% decrease in modulus ( $E_x$ ) over the temperature interval with the room temperature modulus being 73.3 G Pa ( $11.5 \times 10^6$  psi) and the  $177^\circ\text{C}$  ( $350^\circ\text{F}$ ) modulus being 67.0 G Pa ( $9.7 \times 10^6$  psi). A significantly lower modulus was found for  $e/D = 1.85$  geometry. The apparent change in effective longitudinal modulus can be attributed to strain gage position on the coupon. It is also believed that the large scatter in the data can be explained by small variations in the strain gage position. Finite element model

data shows that variations in the stress field around the hole extend beyond the 4.44 cm. (1-3/4 in.) location of the strain gage.

#### 3.4 Evaluation of e/D Effects on Strength

When failure load as a function of e/D was investigated some interesting effects due to out-of-plane constraint and temperature became apparent. In Figure 3.4.1 failure load as a function of e/D for a quasi-isotropic laminate with out-of-plane constraint shows increasing strength with increasing e/D. The results for the same quasi-isotropic laminate tested in pin bearing without constraint are summarized in Figures 3.4.2-3.4.4. Considering the 21°C (70°F) cases only, it is apparent that strength decreases significantly with increases in e/D for pin bearing loading - the inverse of out-of-plane constraint results.

The strength dependence on e/D has been noted by Van Siclen [7] for a different set of loading conditions. Van Siclen's results show decreases in shear-out strength and increases in bearing strength with increasing e/D for double lap joints made from quasi-isotropic T300/PR286 graphite-epoxy. The present data demonstrate converse behavior for pin bearing tests for a quasi-isotropic laminate which failed in bearing. Bearing strength decreased for pinned tests while the imposition of out-of-plane constraint resulted in a duplication of Van Siclen's findings.

Insufficient data were available to fully characterize this behavior for the  $0^\circ$  dominated laminate due to a transition in failure mode from shear-out to bearing. Ignoring failure mode, the  $e/D$  dependent strength behavior exhibited by this system for pin bearing loading conditions was similar to the quasi-isotropic case. These results further substantiate the role of out-of-plane deformation in the bearing failure mechanism, while the implications for shear-out are not clear due to the change in failure mode for that data.

### 3.5 Evaluation of Combined $e/D$ , $W/D$ and Temperature Effects on Joint Strength

Results from the pin bearing tests of the quasi-isotropic laminate reveal a change in the load carrying ability with temperature. At  $350^\circ\text{F}$  the laminate failure load increases with  $e/D$  or for the  $W/D = 7.43$  case remains unchanged. The  $0^\circ$  dominated laminate does not show this sensitivity to temperature as seen in Figures 3.5.1-3.5.3. There is an obvious  $W/D$  effect, however.

The region of the joint between the hole and the edge can be modelled simplistically as a short beam in bending (Fig. 3.5.4). The joint's strength in bearing is dependent upon the state of stress at the bearing surface (Point A) and the state of stress in that region is a function of the bending behavior. This was evident when finite element stress distributions and the strength data were analyzed for



values of  $e/D$  of 1.85 and 3.69. The larger bending deformation for the  $e/D$  of 1.85 geometry resulted in larger compressive stresses  $\sigma_y$  (as shown in Fig. 3.5.4) than for  $e/D$  of 3.69 coupons. Since the compressive stresses  $\sigma_x$  due to the pin load introduction were the same for both  $e/D$  values, the bending stresses  $\sigma_y$  were judged to be responsible for the differences in the state of stress at pin bearing location. The experimental results indicate that the geometric parameters  $e/D$  and  $W/D$ , as well as, out-of-plane constraint determine joint strength. Strength decreased with increasing values of  $e/D$  for pin bearing tests and increased with increasing  $e/D$  when out-of-plane constraint was imposed. This behavior varied with temperature for the quasi-isotropic laminate and while it was temperature insensitive for the  $0^\circ$  dominated laminate.  $W/D$  effects on the joint failure strength were also observed. The interaction of plate width, edge distance and temperature coupled with out-of-plane constraint conditions, determines the state of stress in the bearing zone ahead of the pin. The state of stress in this region in turn determines the strength of the joint.

### 3.6 Comparison of Experimental and Finite Element Modeled Net Section Strain Concentrations

Net section strain concentrations found experi-

mentally were compared with those determined from two-dimensional finite element models (3.6.1-3.6.2). The results are shown for 4 cases in tabular form in Table XVI. The correlation between the predicted and observed strain concentrations provided confidence that the model accurately predicted actual joint response.

### 3.7. Edge Deformation Predicted By Finite Element Model

After establishing a level of confidence in the finite element results, the model was used to examine joint in-plane deformations in the regions between the edge and the pin bearing surface of the hole. The deformations predicted for the two  $e/D$  cases are shown in Figure 3.7.1. The joint with an  $e/D = 2$  (Figure 3.7.1) exhibits large deformations at the coupon free end and the deformations take on a bending configuration. The deformation of the specimen with  $e/D = 4$  (Figure 3.7.1) does not exhibit bending characteristics and the magnitude of deformation is relatively small.

### 3.8. Bearing Stress Distribution Predicted By Finite Element Model

The finite element model was employed to predict bearing stress profiles ahead of the hole under pin bearing

loads. The results shown in Figures 3.8.1 and 3.8.2 indicate that the stress magnitudes are similar for both values of the  $e/D$  parameter. The model's prediction of similar bearing stress magnitudes for the two  $e/D$  values is not surprising. Regardless of  $e/D$  the coupon has the same bearing area. The difference in the strength for the two  $e/D$  values comes from the bending deformations discussed in section 3.7 and the associated change in the state of stress in front of the joint.

Predicted compressive stress concentrations for the  $e/D$  of 2.00 coupons were the same as those for the  $e/D$  of 4.00 coupons, thus verifying that the stress concentrations are not a factor in the  $e/D$  strength dependence. Differences in the  $\sigma_y$  stress magnitudes were observed and do verify that the state of stress in front of the joint is a factor in the pin bearing strength. The role of this state of stress in the failure mechanism is explained by the beam bending model in section 3.5. Important out-of-plane stress and deformation information could not be obtained from this two-dimensional model.

### 3.9 NDE of Damage State of Failed Coupons

Ultrasonic "C" scan inspection of the failed coupons produced the scans in Figures 3.9.2-3.9.6. These scans were used to assess the extent and type of damage at failure.

The ability to detect non-visible damage was found very useful in verifying the failure modes of coupons where visible damage was minimal. Figure 3.9.1 shows the three failure types encountered in this test program, bearing, shear-out and combination net-tension-shear-out.

Examples of the bearing failure "C" scans are shown in Figure 3.9.3. The hole elongation appears as an extension of the white region of the hole. The light grey regions ahead of the hole are characteristic of a change in thickness of the material and also some types of slight surface ply delaminations. The dark grey areas shown in Figure 3.9.3 are areas of severe delaminations and ply tear-outs. These characteristic patterns on the "C" scans were correlated visually with the types of damage described above for the failed specimens. All of the quasi-isotropic laminates shown in Figures 3.9.2 and 3.9.3 failed in bearing. Damage is localized with primary damage being an increase in thickness ahead of the loaded hole and very small areas of delamination (small dark areas) in the same region. The extent of damage did not change with temperature. The  $0^\circ$  dominated laminate exhibited bearing failure for all cases for  $e/D$  of 3.69 (Figure 3.9.5), but showed both bearing and shear-out failure for the  $e/D$  of 1.85 (Figure 3.9.4). Scans of the  $e/D$  3.69 coupons show small damage areas similar to the quasi-isotropic case. Some delaminations can be seen

along the  $\pm 45^\circ$  directions and again no changes in failure mode are seen with temperature. The e/D 1.85 scans show some interesting damage zone size effects. At room temperature the damage zone is a large region of severe delamination typical of a shear-out failure. At  $121^\circ\text{C}$  ( $250^\circ\text{F}$ ) the failure mode transitions from shear-out to predominantly bearing failure. At  $177^\circ\text{C}$  ( $350^\circ\text{F}$ ) the failure mode is again primarily shear-out. Notice that the damage extent is smaller and localized directly in front of the hole for the  $177^\circ\text{C}$  ( $350^\circ\text{F}$ ) samples. Scans of failed specimens tested with out-of-plane constraint shown in Figure 3.9.6 exhibit damage zones similar to those of pin bearing tests. The failure mode for the  $0^\circ$  dominated laminate with  $3/D = 1.85$  and  $W/D = 3.71$  was a combination net section, tension shear-out failure mode when out-of-plane constraint was imposed, whereas the failure was shear-out for simple pin bearing.

### 3.10 Delayed Test Strength Degradation Phenomenon

Most of the instrumented samples were tested 150 days after laminate fabrication. The test results from these samples exhibited a significant decrease in strength as compared to the coupons tested under the same conditions 30 - 60 days after fabrication. The degradation in strength was evaluated by normalizing the residual strength of the 150 day coupons with respect to the average strength of the 30 - 60

day coupons tested under identical conditions. Figures 3.10.1 and 3.10.2 summarize the reduction in strength over the range of test temperatures explored. At 177°C (350°F) the effect was more pronounced than for the lower two test temperatures.

The processing, machining and testing histories for all test coupons were identical. Variability between panels was also ruled out as a cause since both the 150 day and 30 day test coupons were from the same set of panels and no strength variation between panels was detected in the previous tests. The moisture and thermal histories were the only differences between the two groups of test coupons. The instrumented test coupons were stored in sealed plastic bags containing desiccant for the 150 day period prior to test, but no moisture content measurements were taken. Each 121°C (250°F) and 177°C (350°F) instrumented test coupon underwent two thermal cycles to 163°C (325°F) in order to cure the elevated temperature adhesives for mounting the strain gages.

Results reported by Kim and Whitney [4] showed a decrease in strength of 10 percent due to moisture alone and no interaction between temperature and moisture could be ascertained. The present phenomena exhibits decreases in strength ranging from 11% to 50%. The effective decreases in strength show trends between 15% and 30% at the

21°C (70°F) and 121°C (250°F) temperatures and 30% to 40% decreases for the 177°C (350°F) tests. The strength reduction reported is significantly greater than 10%. This raises important questions about moisture and temperature effects on pin loaded composite joint strength.

#### 4.0 CONCLUSIONS

Clamped tests (tests with controlled out-of-plane constraint) are much more useful than pinned tests from a design standpoint. A careful study of pinned and clamped tests with instrumentation monitoring the load and strain data in three dimensions would be very effective in clarifying bolted joint failure mechanisms.

In a comparison of strengths for pin bearing and out-of-plane constraint pin bearing loading conditions, the out-of-plane constraint was shown to increase the failure loads significantly for both bearing and shear-out failure modes. This finding implies a relationship between out-of-plane deformation and the bearing and shear-out failure mechanisms.

Increasing temperatures over the 21°C (70°F) to 177°C (350°F) range result in a decrease in pin bearing strength for the two laminates tested. This temperature dependent strength behavior is more pronounced for bearing failure than shear-out failure at lower temperatures, but both mechanisms exhibit similar behavior at temperatures approaching 177°C (350°F). Since the matrix is the temperature sensitive component of the system, the different temperature effects for the bearing and shear-out failure modes imply that the two modes are unique with respect to the matrix governed aspects of their failure mechanisms.



Laminate Young's modulus decreased with increasing temperature due to the change in matrix material properties with temperature. The reduction of stiffness with increased temperature allows increased laminate deformation for a given joint load level. The role of these deformations in the failure mechanism is explained next.

The net section strain concentrations predicted by a two-dimensional finite element model correlated well with experimentally measured values. Model-predicted deformations for the two e/D geometries, verified the presence of bending deformation ahead of the pin in the xy plane<sup>1</sup> for e/D of 1.85 while showing only extensional deformations for e/D of 3.69 as shown in Figure 3.7.1.

The effectiveness of ultrasonic "C" scan inspection of failed joints to evaluate damage size and type was demonstrated.

Results from the instrumented samples tested approximately 150 days after fabrication indicated a significant strength degradation when compared to test results at 30 - 60 days. Careful examination of the sample fabrication and test histories eliminated all test variables except moisture and thermal history. Insufficient data

---

<sup>1</sup>The xy plane is in the plane of the laminate with z being normal to the laminate.

were available to attribute the strength degradation phenomena to either of these variables. Results reported by Wilkins (8) and Kim and Whitney (4) indicate that moisture alone results in only a ten percent strength reduction at a given temperature. Since the magnitude of the strength reduction observed was significantly larger than that which might be attributed to moisture alone, the observed phenomena requires further study.

## 5.0 REFERENCES

1. Ashton, J.E., Burdouf, M.L., and Olson, F.O.; Design, Analysis and Testing Advanced Composite F-111 Fuselage. Convair/General Dynamics, SMD-059, 20 April 1971.
2. Hart-Smith, L.J.; Bolted Joints in Graphite-Epoxy Composites. Douglas Aircraft Company, NASA Contract Report NASA CR-144899, June 1976.
3. Jong, Theo de; "Stresses Around Pin-Loaded Holes in Elastically Orthotropic or Isotropic Plates", J. Composite Materials, Vol. 11, July 1977, p. 313.
4. Kim, R.Y. and Whitney, J.M., "Effect of Temperature and Moisture on Pin Bearing Strength of Composite Laminates", J. Composite Materials, Vol. 10, April 1976, p. 149.
5. Quinn, W.J. and Matthews, F.L., "The Effect of Stacking Sequence on the Pin-Bearing Strength in Glass Fibre Reinforced Plastic", J. Composite Materials, Vol. 11, April 1977, p. 139.
6. Padawer, G.E., "The Strength of Bolted Connections in Graphite/Epoxy Composites Reinforced by Colaminated Boron Film", Composite Material: Testing and Design (Second Conference), ASTM STP 497, American Society for Testing and Materials, 1972, pp. 396-414.
7. Van Siclen, R.C.: "Evaluation of Bolted Joints in Graphite-Epoxy," Proceedings of the Army Symposium on Solid Mechanics, AMMRC MS74-8, September 1974.
8. Wilkins, D.J., "Environmental Sensitivity Tests of Graphite-Epoxy Bolt Bearing Properties," Composite Materials: Testing and Design (Fourth Conference) ASTM STP 617, American Society for Testing and Materials, 1977, pp. 497-513.
9. Advanced Composites Design Guide, Vol. I, Design, Third Edition, Contract F33615-74-C-5075, North American Rockwell/Los Angeles Division, January 1973.
10. Waszczak, J.P. and Cruse, T.A., "Failure Mode and Strength Predictions of Anisotropic Bolt Bearing Specimens", J. of Composite Materials, Vol. 5, July 1971, p. 421.

11. Waszczak, J.P. and Cruse, T.A., "A Synthesis Procedure for Mechanically Fastened Joints in Advanced Composite Materials", AIAA/ASME/SAE 14th Structures, Structural Dynamics, and Materials Conference, March 1973.
12. Harris, H.G. and Ojalvo, I.U.: "Simplified Three-Dimensional Analysis of Mechanically Fastened Joints", Proceedings of the Army Symposium on Solid Mechanics, AMMRC MS74-8, September 1974.

6.0 ACKNOWLEDGEMENTS

The authors would like to recognize David A. Riegner for his contribution in the development of the finite element models of the two bolted joint configurations.

7.0 APPENDIX A (Data Tables)

[Faint, illegible data tables and text are visible on the right side of the page, likely representing the data tables mentioned in the section header.]

TABLE I A  
 [45/0/-45/0<sub>2</sub>/-45/0/45/0<sub>2</sub>/90]<sub>g</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 70°F

English Units

| Sample | e/D  | T <sup>†</sup><br>(in.) | W<br>(in.) | Pin<br>Dia.<br>(in.) | Failure<br>Load<br>(lb <sub>f</sub> ) | Bearing<br>Stress<br>(10 <sup>4</sup> PSI) | Shear<br>Stress<br>(10 <sup>4</sup> PSI) | Net Tension<br>Stress<br>(10 <sup>4</sup> PSI) | Mode |
|--------|------|-------------------------|------------|----------------------|---------------------------------------|--|--|--|------|
| 02C2B  | 3.69 | 0.117                   | 0.998      | 0.202                | 1996                                  | 8.45                                       | 0.24                                     | 2.14   | B    |
| 01R2B  | 3.69 | 0.117                   | 0.997      | 0.202                | 2073                                  | 8.86                                       | 0.25                                     | 2.23   | B    |
| 02C2T  | 3.69 | 0.118                   | 0.999      | 0.202                | 1974                                  | 8.28                                       | 0.24                                     | 2.10   | B    |
| 01C1B  | 3.69 | 0.118                   | 1.497      | 0.202                | 2062                                  | 8.65                                       | 0.25                                     | 1.35   | B    |
| 02R1B  | 3.69 | 0.117                   | 1.498      | 0.202                | 1941                                  | 8.21                                       | 0.24                                     | 1.28   | B    |
| 01R1B  | 3.69 | 0.116                   | 1.508      | 0.202                | 1720                                  | 7.22                                       | 0.21                                     | 1.14   | B    |
| 01C3B  | 3.69 | 0.122                   | 0.747      | 0.202                | 1985                                  | 8.10                                       | 0.23                                     | 2.99   | B    |
| 01R3B  | 3.69 | 0.114                   | 0.747      | 0.202                | 1897                                  | 8.23                                       | 0.24                                     | 3.05   | B    |
| 02C3B  | 3.69 | 0.119                   | 0.748      | 0.202                | 1776                                  | 7.39                                       | 0.21                                     | 2.73   | B    |

TABLE 1 B  
 [45/0/-45/0<sub>2</sub>/-45/0/45/0<sub>2</sub>/90]<sub>s</sub> BOLTED JOINT STRENGTH DATA  
 TEST TEMP. = 70°F (21°C)

S.I. Units

| Sample | e/D  | T<br>(cm.) | W<br>(cm.) | Pin<br>Dia.<br>(cm.) | Failure<br>Load<br>(Newtons) | Bearing<br>Stress<br>M Pa | Shear<br>Stress<br>M Pa | Net Tension<br>Stress<br>M Pa | Mode |
|--------|------|------------|------------|----------------------|------------------------------|---------------------------|-------------------------|-------------------------------|------|
| 02C2B  | 3.69 | 0.297      | 2.535      | 0.511                | 88.82                        | 582.8                     | 16.6                    | 147.6                         | B    |
| 01R2B  | 3.69 | 0.297      | 2.532      | 0.511                | 92.25                        | 611.1                     | 17.2                    | 153.8                         | B    |
| 02C2T  | 3.69 | 0.300      | 2.537      | 0.511                | 87.84                        | 571.1                     | 16.6                    | 144.8                         | B    |
| 01C1B  | 3.69 | 0.300      | 3.802      | 0.511                | 91.76                        | 596.6                     | 17.2                    | 93.1                          | B    |
| 02R1B  | 3.69 | 0.297      | 3.805      | 0.511                | 86.37                        | 566.2                     | 16.6                    | 88.3                          | B    |
| 01R1B  | 3.69 | 0.295      | 3.830      | 0.511                | 76.54                        | 498.0                     | 14.5                    | 78.6                          | B    |
| 01C3B  | 3.69 | 0.310      | 1.897      | 0.511                | 88.33                        | 558.7                     | 15.9                    | 206.2                         | B    |
| 01R3R  | 3.69 | 0.290      | 1.897      | 0.511                | 84.42                        | 567.6                     | 16.6                    | 210.4                         | B    |
| 02C3B  | 3.69 | 0.302      | 1.900      | 0.511                | 79.03                        | 509.7                     | 14.5                    | 183.3                         | B    |



TABLE II A  
 [45/0/-45/0<sub>2</sub>/-45/0/45/0<sub>2</sub>/90] <sub>g</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 70°F

English Units

| Sample | e/D  | T<br>(in.) | W<br>(in.) | Pin<br>Dia.<br>(in.) | Failure<br>Load<br>(lb <sub>f</sub> ) | Bearing<br>Stress<br>(10 <sup>4</sup> PSI) | Shear<br>Stress<br>(10 <sup>4</sup> PSI) | Net Tension<br>Stress<br>(10 <sup>4</sup> PSI) | Mode |
|--------|------|------------|------------|----------------------|---------------------------------------|--|--|--|------|
| 01L3T  | 1.85 | 0.115      | 0.745      | 0.202                | 2106                                  | 9.06                                       | 0.61                                     | 3.37   | S    |
| 01C3T  | 1.85 | 0.120      | 0.747      | 0.202                | 2205                                  | 9.10                                       | 0.61                                     | 3.37   | S    |
| 01L3B* | 1.85 | 0.117      | 0.744      | 0.202                | 1776                                  | 7.51                                       | 0.51                                     | 2.80   | S    |
| 01L2B  | 1.85 | 0.121      | 0.996      | 0.202                | 2128                                  | 8.71                                       | 0.59                                     | 2.21   | S    |
| 01L2T  | 1.85 | 0.117      | 0.996      | 0.202                | 2117                                  | 8.96                                       | 0.60                                     | 2.28   | S    |
| 01C2T* | 1.85 | 0.116      | 0.997      | 0.202                | 1654                                  | 6.82                                       | 0.46                                     | 1.73   | S    |
| 02L1B  | 1.85 | 0.116      | 1.498      | 0.202                | 1808                                  | 7.72                                       | 0.52                                     | 1.20   | S    |
| 02L1T  | 1.85 | 0.115      | 1.499      | 0.202                | 1919                                  | 8.26                                       | 0.56                                     | 1.29   | S    |
| 02R1T* | 1.85 | 0.118      | 1.498      | 0.202                | 1786                                  | 7.49                                       | 0.51                                     | 1.17   | S    |

\*Indicates tests after 4 month storage.

TABLE II B

[45/0/-45/0<sub>2</sub>/-45/0/45/0<sub>2</sub>/90]<sub>B</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 70°F (21°C)

S.I. Units

| Sample | e/D  | T<br>(cm.) | W<br>(cm.) | Pin<br>Dia.<br>(cm.) | Failure<br>Load<br>(Newtons) | Bearing<br>Stress<br>M Pa | Shear<br>Stress<br>M Pa | Net Tension<br>Stress<br>M Pa | Mode |
|--------|------|------------|------------|----------------------|------------------------------|---------------------------|-------------------------|-------------------------------|------|
| 01L3T  | 1.85 | 0.292      | 1.892      | 0.511                | 9372                         | 624.9                     | 42.1                    | 232.4                         | S    |
| 01C3T  | 1.85 | 0.305      | 1.897      | 0.511                | 9812                         | 627.6                     | 42.1                    | 232.4                         | S    |
| 01L3B  | 1.85 | 0.297      | 1.890      | 0.511                | 7903                         | 518.0                     | 35.2                    | 193.1                         | S    |
| 01L2B  | 1.85 | 0.307      | 2.530      | 0.511                | 9470                         | 600.7                     | 40.7                    | 152.4                         | S    |
| 01L2T  | 1.85 | 0.297      | 2.530      | 0.511                | 9421                         | 618.0                     | 41.4                    | 157.3                         | S    |
| 01C2T  | 1.85 | 0.305      | 2.532      | 0.511                | 7360                         | 470.4                     | 31.7                    | 119.3                         | S    |
| 02L1B  | 1.85 | 0.295      | 3.805      | 0.511                | 8046                         | 532.4                     | 35.9                    | 82.8                          | S    |
| 02L1T  | 1.85 | 0.292      | 3.807      | 0.511                | 8540                         | 569.7                     | 38.6                    | 89.0                          | S    |
| 02R1T  | 1.85 | 0.300      | 3.805      | 0.511                | 7948                         | 516.6                     | 35.2                    | 80.7                          | S    |

TABLE III A

[45/0/-45/0<sub>2</sub>/-45/0/45/0<sub>2</sub>/90]<sub>g</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 250°F

English Units

| Sample | e/D  | T<br>(in.) | W<br>(in.) | Pin<br>Dia.<br>(in.) | Failure<br>Load<br>(lb <sub>f</sub> ) | Bearing<br>Stress<br>(10 <sup>4</sup> PSI) | Shear<br>Stress<br>(10 <sup>4</sup> PSI) | Net Tension<br>Stress<br>(10 <sup>4</sup> PSI) | Mode |
|--------|------|------------|------------|----------------------|---------------------------------------|--|--|--|------|
| 02R3B  | 3.69 | 0.115      | 0.748      | 0.202                | 1535                                  | 6.61                                       | 0.19                                     | 2.45   | B    |
| 01R3T  | 3.69 | 0.114      | 0.747      | 0.202                | 1471                                  | 6.38                                       | 0.18                                     | 2.37   | B    |
| 04L2B* | 3.69 | 0.125      | 0.754      | 0.202                | 1015                                  | 4.02                                       | 0.12                                     | 1.47   | B    |
| 01C2B  | 3.69 | 0.121      | 0.996      | 0.202                | 1535                                  | 6.28                                       | 0.18                                     | 1.60   | B    |
| 02L2B  | 3.69 | 0.116      | 0.998      | 0.202                | 1511                                  | 6.44                                       | 0.19                                     | 1.64   | B    |
| 04R2B* | 3.69 | 0.128      | 1.002      | 0.202                | 1352                                  | 5.23                                       | 0.15                                     | 1.32   | B    |
| 01R1T  | 3.69 | 0.117      | 1.502      | 0.202                | 1495                                  | 6.33                                       | 0.18                                     | 0.98   | B    |
| 02C1T  | 3.69 | 0.122      | 1.505      | 0.202                | 1522                                  | 6.18                                       | 0.18                                     | 0.96   | B    |
| 04C2B* | 3.69 | 0.129      | 1.505      | 0.202                | 1301                                  | 4.99                                       | 0.14                                     | 0.77   | B    |

\*Indicates test after 4 month storage.

TABLE III B

[45/0/-45/0<sub>2</sub>/-45/0/45/0<sub>2</sub>/90]<sub>s</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 121°C (250°F)

S.I. Units

| Sample | e/D  | T<br>(cm.) | W<br>(cm.) | Pin<br>D: a.<br>(cm.) | Failure<br>Load<br>(Newtons) | Bearing<br>Stress<br>M Pa | Shear<br>Stress<br>M Pa | Net Tension<br>Stress<br>M Pa | Mode |
|--------|------|------------|------------|-----------------------|------------------------------|---------------------------|-------------------------|-------------------------------|------|
| 02R3B  | 3.69 | 0.292      | 1.900      | 0.511                 | 6831                         | 455.9                     | 13.1                    | 169.0                         | B    |
| 01R3T  | 3.69 | 0.290      | 1.897      | 0.511                 | 6546                         | 440.0                     | 12.4                    | 163.5                         | B    |
| 04L2B  | 3.69 | 0.318      | 1.915      | 0.511                 | 4517                         | 277.3                     | 8.3                     | 158.3                         | B    |
| 01C2B  | 3.69 | 0.307      | 2.530      | 0.511                 | 6831                         | 433.1                     | 12.4                    | 110.4                         | B    |
| 02L2B  | 3.69 | 0.295      | 2.535      | 0.511                 | 6724                         | 444.2                     | 13.1                    | 113.1                         | B    |
| 04R2B  | 3.69 | 0.325      | 2.545      | 0.511                 | 6016                         | 360.7                     | 10.3                    | 91.0                          | B    |
| 01R1T  | 3.69 | 0.297      | 3.815      | 0.511                 | 6653                         | 436.6                     | 12.4                    | 67.6                          | B    |
| 02C1T  | 3.69 | 0.310      | 3.823      | 0.511                 | 6773                         | 426.2                     | 12.4                    | 60.2                          | B    |
| 04C2B  | 3.69 | 0.328      | 3.823      | 0.511                 | 5789                         | 344.2                     | 9.7                     | 53.1                          | B    |

TABLE IV A  
 [45/0/-45/0<sub>2</sub>/-45/0/45/0<sub>2</sub>/90] s BOLTED JOINT STRENGTH DATA

TEST TEMP. = 250°F

English Units

| Sample | e/D  | T<br>(in.) | W<br>(in.) | Pin<br>Dia.<br>(in.) | Failure<br>Load<br>(lb <sub>f</sub> ) | Bearing<br>Stress<br>(10 <sup>4</sup> PSI) | Shear<br>Stress<br>(10 <sup>4</sup> PSI) | Net Tension<br>Stress<br>(10 <sup>4</sup> PSI) | Mode |
|--------|------|------------|------------|----------------------|---------------------------------------|--|--|--|------|
| 02R2T  | 1.85 | 0.118      | 0.997      | .202                 | 1610                                  | 6.75                                       | 0.46                                     | 1.72   | S    |
| 02L2T  | 1.85 | 0.115      | 0.997      | .202                 | 1654                                  | 7.12                                       | 0.48                                     | 1.81   | B    |
| 04R1T* | 1.85 | 0.129      | 1.000      | .202                 | 1433                                  | 5.50                                       | 0.37                                     | 1.39   | B    |
| 02L4B  | 1.85 | 0.116      | 0.739      | .202                 | 1720                                  | 7.34                                       | 0.49                                     | 1.76   | S    |
| 01C4T  | 1.85 | 0.120      | 0.747      | .202                 | 1643                                  | 6.78                                       | 0.46                                     | 2.51   | B    |
| 02L4T* | 1.85 | 0.116      | 0.745      | .202                 | 1378                                  | 5.88                                       | 0.40                                     | 2.19   | B    |
| 01C1T  | 1.85 | 0.116      | 1.499      | .202                 | 1522                                  | 6.38                                       | 0.43                                     | 0.99   | B    |
| 01L1T  | 1.85 | 0.120      | 1.501      | .202                 | 1467                                  | 6.05                                       | 0.41                                     | 0.94   | B    |
| 01L1B* | 1.85 | 0.121      | 1.501      | .202                 | 1390                                  | 5.69                                       | 0.38                                     | 0.88   | B    |

\*T<sub>1</sub> indicates tests after 4 month storage.

TABLE IV B

[45/0/-45/0<sub>2</sub>/-45/0/45/0<sub>2</sub>/90]<sub>s</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 121°C (250°F)

S.I. Units

| Sample | e/D  | T<br>(cm.) | W<br>(cm.) | Pin<br>Dia.<br>(cm.) | Failure<br>Load<br>(Newtons) | Bearing<br>Stress<br>M Pa | Shear<br>Stress<br>M Pa | Net Tension<br>Stress<br>M Pa | Mode |
|--------|------|------------|------------|----------------------|------------------------------|---------------------------|-------------------------|-------------------------------|------|
| 02R2T  | 1.85 | 0.300      | 2.532      | 0.511                | 7165                         | 465.5                     | 31.7                    | 118.6                         | S    |
| 02L2T  | 1.85 | 0.292      | 2.532      | 0.511                | 7360                         | 491.1                     | 33.1                    | 124.8                         | B    |
| 04R1T  | 1.85 | 0.328      | 2.540      | 0.511                | 6377                         | 379.3                     | 25.5                    | 95.9                          | B    |
| 02L4B  | 1.85 | 0.295      | 1.877      | 0.511                | 7654                         | 506.2                     | 33.8                    | 190.4                         | S    |
| 01C4T  | 1.85 | 0.305      | 1.897      | 0.511                | 7311                         | 467.6                     | 31.7                    | 173.1                         | U    |
| 02L4T  | 1.85 | 0.295      | 1.892      | 0.511                | 6132                         | 405.5                     | 27.6                    | 151.0                         | B    |
| 01C1T  | 1.85 | 0.300      | 3.807      | 0.511                | 6773                         | 440.0                     | 29.7                    | 68.3                          | B    |
| 01L1T  | 1.85 | 0.305      | 3.813      | 0.511                | 6528                         | 417.3                     | 28.3                    | 64.8                          | B    |
| 01L1B  | 1.85 | 0.307      | 3.813      | 0.511                | 6186                         | 392.4                     | 26.2                    | 60.7                          | B    |

TABLE V A  
 [45/0/-45/0<sub>2</sub>/-45/0/45/0<sub>2</sub>/90]<sub>s</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 350°F

English Units

| Sample | e/D  | T<br>(in.) | W<br>(in.) | Pin<br>Dia.<br>(in.) | Failure<br>Load<br>(lb <sub>f</sub> ) | Bearing<br>Stress<br>(10 <sup>4</sup> PSI) | Shear<br>Stress<br>(10 <sup>4</sup> PSI) | Net Tension<br>Stress<br>(10 <sup>4</sup> PSI) | Mode |
|--------|------|------------|------------|----------------------|---------------------------------------|--|--|--|------|
| 05R3T  | 3.69 | 0.119      | 0.752      | 0.202                | 1169                                  | 4.86                                       | 0.14                                     | 1.79   | B    |
| 05R3B  | 3.69 | 0.122      | 0.752      | 0.202                | 1102                                  | 4.47                                       | 0.13                                     | 1.64   | B    |
| 05L3T* | 3.69 | 0.119      | 0.753      | 0.202                | 860                                   | 3.58                                       | 0.10                                     | 1.31   | B    |
| 05R2T  | 3.69 | 0.119      | 1.001      | 0.202                | 1147                                  | 4.77                                       | 0.14                                     | 1.21   | B    |
| 05L4B  | 3.69 | 0.119      | 1.004      | 0.202                | 1171                                  | 4.87                                       | 0.14                                     | 1.23   | B    |
| 05R2B* | 3.69 | 0.121      | 1.001      | 0.202                | 717                                   | 2.93                                       | 0.08                                     | 0.74   | B    |
| 05L1B  | 3.69 | 0.120      | 1.500      | 0.202                | 1103                                  | 4.55                                       | 0.13                                     | 0.70   | B    |
| 05C1B  | 3.69 | 0.123      | 1.498      | 0.202                | 1202                                  | 4.84                                       | 0.14                                     | 0.75   | B    |
| 05L1T* | 3.69 | 0.118      | 1.500      | 0.202                | 750                                   | 3.15                                       | 0.09                                     | 0.49   | B    |

Indicates test after 4 month storage.

TABLE V B  
 [45/0/-45/0<sub>2</sub>/-45/0/45/0<sub>2</sub>/90]<sub>s</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 350°F (177°C)

S.I. Units

| Sample | e/D  | T<br>(cm.) | W<br>(cm.) | Pin<br>Dia.<br>(cm.) | Failure<br>Load<br>(Newtons) | Bearing<br>Stress<br>M Pa | Shear<br>Stress<br>M Pa | Net Tension<br>Stress<br>M Pa | Mode |
|--------|------|------------|------------|----------------------|------------------------------|---------------------------|-------------------------|-------------------------------|------|
| 05R3T  | 3.69 | 0.302      | 1.910      | 0.511                | 5202                         | 335.2                     | 9.7                     | 123.5                         | B    |
| 05R3B  | 3.69 | 0.310      | 1.910      | 0.511                | 4904                         | 308.3                     | 9.0                     | 113.1                         | B    |
| 05L3T  | 3.69 | 0.302      | 1.913      | 0.511                | 3827                         | 246.9                     | 6.9                     | 90.4                          | B    |
| 05R2T  | 3.69 | 0.302      | 2.543      | 0.511                | 5704                         | 329.0                     | 9.7                     | 83.5                          | B    |
| 05L4B  | 3.69 | 0.302      | 2.550      | 0.511                | 5211                         | 335.9                     | 9.7                     | 84.8                          | B    |
| 05R2B  | 3.69 | 0.307      | 2.543      | 0.511                | 3191                         | 202.1                     | 5.5                     | 51.0                          | B    |
| 05L1B  | 3.69 | 0.305      | 3.810      | 0.511                | 4908                         | 313.8                     | 9.0                     | 48.3                          | B    |
| 05C1B  | 3.69 | 0.312      | 3.805      | 0.511                | 5349                         | 333.8                     | 9.7                     | 51.7                          | B    |
| 05L1T  | 3.69 | 0.300      | 3.810      | 0.511                | 3338                         | 217.3                     | 6.2                     | 33.8                          | B    |



TABLE VI A  
 [45/0/-45/0<sub>2</sub>/-45/0/45/0<sub>2</sub>/90] S BOLTED JOINT STRENGTH DATA

TEST TEMP. = 350°F

English Units

| Sample | e/D  | T <sup>1</sup><br>(in.) | W<br>(in.) | Pin<br>Dia.<br>(in.) | Failure<br>Load<br>(lb <sub>f</sub> ) | Bearing<br>Stress<br>(10 <sup>4</sup> PSI) | Shear<br>Stress<br>(10 <sup>4</sup> PSI) | Net Tension<br>Stress<br>(10 <sup>4</sup> PSI) | Mode |
|--------|------|-------------------------|------------|----------------------|---------------------------------------|--|--|--|------|
| 05R4B  | 1.85 | 0.121                   | 0.748      | .202                 | 1257                                  | 5.14                                       | 0.35                                     | 1.90   | B    |
| 05L3B  | 1.85 | 0.119                   | 0.752      | .202                 | 1301                                  | 5.28                                       | 0.36                                     | 1.99   | S/B  |
| 05L2T* | 1.85 | 0.122                   | 0.753      | .202                 | 860                                   | 3.49                                       | 0.24                                     | 1.28   | S/B  |
| 05C3T  | 1.85 | 0.127                   | 1.002      | .202                 | 1257                                  | 4.90                                       | 0.33                                     | 1.24   | S/B  |
| 05R1T  | 1.85 | 0.125                   | 0.998      | .202                 | 1279                                  | 5.07                                       | 0.34                                     | 1.29   | S/B  |
| 05L4T* | 1.85 | 0.120                   | 1.005      | .202                 | 871                                   | 3.59                                       | 0.24                                     | 0.90   | B    |
| 05C2T  | 1.85 | 0.126                   | 1.505      | .202                 | 1235                                  | 4.85                                       | 0.32                                     | 0.75   | S/B  |
| 05C2B  | 1.85 | 0.126                   | 1.505      | .202                 | 1235                                  | 4.85                                       | 0.32                                     | 0.75   | S/B  |
| 05C1T* | 1.85 | 0.122                   | 1.495      | .202                 | 915                                   | 3.71                                       | 0.25                                     | 0.58   | S/B  |

\*Indicates tests after 4 month storage.

TABLE VI B  
 [45/0/-45/0<sub>2</sub>/-45/0/45/0/90]<sub>s</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 350°F (177°C)

S.I. Units

| Sample | e/D  | T<br>(cm.) | W<br>(cm.) | in<br>Dia.<br>(cm.) | Failure<br>Load<br>(Newtons) | Bearing<br>Stress<br>M Pa | Shear<br>Stress<br>M Pa | Net Tension<br>Stress<br>M Pa | Mode |
|--------|------|------------|------------|---------------------|------------------------------|---------------------------|-------------------------|-------------------------------|------|
| 05R4B  | 1.85 | 0.307      | 1.900      | 0.511               | 5594                         | 354.5                     | 24.1                    | 131.0                         | B    |
| 05L3B  | 1.85 | 0.302      | 1.910      | 0.511               | 5789                         | 364.2                     | 24.8                    | 137.3                         | S/B  |
| 05L2T  | 1.85 | 0.310      | 1.913      | 0.511               | 3827                         | 240.7                     | 16.6                    | 88.3                          | S/B  |
| 05C3T  | 1.85 | 0.323      | 2.545      | 0.511               | 5594                         | 338.0                     | 22.8                    | 85.5                          | S/B  |
| 05R1T  | 1.85 | 0.318      | 2.535      | 0.511               | 5692                         | 349.7                     | 23.4                    | 89.0                          | S/B  |
| 05L4T  | 1.85 | 0.305      | 2.553      | 0.511               | 3876                         | 247.6                     | 16.6                    | 62.1                          | B    |
| 05C2T  | 1.85 | 0.320      | 3.823      | 0.511               | 5496                         | 334.5                     | 22.1                    | 51.7                          | S/B  |
| 05C2B  | 1.85 | 0.320      | 3.823      | 0.511               | 5496                         | 334.5                     | 22.1                    | 51.7                          | S/B  |
| 05C1T  | 1.85 | 0.122      | 3.797      | 0.511               | 4072                         | 255.9                     | 17.2                    | 40.0                          | S/B  |

TABLE VII A  
 [0/±45/90]<sub>2s</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 70°F

English Units

| Sample | e/D  | T<br>(in.) | W<br>(in.) | Pin<br>Dia.<br>(in.) | Failure<br>Load<br>(lb <sub>f</sub> ) | Bearing<br>Stress<br>(10 <sup>4</sup> PSI) | Shearout<br>Stress<br>(10 <sup>4</sup> PSI) | Net Tension<br>Stress<br>(10 <sup>4</sup> PSI) | Mode |
|--------|------|------------|------------|----------------------|---------------------------------------|--|---|--|------|
| 44C2B  | 3.69 | .092       | .997       | .201                 | 1213                                  | 6.56                                       | 0.19  | 1.66   | B    |
| 44C3B  | 3.69 | .092       | .997       | .201                 | 1279                                  | 6.92                                       | 0.20  | 1.75   | B    |
| 44C3T  | 3.69 | .090       | .996       | .201                 | 891                                   | 4.81                                       | 0.14  | 1.25   | B    |
| 44C1B  | 3.69 | .090       | 1.500      | .201                 | 1213                                  | 6.71                                       | 0.19  | 1.04   | B    |
| 46L1B  | 3.69 | .088       | 1.499      | .201                 | 1279                                  | 7.23                                       | 0.21  | 1.12   | B    |
| 46L1T  | 3.69 | .089       | 1.501      | .201                 | 1213                                  | 6.78                                       | 0.19  | 1.05   | B    |
| 44R4B  | 3.69 | .089       | .748       | .201                 | 1191                                  | 6.66                                       | 0.19  | 2.45   | B    |
| 44R4T  | 3.69 | .088       | .748       | .201                 | 1213                                  | 6.85                                       | 0.20  | 2.52   | B    |
| 44R3T  | 3.69 | .089       | .747       | .201                 | 1191                                  | 6.66                                       | 0.19  | 2.45   | B    |

TABLE VII B  
 [0/+45/90]<sub>2B</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 21°C (70°F)

S.I. Units

| Sample | e/D  | T<br>(cm.) | W<br>(cm.) | Pin<br>Dia.<br>(cm.) | Failure<br>Load<br>(Newtons) | Bearing<br>Stress<br>M Pa | Shear<br>Stress<br>M Pa | Net Tension<br>Stress<br>M Pa | Mode |
|--------|------|------------|------------|----------------------|------------------------------|---------------------------|-------------------------|-------------------------------|------|
| 44C2B  | 3.69 | 0.234      | 2.532      | 0.511                | 5398                         | 452.5                     | 13.0                    | 114.5                         | B    |
| 44C3B  | 3.69 | 0.234      | 2.532      | 0.511                | 5692                         | 477.3                     | 13.8                    | 120.7                         | B    |
| 44C3T  | 3.69 | 0.229      | 2.530      | 0.511                | 3965                         | 331.7                     | 9.7                     | 86.2                          | B    |
| 44C1B  | 3.69 | 0.229      | 3.810      | 0.511                | 5398                         | 462.8                     | 13.1                    | 77.3                          | B    |
| 46L1B  | 3.69 | 0.224      | 3.807      | 0.511                | 5692                         | 498.7                     | 14.5                    | 72.4                          | H    |
| 46L1T  | 3.69 | 0.226      | 3.813      | 0.511                | 5398                         | 467.6                     | 13.1                    | 90.4                          | B    |
| 44R4B  | 3.69 | 0.226      | 1.900      | 0.511                | 5300                         | 459.3                     | 13.1                    | 169.0                         | B    |
| 44R4T  | 3.69 | 0.224      | 1.900      | 0.511                | 5398                         | 472.4                     | 13.8                    | 173.8                         | B    |
| 44R3T  | 3.69 | 0.226      | 1.897      | 0.511                | 5300                         | 459.3                     | 13.1                    | 168.9                         | B    |

TABLE VIII A  
 [0/±45/90]<sub>2s</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 70°F

English Units

| Sample | e/D  | T<br>(in.) | W<br>(in.) | Pin<br>Dia.<br>(in.) | Failure<br>Load<br>(lb <sub>f</sub> ) | Bearing<br>Stress<br>(10 <sup>4</sup> PSI) | Shear<br>Stress<br>(10 <sup>4</sup> PSI) | Net Tension<br>Stress<br>(10 <sup>4</sup> PSI) | Mode |
|--------|------|------------|------------|----------------------|---------------------------------------|--|--|--|------|
| 45L3T  | 1.85 | 0.088      | 0.748      | .202                 | 1356                                  | 7.63                                       | 0.51                                     | 2.82   | B    |
| 45L3B  | 1.85 | 0.089      | 0.751      | .202                 | 1478                                  | 8.22                                       | 0.55                                     | 5.02   | B    |
| 44R3B* | 1.85 | 0.089      | 0.747      | .202                 | 1169                                  | 6.50                                       | 0.44                                     | 2.41   | B    |
| 44C2T  | 1.85 | 0.091      | 0.997      | .202                 | 1434                                  | 7.80                                       | 0.53                                     | 1.94   | B    |
| 44L2B  | 1.85 | 0.088      | 0.996      | .202                 | 1356                                  | 7.63                                       | 0.51                                     | 1.94   | B    |
| 44L2T* | 1.85 | 0.089      | 0.996      | .202                 | 1136                                  | 6.30                                       | 0.51                                     | 1.92   | B    |
| 44L1B  | 1.85 | 0.090      | 1.499      | .202                 | 1389                                  | 7.56                                       | 0.51                                     | 1.19   | B    |
| 44L1T  | 1.85 | 0.090      | 1.500      | .202                 | 1434                                  | 7.89                                       | 0.53                                     | 1.23   | B    |
| 44R1T* | 1.85 | 0.089      | 1.503      | .202                 | 1257                                  | 6.99                                       | 0.47                                     | 1.09   | B    |

\*Indicate test took place after 4 month storage.

TABLE VIII B

[0/±45/90]<sub>2s</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 21°C (70°F)

S.I. Units

| Sample | e/D  | T<br>(cm.) | W<br>(cm.) | Pin<br>Dia.<br>(cm.) | Failure<br>Load<br>(Newtons) | Bearing<br>Stress<br>M Pa | Shear<br>Stress<br>M Pa | Net Tension<br>Stress<br>M Pa | Mode |
|--------|------|------------|------------|----------------------|------------------------------|---------------------------|-------------------------|-------------------------------|------|
| 45L3T  | 1.85 | 0.224      | 1.900      | 0.511                | 6034                         | 562.2                     | 35.2                    | 194.5                         | B    |
| 45C3B  | 1.85 | 0.226      | 1.908      | 0.511                | 6577                         | 566.9                     | 37.9                    | 208.3                         | B    |
| 44R3B  | 1.85 | 0.226      | 1.897      | 0.511                | 5202                         | 448.3                     | 30.3                    | 166.2                         | B    |
| 44C2T  | 1.85 | 0.231      | 2.532      | 0.511                | 6381                         | 538.0                     | 36.6                    | 136.6                         | B    |
| 44L2B  | 1.85 | 0.224      | 2.530      | 0.511                | 6034                         | 526.2                     | 35.2                    | 133.8                         | B    |
| 44L2T  | 1.85 | 0.226      | 2.530      | 0.511                | 5055                         | 434.5                     | 35.2                    | 132.4                         | B    |
| 44LLB  | 1.85 | 0.229      | 3.807      | 0.511                | 6181                         | 521.4                     | 35.2                    | 82.1                          | B    |
| 44LLT  | 1.85 | 0.229      | 3.810      | 0.511                | 6381                         | 544.2                     | 36.6                    | 84.8                          | B    |
| 44RLT  | 1.85 | 0.226      | 3.818      | 0.511                | 5594                         | 482.1                     | 32.4                    | 75.2                          | B    |

TABLE IX A

[0/+45/90]<sub>2S</sub> BOI-TED JOINT STRENGTH DATA

TEST TEMP. - 250°F

English Units

| Sample | e/D  | T<br>(in.) | W<br>(in.) | Pin<br>Dia.<br>(in.) | Failure<br>Load<br>(lb <sub>f</sub> ) | Bearing<br>Stress<br>(10 <sup>4</sup> PSI) | Shearout<br>Stress<br>(10 <sup>4</sup> PSI) | Net Tension<br>Stress<br>(10 <sup>4</sup> PSI) | Mode |
|--------|------|------------|------------|----------------------|---------------------------------------|--|---|--|------|
| 45R2B  | 3.69 | .088       | .996       | .201                 | 915                                   | 4.95                                       | 0.15  | 1.31   | B    |
| 46L3T  | 3.69 | .090       | 1.000      | .201                 | 1058                                  | 5.80                                       | 0.17  | 1.47   | B    |
| 46L3B  | 3.69 | .090       | .999       | .201                 | 1021                                  | 5.65                                       | 0.16  | 1.42   | B    |
| 46L4B  | 3.69 | .091       | .749       | .201                 | 1003                                  | 5.48                                       | 0.16  | 2.01   | B    |
| 46C3T  | 3.69 | .089       | .755       | .201                 | 970                                   | 5.43                                       | 0.16  | 1.97   | B    |
| 46L4T  | 3.69 | .090       | .750       | .201                 | 1032                                  | 5.70                                       | 0.16  | 2.09   | B    |
| 46L2T  | 3.69 | .090       | 1.500      | .201                 | 992                                   | 5.48                                       | 0.16  | 0.85   | B    |
| 45R1B  | 3.69 | .089       | 1.504      | .201                 | 1047                                  | 5.85                                       | 0.17  | 0.90   | B    |
| 45R1T  | 3.69 | .087       | 1.502      | .201                 | 946                                   | 5.42                                       | 0.16  | 0.84   | B    |

TABLE IX B

[0/±45/90]<sub>2s</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 121°C (250°F)

S.I. Units

| Sample | e/D  | T (cm.) | W (cm.) | Pin Dia. (cm.) | Failure Load (Newtons) | Bearing Stress M Pa | Shear Stress M Pa | Net Tension Stress M Pa | Mode |
|--------|------|---------|---------|----------------|------------------------|---------------------|-------------------|-------------------------|------|
| 45R2B  | 3.69 | 0.224   | 2.530   | 0.511          | 4072                   | 341.4               | 10.3              | 90.4                    | B    |
| 46L3T  | 3.69 | 0.229   | 2.540   | 0.511          | 4708                   | 400.0               | 11.7              | 101.4                   | B    |
| 46L3B  | 3.69 | 0.229   | 2.537   | 0.511          | 4543                   | 389.7               | 11.0              | 97.9                    | B    |
| 46L4B  | 3.69 | 0.231   | 1.902   | 0.511          | 4463                   | 378.0               | 11.0              | 138.6                   | B    |
| 46C3T  | 3.69 | 0.226   | 1.918   | 0.511          | 4317                   | 374.5               | 11.0              | 135.9                   | B    |
| 46L4T  | 3.69 | 0.229   | 1.905   | 0.511          | 4592                   | 393.1               | 11.0              | 144.1                   | B    |
| 46L2T  | 3.69 | 0.229   | 3.810   | 0.511          | 4414                   | 378.0               | 11.0              | 58.6                    | B    |
| 45R1B  | 3.69 | 0.226   | 3.820   | 0.511          | 4659                   | 403.5               | 11.7              | 62.1                    | B    |
| 45R1T  | 3.69 | 0.221   | 3.815   | 0.511          | 4219                   | 373.8               | 11.0              | 57.9                    | B    |



TABLE X A

[0/±45/90]<sub>2s</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. - 250°F

English Units

| Sample | e/D  | T<br>(in.) | W<br>(in.) | Pin<br>Dia.<br>(in.) | Failure<br>Load<br>(lb <sub>f</sub> ) | Bearing<br>Stress<br>(10 <sup>4</sup> PSI) | Shear<br>Stress<br>(10 <sup>4</sup> PSI) | Net Tension<br>Stress<br>(10 <sup>4</sup> PSI) | Mode |
|--------|------|------------|------------|----------------------|---------------------------------------|--|--|--|------|
| 45L4T  | 1.85 | 0.088      | 0.746      | .202                 | 1059                                  | 5.96                                       | 0.40                                     | 2.21   | B    |
| 45L4B  | 1.85 | 0.088      | 0.749      | .202                 | 1036                                  | 5.83                                       | 0.39                                     | 2.15   | B    |
| 45C4T* | 1.85 | 0.090      | 0.751      | .202                 | 905                                   | 4.98                                       | 0.34                                     | 1.83   | B    |
| 45L2T  | 1.85 | 0.088      | 0.997      | .202                 | 1103                                  | 6.20                                       | 0.42                                     | 1.58   | B    |
| 45L2B  | 1.85 | 0.088      | 0.978      | .202                 | 1092                                  | 6.14                                       | 0.41                                     | 1.56   | B    |
| 44R2B* | 1.85 | 0.090      | 0.998      | .202                 | 889                                   | 4.89                                       | 0.33                                     | 1.24   | B    |
| 45L1T  | 1.85 | 0.089      | 1.496      | .202                 | 1014                                  | 5.64                                       | 0.38                                     | 0.89   | B    |
| 44L3B  | 1.85 | 0.088      | 1.499      | .202                 | 1014                                  | 5.70                                       | 0.38                                     | 0.83   | B    |
| 44L3T* | 1.85 | 0.089      | 1.499      | .202                 | 785                                   | 4.37                                       | 0.29                                     | 0.68   | B    |

\*Indicates test after 4 month storage.

TABLE X B

[0/±45/90]<sub>2s</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 121°C (250°F)

S.I. Units

| Sample | e/D  | T<br>(cm.) | W<br>(cm.) | Pin<br>Dia.<br>(cm.) | Failure<br>Load<br>(Newtons) | Bearing<br>Stress<br>M Pa | Shear<br>Stress<br>M Pa | Net Tension<br>Stress<br>M Pa | Mode |
|--------|------|------------|------------|----------------------|------------------------------|---------------------------|-------------------------|-------------------------------|------|
| 45L4T  | 1.85 | 0.224      | 1.895      | 0.511                | 4712                         | 411.1                     | 27.6                    | 152.4                         | B    |
| 45L4B  | 1.85 | 0.224      | 1.902      | 0.511                | 4610                         | 402.1                     | 26.9                    | 148.3                         | B    |
| 45C4T  | 1.85 | 0.229      | 1.908      | 0.511                | 4027                         | 343.5                     | 23.4                    | 126.2                         | B    |
| 45L2T  | 1.85 | 0.224      | 2.532      | 0.511                | 4908                         | 427.6                     | 29.0                    | 109.0                         | B    |
| 45L2B  | 1.85 | 0.224      | 2.535      | 0.511                | 4859                         | 423.5                     | 28.3                    | 107.6                         | B    |
| 44R2B  | 1.85 | 0.229      | 2.535      | 0.511                | 3956                         | 337.3                     | 22.8                    | 85.5                          | B    |
| 45L1T  | 1.85 | 0.226      | 3.800      | 0.511                | 4512                         | 389.0                     | 26.2                    | 61.4                          | B    |
| 44L3B  | 1.85 | 0.224      | 3.807      | 0.511                | 4512                         | 393.1                     | 26.2                    | 61.4                          | B    |
| 44L3T  | 1.85 | 0.226      | 3.807      | 0.511                | 3493                         | 301.4                     | 20.2                    | 46.9                          | B    |

TABLE XI A

10/145/901<sub>2B</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 350°F

English Units

| Sample | e/D  | T<br>(in.) | W<br>(in.) | Pin<br>Dia.<br>(in.) | Failure<br>Load<br>(lb <sub>f</sub> ) | Bearing<br>Stress<br>(10 <sup>4</sup> PSI) | Shear<br>Stress<br>(10 <sup>4</sup> PSI) | Net Tension<br>Stress<br>(10 <sup>4</sup> PSI) | Mode |
|--------|------|------------|------------|----------------------|---------------------------------------|--|--|--|------|
| 47C3T  | 3.69 | .091       | 0.753      | .202                 | 810                                   | 4.41                                       | 0.13                                     | 1.61   | B    |
| 47L3T  | 3.69 | .089       | 0.752      | .202                 | 849                                   | 4.72                                       | 0.14                                     | 1.73   | B    |
| 47C4T* | 3.69 | .089       | 0.755      | .202                 | 348                                   | 1.94                                       | 0.06                                     | 0.71   | B    |
| 47R3B  | 3.69 | .090       | 1.004      | .202                 | 838                                   | 4.61                                       | 0.13                                     | 1.16   | B    |
| 47C1T  | 3.69 | .092       | 0.999      | .202                 | 882                                   | 4.74                                       | 0.14                                     | 1.20   | B    |
| 47C2T* | 3.69 | .091       | 1.002      | .202                 | 518                                   | 2.82                                       | 0.08                                     | 0.71   | B    |
| 47R2B  | 3.69 | .091       | 1.495      | .202                 | 783                                   | 4.26                                       | 0.12                                     | 0.67   | B    |
| 47L1T  | 3.69 | .089       | 1.503      | .202                 | 728                                   | 4.05                                       | 0.12                                     | 0.63   | B    |
| 47R1B* | 3.69 | .089       | 1.496      | .202                 | 650                                   | 3.62                                       | 0.10                                     | 0.56   | B    |

\*Indicates sample was tested after 4 month storage.

TABLE XI B

[0/±45/90]<sub>2s</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 177°C (350°F)

S.I. Units

| Sample | e/D  | T<br>(cm.) | W<br>(cm.) | Pin<br>Dia.<br>(cm.) | Failure<br>Load<br>(Newtons) | Bearing<br>Stress<br>M Pa | Shear<br>Stress<br>M Pa | Net Tension<br>Stress<br>M Pa | Mode |
|--------|------|------------|------------|----------------------|------------------------------|---------------------------|-------------------------|-------------------------------|------|
| 47C3T  | 3.69 | 0.231      | 1.913      | 0.511                | 3605                         | 304.2                     | 9.0                     | 111.0                         | B    |
| 47L3T  | 3.69 | 0.226      | 1.910      | 0.511                | 3778                         | 325.5                     | 9.7                     | 119.3                         | B    |
| 47C4T  | 3.69 | 0.226      | 1.918      | 0.511                | 1549                         | 133.8                     | 4.1                     | 49.0                          | B    |
| 47R3B  | 3.69 | 0.229      | 2.550      | 0.511                | 3729                         | 318.0                     | 9.0                     | 80.0                          | B    |
| 47C1T  | 3.69 | 0.234      | 2.537      | 0.511                | 3925                         | 326.9                     | 9.7                     | 82.8                          | B    |
| 47C2T  | 3.69 | 0.231      | 2.545      | 0.511                | 2305                         | 195.9                     | 5.5                     | 49.0                          | B    |
| 47R2B  | 3.69 | 0.231      | 3.797      | 0.511                | 3484                         | 293.8                     | 8.3                     | 46.2                          | B    |
| 47L1T  | 3.69 | 0.226      | 3.818      | 0.511                | 3240                         | 279.3                     | 8.3                     | 43.5                          | B    |
| 47R1B  | 3.69 | 0.226      | 3.800      | 0.511                | 2893                         | 249.7                     | 6.9                     | 38.6                          | B    |

TABLE XII A

[0/±45/90]<sub>2s</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 350°F

English Units

| Sample | e/D  | T<br>(in.) | W<br>(in.) | Pin<br>Dia.<br>(in.) | Failure<br>Load<br>(lb <sub>f</sub> ) | Bearing<br>Stress<br>(10 <sup>4</sup> PSI) | Shear<br>Stress<br>(10 <sup>4</sup> PSI) | Net Tension<br>Stress<br>(10 <sup>4</sup> PSI) | Mode |
|--------|------|------------|------------|----------------------|---------------------------------------|--|--|--|------|
| 47L3B  | 1.85 | 0.088      | 0.753      | .202                 | 694                                   | 3.90                                       | .26                                      | 1.43   | B    |
| 47C3B  | 1.85 | 0.092      | 0.753      | .202                 | 673                                   | 3.62                                       | .24                                      | 1.33   | B    |
| 47L4B* | 1.85 | 0.091      | 0.753      | .202                 | 496                                   | 2.69                                       | .18                                      | 0.99   | B    |
| 47C2B  | 1.85 | 0.093      | 1.002      | .202                 | 716                                   | 3.81                                       | .26                                      | 0.96   | B    |
| 47C1B  | 1.85 | 0.092      | 0.999      | .202                 | 750                                   | 4.04                                       | .27                                      | 1.02   | B    |
| 47L2B* | 1.85 | 0.089      | 1.002      | .202                 | 507                                   | 2.82                                       | .19                                      | .71  | B    |
| 47R2T  | 1.85 | 0.089      | 1.504      | .202                 | 750                                   | 4.17                                       | .28                                      | .65  | B    |
| 47R1T  | 1.85 | 0.091      | 1.491      | .202                 | 783                                   | 4.23                                       | .29                                      | .69  | B    |
| 47L1B* | 1.85 | 0.087      | 1.496      | .202                 |                                       |  |  |  | B    |

\*Indicates test after 4 month storage.

TABLE XII B

[0/±45/90]<sub>2s</sub> BOLTED JOINT STRENGTH DATA

TEST TEMP. = 177°C (350°F)

S.I. Units

| Sample | e/D  | T<br>(cm.) | W<br>(cm.) | Pin<br>Dia.<br>(cm.) | Failure<br>Load<br>(Newtons) | Bearing<br>Stress<br>M Pa | Shear<br>Stress<br>M Pa | Net Tension<br>Stress<br>M Pa | Mode |
|--------|------|------------|------------|----------------------|------------------------------|---------------------------|-------------------------|-------------------------------|------|
| 47L3B  | 1.85 | 0.224      | 1.913      | 0.511                | 1763                         | 269.0                     | 17.9                    | 98.6                          | B    |
| 47C3B  | 1.85 | 0.234      | 1.913      | 0.511                | 1709                         | 249.7                     | 16.6                    | 91.7                          | B    |
| 47C4B  | 1.85 | 0.231      | 1.913      | 0.511                | 1260                         | 185.5                     | 12.4                    | 68.3                          | B    |
| 47C2B  | 1.85 | 0.236      | 2.545      | 0.511                | 1819                         | 262.8                     | 17.9                    | 66.2                          | B    |
| 47C1B  | 1.85 | 0.234      | 2.537      | 0.511                | 1905                         | 278.6                     | 18.6                    | 70.3                          | B    |
| 47L2B  | 1.85 | 0.226      | 2.545      | 0.511                | 1288                         | 194.5                     | 13.1                    | 49.0                          | B    |
| 47R2T  | 1.85 | 0.226      | 3.820      | 0.511                | 1905                         | 287.6                     | 19.3                    | 44.8                          | B    |
| 47R1T  | 1.85 | 0.231      | 3.787      | 0.511                | 1989                         | 291.7                     | 20.0                    | 47.6                          | B    |
| 47L1B  | 1.85 | 0.221      | 3.800      | 0.511                |                              |                           |                         |                               | B    |

TABLE XIII A

## OUT OF PLANE CONSTRAINT BOLTED JOINT STRENGTH DATA

[0/±45/90]<sub>2s</sub> LAMINATE

English Units

| Sample | e/D  | T<br>(in.) | W<br>(in.) | Pin<br>Dia.<br>(in.) | Failure<br>Load<br>(lb <sub>f</sub> ) | Bearing<br>Stress<br>(10 <sup>4</sup> PSI) | Shear<br>Stress<br>(10 <sup>4</sup> PSI) | Net Tension<br>Stress<br>(10 <sup>4</sup> PSI) | Mode |
|--------|------|------------|------------|----------------------|---------------------------------------|--|--|--|------|
| 46C3B  | 3.69 | 0.091      | 0.754      | 0.202                | 1996                                  | 10.9                                       | 0.31                                     | 3.97   | B    |
| 46R3T  | 3.69 | 0.088      | 0.751      | 0.202                | 1974                                  | 11.1                                       | 0.32                                     | 4.09   | R    |
| 46C2B  | 3.69 | 0.090      | 1.000      | 0.202                | 1941                                  | 10.7                                       | 0.31                                     | 2.70   | B    |
| 45C2B  | 3.69 | 0.089      | 0.996      | 0.202                | 2117                                  | 11.8                                       | 0.34                                     | 3.00   | B    |
| 46C1B  | 3.69 | 0.092      | 1.501      | 0.202                | 2294                                  | 12.3                                       | 0.36                                     | 1.92   | B    |
| 46C1T  | 3.69 | 0.090      | 1.500      | 0.202                | 2382                                  | 13.1                                       | 0.39                                     | 2.04   | B    |

TABLE XIII B

## OUT-OF-PLANE CONSTRAINT BOLTED JOINT STRENGTH DATA

[0/±45/90]<sub>2s</sub> LAMINATE

S.I. Units

| Sample | e/D  | T<br>(cm.) | W<br>(cm.) | Pin<br>Dia.<br>(cm.) | Failure<br>Load<br>(Newtons) | Bearing<br>Stress<br>M Pa | Shear<br>Stress<br>M Pa | Net Tension<br>Stress<br>M Pa | Mode |
|--------|------|------------|------------|----------------------|------------------------------|---------------------------|-------------------------|-------------------------------|------|
| 46C3B  | 3.69 | 0.231      | 1.915      | 0.513                | 8882                         | 751.6                     | 21.4                    | 273.7                         | B    |
| 46R3T  | 3.69 | 0.224      | 1.908      | 0.513                | 8784                         | 765.3                     | 22.1                    | 282.0                         | B    |
| 46C2B  | 3.69 | 0.229      | 2.540      | 0.513                | 8637                         | 737.8                     | 21.4                    | 186.2                         | B    |
| 45C2B  | 3.69 | 0.226      | 2.530      | 0.513                | 9420                         | 813.6                     | 23.4                    | 206.9                         | B    |
| 46C1B  | 3.69 | 0.234      | 3.813      | 0.513                | 10208                        | 848.1                     | 24.8                    | 132.4                         | B    |
| 46C1T  | 3.69 | 0.229      | 3.810      | 0.513                | 10600                        | 903.2                     | 26.9                    | 140.7                         | B    |



TABLE XIV A

OUT OF PLANE CONSTRAINT BOLTED JOINT STRENGTH DATA

[0/±45/90]<sub>2s</sub> LAMINATE

English Units

| Sample | e/D  | T (in.) | W (in.) | Pin Dia. (in.) | Failure Load (lb <sub>f</sub> ) | Bearing Stress (10 <sup>4</sup> PSI) | Shear Stress (10 <sup>4</sup> PSI) | Net Tension Stress (10 <sup>4</sup> PSI) | Mode |
|--------|------|---------|---------|----------------|---------------------------------|--------------------------------------|------------------------------------|--|------|
| 46R3B  | 1.85 | 0.089   | 0.752   | 0.202          | 1875                            | 10.4                                 | 0.70                               | 1.84                                     | B    |
| 45R4T  | 1.85 | 0.089   | 0.749   | 0.202          | 1919                            | 10.7                                 | 0.72                               | 3.94                                     | B    |
| 47R3T  | 1.85 | 0.091   | 1.005   | 0.202          | 2007                            | 10.9                                 | 0.74                               | 2.75                                     | B    |
| 46L2B  | 1.85 | 0.090   | 1.500   | 0.202          | 1941                            | 10.7                                 | 0.72                               | 1.66                                     | B    |
| 45C1B  | 1.85 | 0.088   | 1.495   | 0.202          | 2051                            | 11.5                                 | 0.78                               | 1.80                                     | B    |

TABLE XIV B

## OUT OF PLANE CONSTRAINT BOLTED JOINT DATA

[0/±45/90]<sub>2s</sub> LAMINATE

S.I. Units

| Sample | $g/D$ | T<br>(cm.) | W<br>(cm.) | Pin.<br>Dia.<br>(cm.) | Failure<br>Load<br>(Newtons) | Bearing<br>Stress<br>M Pa | Shear<br>Stress<br>M Pa | Net Tension<br>Stress<br>M Pa | Mode |
|--------|-------|------------|------------|-----------------------|------------------------------|---------------------------|-------------------------|-------------------------------|------|
| 46R3B  | 1.85  | 0.226      | 1.910      | 0.513                 | 8344                         | 717.1                     | 48.1                    | 264.8                         | B    |
| 45R4T  | 1.85  | 0.226      | 1.902      | 0.513                 | 8539                         | 737.8                     | 49.6                    | 271.7                         | B    |
| 47R3T  | 1.85  | 0.231      | 2.553      | 0.513                 | 8931                         | 751.6                     | 51.0                    | 189.6                         | B    |
| 46L2B  | 1.85  | 0.229      | 3.810      | 0.513                 | 8637                         | 737.8                     | 49.6                    | 114.5                         | B    |
| 45C1B  | 1.85  | 0.224      | 3.797      | 0.513                 | 9126                         | 792.9                     | 53.8                    | 124.1                         | B    |

TABLE XVI COMPARISON OF EXPERIMENTAL AND FINITE  
ELEMENT MODEL NET SECTION STRAIN  
CONCENTRATIONS

| Case | W<br>in./cm | e/D | $E_x$   | $E_x$                                 | $K_{ntf}$         | $K_{nte}$ |
|------|-------------|-----|---|---------------------------------------|-------------------|-----------|
|      |             |     | Finite<br>Element<br>PSI $\times 10^6$ /<br>GPa | Experi.<br>PSI $\times 10^6$ /<br>GPa | Finite<br>Element | Experi.   |
| 1    | .75/1.91    | 4   | 11.4/<br>78.6                                   | 11.23/<br>77.7                        | 3.01              | 3.06      |
| 2    | .75/1.91    | 4   | 7.13/<br>49.2                                   | 6.82/<br>47.0                         | 3.26              | 3.10      |
| 3    | .75/1.91    | 2   | 11.4/<br>78.6                                   | 9.62/<br>66.3                         | 2.11              | 2.13      |
| 4    | .75/1.91    | 2   | 7.13/<br>49.2                                   | 6.83/<br>47.2                         | 2.43              | 2.57      |

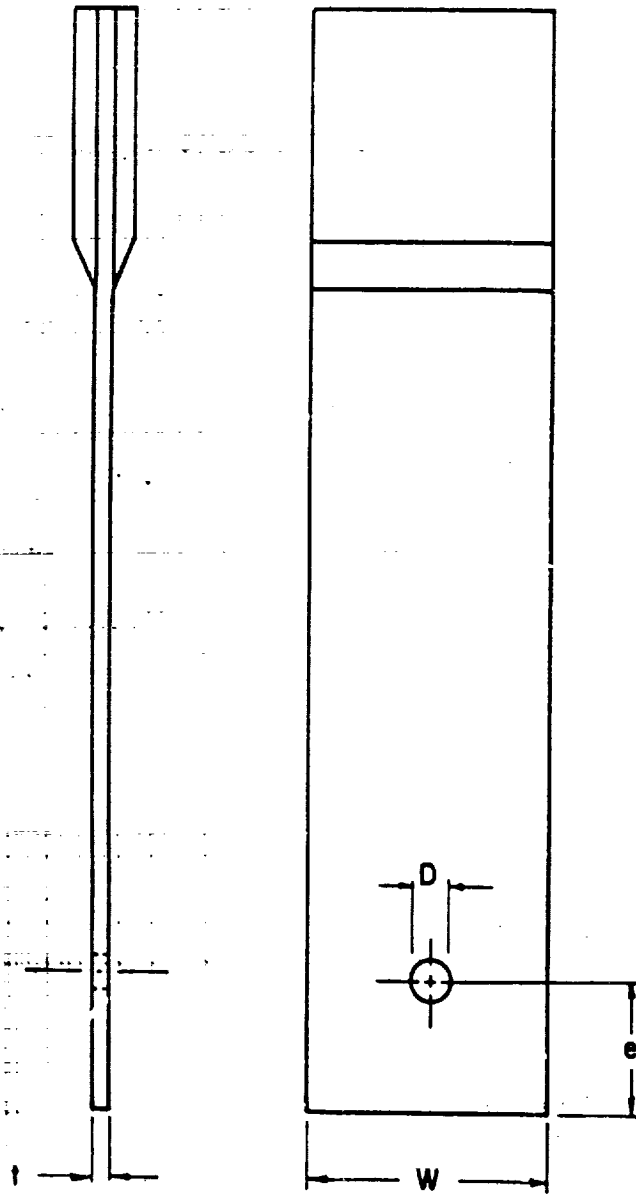


FIGURE 2.2.1 - BOLTED JOINT TEST COUPON GEOMETRY

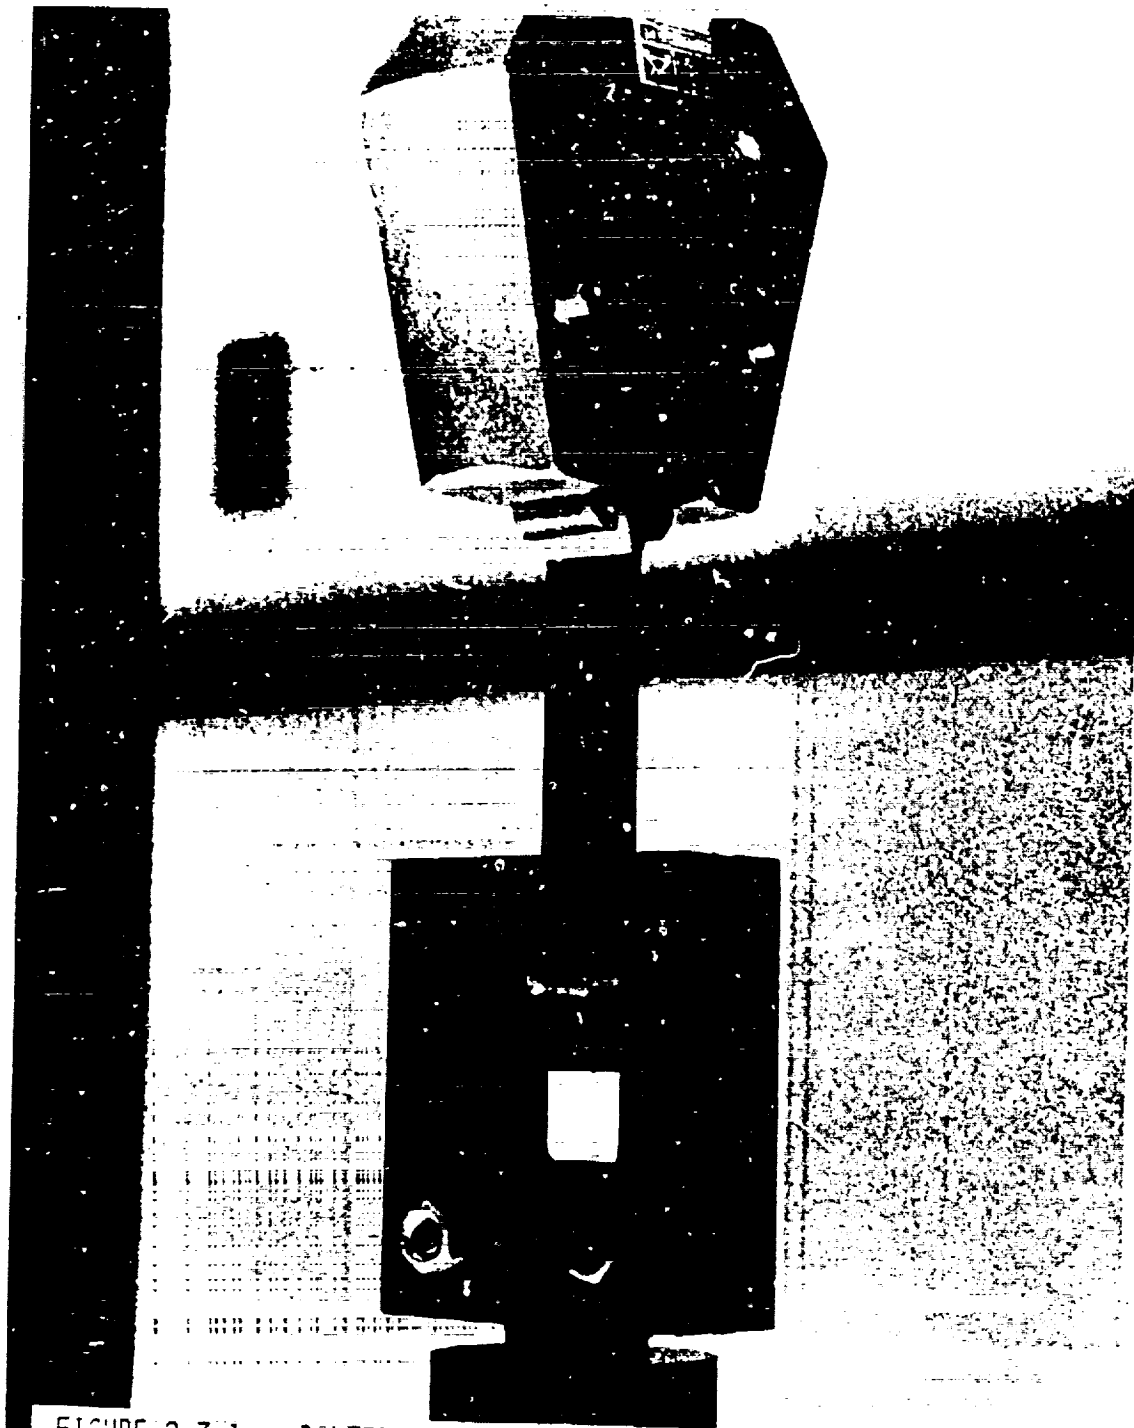


FIGURE 2.3.1 - BOLTED JOINT TEST FIXTURE USED FOR PIN BEARING TESTS

ORIGINAL PAGE IS  
OF POOR QUALITY

TABLE XV A  
 OUT OF PLANE CONSTRAINT BOLTED JOINT STRENGTH DATA

[45/0/-45/0<sub>2</sub>/-45/0/45/0<sub>2</sub>/90]<sub>s</sub> LAMINATE

English Units

| Sample | e/D  | T<br>(in.) | W<br>(in.) | Pin<br>Dia.<br>(in.) | Load | Bearing<br>Stress<br>(10 <sup>4</sup> PSI) | Shear<br>Stress<br>(10 <sup>4</sup> PSI) | Net Tension<br>Stress<br>(10 <sup>4</sup> PSI) | Mode |
|--------|------|------------|------------|----------------------|------|--|--|--|------|
| 04L4B  | 1.85 | 0.122      | 0.753      | 0.202                | 2427 | 9.85                                       | 0.66                                     | 3.61   | S/NT |
| 04L5B  | 1.85 | 0.125      | 0.754      | 0.202                | 2482 | 9.83                                       | 0.66                                     | 3.60   | S/NT |
| 04R4T  | 1.85 | 0.126      | 1.004      | 0.202                | 2427 | 9.54                                       | 0.64                                     | 2.40   | S    |
| 04R4B  | 1.85 | 0.125      | 1.003      | 0.202                | 2294 | 9.09                                       | 0.61                                     | 2.29   | S    |
| 04C1T  | 1.85 | 0.124      | 1.498      | 0.202                | 2250 | 8.98                                       | 0.61                                     | 1.40   | S    |
| 04L1B  | 1.85 | 0.124      | 1.498      | 0.202                | 2206 | 8.81                                       | 0.59                                     | 1.37   | S    |

TABLE XV B

## OUT OF PLANE CONSTRAINT BOLTED JOINT STRENGTH DATA

[45/0/-45/0<sub>2</sub>/-45/0/45/0<sub>2</sub>/90]<sub>s</sub> LAMINATE

S.I. Units

| Sample | e/D  | T<br>(cm.) | W<br>(cm.) | Pin<br>Dia.<br>(cm.) | Failure<br>Load<br>(Newtons) | Bearing<br>Stress<br>M Pa | Shear<br>Stress<br>M Pa | Net Tension<br>Stress<br>M Pa | Mode |
|--------|------|------------|------------|----------------------|------------------------------|---------------------------|-------------------------|-------------------------------|------|
| 04L4B  | 1.85 | 0.310      | 1.913      | 0.513                | 10,800                       | 679.2                     | 45.5                    | 248.9                         | S/NT |
| 04L5B  | 1.85 | 0.318      | 1.915      | 0.513                | 11,045                       | 677.8                     | 45.5                    | 248.2                         | S/NT |
| 04R4T  | 1.85 | 0.320      | 2.550      | 0.513                | 10,800                       | 657.8                     | 44.1                    | 165.5                         | S    |
| 04R4B  | 1.85 | 0.318      | 2.548      | 0.513                | 10,208                       | 626.8                     | 42.1                    | 157.9                         | S    |
| 04C1T  | 1.85 | 0.315      | 3.805      | 0.518                | 10,012                       | 619.2                     | 42.1                    | 96.5                          | S    |
| 04L1B  | 1.85 | 0.315      | 3.805      | 0.513                | 9,816                        | 607.4                     | 40.7                    | 95.4                          | S    |

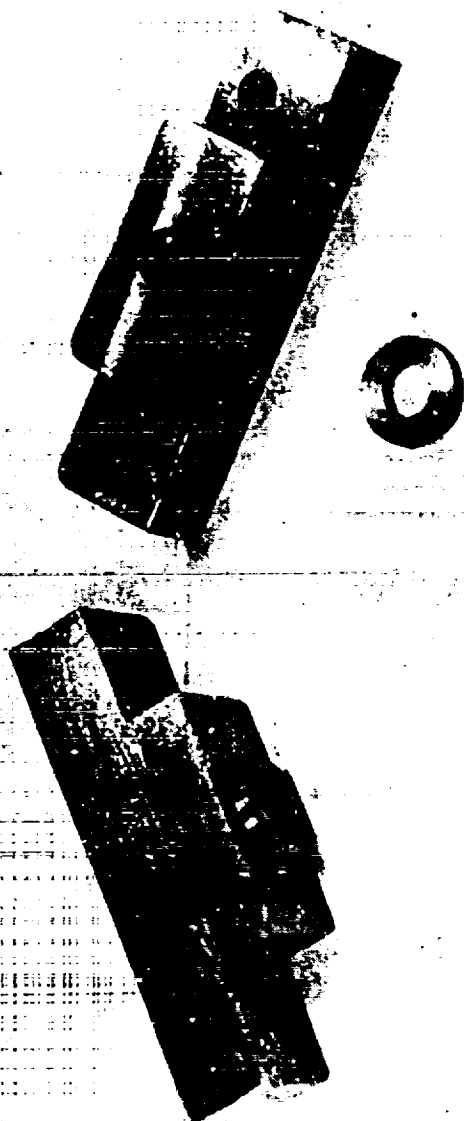


FIGURE 2.3.2 - INSERTS USED TO APPLY OUT-OF-PLANE CONSTRAINTS

ORIGINAL PAGE IS  
OF POOR QUALITY

1111



## Strain Gage Locations

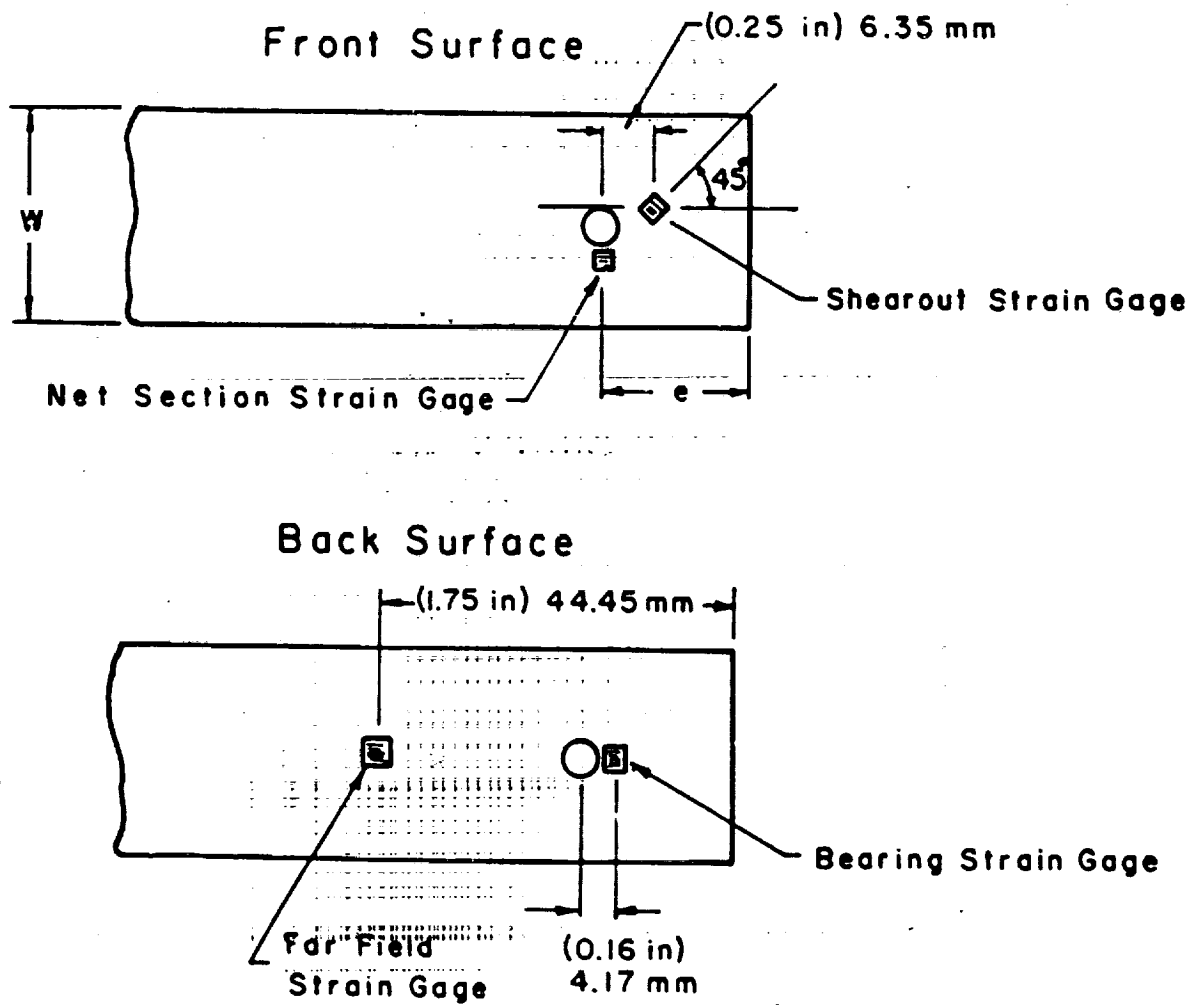


FIGURE 2.4.1 - INSTRUMENTATION LOCATIONS ON TEST COUPON

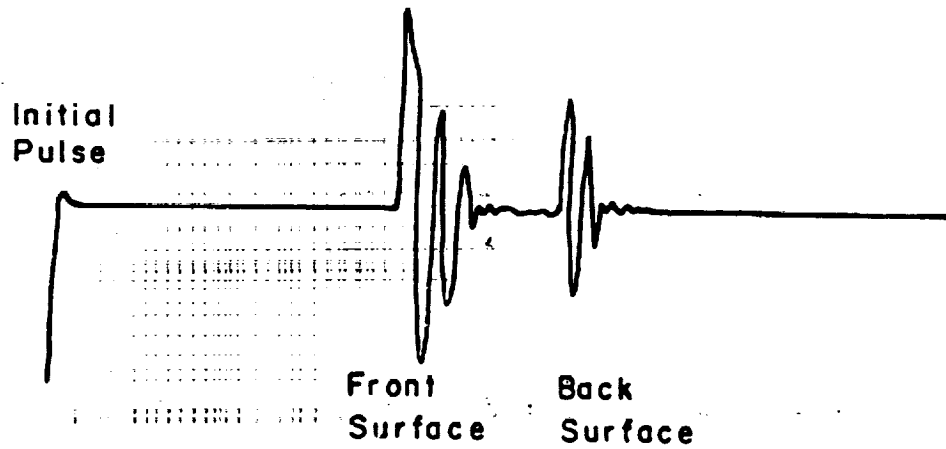
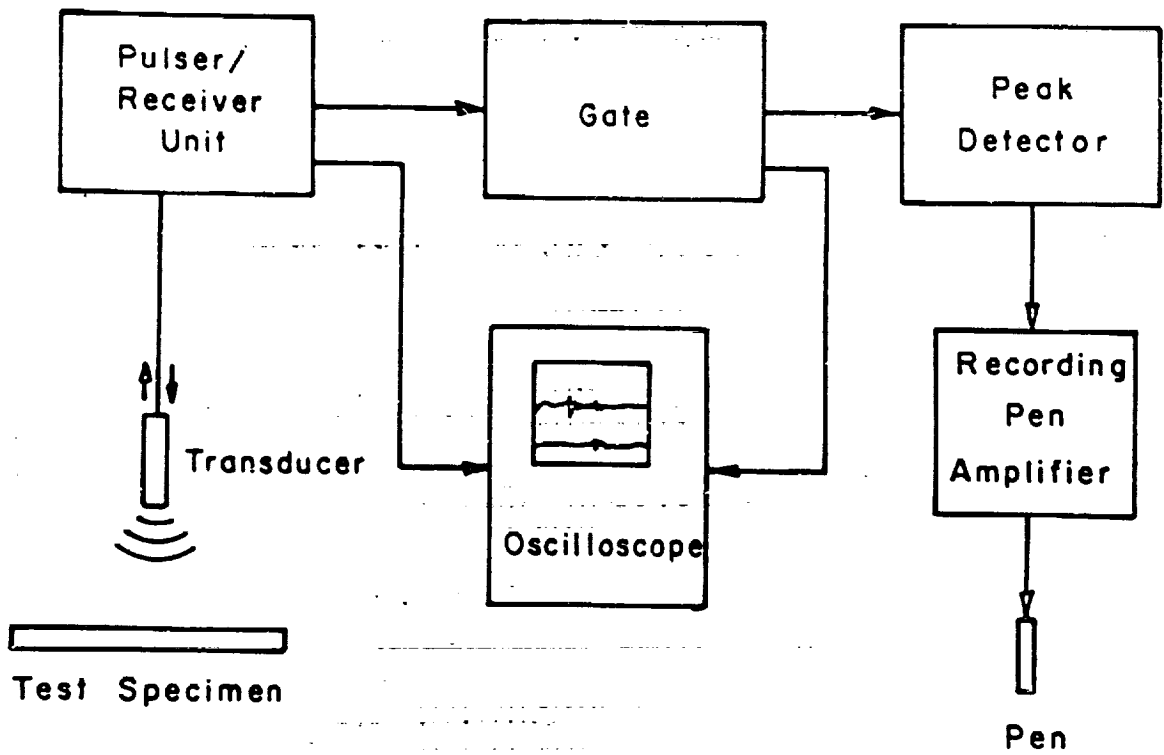


FIGURE 2.6.1 - ULTRASONIC "C" SCAN BLOCK DIAGRAM


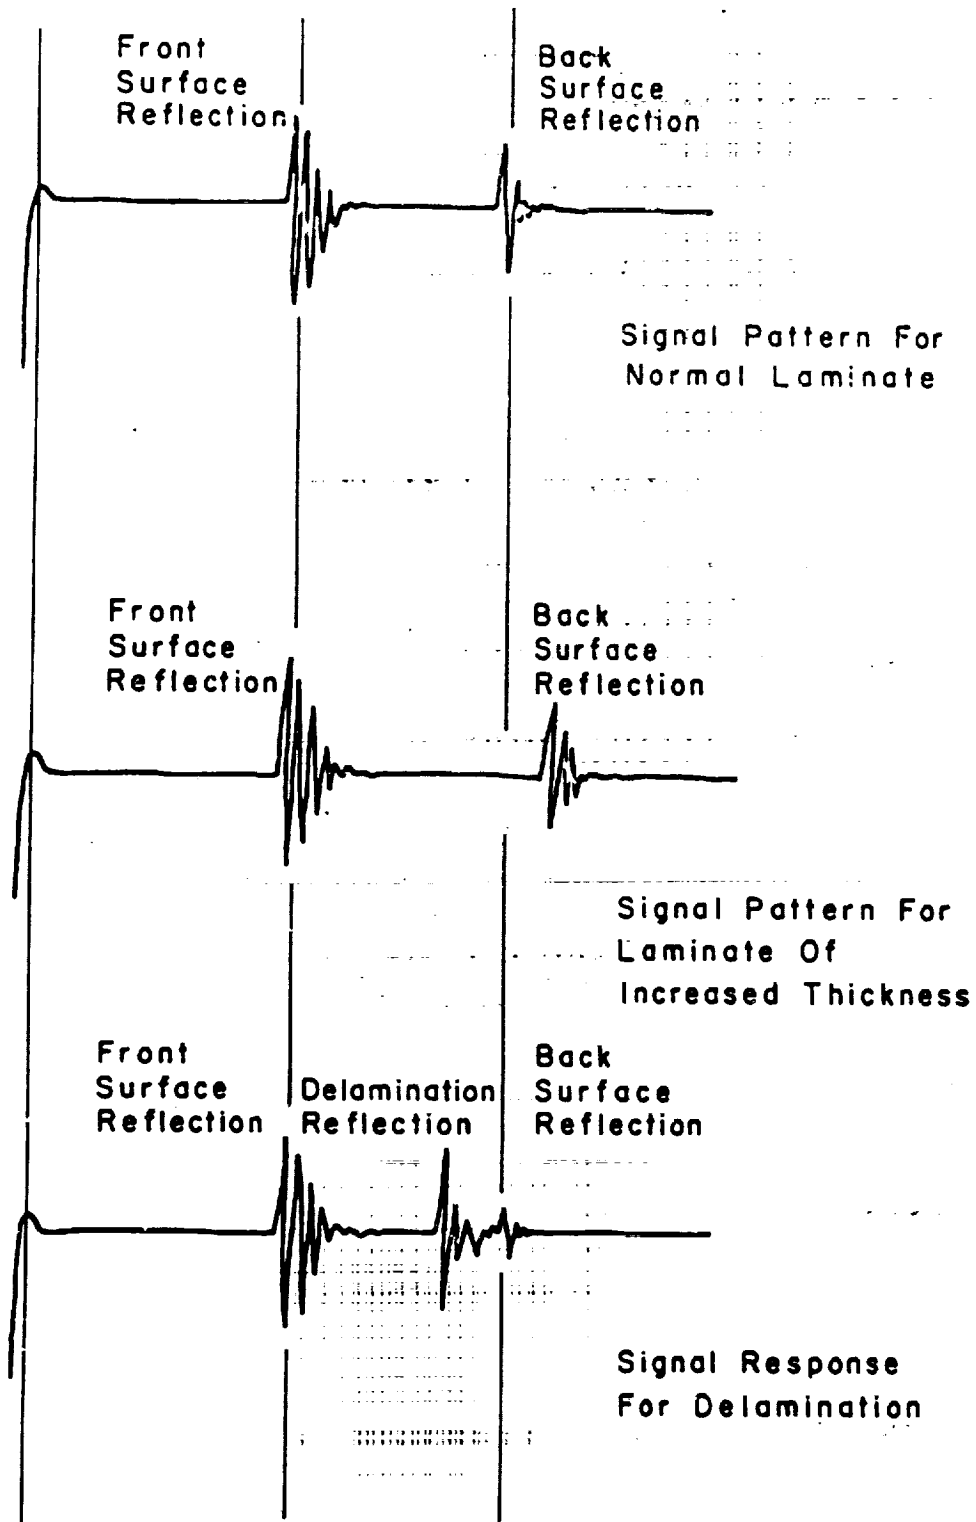


FIGURE 2.6.2 - SIGNAL WAVEFORMS CHARACTERISTIC OF DEFECTS

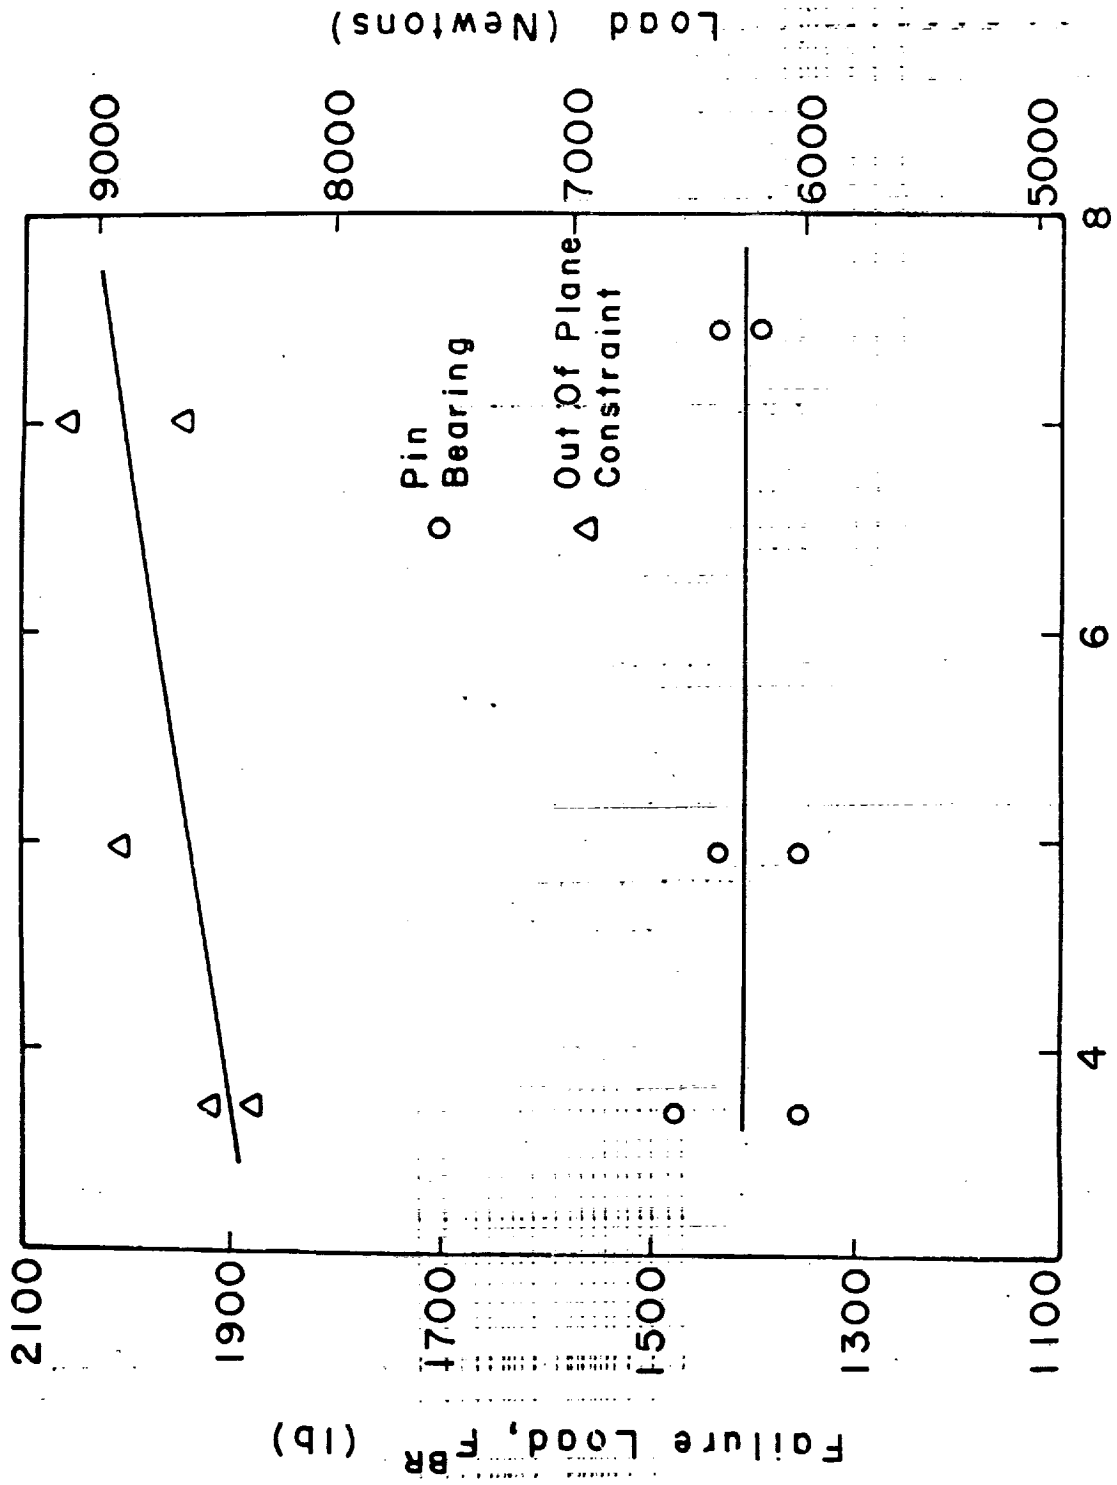

W/D

FIGURE 3.1.1.1 - COMPARISON OF PIN LOADED AND OUT-OF-PLANE CONSTRAINT STRENGTH FOR AS/3501-6 GRAPHITE EPOXY QUASI-ISOTROPIC LAMINATE,  $e/D = 1.85$

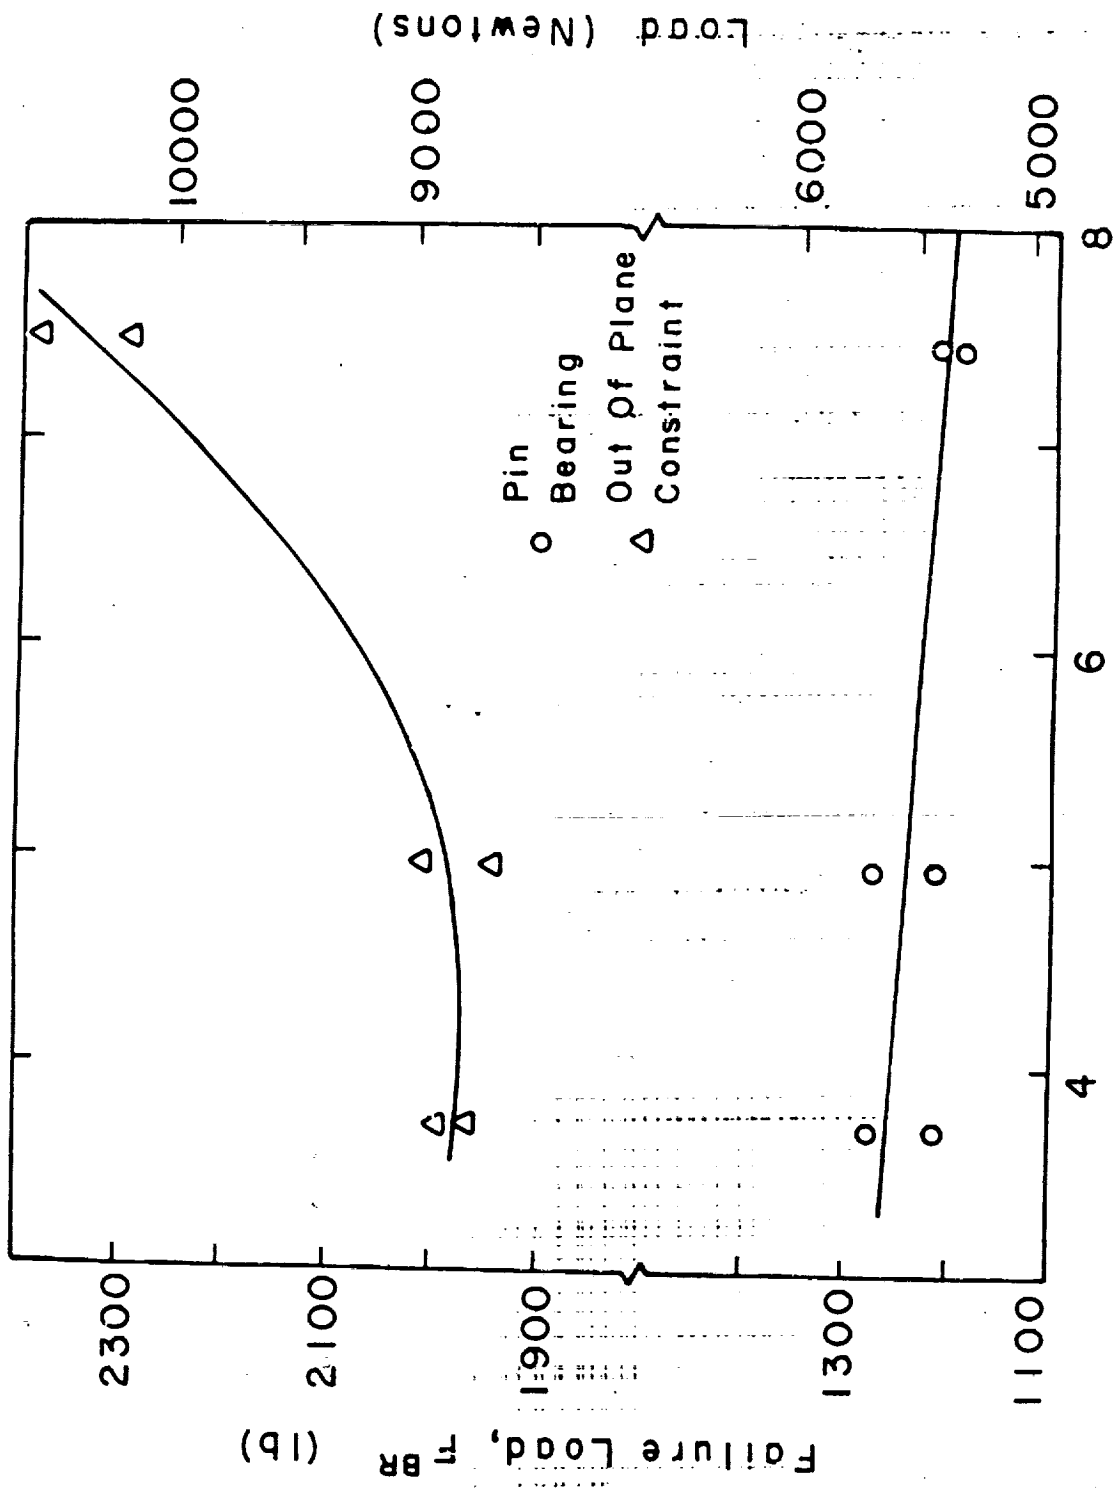


FIGURE 3.1.1.2 - COMPARISON OF PIN LOADED AND OUT-OF-PLANE CONSTRAINT STRENGTH FOR AS/3501-6 GRAPHITE EPOXY QUASI-ISOTROPIC LAMINATE,  $e/D = 3.69$

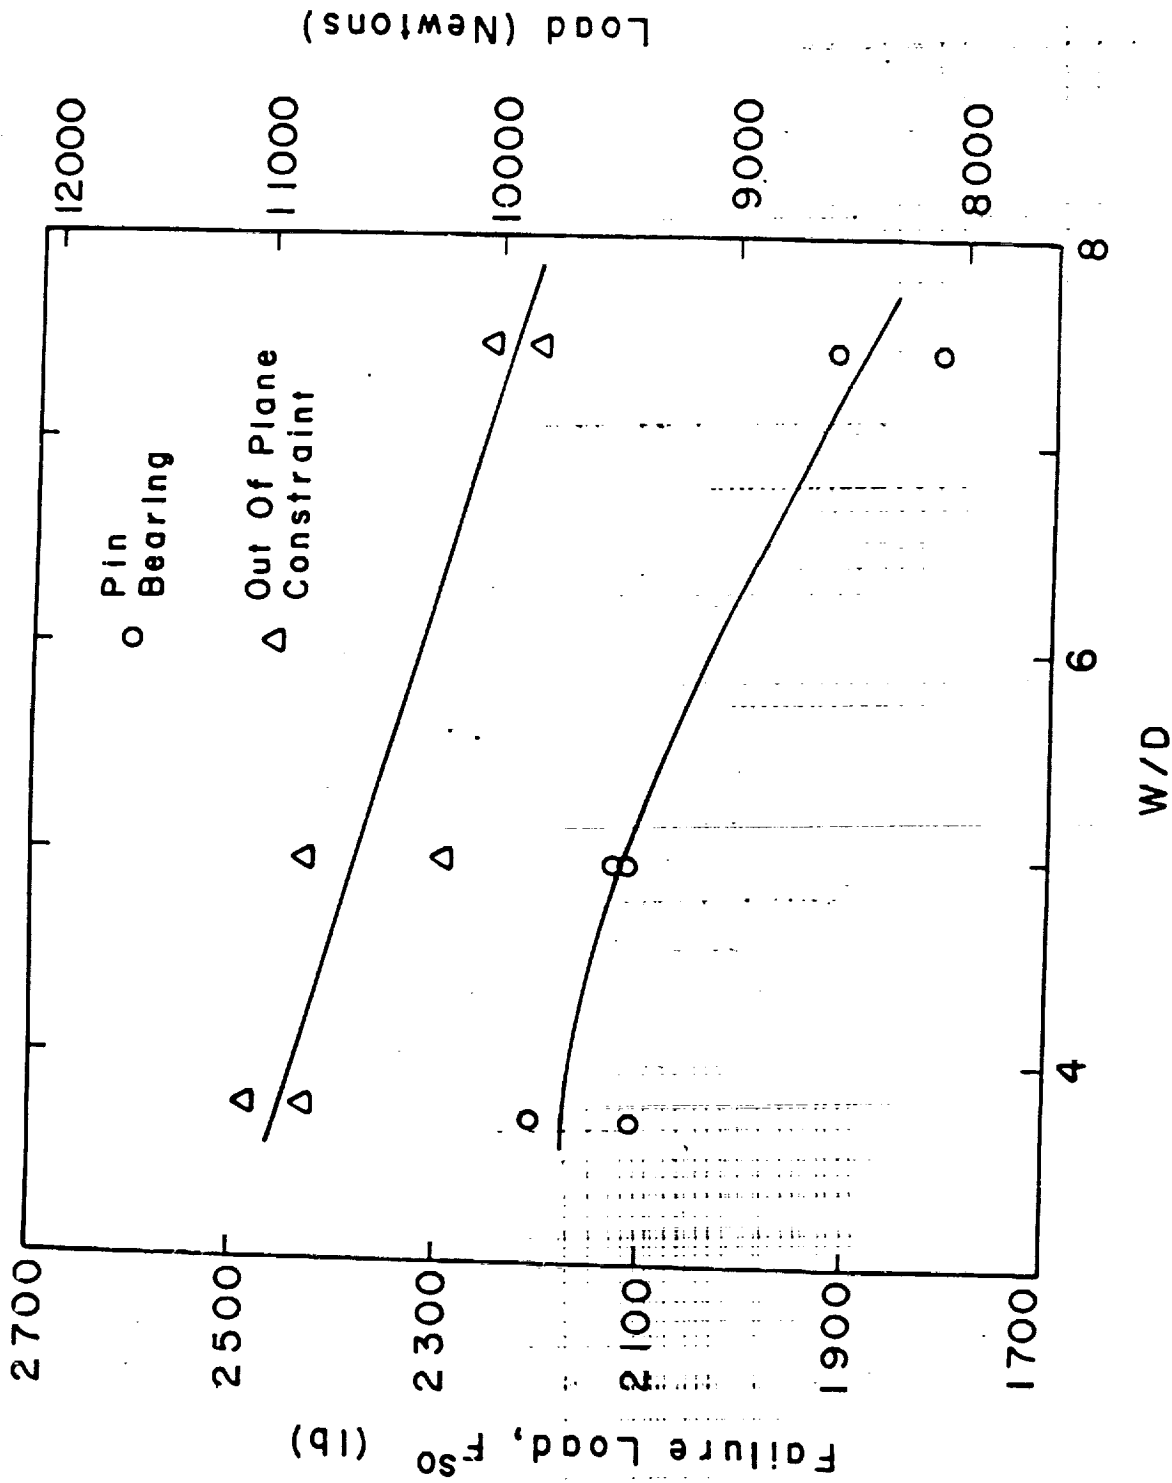


FIGURE 3.1.1.3 - COMPARISON OF PIN LOADED AND OUT-OF-PLANE CONSTRAINT STRENGTH FOR AS/3501-6 GRAPHITE EPOXY 0° DOMINATED LAMINATE

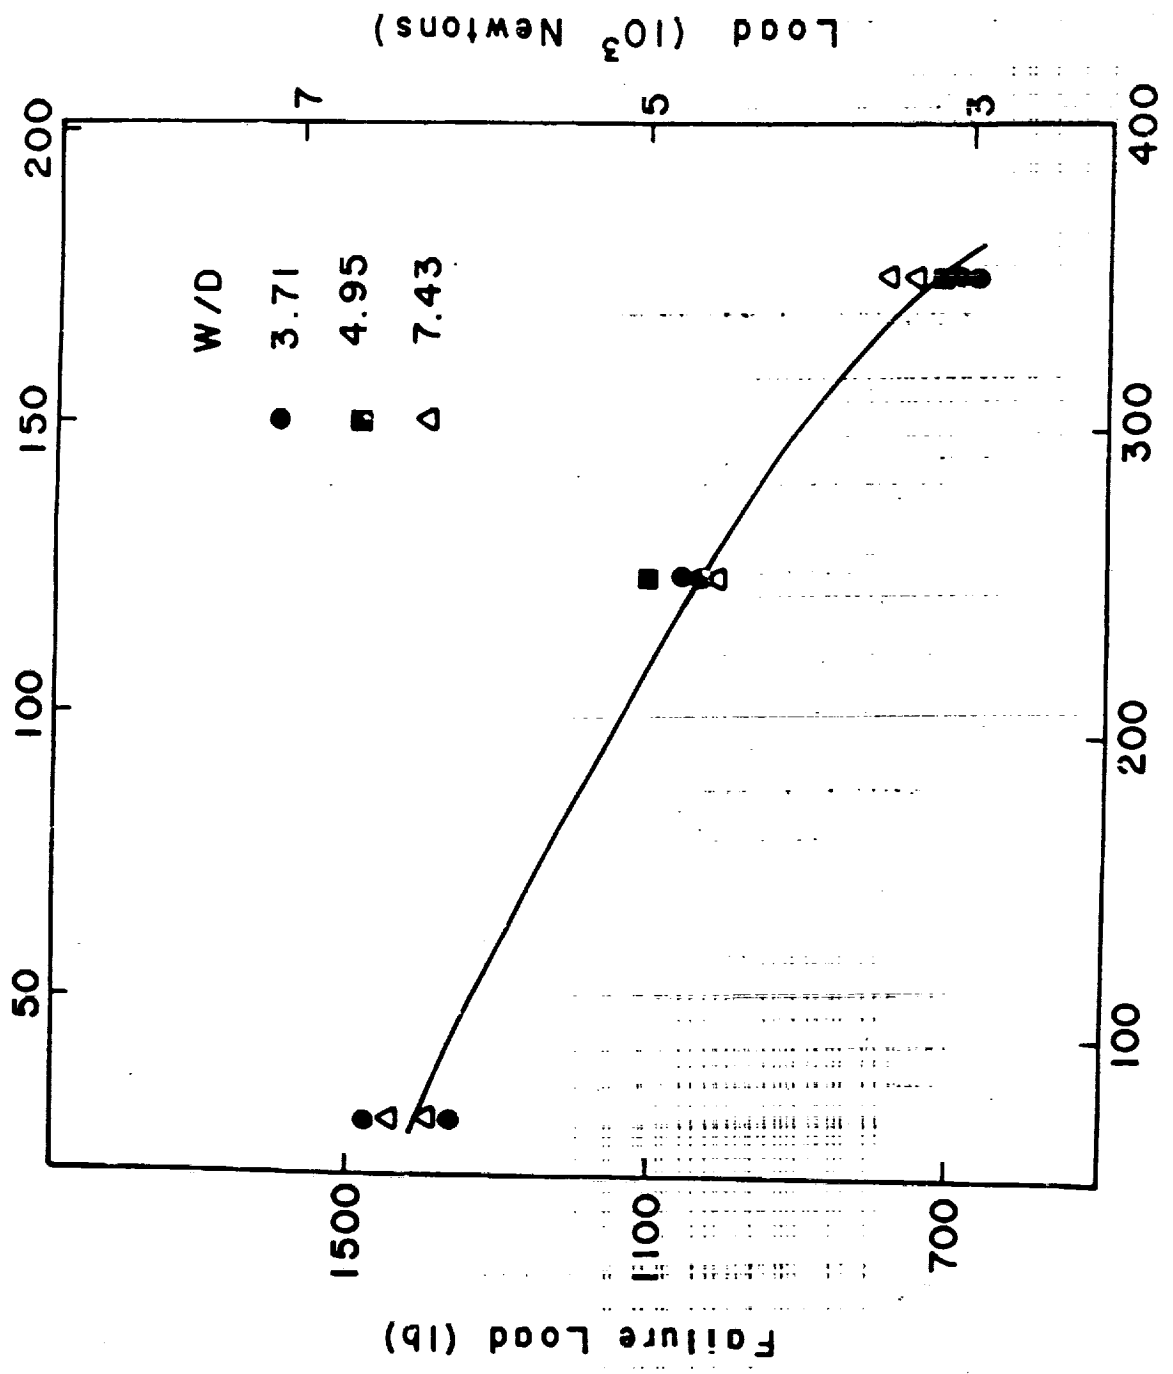


FIGURE 3.2.1 - FAILURE LOAD VERSUS TEMPERATURE FOR AS/3501-6 GRAPHITE EPOXY QUASI-ISOTROPIC LAMINATE,  $\bullet/D = 1.85$

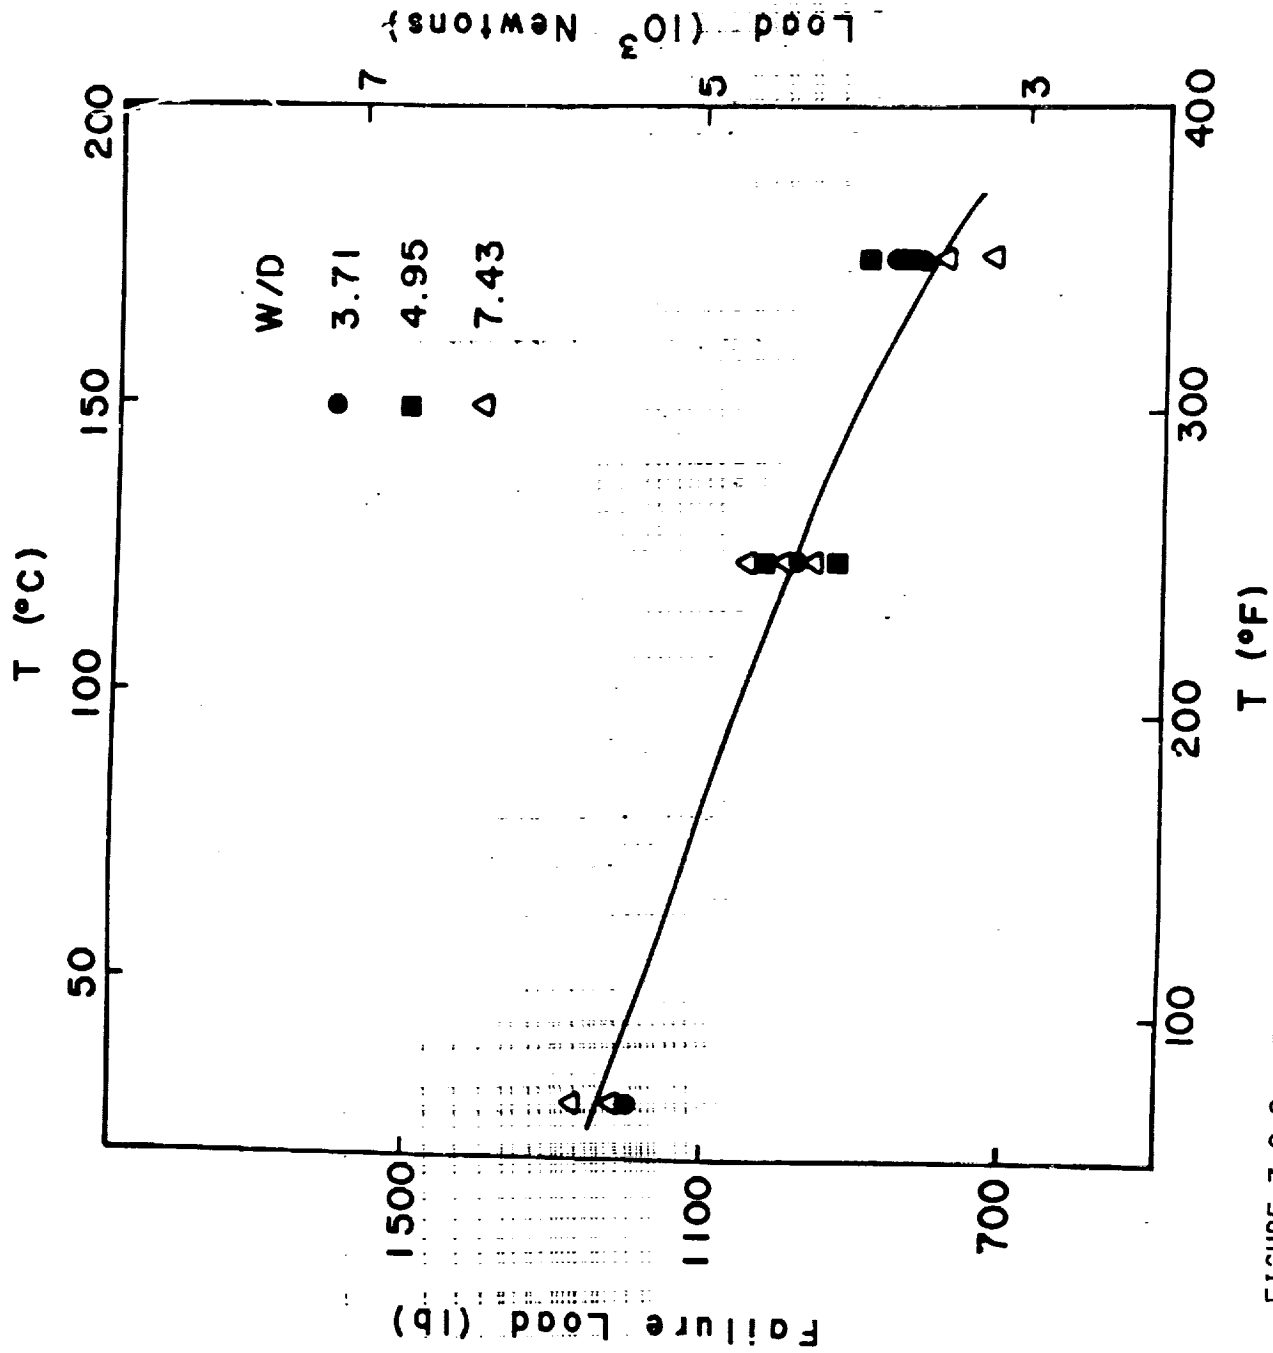


FIGURE 3.2.2 - FAILURE LOAD VERSUS TEMPERATURE FOR AS/3501-6 GRAPHITE EPOXY QUASI-ISOTROPIC LAMINATE, W/D = 3.69



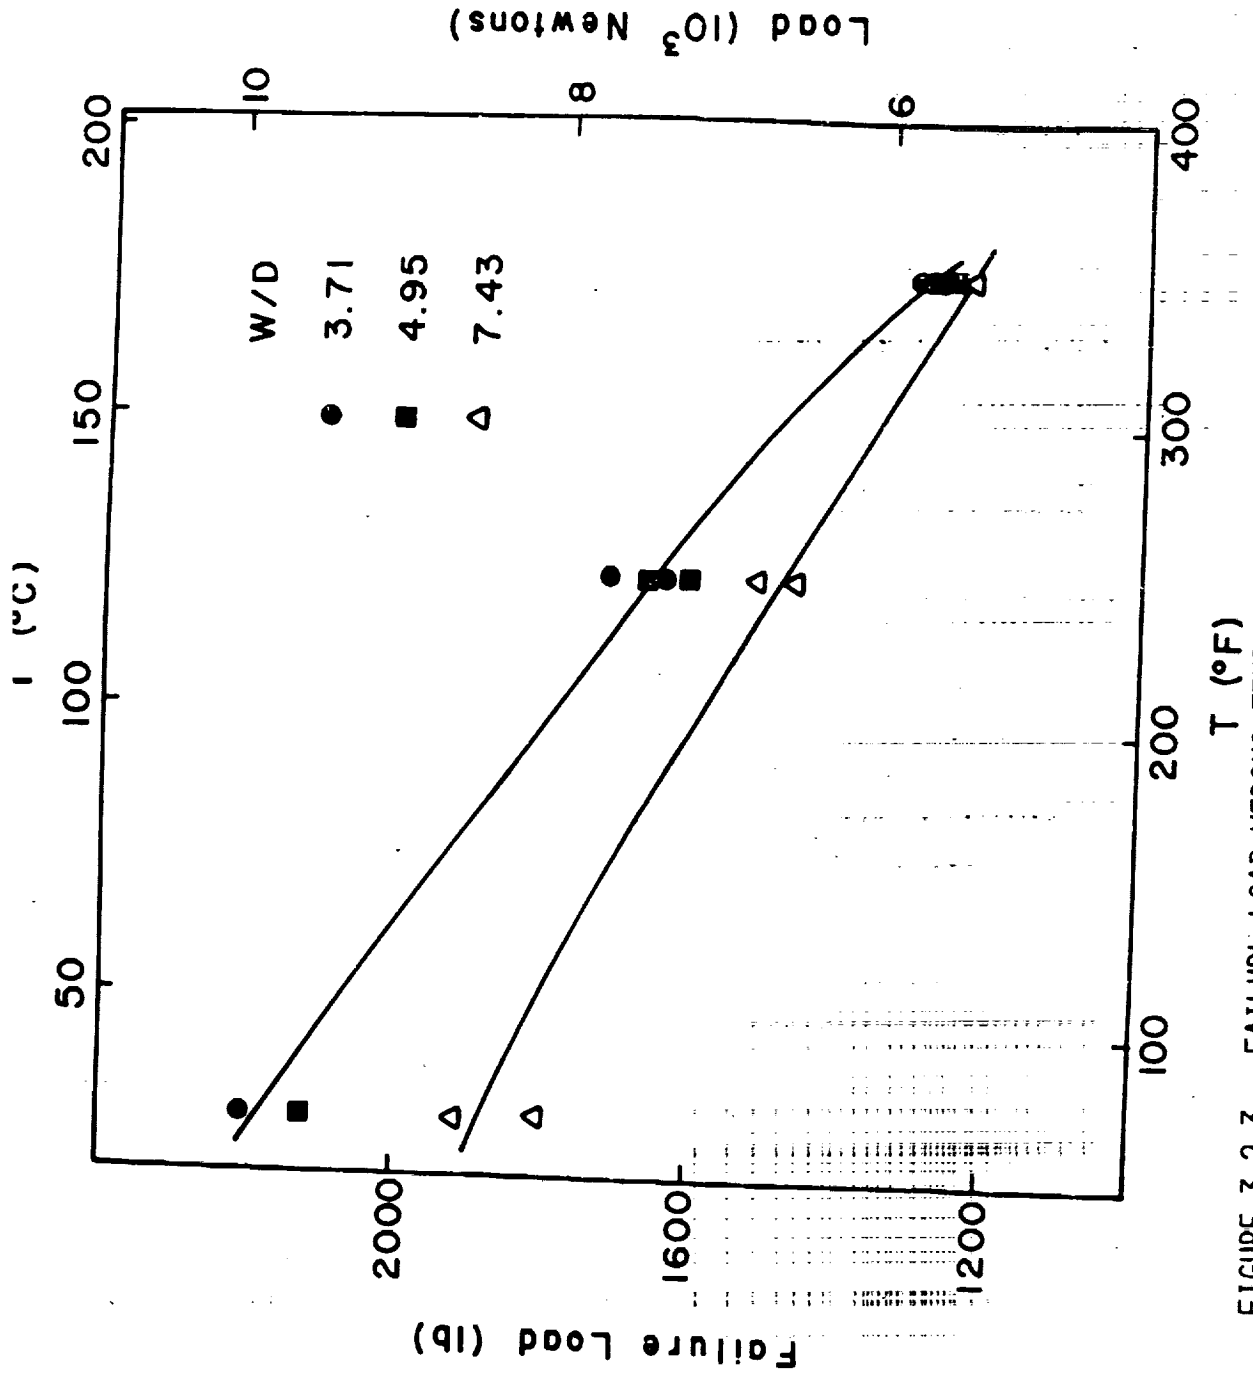


FIGURE 3.2.3 - FAILURE LOAD VERSUS TEMPERATURE FOR AS/3501-6 GRAPHITE EPOXY  
 0° DOMINATED LAMINATE, e/D = 1.85

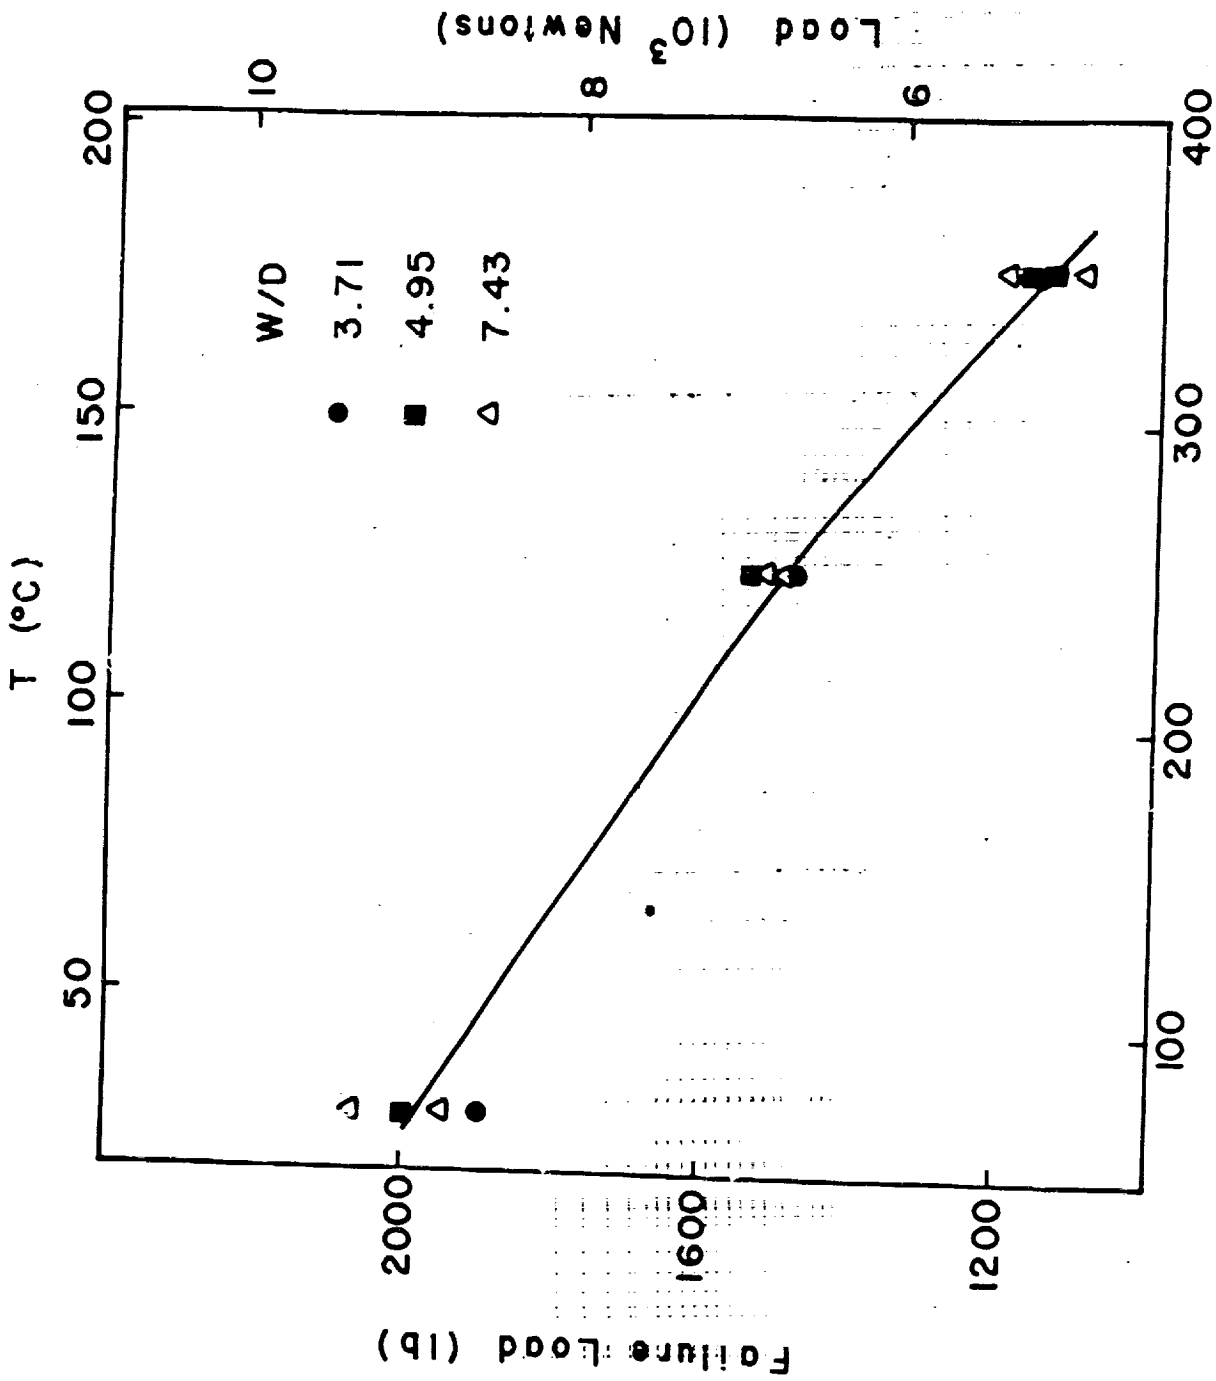


FIGURE 3.2.4 - FAILURE LOAD VERSUS TEMPERATURE FOR AS/3501-6 GRAPHITE EPOXY  
 0° DOMINATED LAMINATE, e/D = 3.69

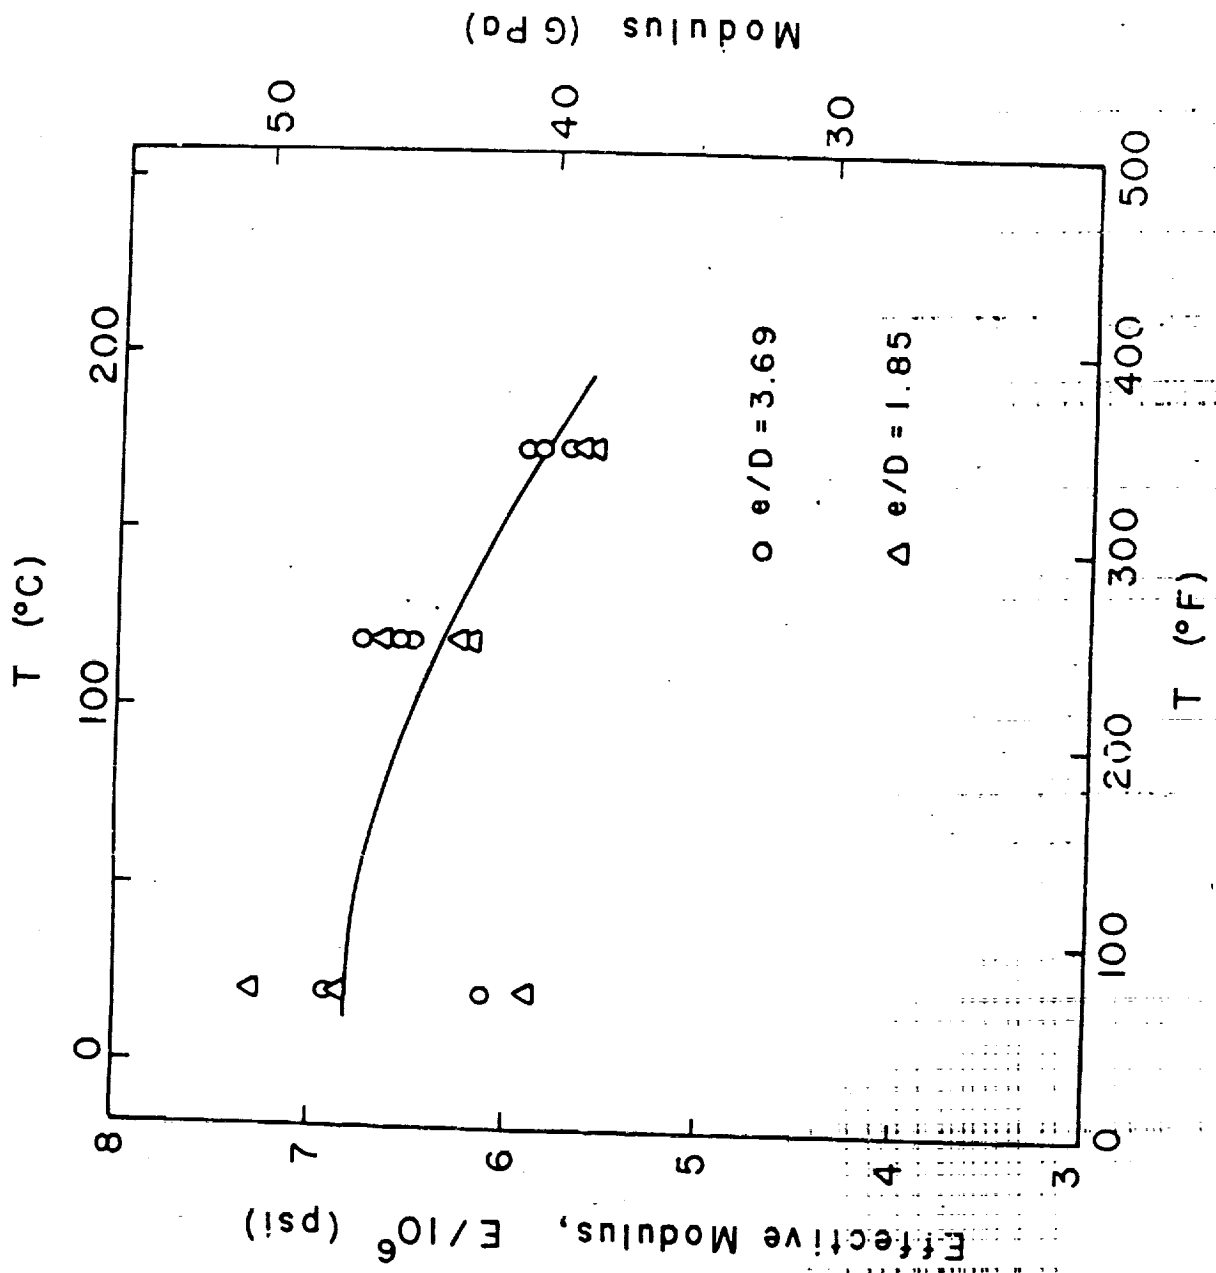


FIGURE 3.3.1 - VARIATION OF LAMINATE MODULUS WITH TEMPERATURE FOR QUASI-ISOTROPIC LAMINATE

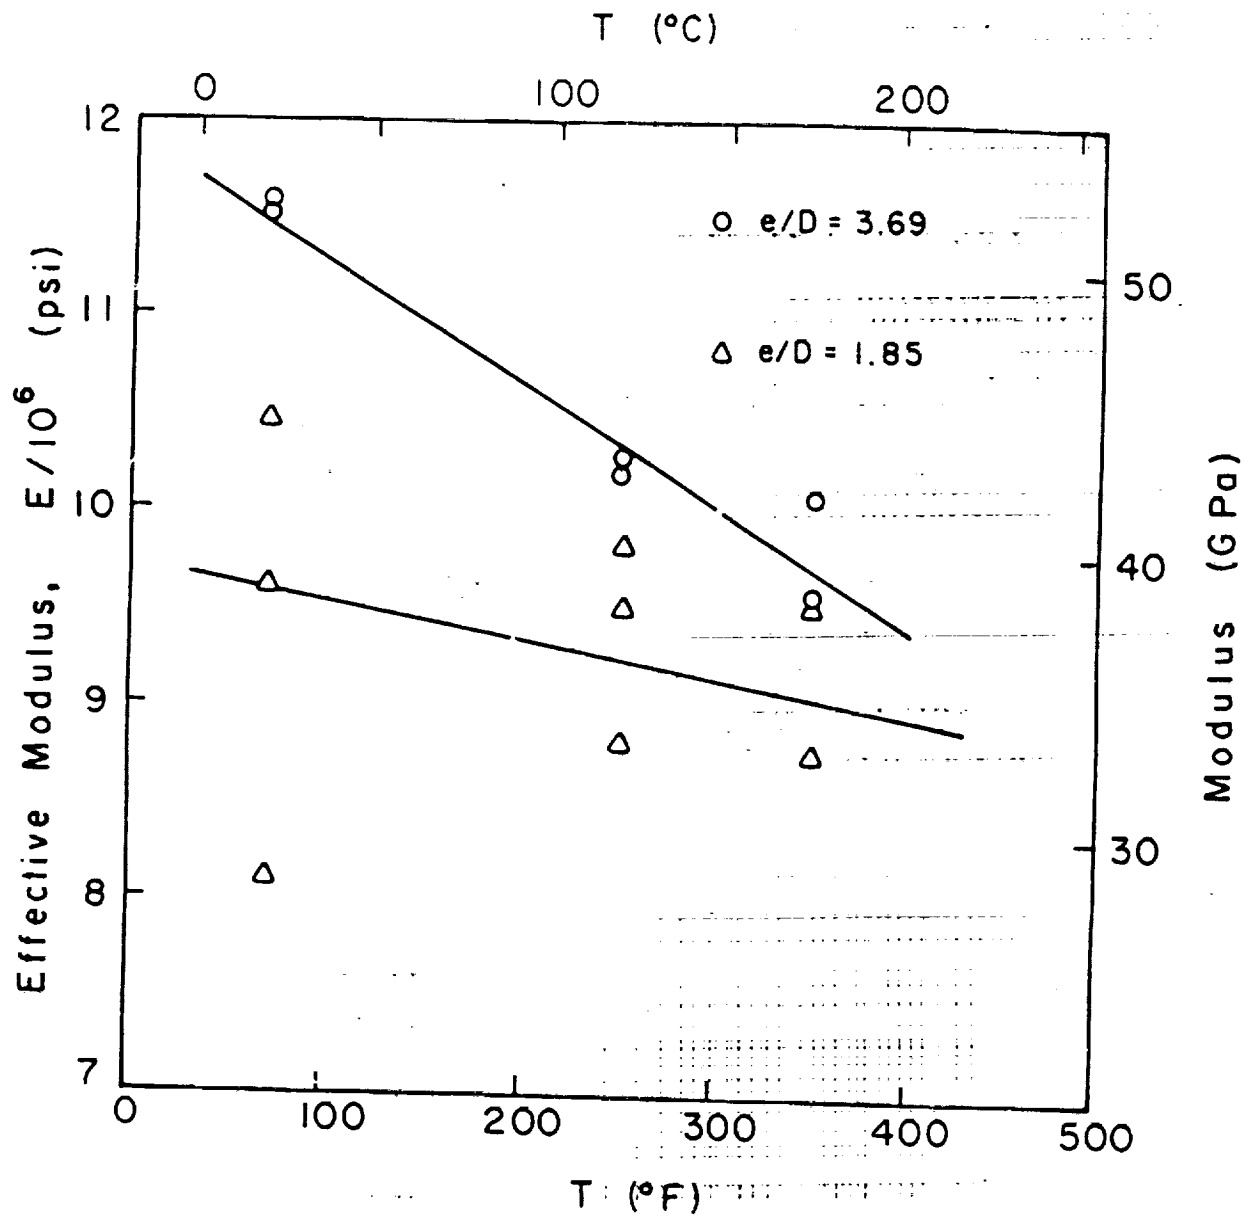


FIGURE 3.3.2 - VARIATION OF LAMINATE MODULUS WITH TEMPERATURE FOR 0° DOMINATED LAMINATE

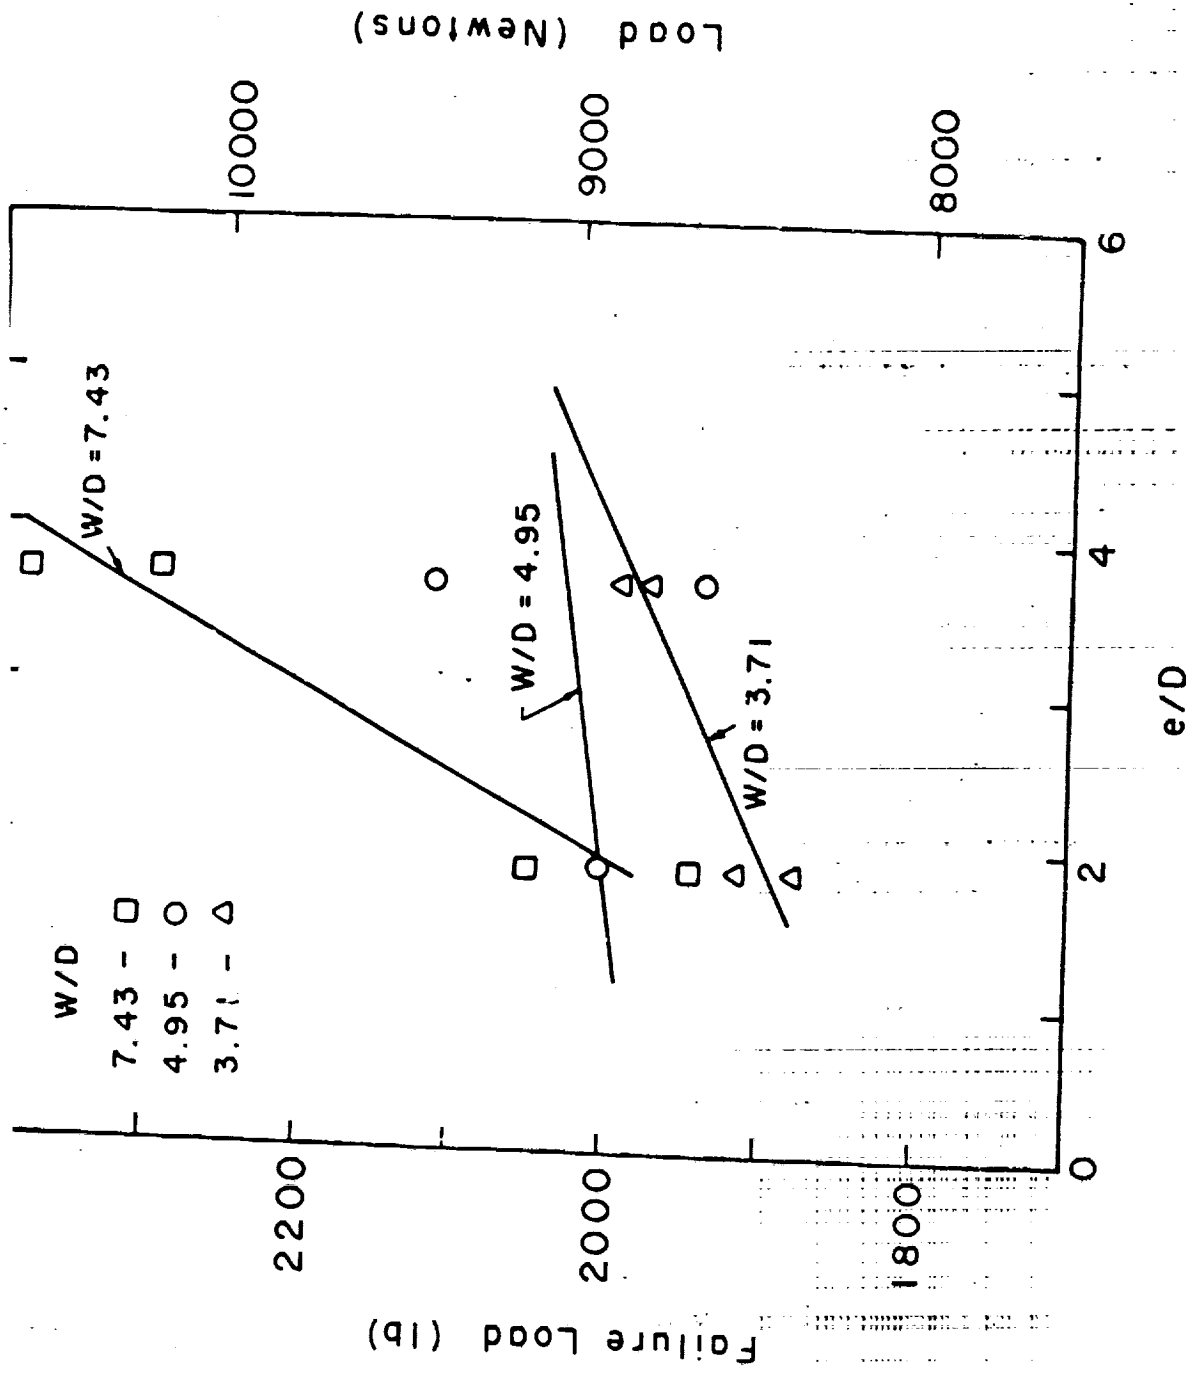


FIGURE 3.4.1 - FAILURE LOAD VERSUS  $e/D$  FOR AS/3501-6 GRAPHITE EPOXY QUASI-ISOTROPIC LAMINATE WITH OUT-OF-PLANE CONSTRAINTS

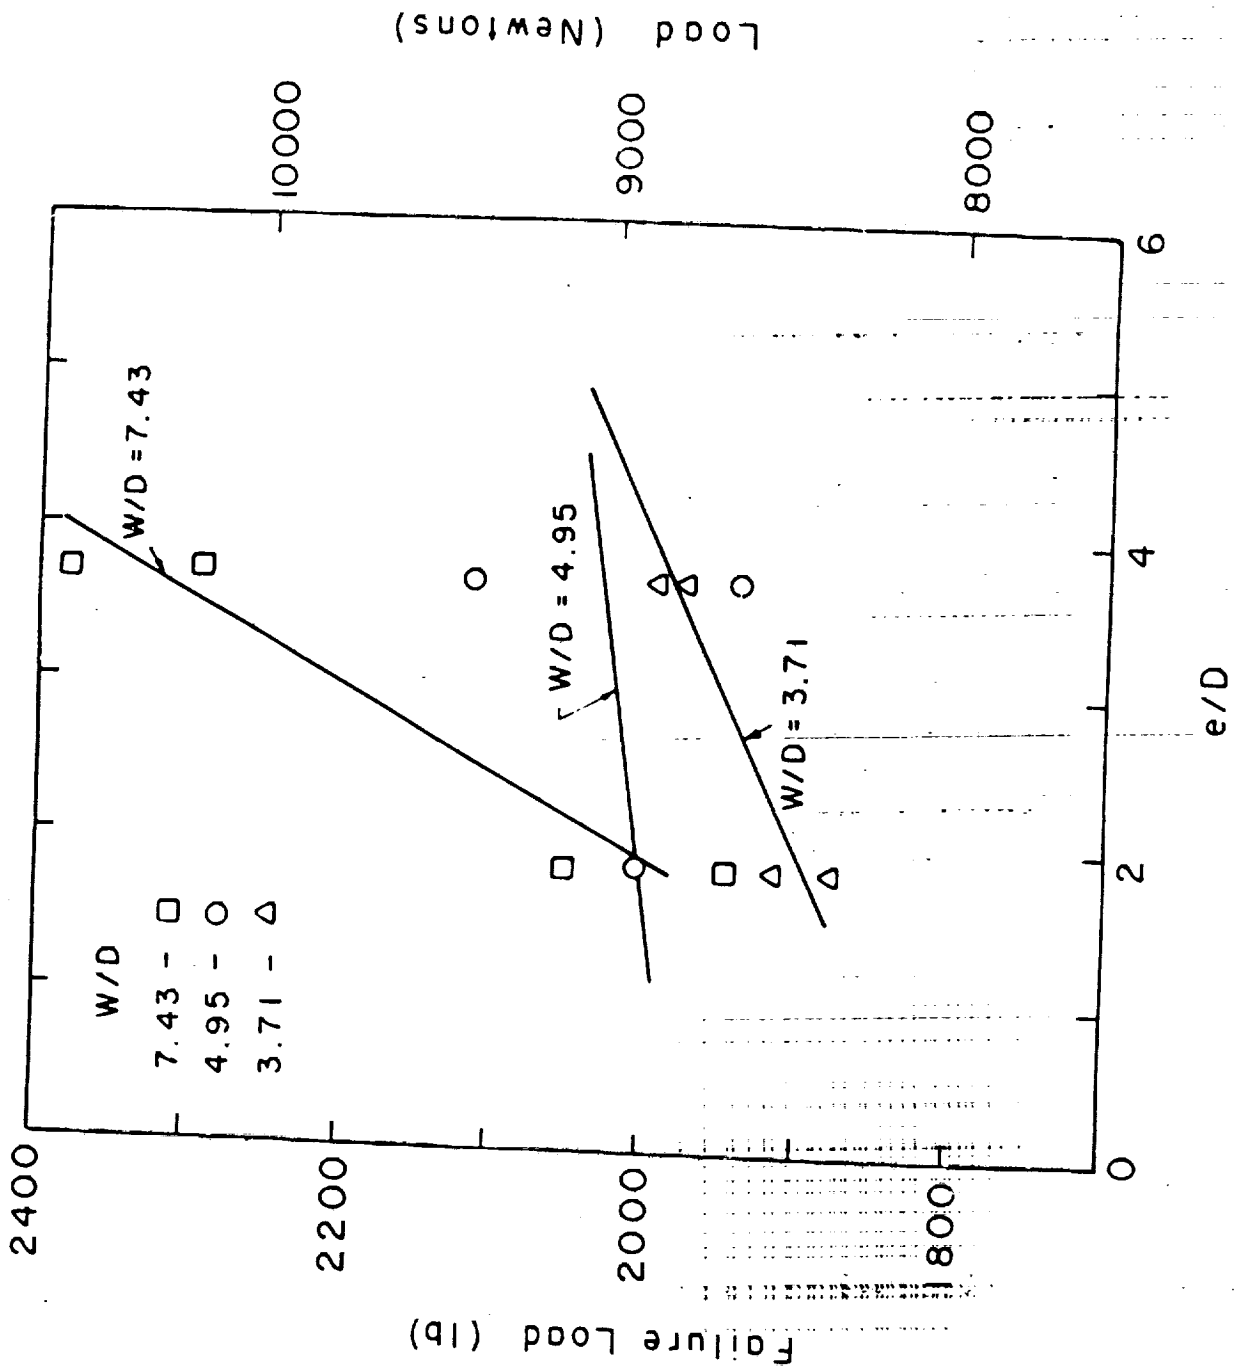


FIGURE 3.4.1 - FAILURE LOAD VERSUS  $e/D$  FOR AS/3501-6 GRAPHITE EPOXY QUASI-ISOTROPIC LAMINATE WITH OUT-OF-PLANE CONSTRAINTS

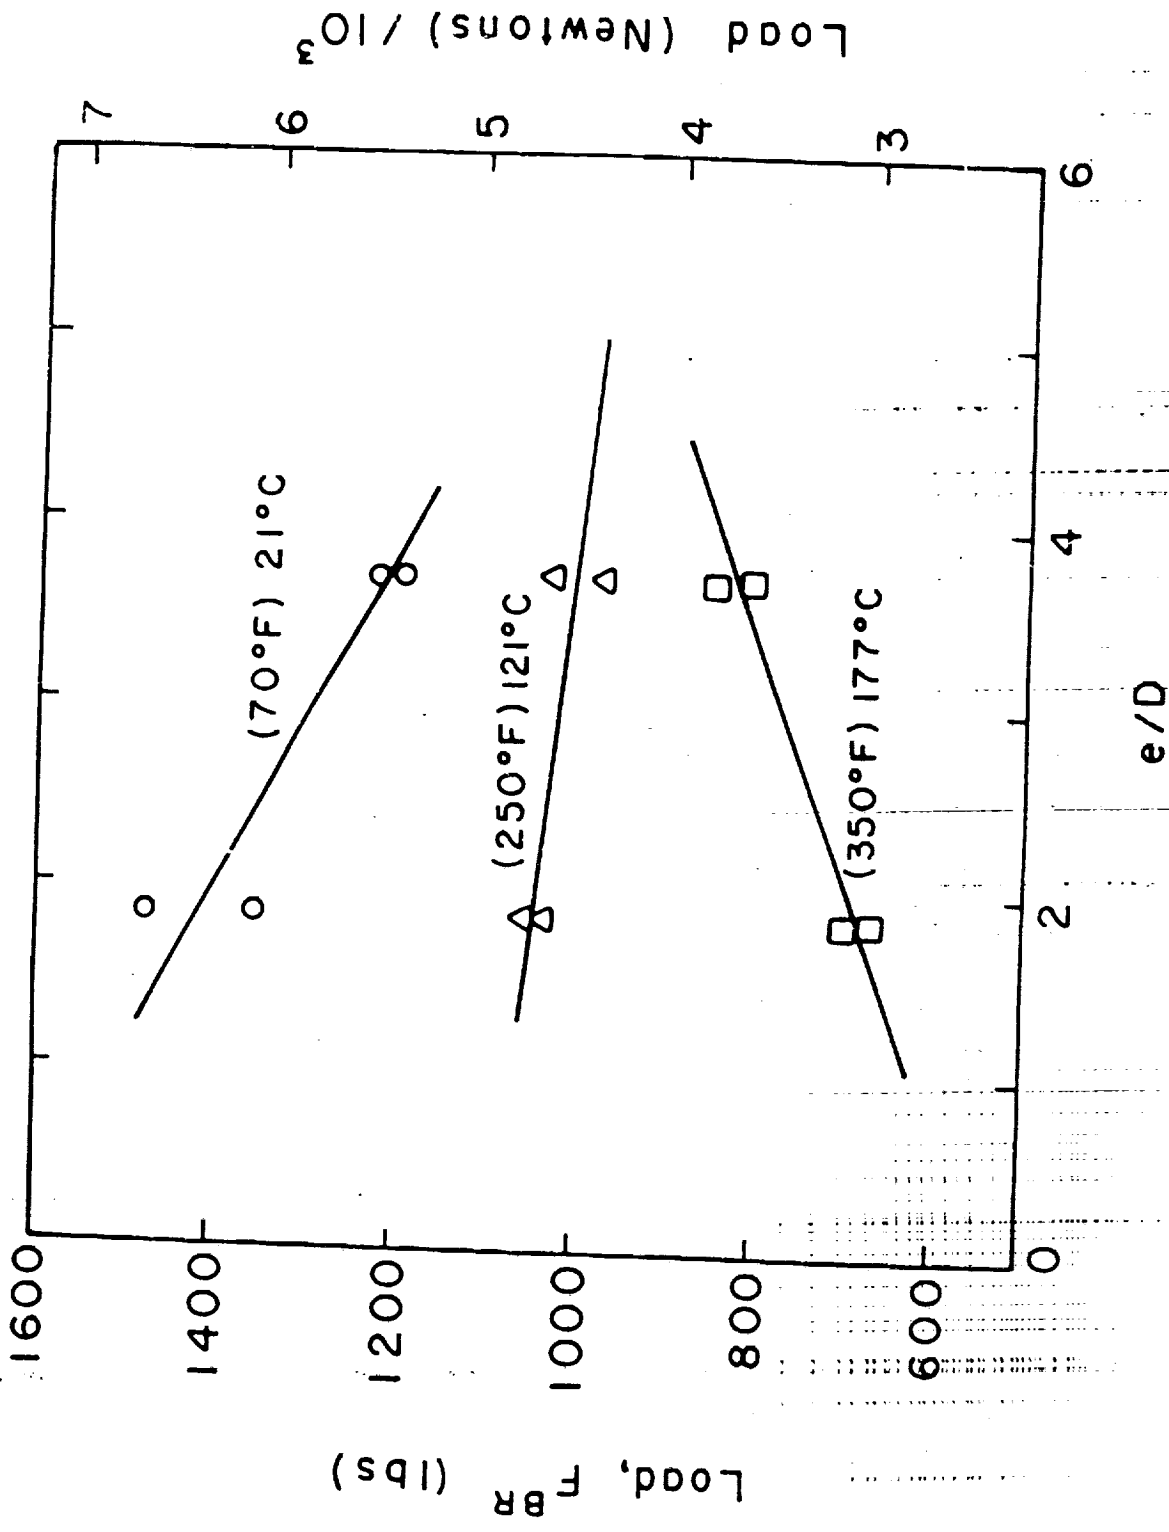


FIGURE 3.4.2 - PIN BEARING FAILURE LOAD VERSUS  $e/D$  FOR QUASI-ISOTROPIC LAMINATE,  $W/D = 3.71$

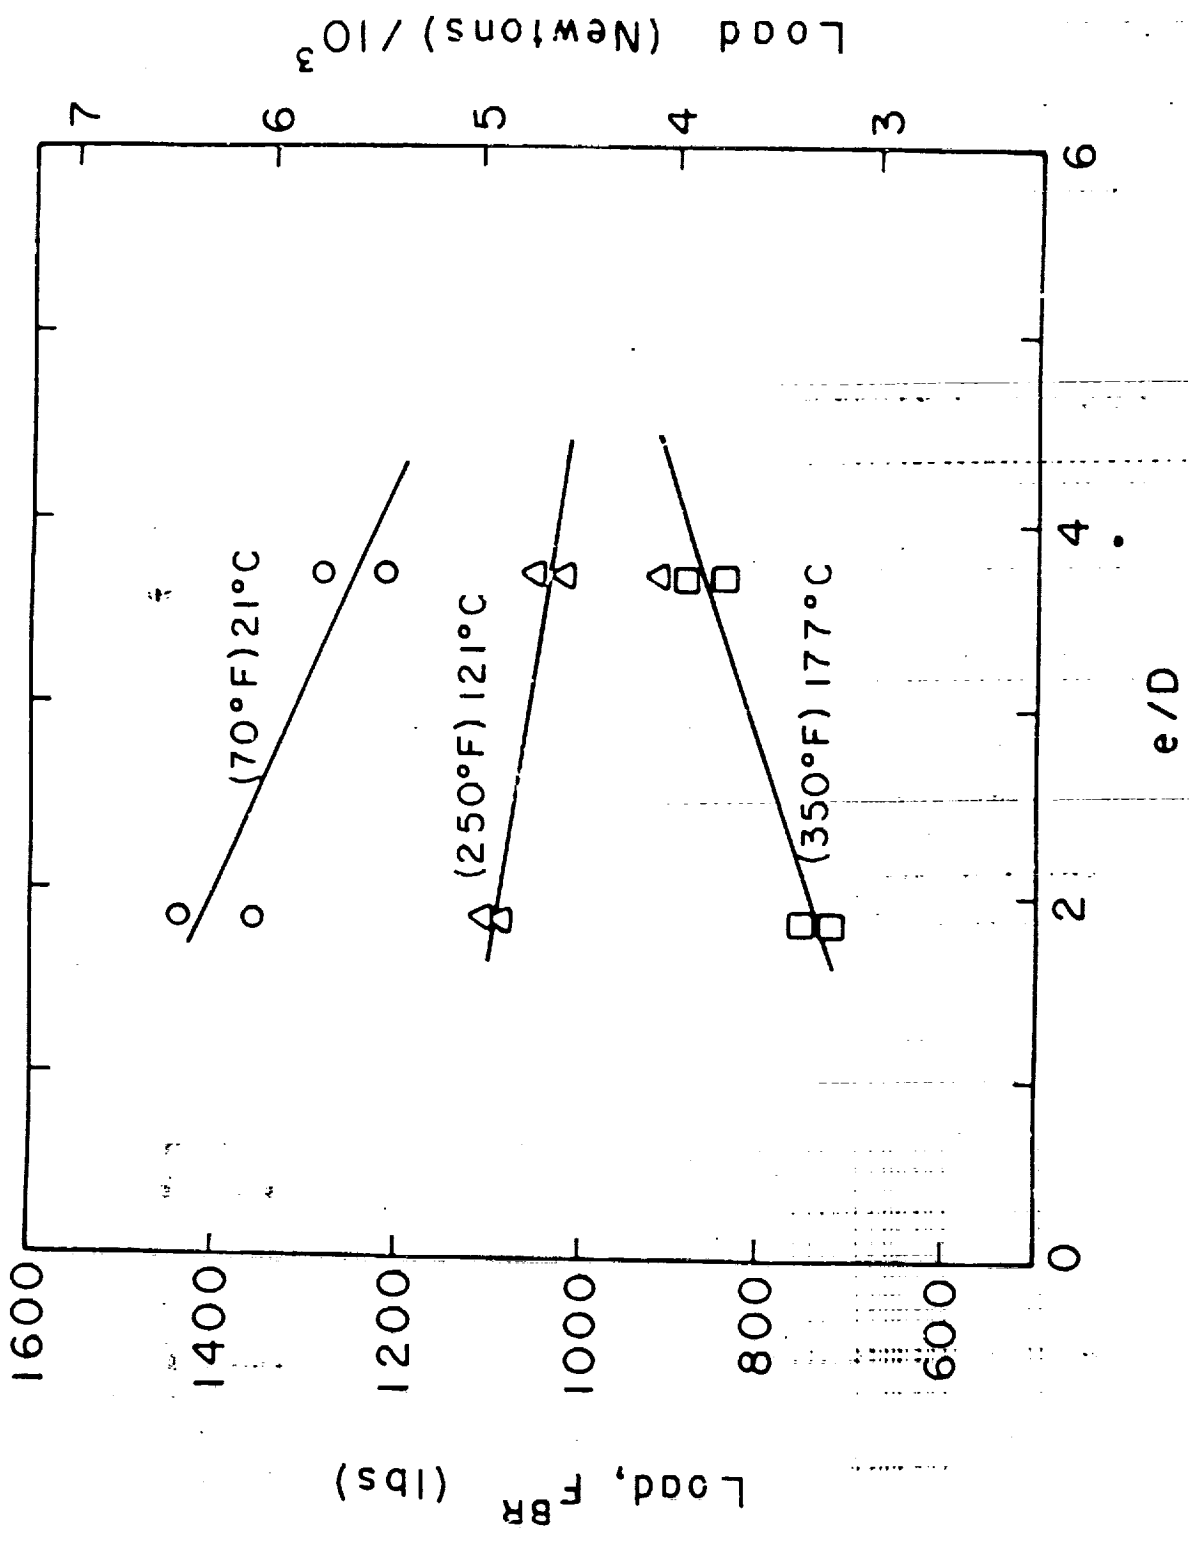


FIGURE 3.4.3 - PIN BEARING FAILURE LOAD VERSUS  $e/D$  FOR QUANTAL ISOTROPIC LAMINATE,  $W/D = 4.35$



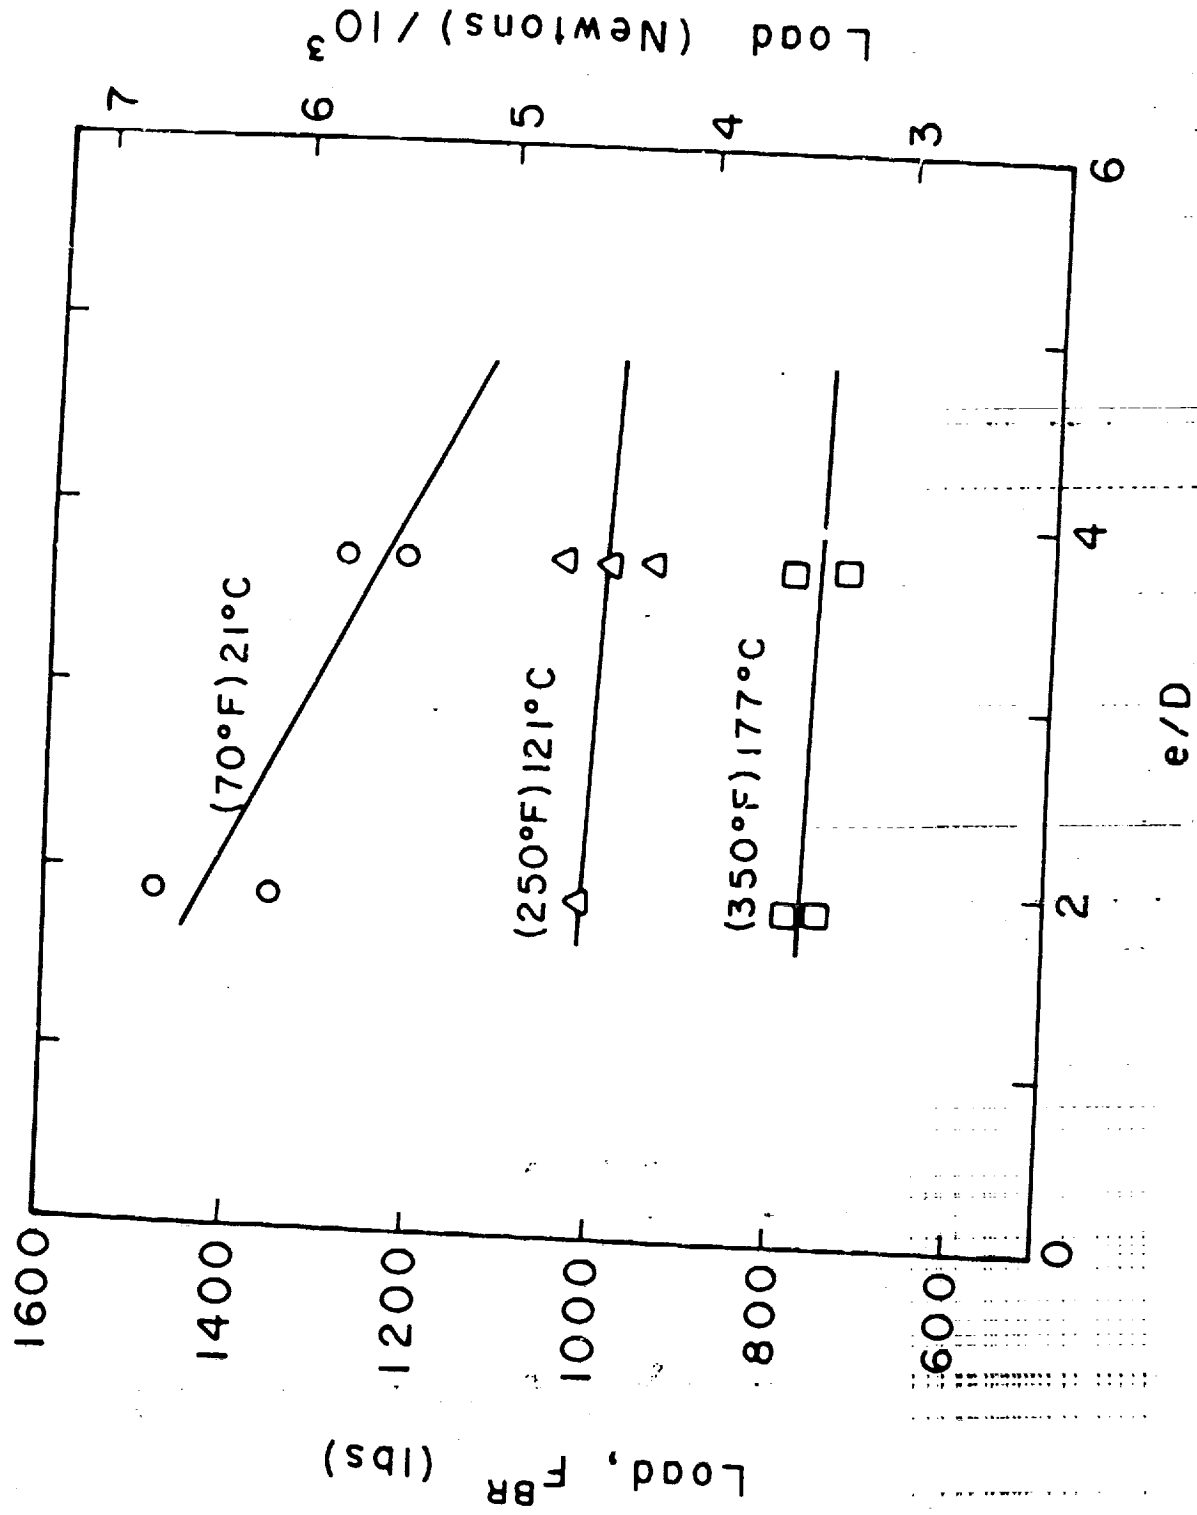


FIGURE 3.4.4 - PIN BEARING FAILURE LOAD VERSUS  $e/D$  FOR QUASI-ISOTROPIC LAMINATE,  $W/D = 7.43$

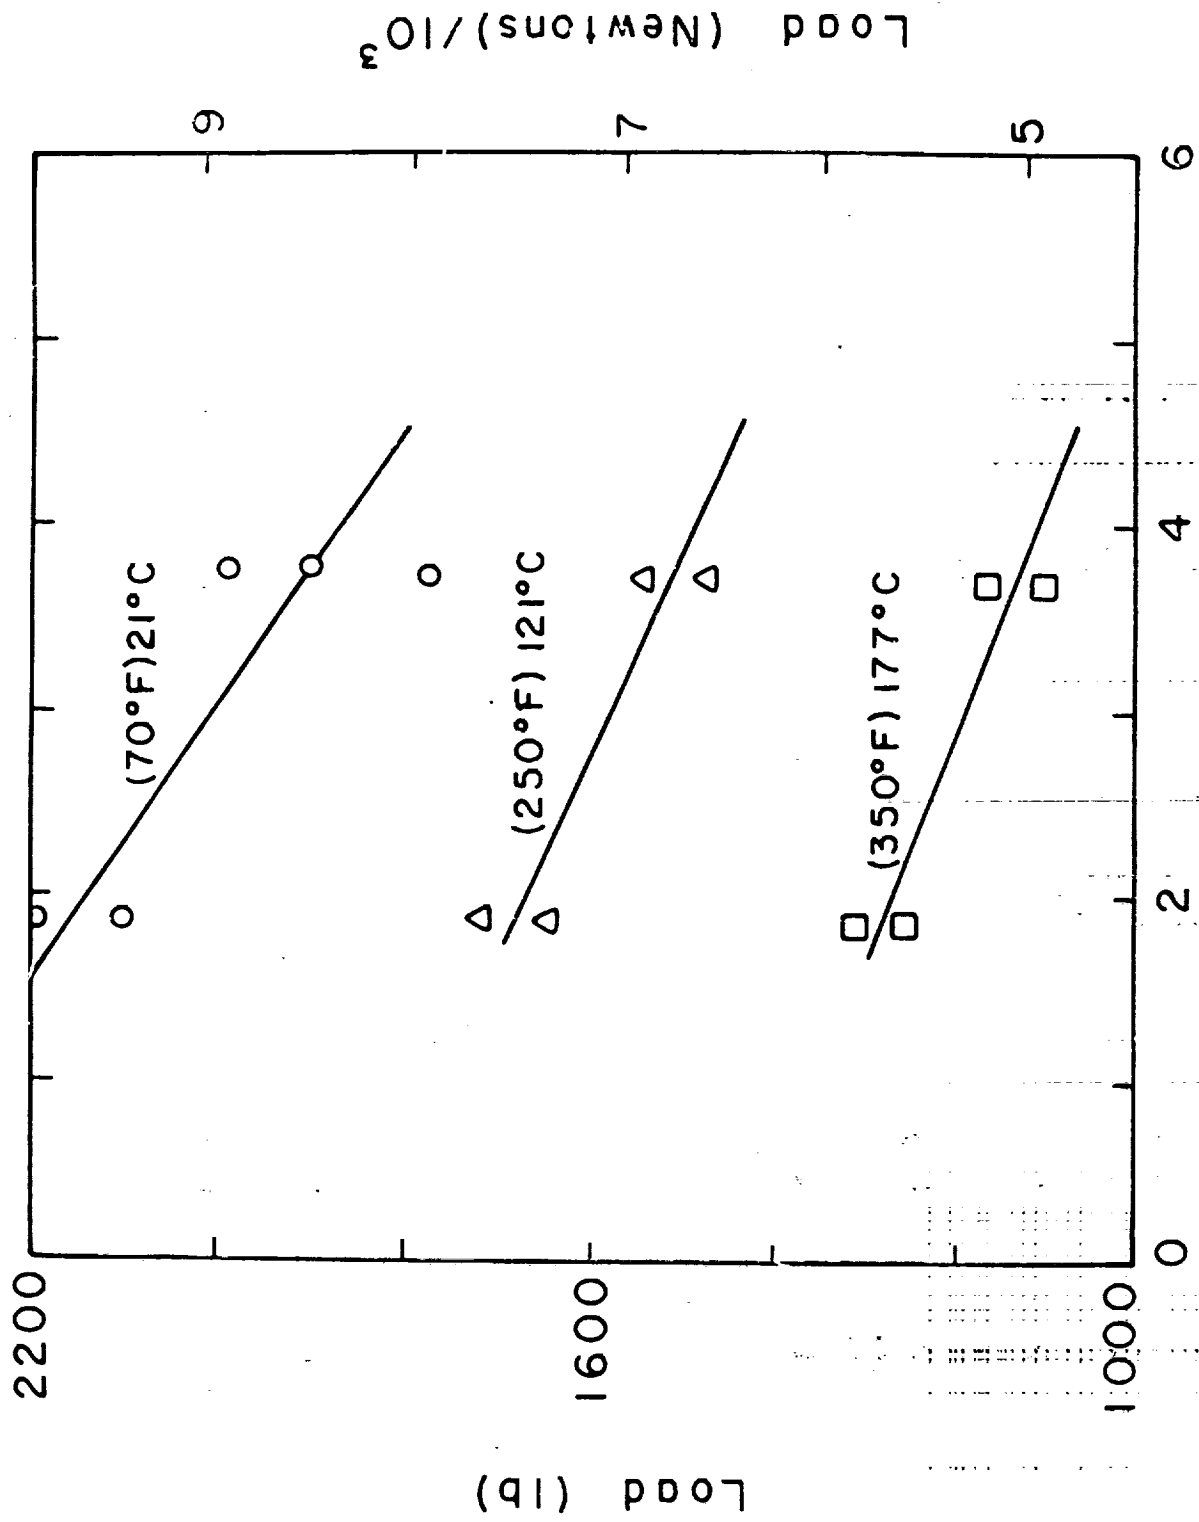


FIGURE 3.5.1 - PIN BEARING FAILURE LOAD VERSUS  $e/D$  FOR  $0^\circ$  DOMINATED LAMINATE,  $W/D = 3.71$

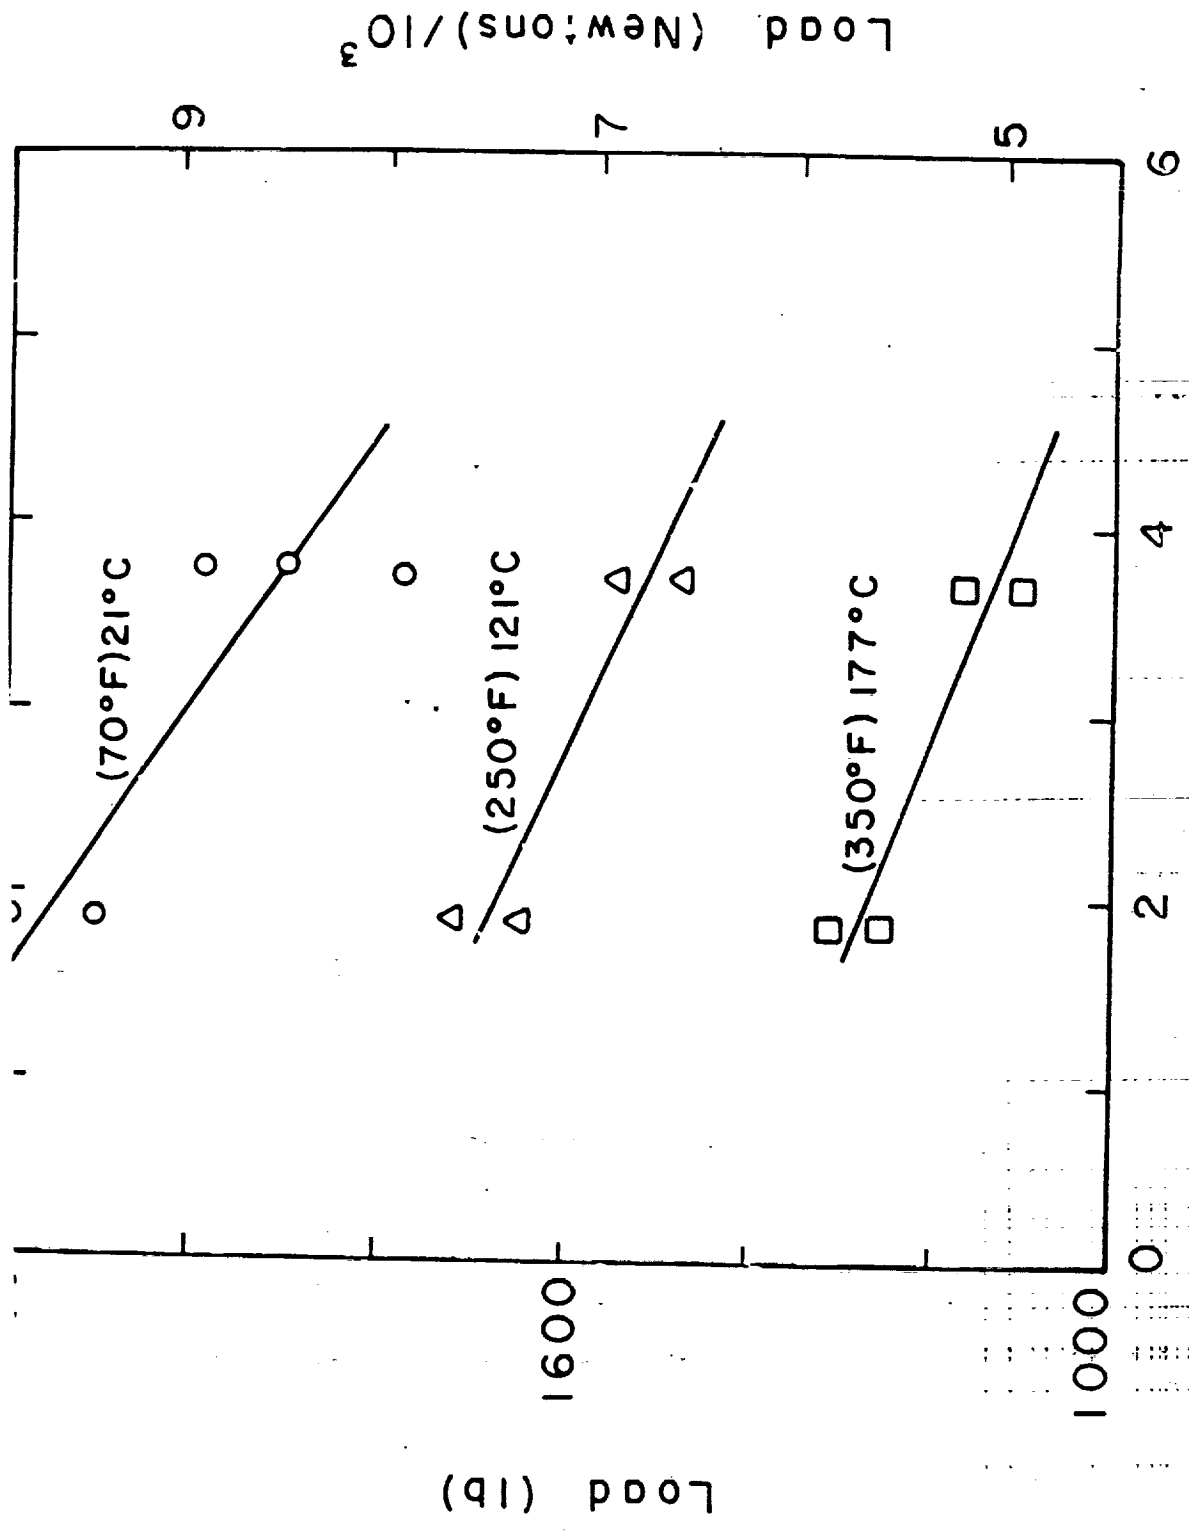


FIGURE 3.5.1 - PIN BEARING FAILURE LOAD VERSUS  $e/D$  FOR  $0^\circ$  DOMINATED LAMINATE,  $h/D = 3.71$

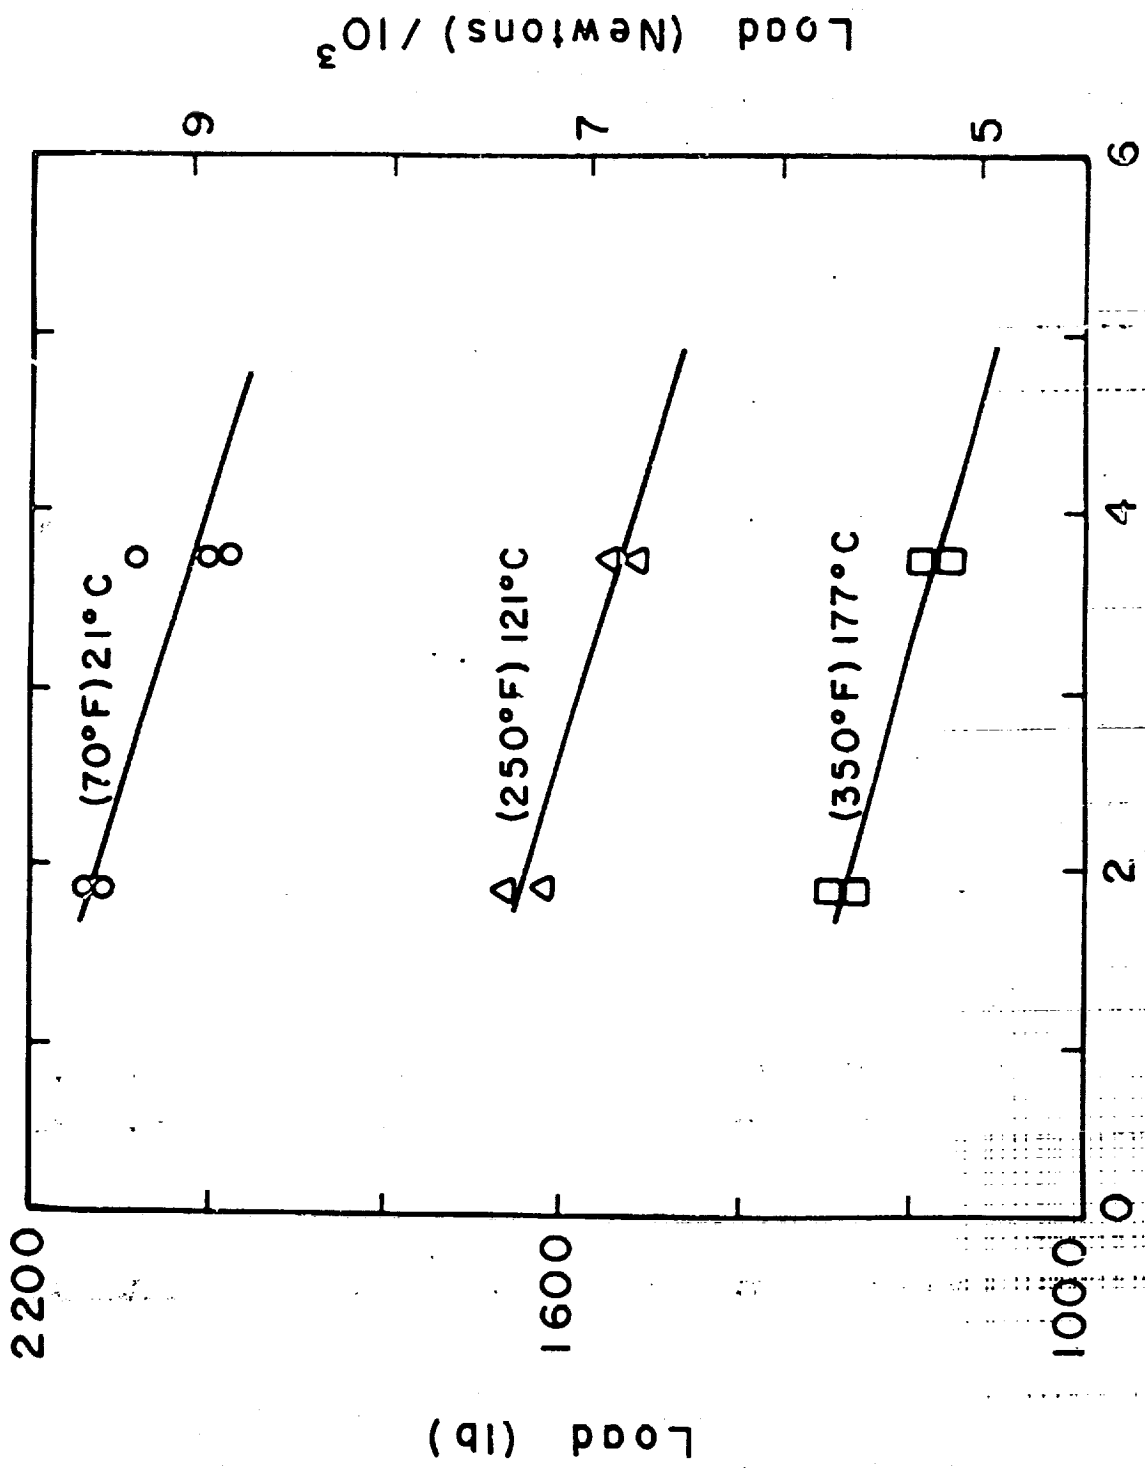


FIGURE 3.5.2 - PIN BEARING FAILURE LOAD VERSUS  $e/D$  FOR 0° DOMINATED LAMINATE,  $h/D = 4.95$

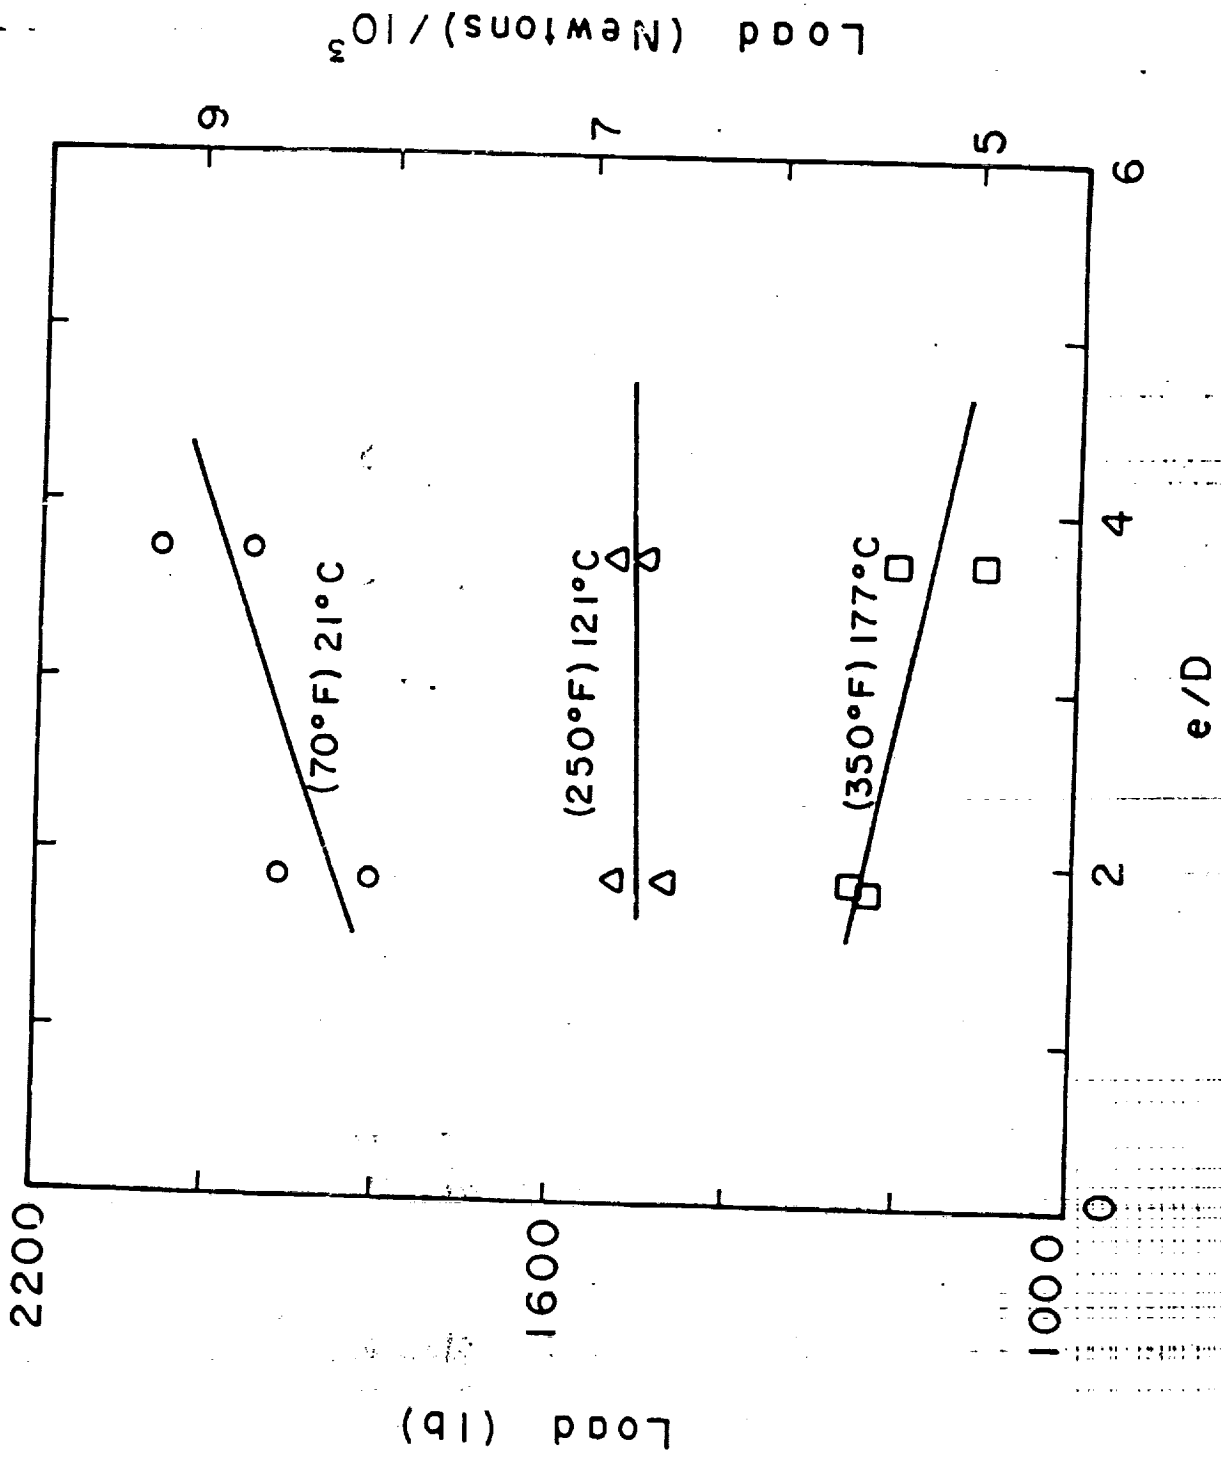


FIGURE 3.5.3 - PIN BEARING FAILURE LOAD VERSUS  $e/D$  FOR  $0^\circ$  DOMINATED LAMINATE,  $W/D = 7.43$

Load (Newtons) /  $10^3$

Load (lb)

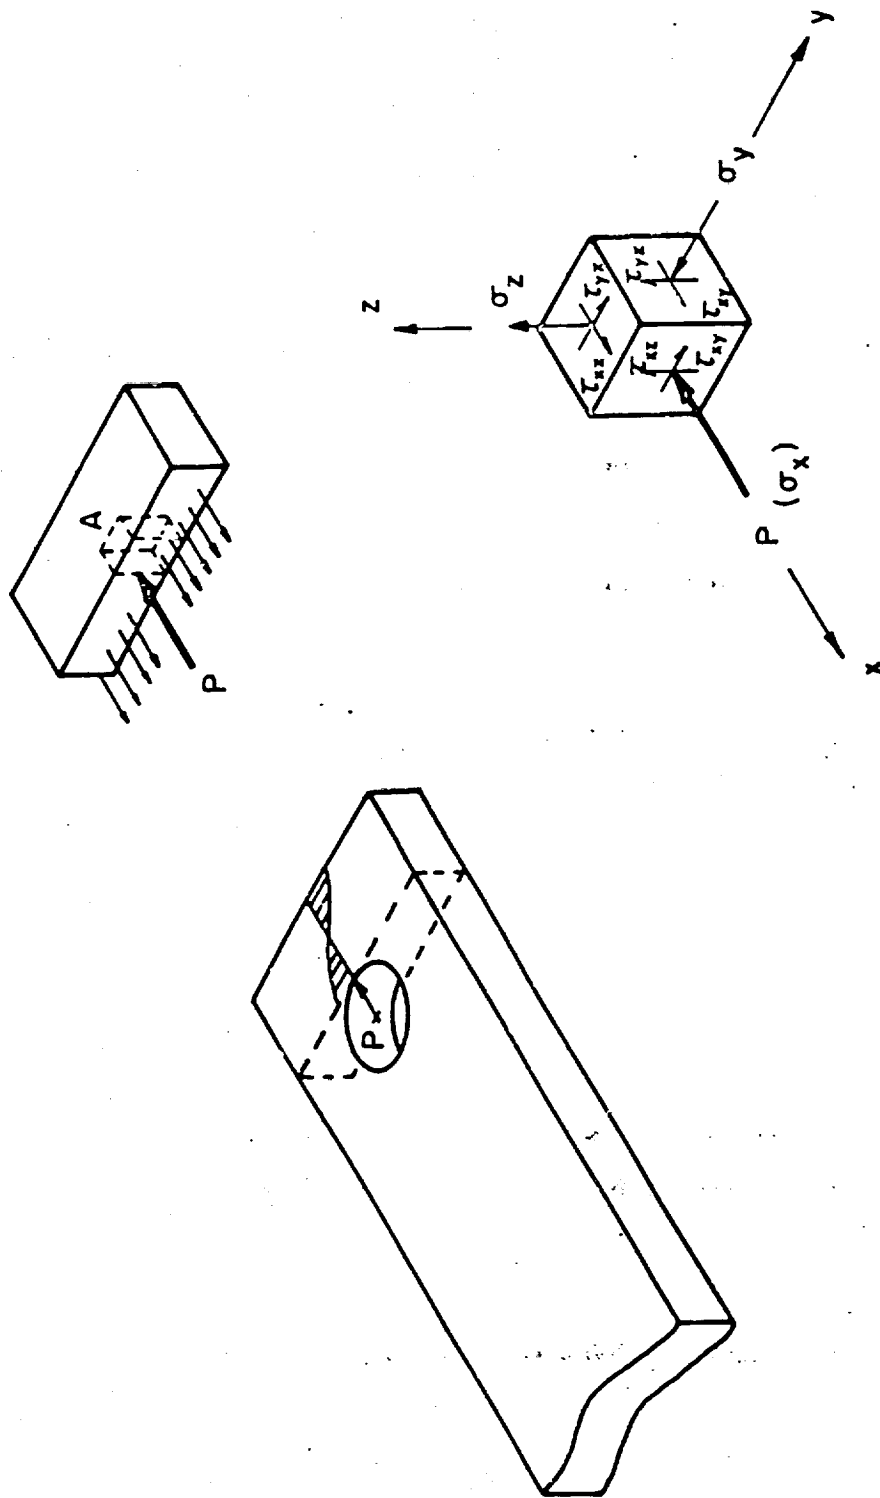


FIGURE 3.514 - BEAM BENDING ANALOGY FOR PIN LOADED JOINT

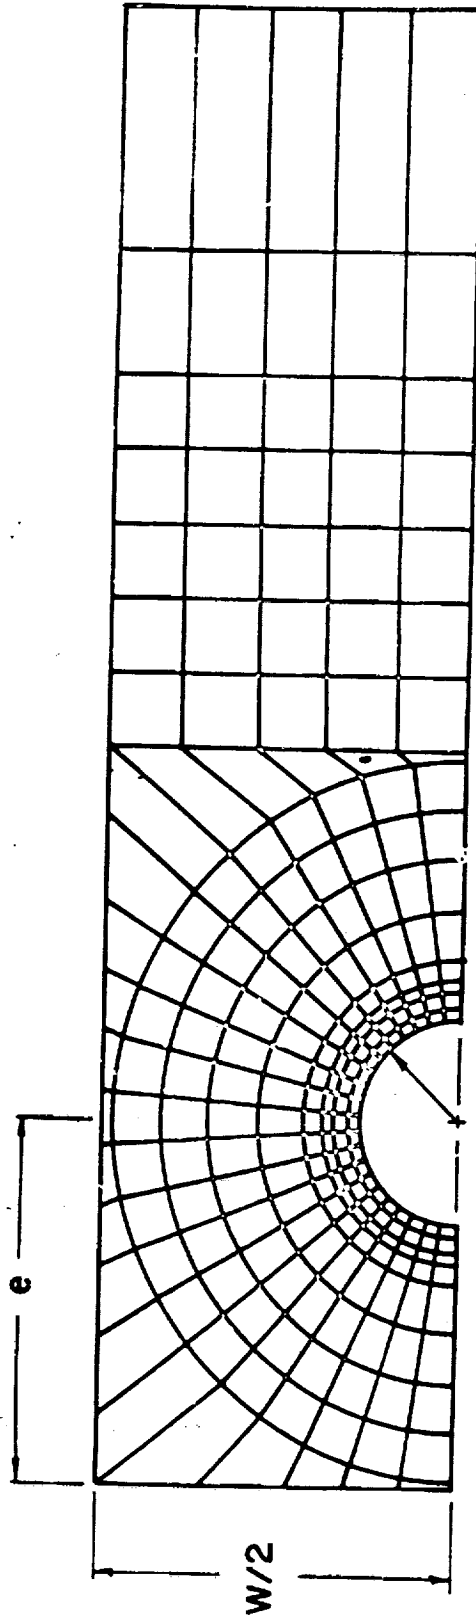


FIGURE 3.6.1 - FINITE ELEMENT MODEL OF  $e/D = 2$  PIN LOADED JOINT

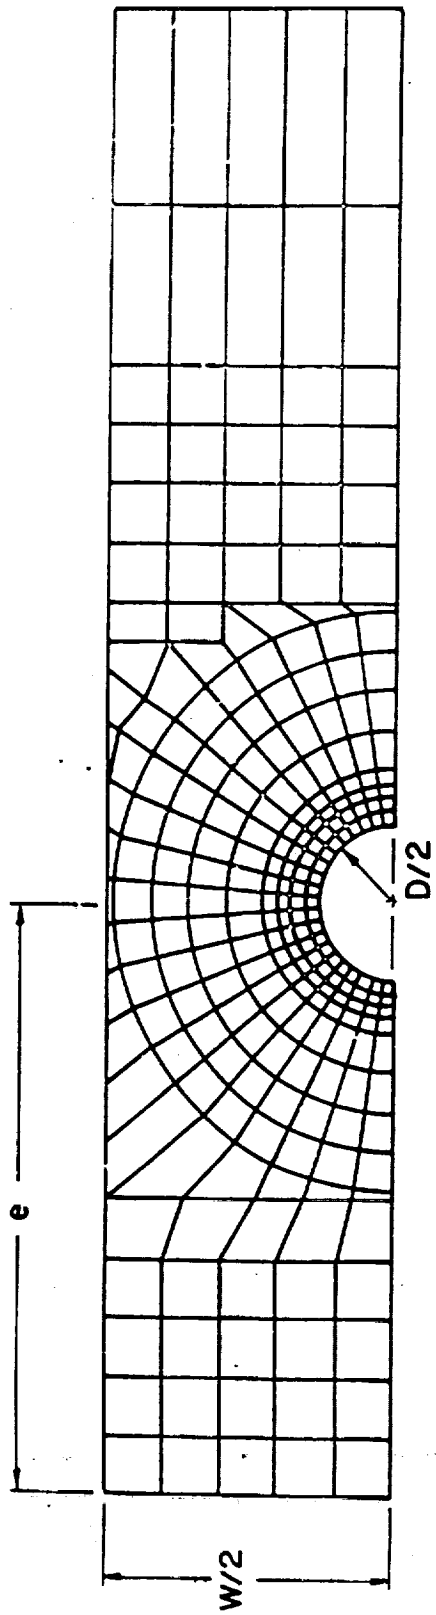


FIGURE 3.6.2 - FINITE ELEMENT MODEL OF  $e/D = 4$  PIN-LOADED JOINT



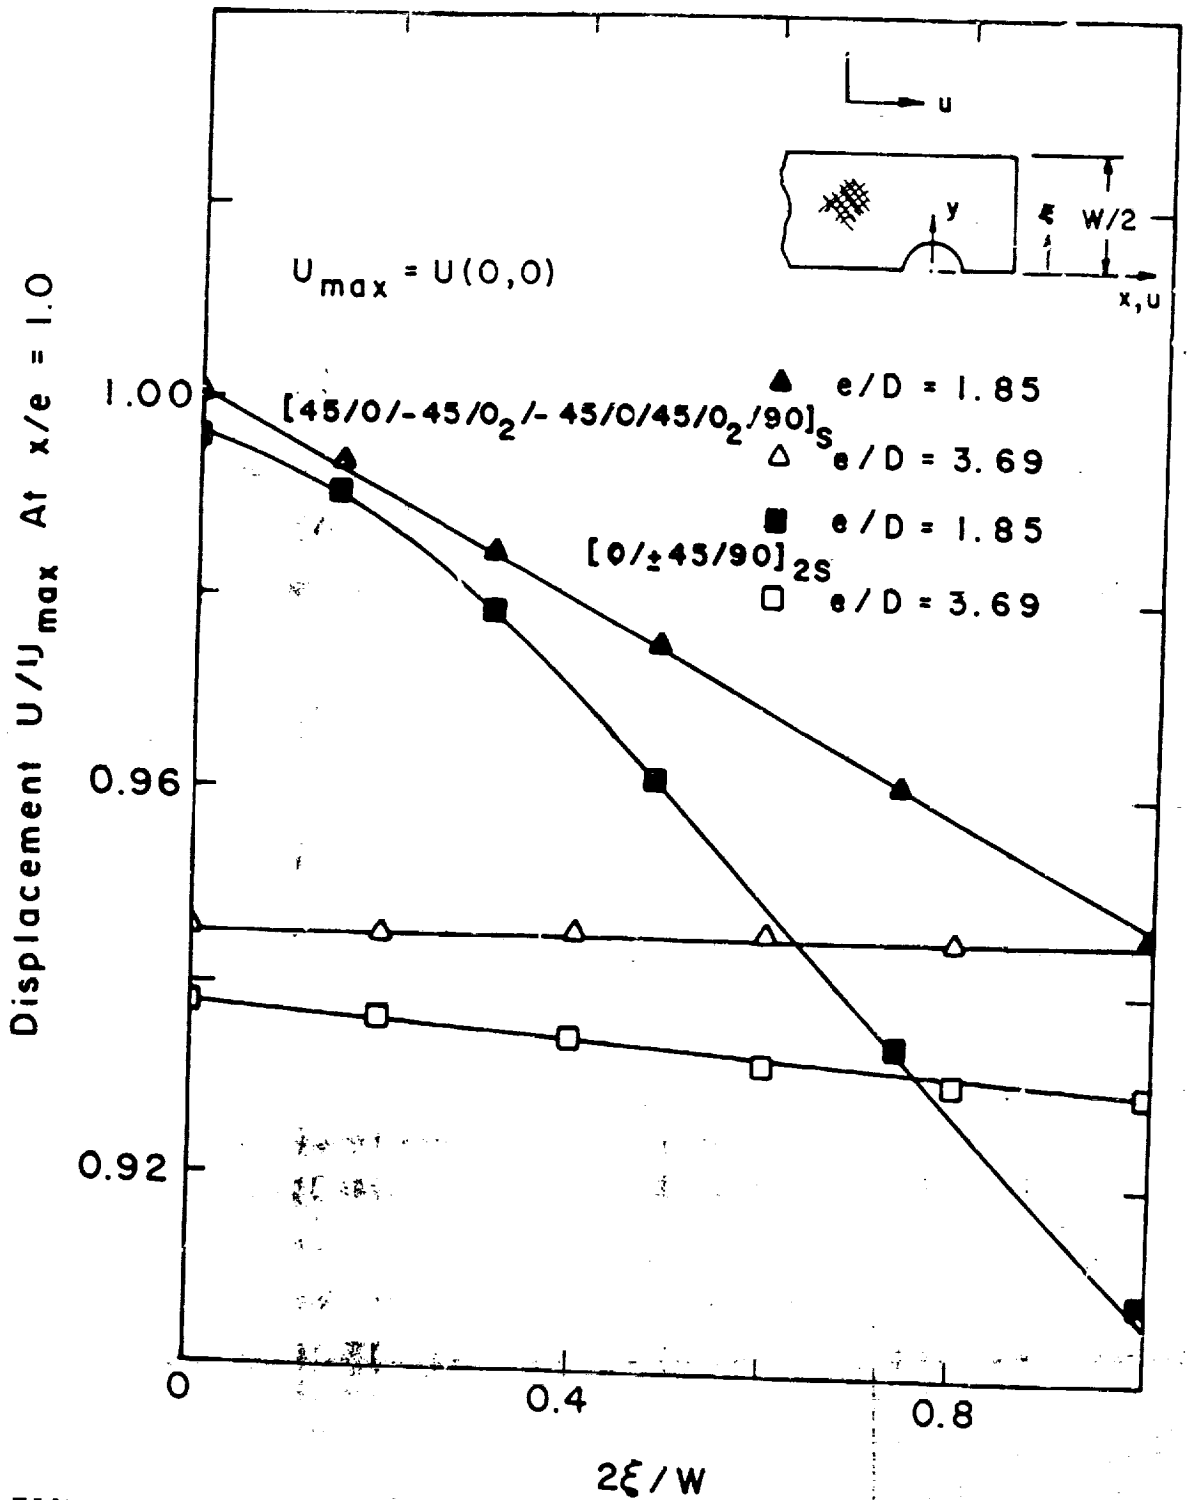


FIGURE 3.7.1 - DEFORMATION OF EDGE UNDER PIN LOADING FOR AS/3501-6 GRAPHITE EPOXY

COMPOSITE BATHS AND ...

BEARING FAILURE

SEPARATION FAILURE

ORIGINAL PAGE IS  
OF POOR QUALITY

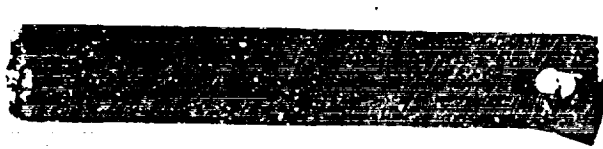
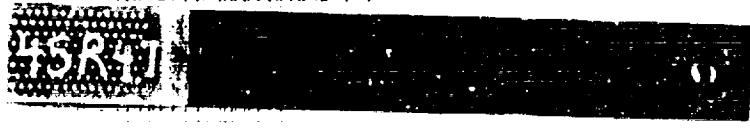


FIGURE 3.9.1 - TYPICAL FAILURE MODES OF THE COUPONS

Damage Zone "C" Scan Of  
 [0/±45/90]<sub>2S</sub> Laminate  
 e/D = 2


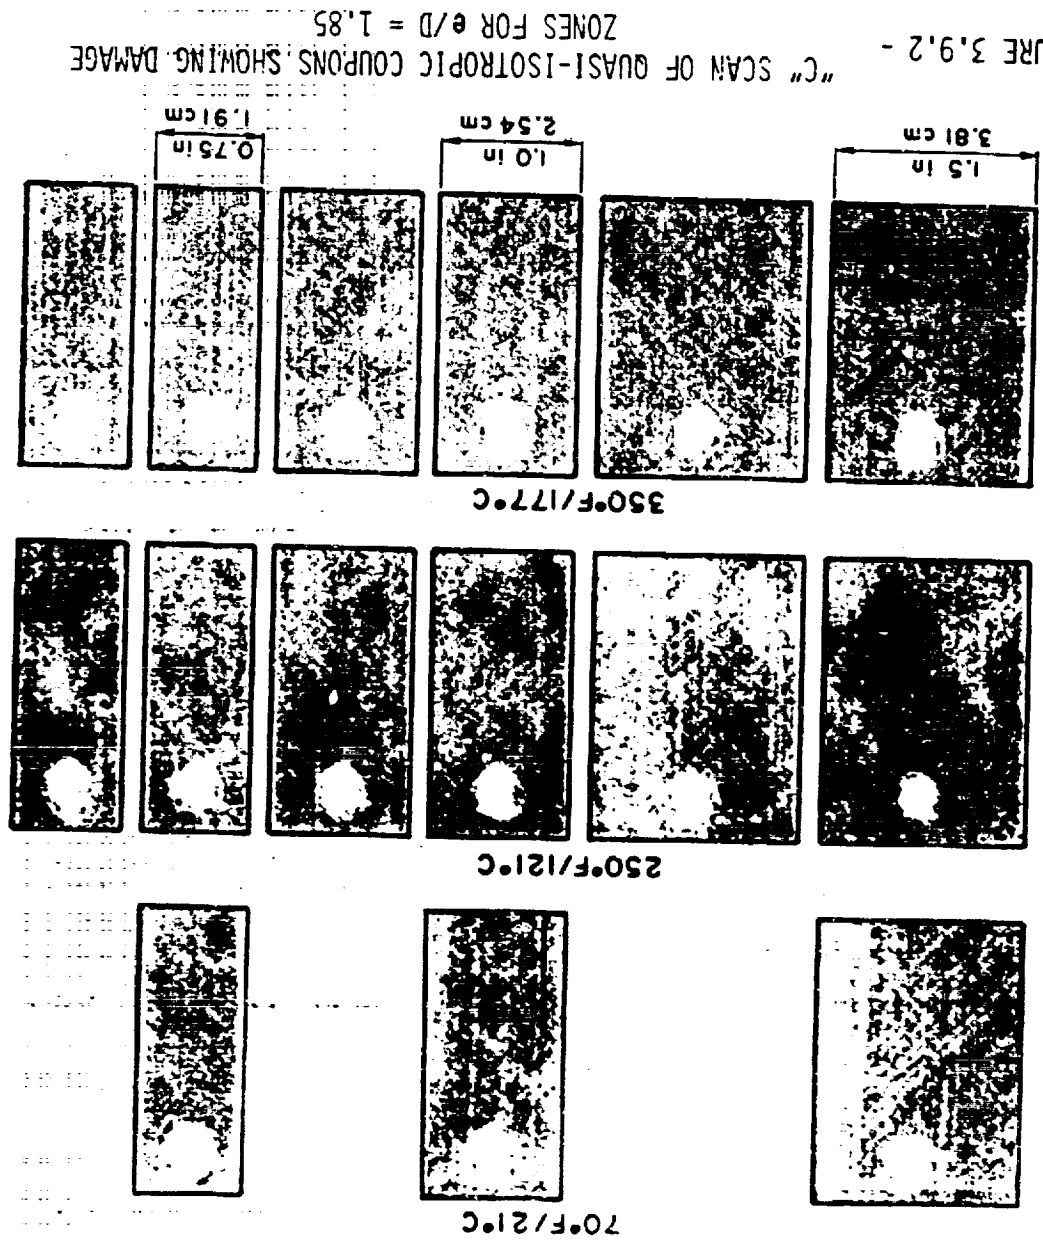


FIGURE 3.9.2 - "C" SCAN OF QUASI-ISOTROPIC COUPONS SHOWING DAMAGE ZONES FOR  $e/D = 1.85$


Damage Zone "C" Scan Of  
 [0/±45/90]<sub>25</sub> Laminate

$e/D = 4$

70°F/21°C

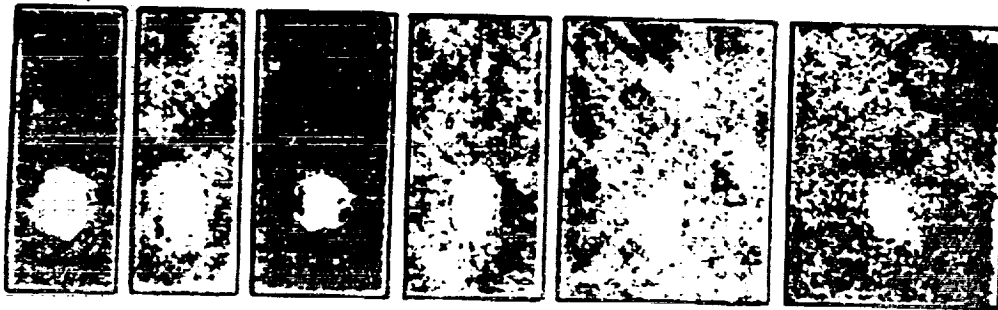

250°F/121°C

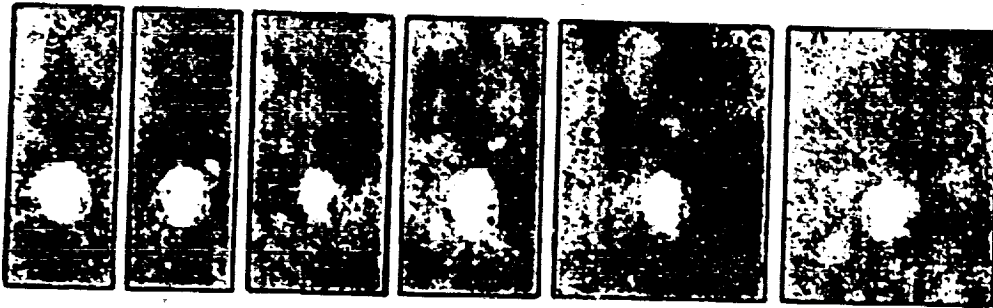

350°F/177°C


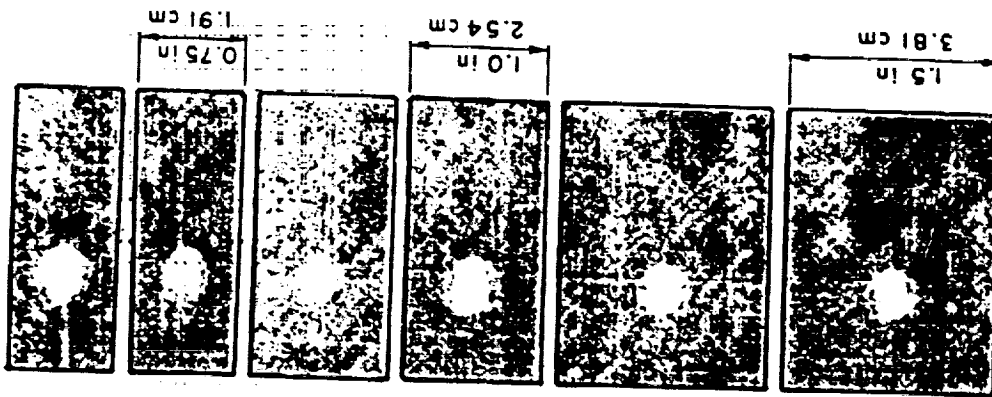


FIGURE 3.9.3 - "C" SCAN OF QUASI-ISOTROPIC COUPONS SHOWING DAMAGE ZONES FOR  $e/D = 3.69$

ORIGINAL PAGE IS  
OF POOR QUALITY

FIGURE 3.9.4 - "C" SCAN OF 0° DOMINATED COUPONS SHOWING DAMAGE ZONES FOR  $e/D = 1.85$

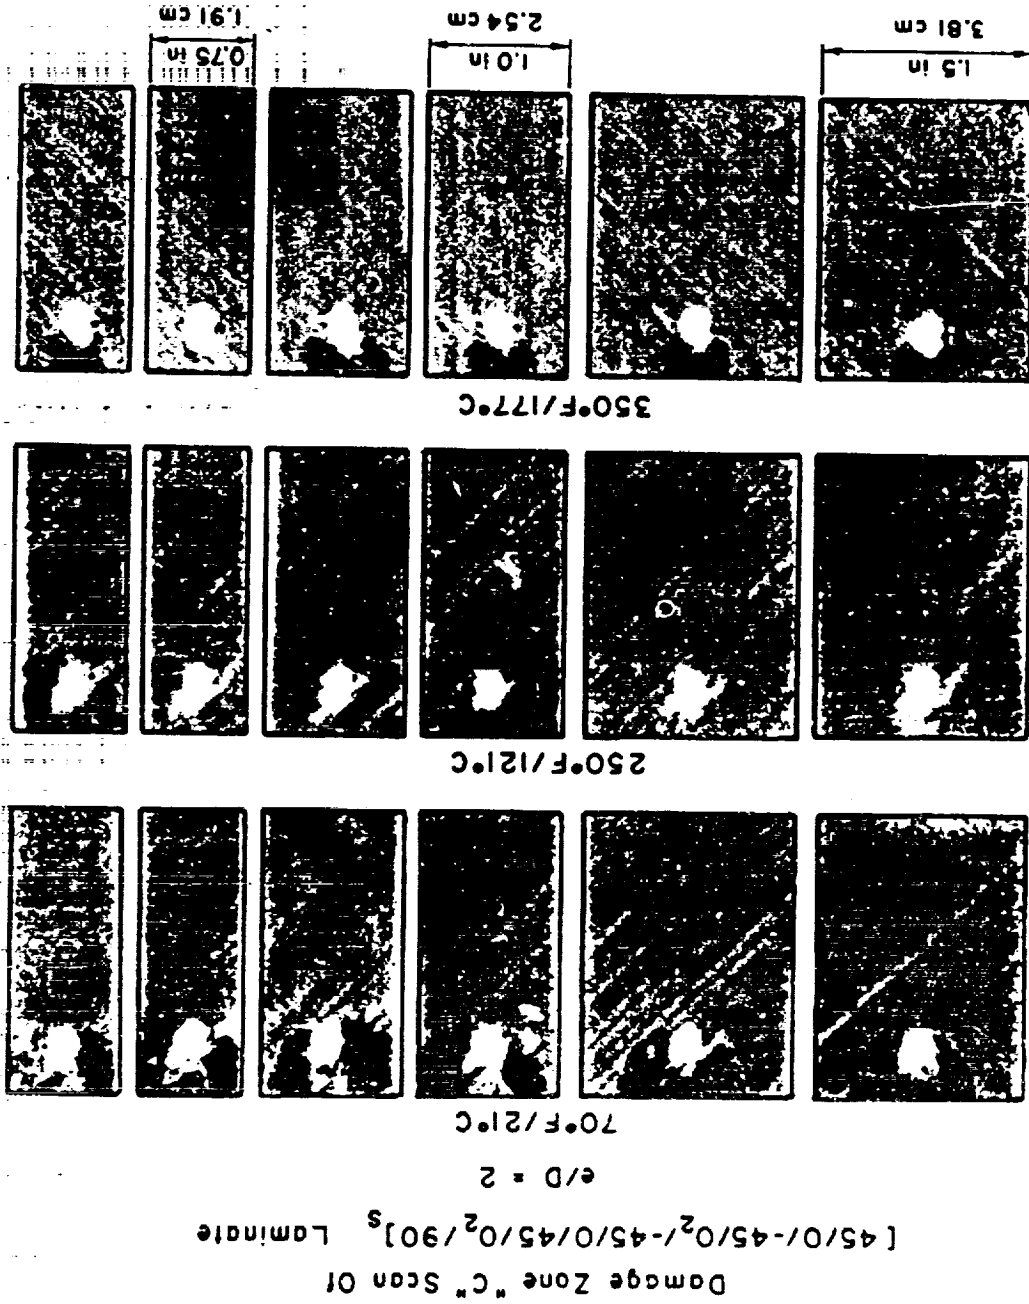

Damage Zone "C" Scan Of  
 [45/0/-45/0<sub>2</sub>-45/0/45/0<sub>2</sub>/90]<sub>s</sub> Laminar  
 t/D = 4


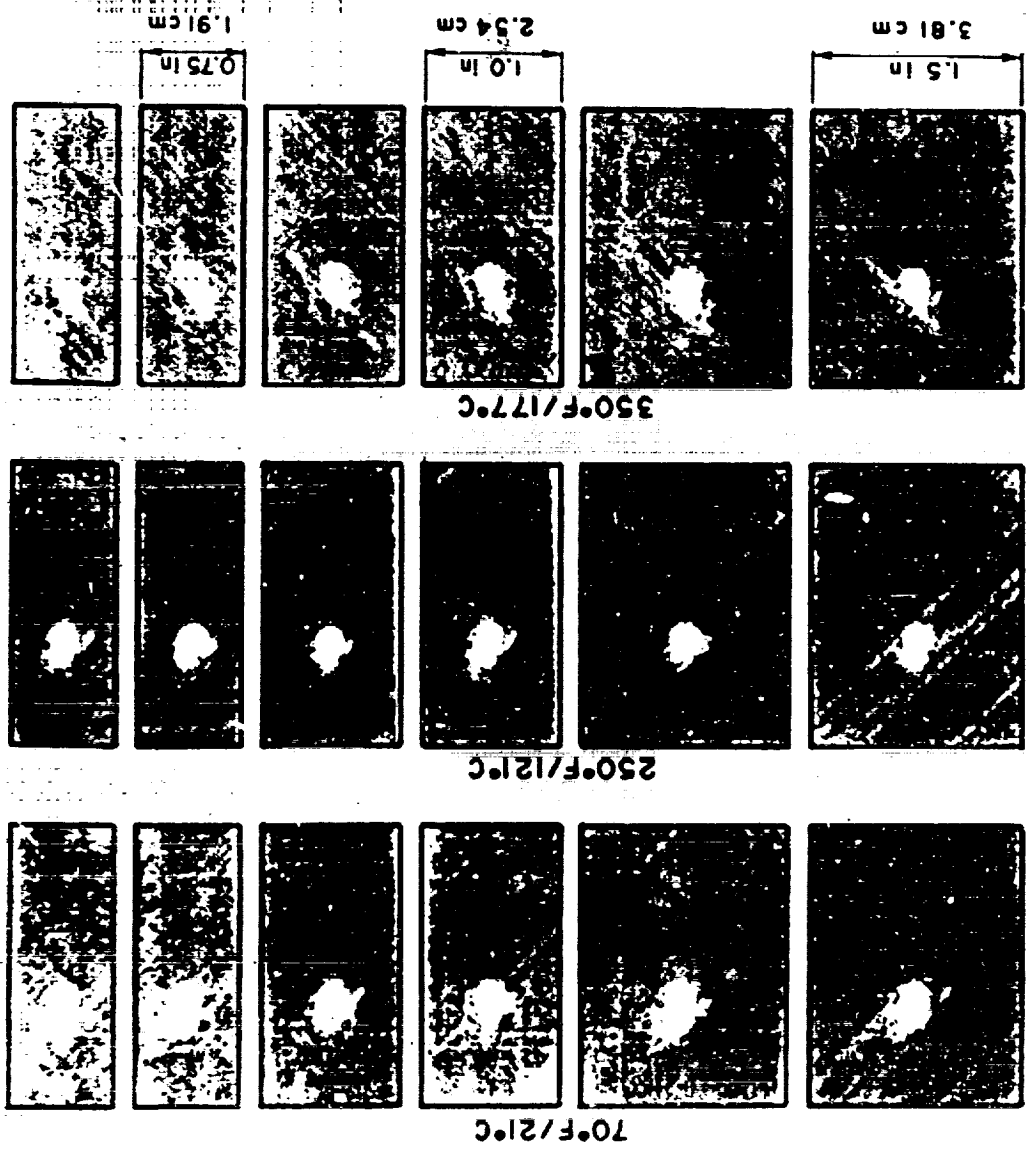


FIGURE 3.9.5 - "C" SCAN OF 0° DOMINATED COUPONS SHOWING DAMAGE ZONES FOR t/D = 3.63

FIGURE 3.9.6 - "C" SCAN OF COUPONS TESTED WITH OUT-OF-PLANE CONSTRAINT

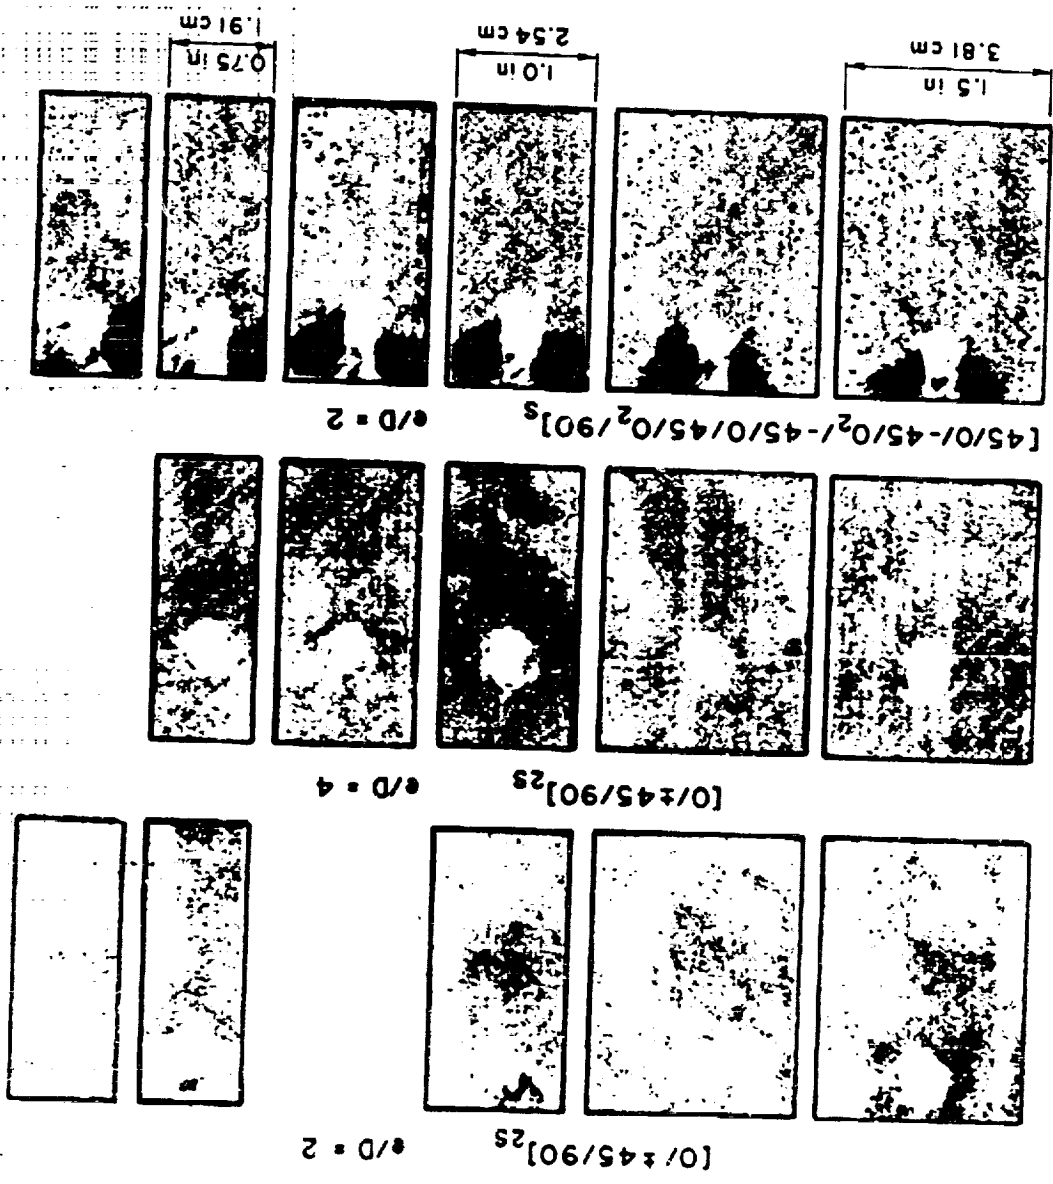

Damage Zone "C" Scan Of Bolted Joint Laminates  
With Out-Of-Plane Constraint

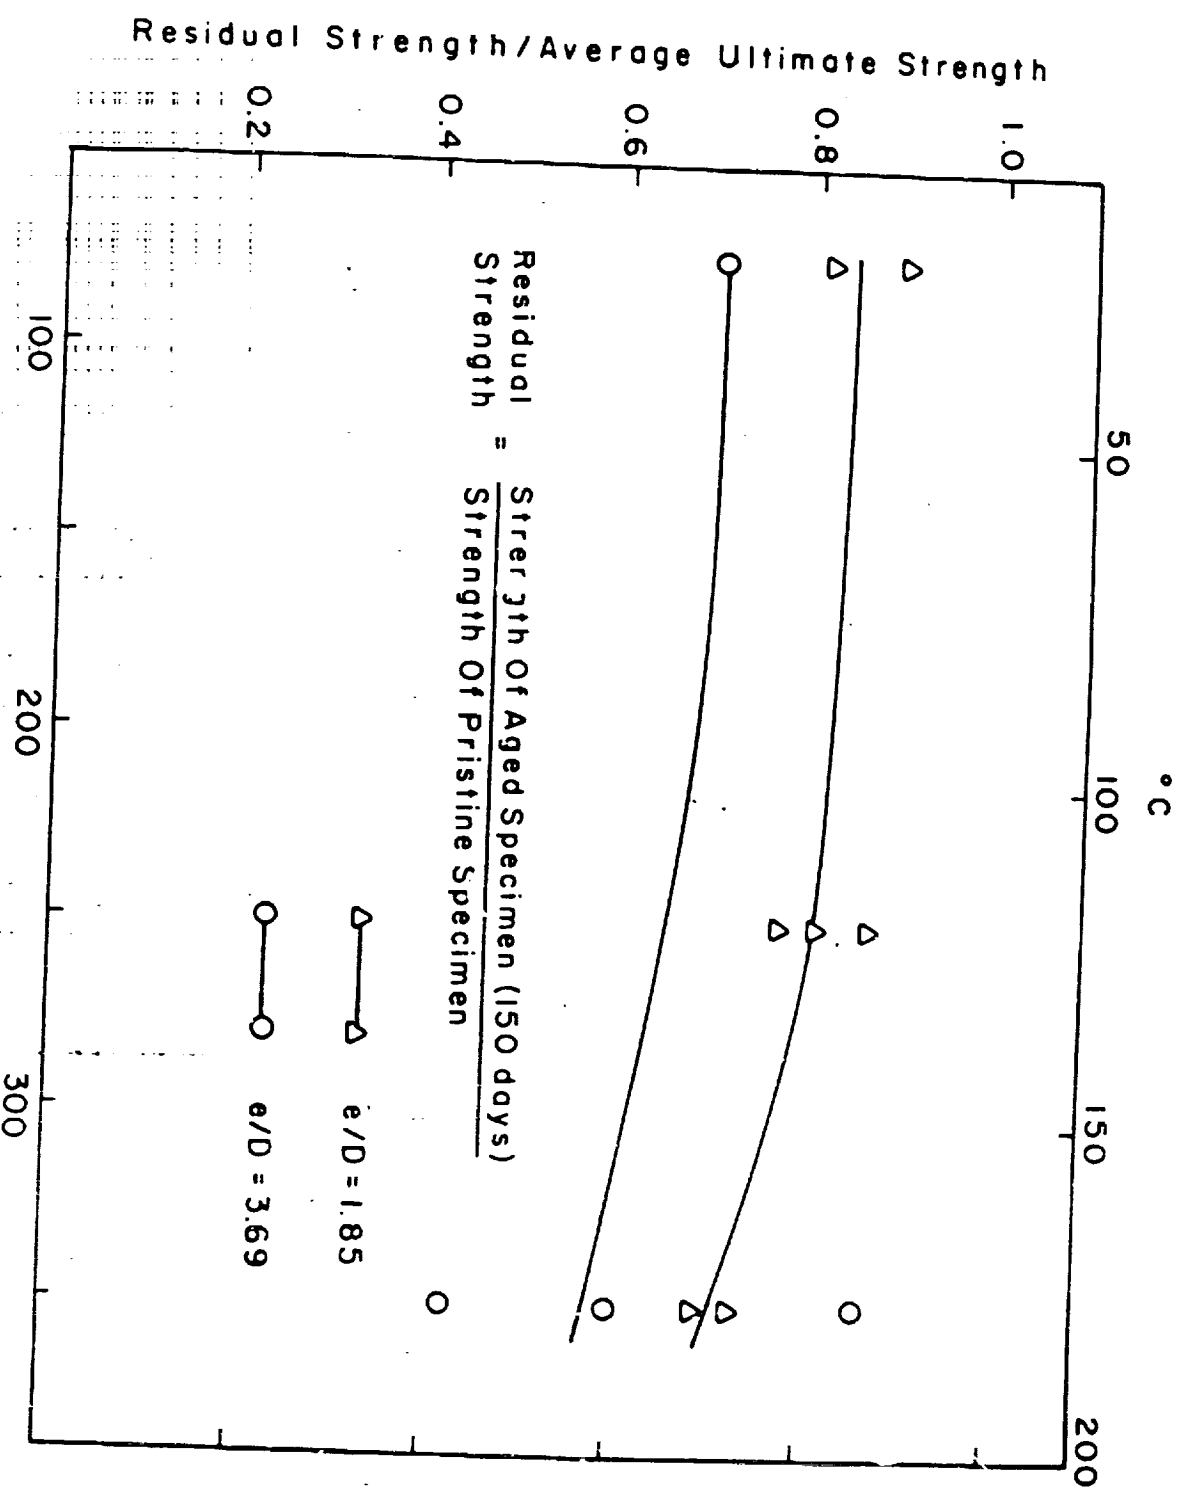


FIGURE 3.10.1 - DECREASED STRENGTH EXHIBITED BY SAMPLES TESTED AFTER 4 MONTH DELAY, QUASI-ISOTROPIC LAMINAIE



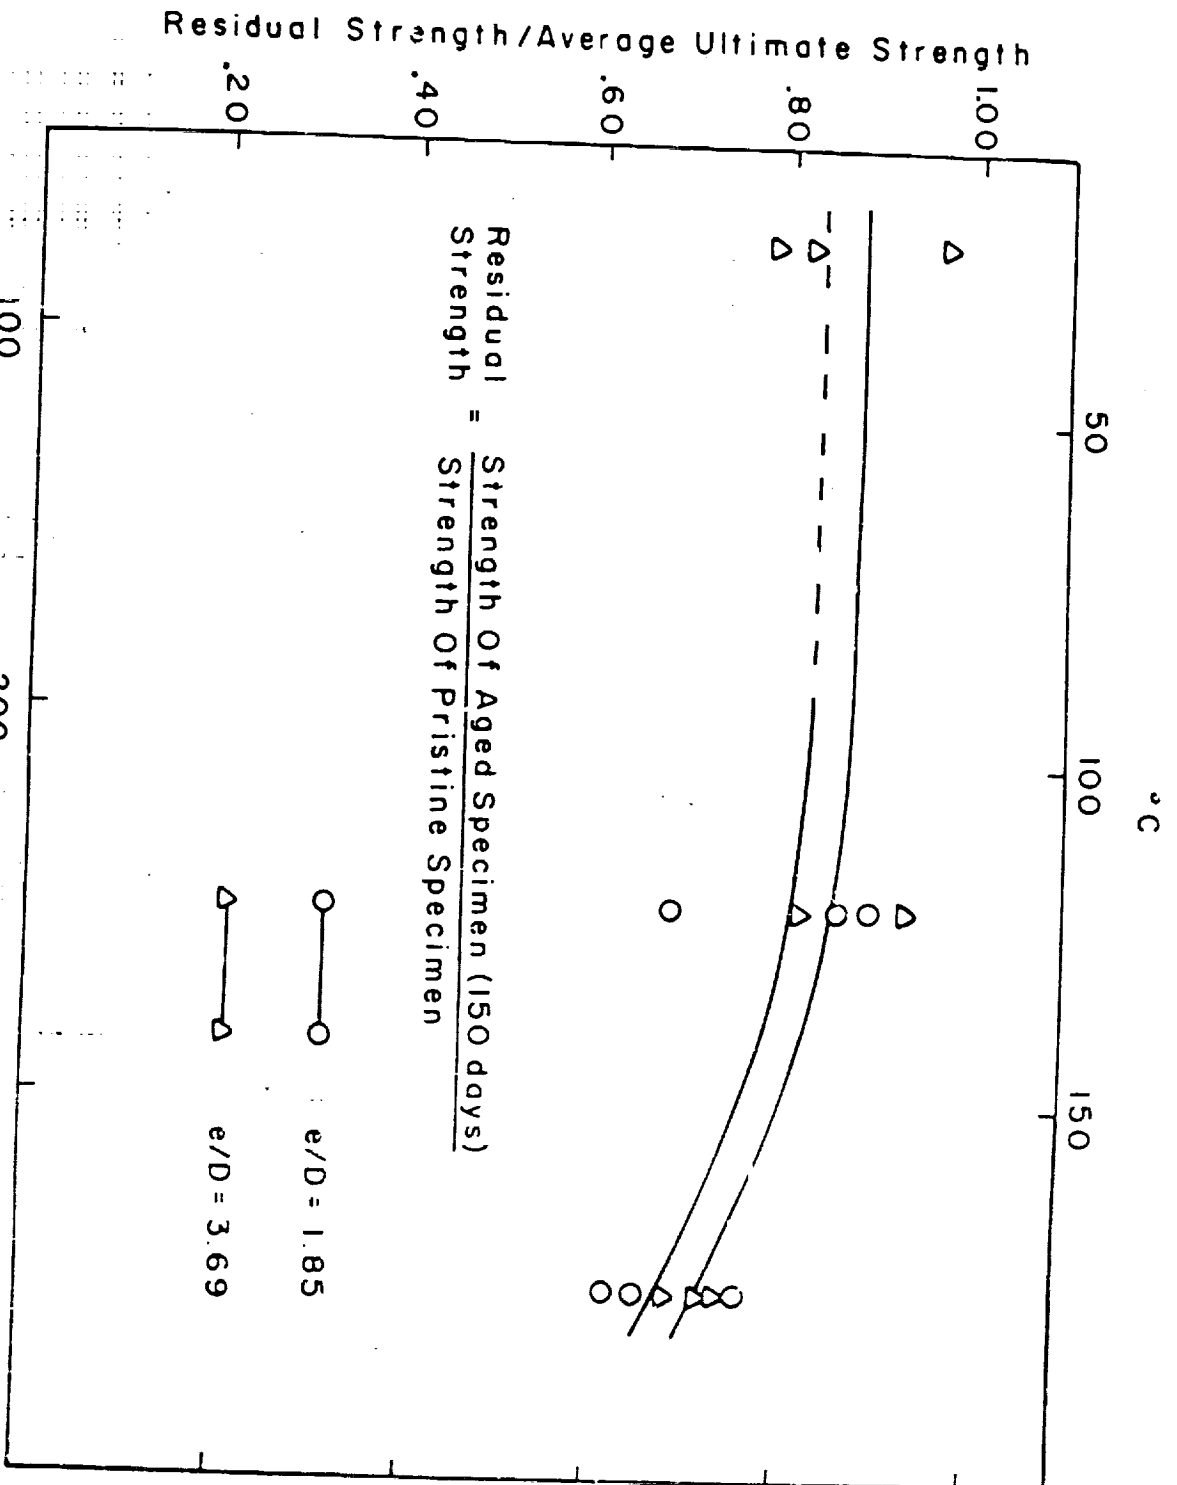
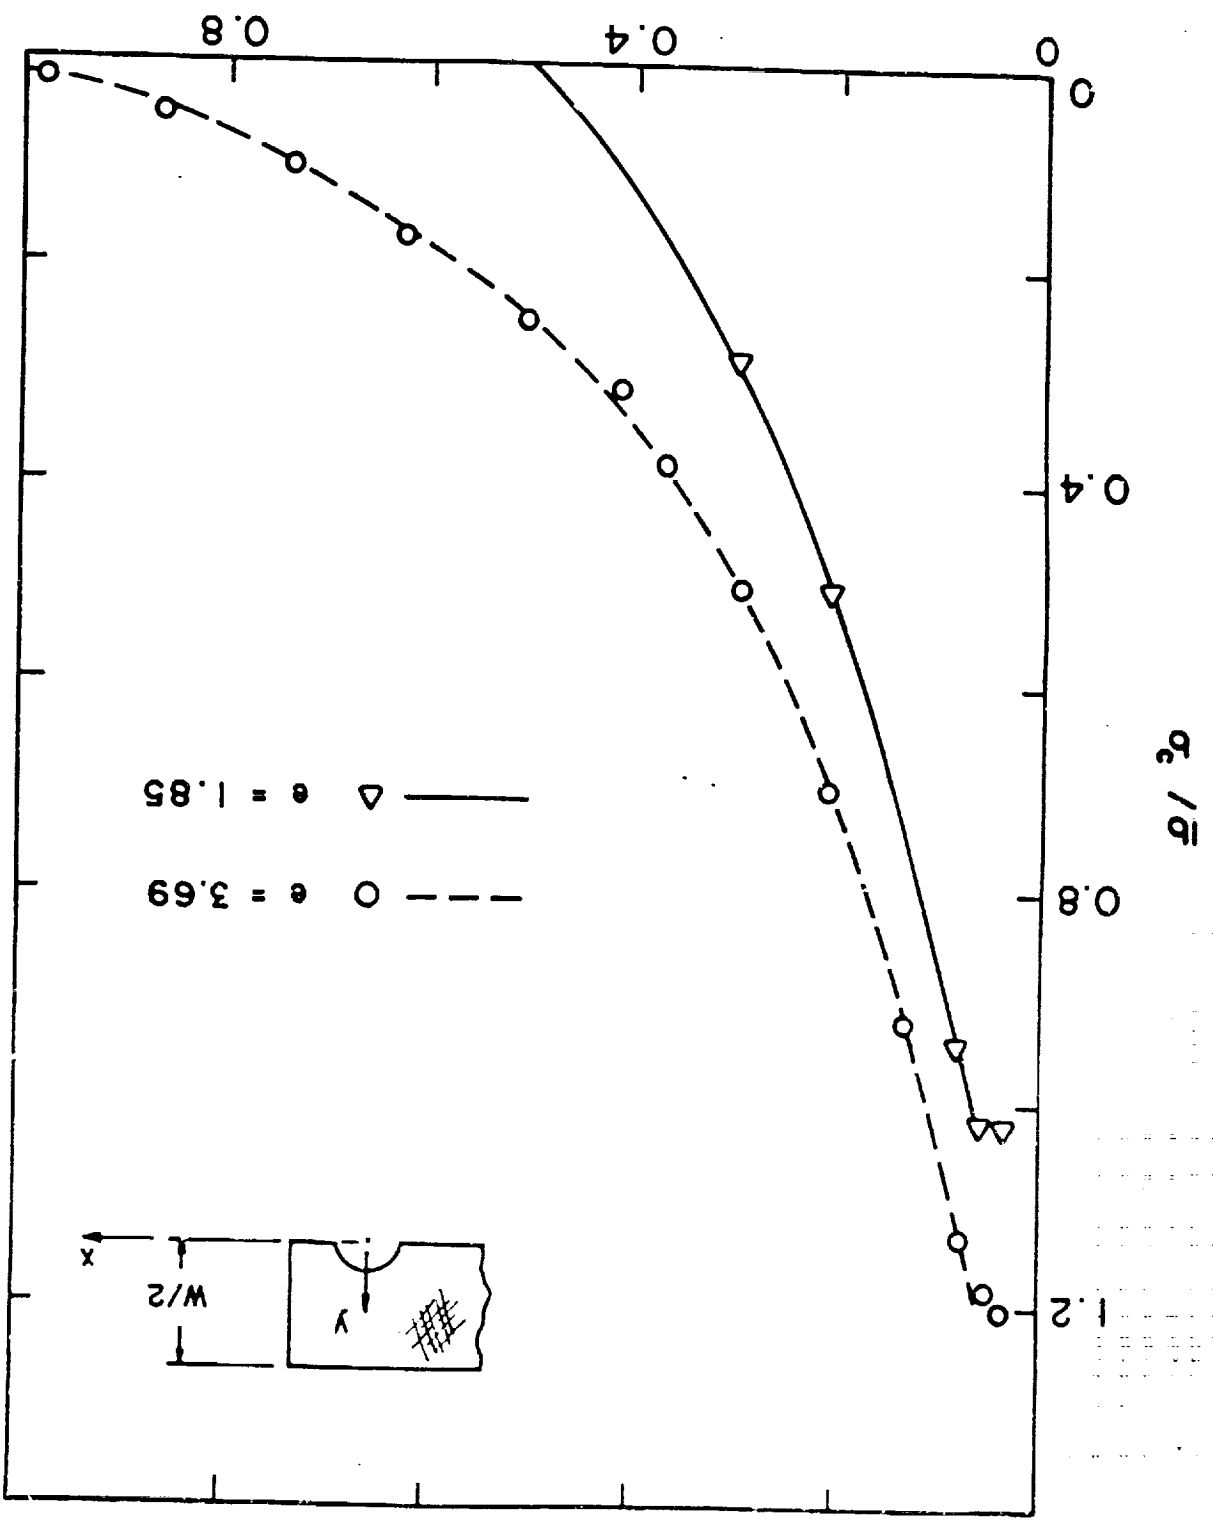


FIGURE 3.10.2 - DECREASED STRENGTH EXHIBITED BY SAMPLES TESTED AFTER 4 MONTH DELAY OF DOMINATED LAMINATE

FIGURE 3,8,1 - COMPARISON OF BEARING STRESSES IN QUASI-ISOTROPIC BOLTED JOINT WITH  $e/D$ 'S OF 1.85 AND 3.69

C-2



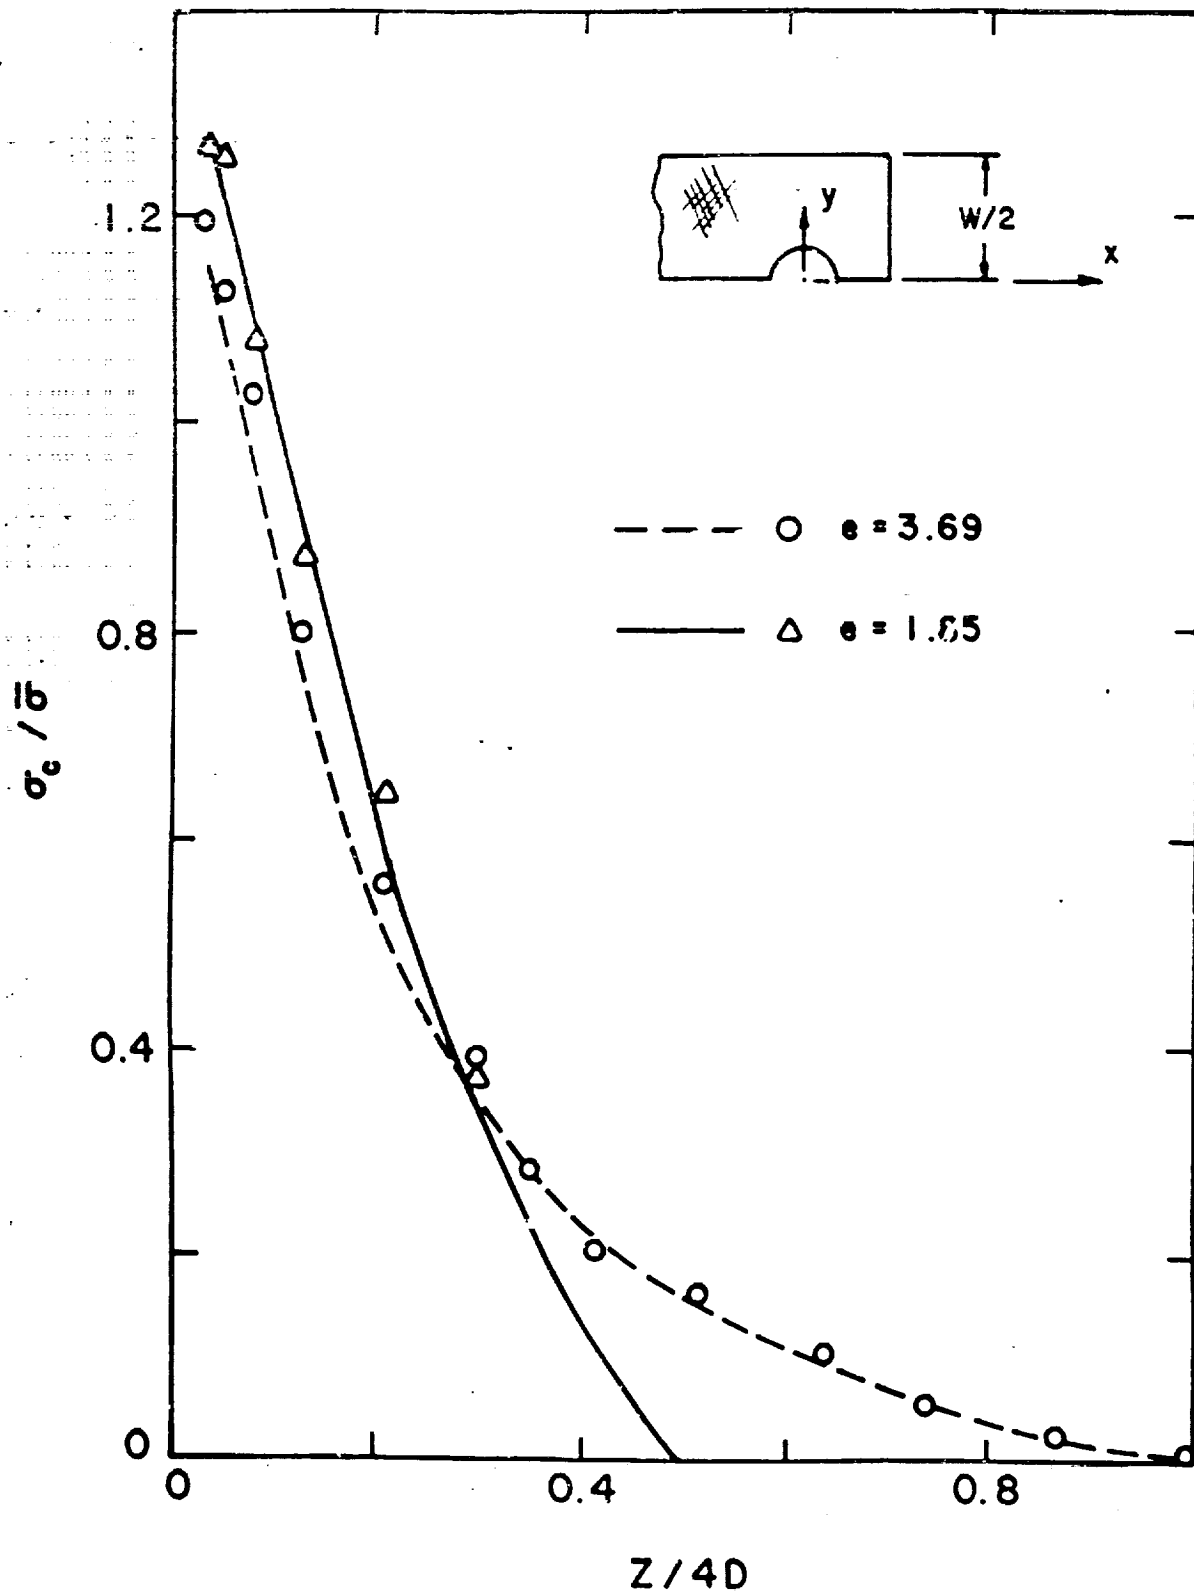


FIGURE 3.8.2 - COMPARISON OF BEARING STRESSES IN  $0^\circ$  DOMINATED  
 BOLTED JOINT WITH  $e/D$ 'S OF 2 AND 4