

0

FACILITY FORM 802

N65-10840  
(ACCESSION NUMBER)


25  
(PAGES)

CR 59500  
(NASA CR OR TMX OR AD NUMBER)

\_\_\_\_\_  
(THRU)

1  
(CODE)

03  
(CATEGORY)

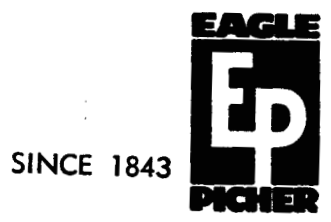

# EAGLE-PICHER

THE EAGLE - PICHER COMPANY • COUPLES DEPARTMENT: JOPLIN, MISSOURI

OTS PRICE	
XEROX	\$ <u>1.00</u>
MICROFILM	\$ <u>.50</u>

SPT 22699

INVESTIGATIONS LEADING TO THE DEVELOPMENT  
OF A PRIMARY ZINC-SILVER OXIDE BATTERY  
OF IMPROVED PERFORMANCE CHARACTERISTICS

PROGRESS REPORT NO. 11

Contract No. NAS 8-5493

Control Number TP3-83728 (1F)

CPB 15-1600-63

GEORGE C. MARSHALL SPACE FLIGHT CENTER  
Huntsville, Alabama

Reporting Period  
1 May 1964 through 31 May 1964

THE EAGLE-PICHER COMPANY  
COUPLES DEPARTMENT  
Joplin, Missouri

Prepared by: Bill R. Hawkins  
B. R. Hawkins, Project Engineer

Reviewed by: J. F. Dittmann  
J. F. Dittmann, Engineering Supervisor

Approved by: E. M. Morse  
E. M. Morse, Engineering Manager

TABLE OF CONTENTS

	<u>Page</u>
I. PURPOSE . . . . .	1
II. ABSTRACT . . . . .	2
III. FACTUAL DATA AND DISCUSSION . . . . .	3
A. Curve-Fitting by Computer	3
B. Preprototype and Prototype Cell Design	10
IV. SUMMARY . . . . .	20
V. PROGRAM FOR THE NEXT INTERVAL . . . . .	21
VI. PERSONNEL . . . . .	21

APPENDIX

    Master Schedule

FIGURES

No. 1 - Predicted Capacity Response - Following Eight Days Activated Stand at 130°F	8
No. 2 - Predicted Voltage Responses	9
No. 3 - Open-Circuit Voltage Retention at 130°F (Silver vs Nickel Positive Grid Metal)	13
No. 4 - Discharge Characteristics Following Acti- vated Stand at Three Days at 130°F	14
No. 5 - Discharge Characteristics Following Acti- vated Stand at Five Days at 130°F	15
No. 6 - Discharge Characteristics Following Acti- vated Stand at Seven Days at 130°F	16
No. 7 - Discharge Characteristics Following Acti- vated Stand at Eleven Days at 130°F	17
No. 8 - Discharge Characteristics Following Acti- vated Stand at Seventeen Days at 130°F	18

TABLES

No. I - Values Used in Calculating Voltage Res- ponse By Use of Least Squares Equation (1)	5
No. II - Responses (Voltage)	6
No. III - Open-Circuit Voltages on Stand - Prepro- totype Cell - Silver Positive Grid	11
No. IV - Open-Circuit Voltages on Stand - Prepro- totype Cell - Nickel Positive Grid	12

I. PURPOSE

The purpose of this contract is to generate design data making possible the construction of a reliable primary zinc-silver oxide battery of improved activated charge retention characteristics, greater voltage control, high energy density, increased temperature stability, and reduced gassing characteristics.

## II. ABSTRACT

Studies conducted under the supervision of the National Aeronautics and Space Administration, Contract NAS 8-5493, have resulted in a primary zinc-silver oxide cell of improved design. Use of silver positive grid results in greater voltage control and increased activated cell life. Design factors for an improved cell design are presented. Reliable activated stand life of four days at 130°F and two weeks at 70°F are indicated..

### III. FACTUAL DATA AND DISCUSSION

#### A. Curve-Fitting by Computer

An attempt has been made to determine an equation describing voltage and capacity responses for cells of varying design characteristics.\* The equation is of the type  $Y = a_i + B_1b + B_2b^2 + C_1c + C_2c^2 + d_j + d_1e + d_2e^2 + K_1f + K_2^2 + g_k + h_e$ . (1) The letters b, c, e and f refer to the variable level numbers employed in a certain cell. The terms  $a_i$ ,  $d_j$ ,  $g_k$  and  $h_e$  represent values calculated by computer to represent the effect of levels of the qualitative factors A, D, G and H. The terms  $B_1$ ,  $B_2$ ,  $C_1$ ,  $C_2$ ,  $d_1$ ,  $d_2$ ,  $K_1$ , and  $K_2$  were also determined by computer by the method of least squares.

Values were determined for all terms included in equation (1) to allow description of both capacity and voltage responses for stand periods of two hours, four days, six days, eight days and ten days at a temperature of 130°F. Table No. I reveals values used in calculating voltage responses.

In the experimental series, which yielded data for the determination of equation (1), actual responses were obtained from a maximum of eighteen of the more than five thousand included in the full factorial replicate set. It was anticipated that if effects of the test variables were consistent and included no important interactions, equation (1) might satisfactorily predict responses for any of the five thousand possible cell designs. This has proved to be impractical, however. For instance, after a stand period of eight days at 130°F, Cell Nos. 19 and 25 were internally shorted. Therefore, terms of the least squares equation were determined from sixteen, rather than eighteen responses. Table No. II

\*See Progress Report No. 10, pp 12 and 13, NAS 8-5493 for a presentation of the construction variables associated with this series of experimental cells.

contains comparative data whereby the response deterioration characteristics were used to estimate closely responses which Cell Nos. 19 and 25 might have exhibited, had they not suffered premature electrical failure. Responses were also calculated by means of equation (1).

TABLE NO. I

Values Used in Calculating Voltage Response  
By Use of Least Squares Equation (1)

TERM	2 Hr.	4 Days	6 Days	8 Days	10 Days
$A$	91.103	76.866	84.841	72.325	80.733
$a_0$	-0.916	-5.975	-0.284	-5.770	-4.333
$a_1$	1.758	3.325	-1.598	5.209	3.000
$a_2$	0.577	5.958	-0.760	3.997	1.060
$a_3$	-1.419	-3.308	2.639	-3.437	0.267
$B_1$	0.187	-7.083	-1.202	-6.231	3.816
$B_2$	-0.477	1.983	-0.416	0.499	-3.116
$\gamma_1$	2.340	5.550	4.243	11.183	8.433
$\gamma_2$	-0.929	0.649	-1.846	-2.008	-3.766
$d_0$	-2.069	-4.649	-2.221	-0.685	-2.483
$d_1$	2.069	4.649	2.221	0.685	2.483
$d_2$	-0.342	-2.350	5.327	-5.097	0.333
$c_2$	-0.262	1.283	-2.510	3.239	-0.800
$K_1$	3.869	18.499	-5.852	15.088	2.383
$K_2$	-1.360	-7.633	3.259	-5.463	-0.083
$s_0$	0.331	2.200	1.343	2.779	-1.179
$s_1$	-0.562	-0.233	-2.090	-3.163	1.089
$s_2$	0.232	-1.966	0.747	0.384	0.090
$h_1$	-0.005	-0.099	0.368	0.079	0.084
$h_2$	0.005	0.0099	-0.368	-0.079	-0.084



TABLE NO. II

RESPONSES (voltage\*\*)

Cell No.	2 Hr.	4 Da.	6 Da.	8 Da.	10 Da.
2	96.0	86.0	85.3	84.0	84.0
3	88.7	78.7	81.3	73.3	76.0
4	92.7	86.0	85.0*	84.0	84.7
6	94.7	89.3	86.0	80.7	82.7
7	96.0	92.0	88.0	85.3	88.7
8	90.7	79.3	82.0	78.7	83.3
10	96.0	92.0	92.0	88.0	89.3
12	90.7	76.0	76.0	74.0	79.3
13	90.7	84.7	85.3	82.0	86.0
14	94.7	95.3	92.0	89.3	89.3
17	87.3	77.3	82.0	73.3	82.0
18	93.3	85.3	85.3	74.7	77.3
19	90.7	83.0*	84.0	80.0*	77.3
20	91.3	84.0*	81.3	77.3	82.0
23	92.0	80.7	85.3	80.0	82.7
24	89.3	76.0	80.7	75.3	79.3
25	92.0	84.7	86.7	84.0*	82.0*
27	90.7	79.3	79.3	76.3	75.0*

\*Responses for these cells (which failed to deliver usable capacity) were estimated from the response pattern.

\*\*These responses are obtained by dividing the cell discharge voltage after 15 seconds by 1.50 volts. This artificial response facilitates handling of data.

These calculated responses are indicated by the points falling away from the response curves in Figure Nos. 1 and 2.

It is indicated that there may be interactions between several of the cell variables, since the effect of including a specific design factor is not predictably constant among a large number of cell design combinations. Such interactions would require a larger orthogonal fractional replicate test group for complete evaluation.


Data in Figure Nos. 1 and 2 also re-emphasize another basic fact. Direct comparison of data disclosed by these figures reveals that several cells representing maxima on the capacity response pattern correspond to minima on the voltage response pattern. Slopes of corresponding straight line segments represented by the two figures are frequently of opposite algebraic sign. This again confirms that common measures taken to improve capacity retention are deleterious to voltage control, and vice versa. This is a graphic indication of the difficulty encountered in producing an optimum "general purpose" cell design.

At the present state-of-the-art, it appears that it is impossible to incorporate maximum capacity retention and maximum voltage regulation in a single cell design.

Data of Figure Nos. 1 and 2 do, however, indicate that Cell Nos. 10 and 14, following eight days stand at 130 F, exhibit the greatest voltage responses, while their capacity responses are also well above the overall mean. Many features of these cell designs have been included in the design of the preprototype and prototype cells.

FIGURE NO. 1

Predicted Capacity Response  
Following Eight Days Activated Stand at 130°F

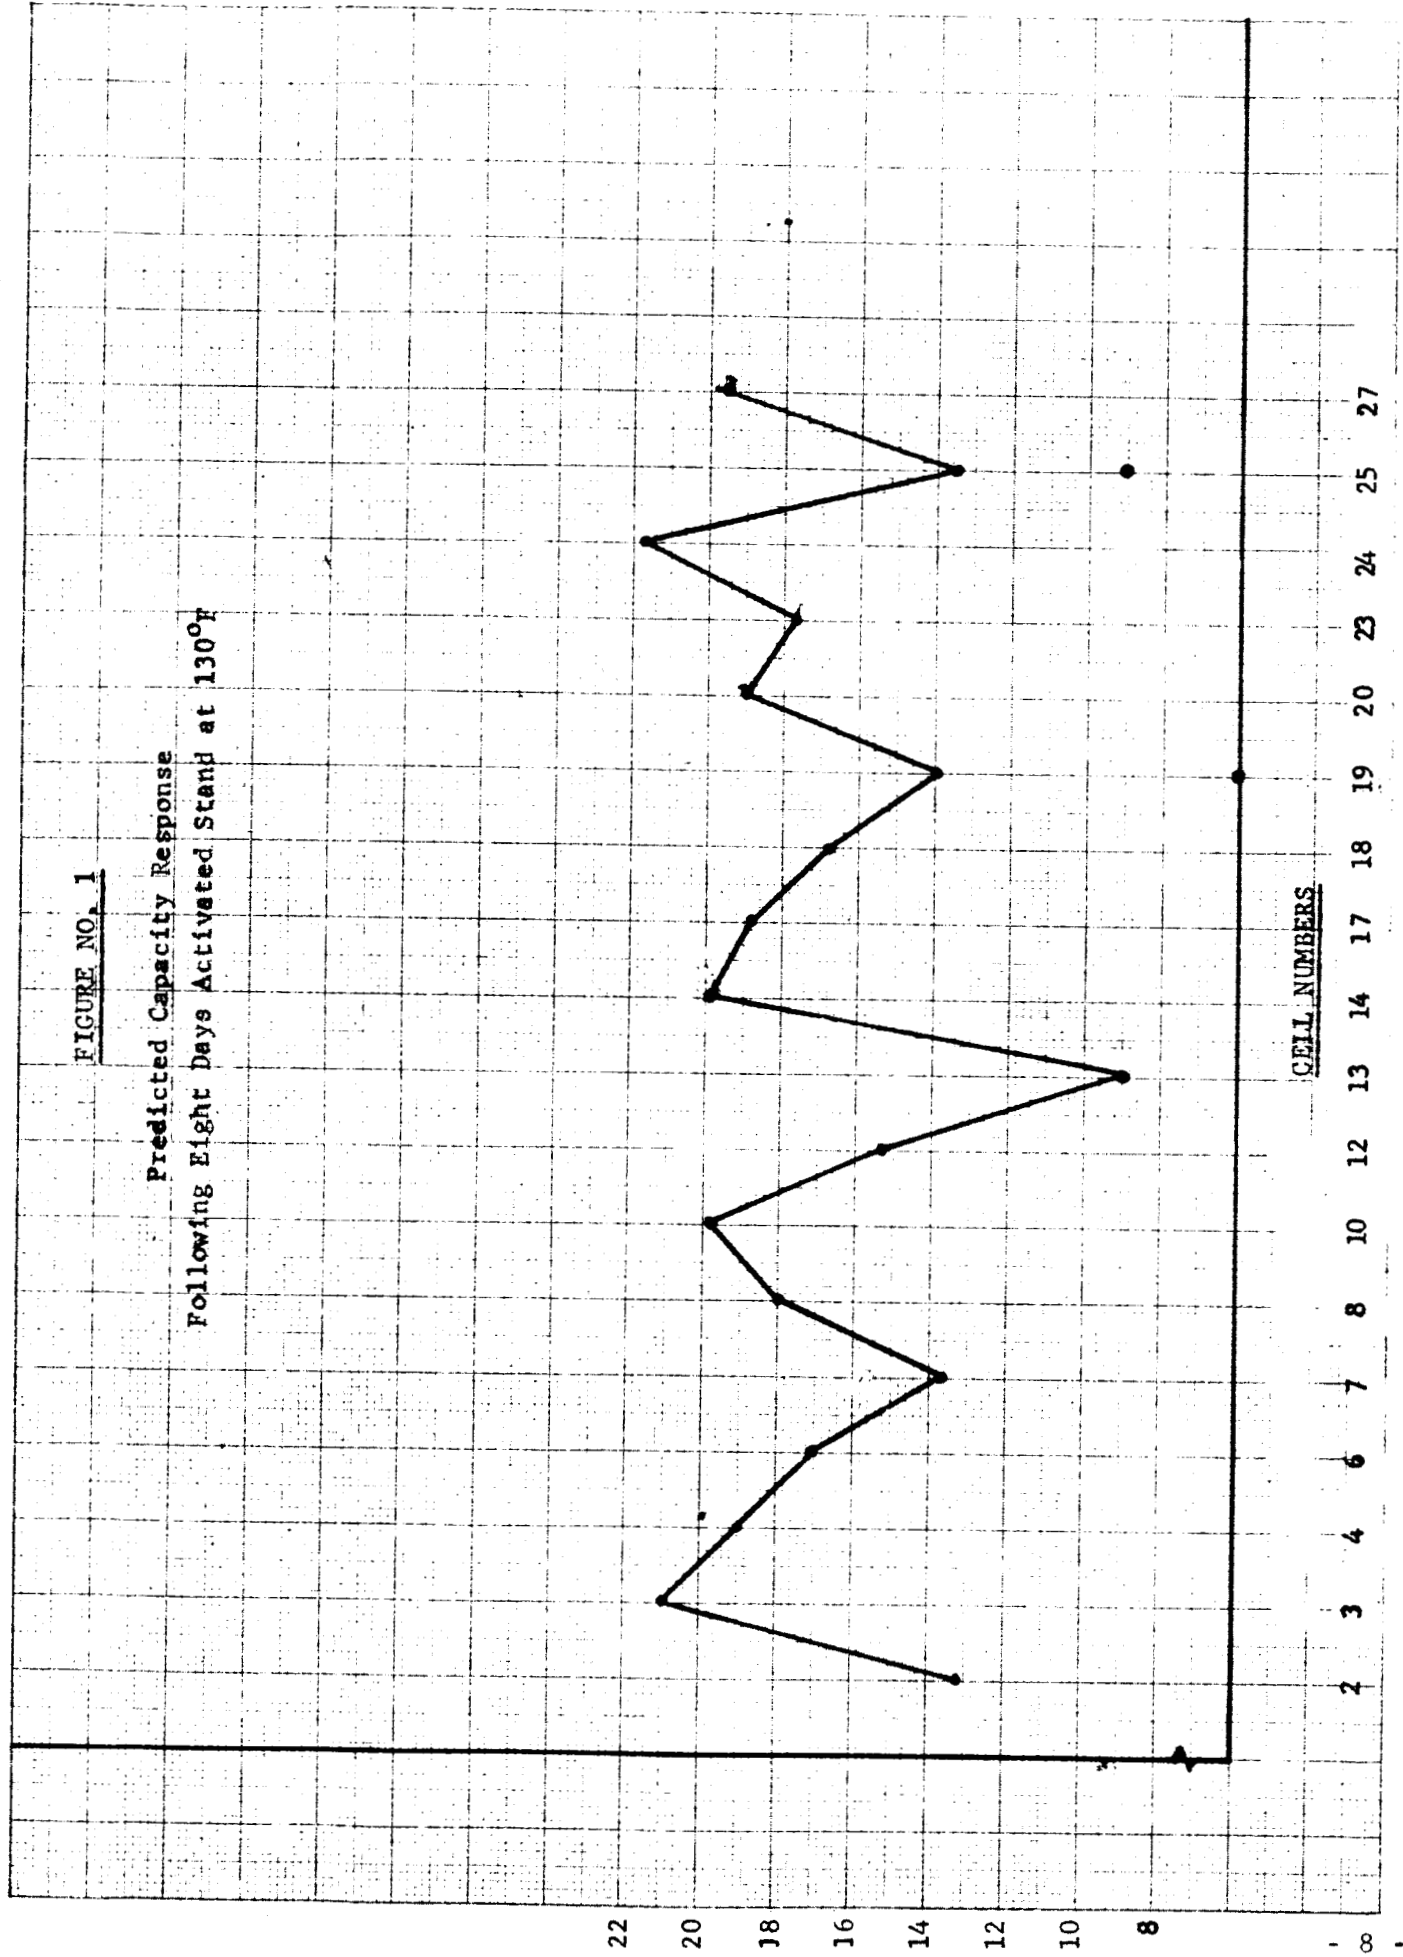


CELL NUMBERS

Capacity (minutes on discharge at 50 Amps)

FIGURE NO. 2

Predicted Voltage Responses

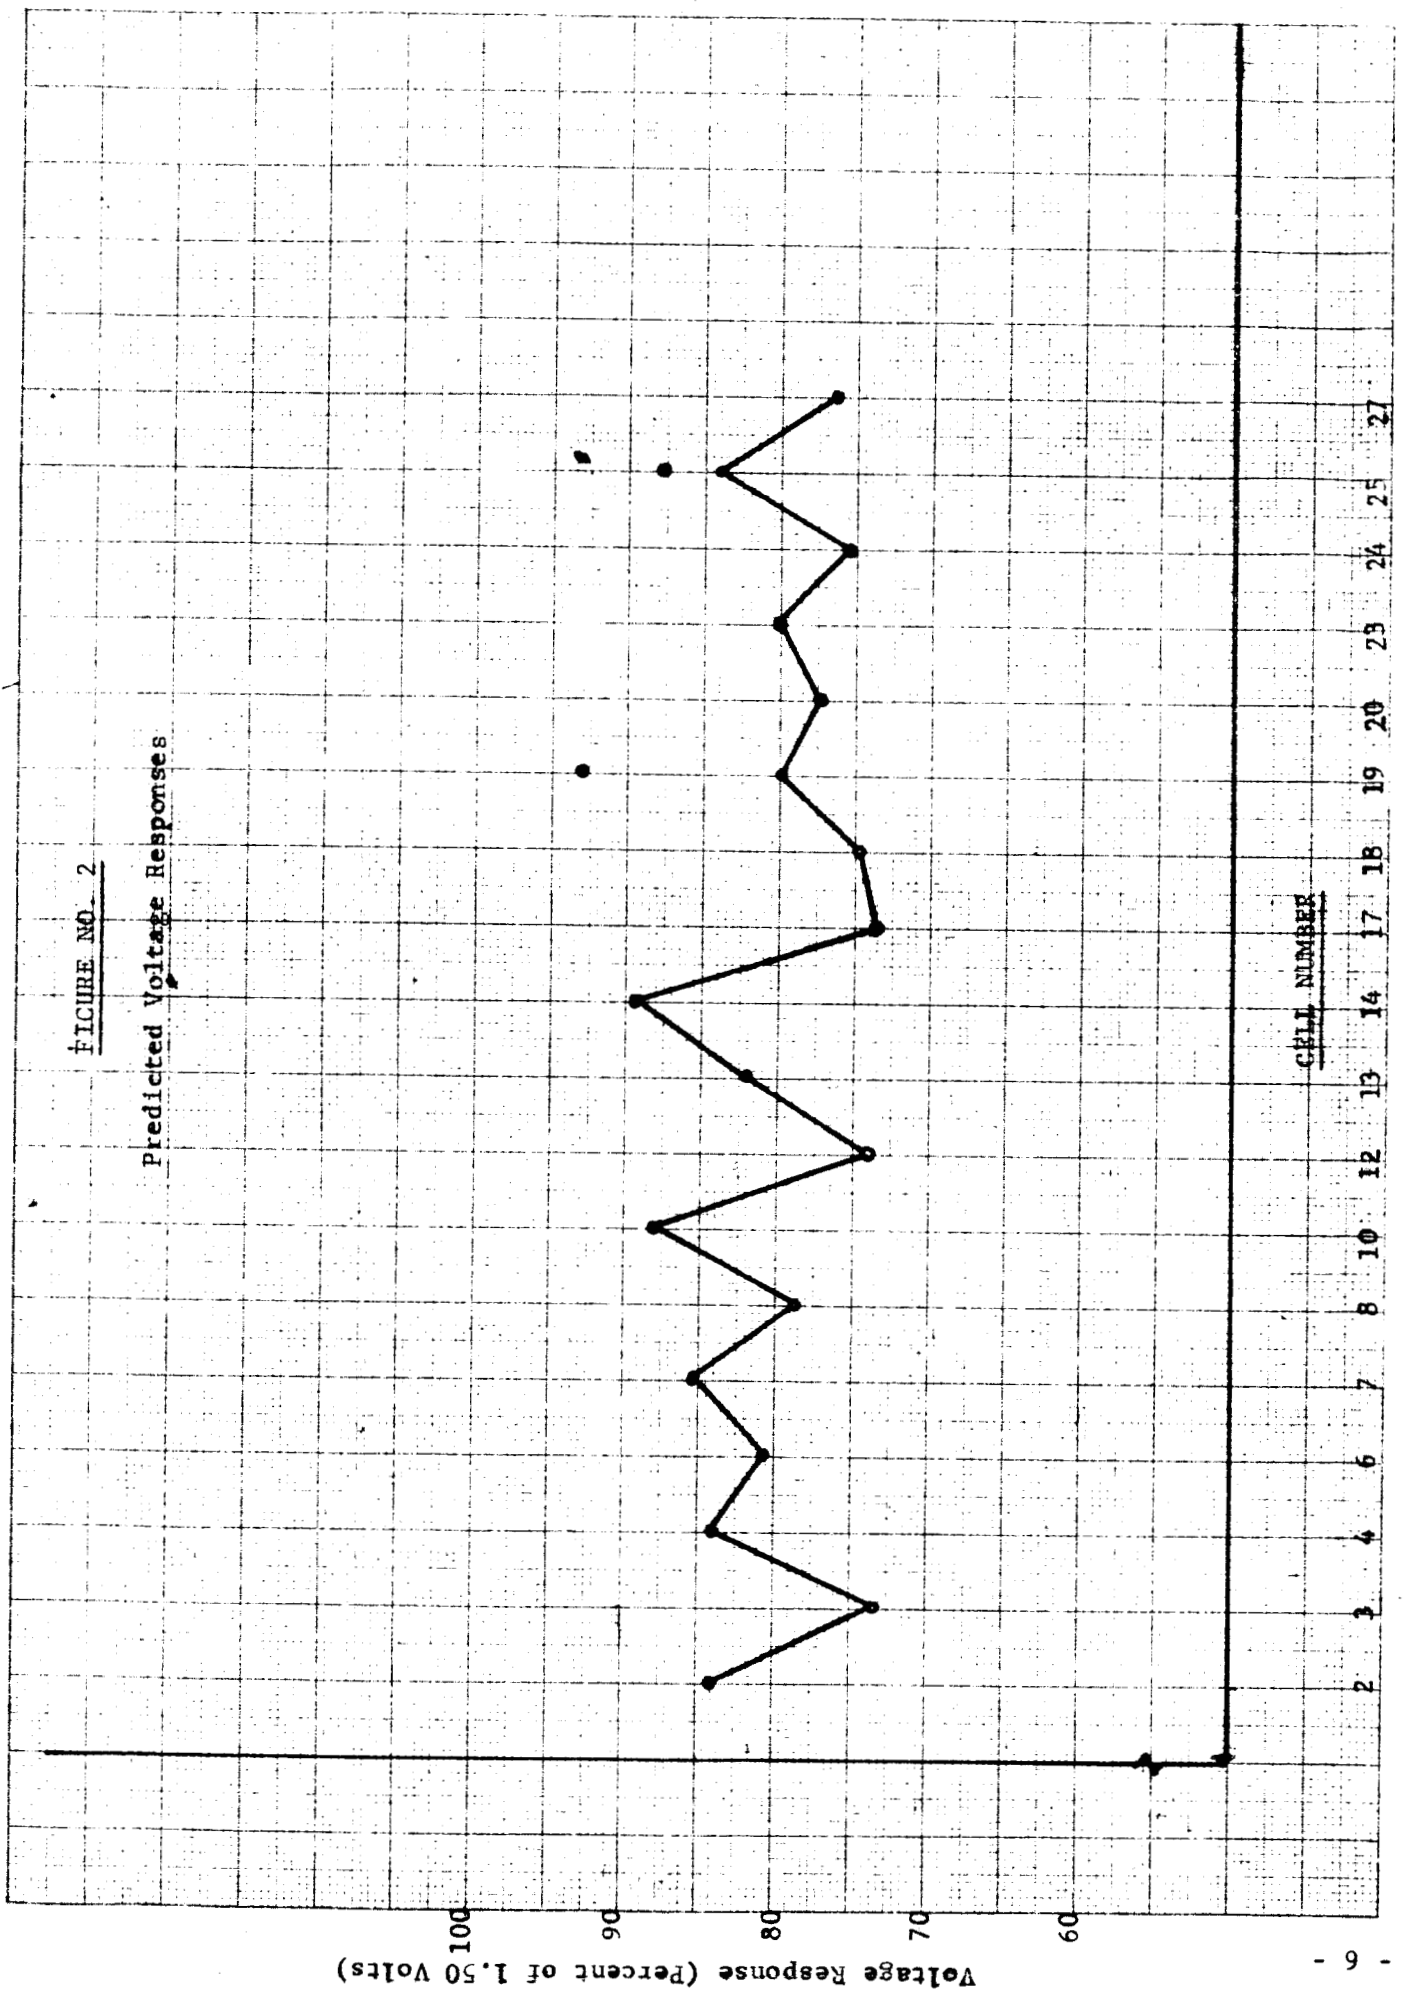

### B. Preprototype and Prototype Cell Design

Prototype cells of improved design have been discharged at room temperature following stand periods, at  $+130^{\circ}\text{F}$ , of three, five, seven, eleven and seventeen days. In addition, open circuit voltages of all cells were monitored and recorded daily while on stand at elevated temperatures. These voltages are displayed by Table Nos. III and IV. Certain cells were constructed with silver positive grid metal, while in others the active material was deposited nickel grid material. Discharge characteristics for cells on stand test are displayed by Figure Nos. 4 through 8. Data in Figure No. 3 reveals a significant variance between open-circuit voltage, retention-of-charge characteristics of the two experimental series of cells. Those cells having silver positive grid metal maintained higher open-circuit voltage. In addition, following seventeen days activated stand, none of the remaining five cells, having nickel positive grid, yielded useable capacity, while all cells having silver positive grid yielded only slightly decreased voltage. Increased open-circuit voltage exhibited by cells having silver positive grid metal is apparently reflected in the initial voltage during the first few minutes on discharge. Cells employing nickel positive grids display slightly greater ampere-hour efficiency initially. However, capacities of the two cell types converge with increased activated stand periods and cells employing nickel positive grid metal were first to suffer total failure, as disclosed by an inability to deliver capacity. Further studies would be necessary to determine which of the many commercial silver grid products may be most economically used without sacrificing cell voltage control during high rate discharges.

TABLE NO. III

OPEN-CIRCUIT VOLTAGES ON STAND  
 Preprototype Cell  
Silver Positive Grid

Cell No.	DAYS ON STAND							
	3	4	5	6	7	10	12	17
2	1.85							
3	1.85	1.84						
4	1.85	1.84	1.84					
5	1.85	1.84	1.84					
6	1.85	1.84	1.84	1.84	1.84	1.84	1.83	
7	1.84	1.84	1.84	1.84	1.84	1.84	1.84	
8	1.84	1.84	1.84	1.84	1.84	1.84	1.84	1.83
9	1.85	1.84	1.84	1.84	1.84	1.84	1.84	1.68
10	1.85	1.84	1.84	1.84	1.84	1.84	1.84	1.74
11	1.85	1.84	1.84	1.84	1.84	1.84	1.78	1.82
Mean	1.85	1.84	1.84	1.84	1.84	1.84	1.83	1.77

TABLE NO. IV

OPEN-CIRCUIT VOLTAGES ON STAND  
PREPROTOTYPE CELL  
NICKEL POSITIVE GRID

Cell No.	DAYS ON STAND							
	3	4	5	6	7	10	12	17
12	1.85							
13	1.85	1.85	1.84					
14	1.85	1.84	1.81	1.81	1.81			
15	1.84	1.82	1.80	1.80	1.80			
16	1.85	1.84	1.83	1.83	1.82	1.72	1.69	
17	1.84	1.84	1.81	1.81	1.81	1.74	1.65	
18	1.85	1.84	1.84	1.84	1.82	1.67	1.58	0.22
19	1.85	1.84	1.84	1.84	1.83	1.72	1.58	0.22
20	1.85	1.84	1.81	1.81	1.81	1.74	1.61	1.56
21	1.84	1.84	1.82	1.82	1.81	1.73	1.67	1.56
22	1.84	1.84	1.84	1.58	1.58	1.58	1.58	1.56
Mean	<1.85	1.84	1.82	>1.79	>1.73	1.70	1.62	1.03

FIGURE NO. 3

Open-Circuit Voltage Retention at 130°F  
(Silver vs Nickel Positive Grid Metal)


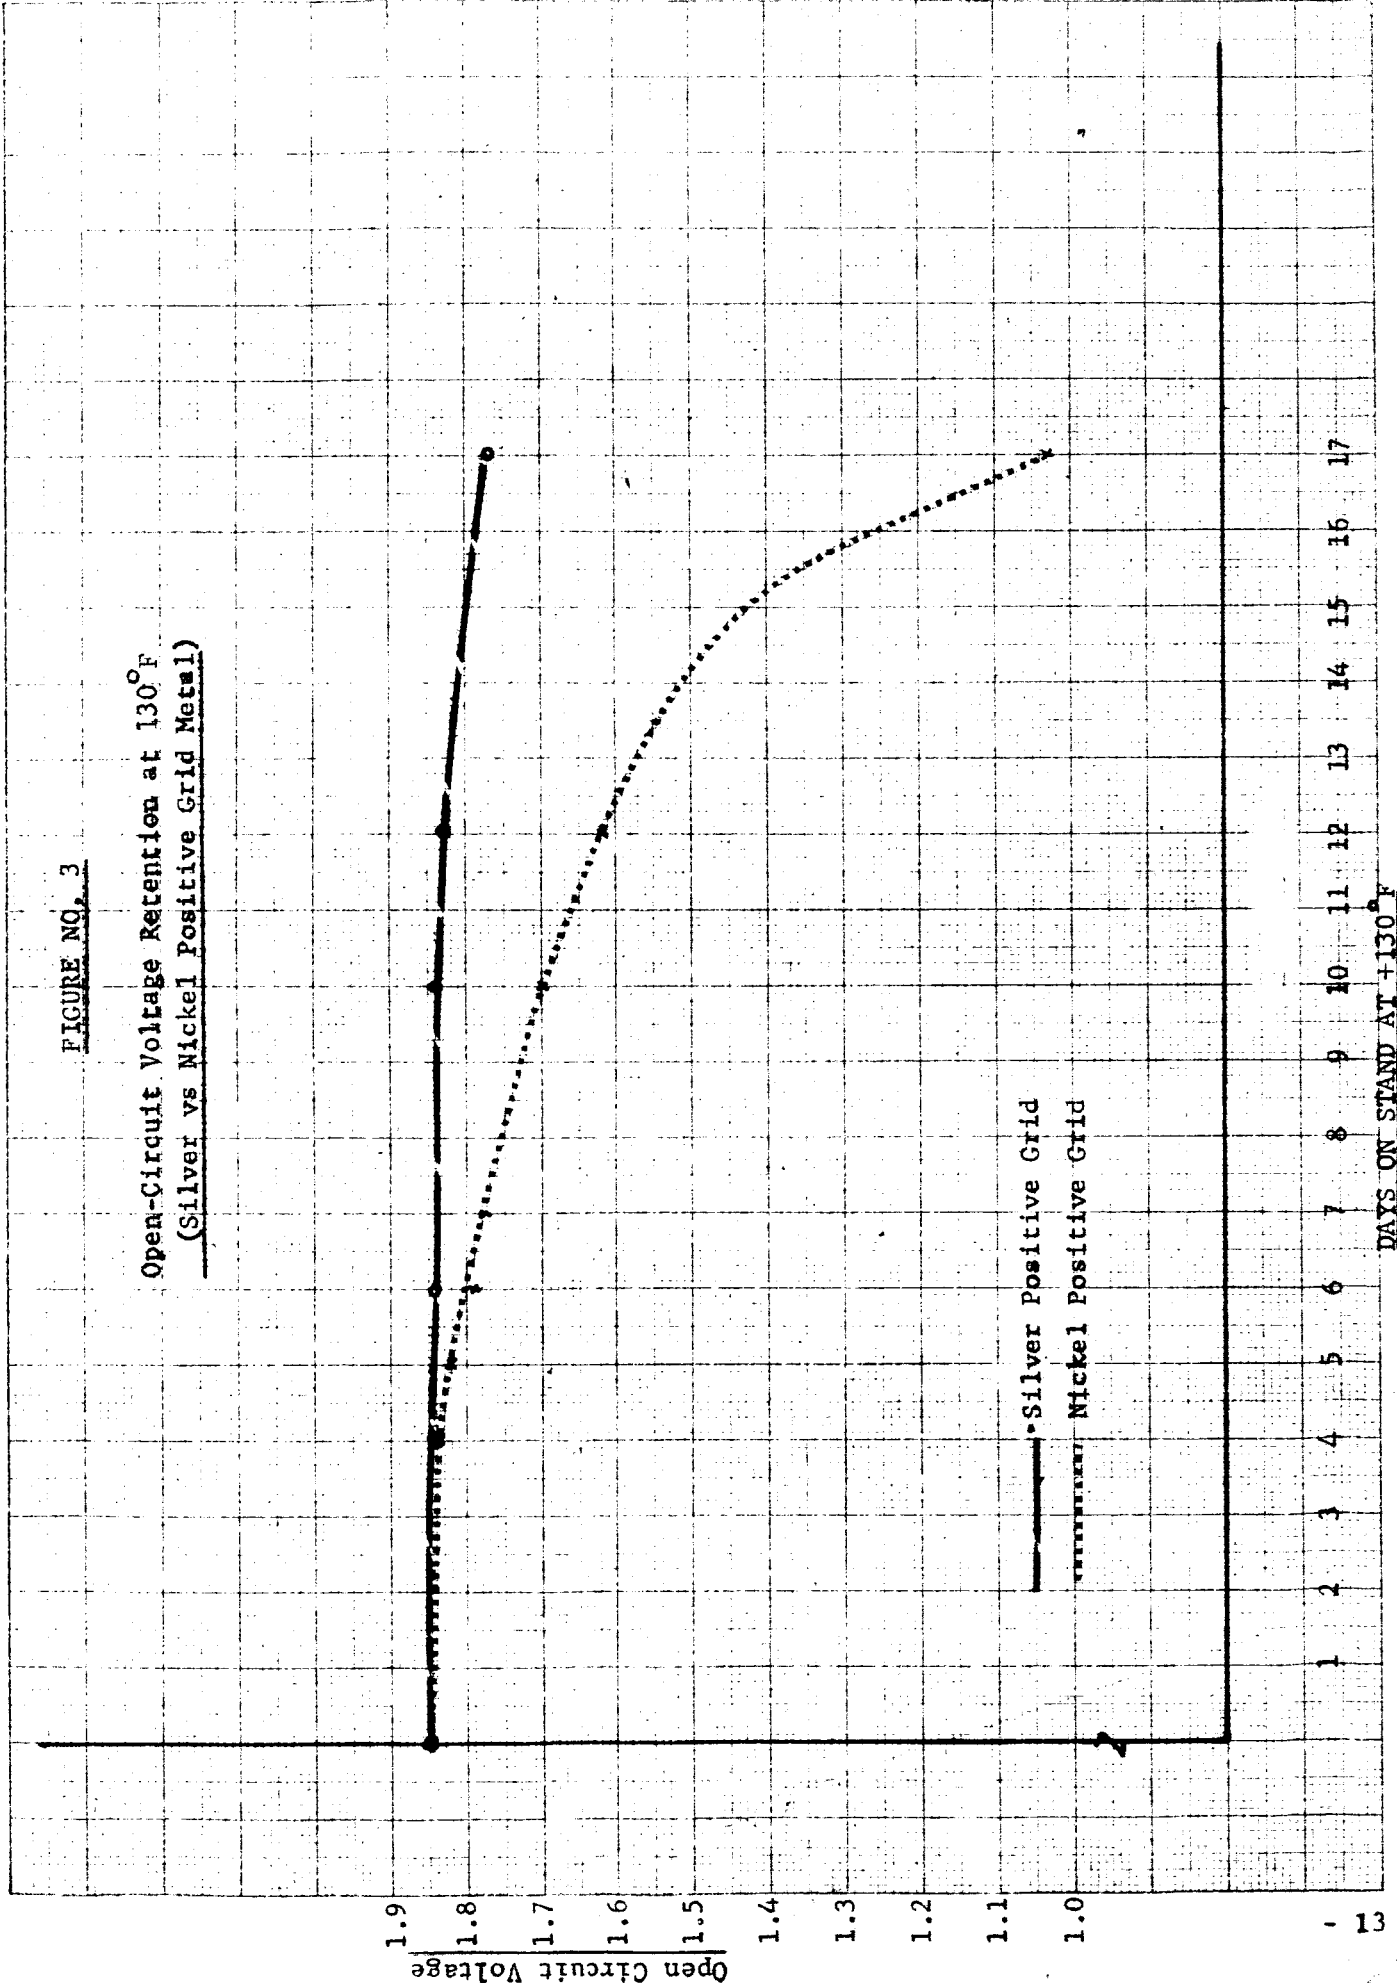




FIGURE NO. 4

Discharge Characteristics Following Activated Stand at  
Three Days at 130°  
(Silver vs Nickel Positive Grid)

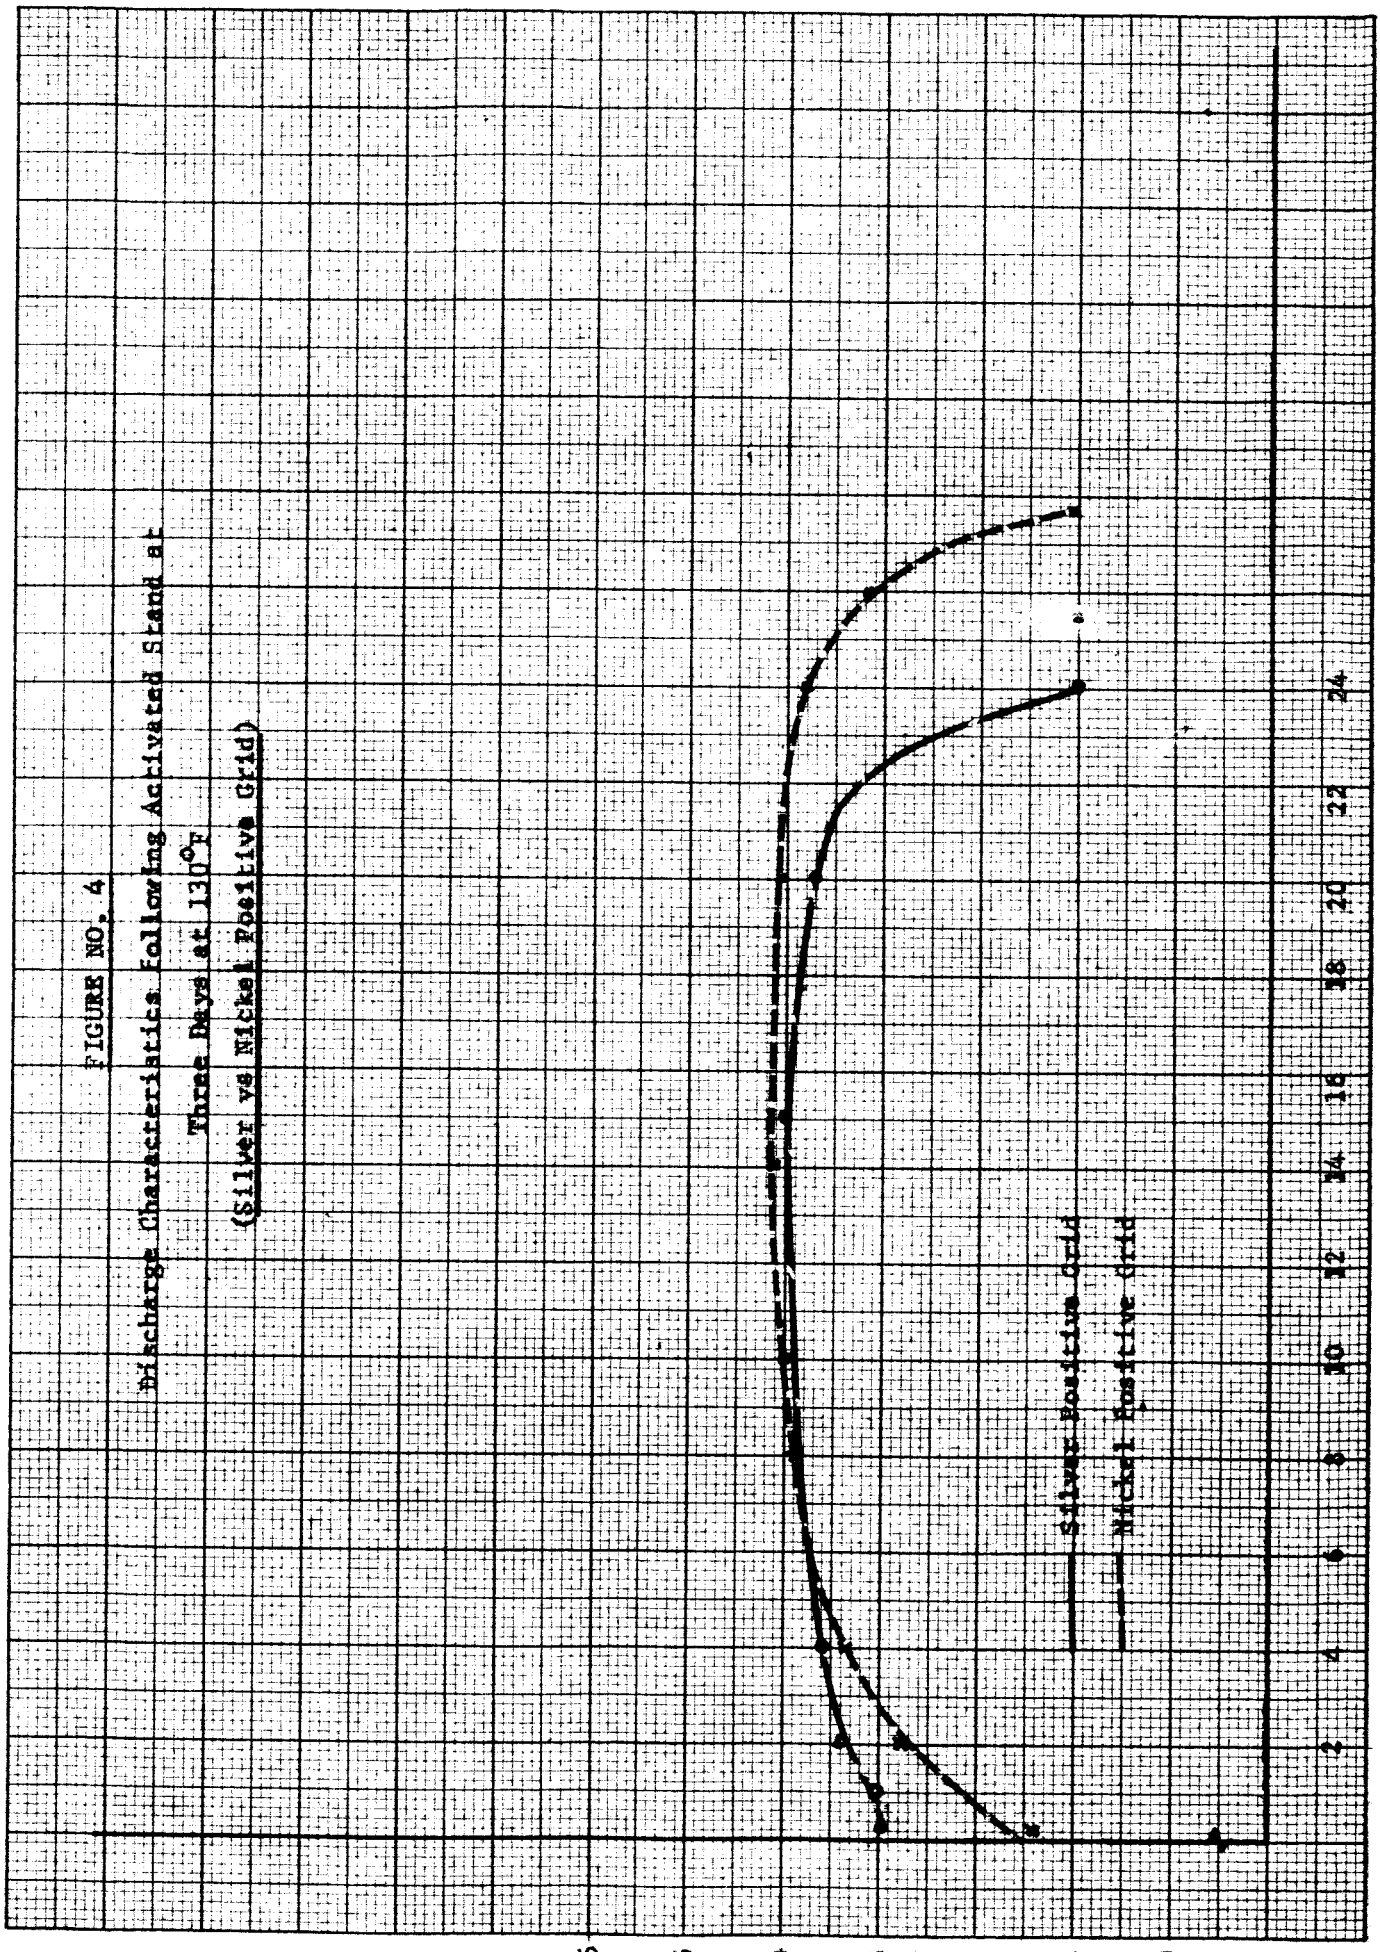

MINUTES ON DISCHARGE AT 30 AMPERES

were observed to have failed after a stand period of four days at +130°F. It is indicated that individual cells may be expected to perform reliably after a minimum of four days stand at +130°F. An activated life of two weeks appears obtainable at a stand temperature of 75°F. These improvements in overall cell performance result from changes in cell design and manufacturing processes as well as greater quality assurance measures. That is, the activated stand life of a primary cell has been significantly increased at no appreciable loss in energy density.

#### IV. SUMMARY

A. Phases of study, as outlined in the Master Schedule, are essentially complete. These studies were accomplished either directly, as in separator evaluations, or indirectly in a fractional factorial experimental series dealing with capacity retention and voltage regulation.

B. Under controlled conditions, individual cells may be expected to perform reliably following four days activated stand at 130°F or two weeks at 70°F. This represents an estimated minimum which might be increased as a result of detailed reliability studies. This increased reliable activated life results from experimental studies which yielded an improved cell design, as well as from continual improvement in the area of quality assurance as related to production procedures.

C. Studies to date indicate that very small fractional replicates may not be adequate to provide data needed to accurately predict responses for an extremely large number of individual cell designs. This apparently arises in part from interactions among design factors. For complete evaluation, these interactions could best be determined by a large fractional replicate or by several full factorials involving only

a few carefully selected variables. Careful consideration will be given to this phase in outlining a master program in the extension of this work.

D. Use of silver positive grid metal and carefully prepared positive and negative active materials results in greater retention of open-circuit voltage as well as improved discharge voltage characteristics.

#### V. PROGRAM FOR THE NEXT INTERVAL

During the twelfth contract month, extensive preparation will be directed toward the planning of enlarged studies to be conducted under the Modification to Contract No. NAS 8-5493. This will include reviews of patents, progress reports and other technical literature, as well as scheduling the various phases of study. All work, both fundamental and applied, will be directed towards improvement of performance characteristics of the primary zinc-silver oxide system, with emphasis on retention of capacity, voltage control, and high rate capabilities throughout long periods of activated stand. The statistical approach of investigation will be employed wherever applicable. Each of the two coming contract months will be shortened by the two-week plant vacation shut-down.

#### VI. PERSONNEL

The following totals of man-hours have been expended during the contract period:

Engineering	- 1500
Technical	- <u>2403</u>
TOTAL	- 3903

A P P E N D I X

